

Eclética Química ISSN: 0100-4670 ISSN: 1678-4618

ecletica@journal.iq.unesp.br

Universidade Estadual Paulista Júlio de Mesquita Filho

Brasil

Madeira, Aline Amaral

Grain-size mineral analysis of verdete rock coarse and fine aggregates and adjustment to two granulometric distribution models Eclética Química, vol. 45, núm. 1, 2020, pp. 56-64
Universidade Estadual Paulista Júlio de Mesquita Filho
Araraquara, Brasil

DOI: https://doi.org/10.26850/1678-4618eqj.v45.1.2020.p56-64

Disponible en: https://www.redalyc.org/articulo.oa?id=42962133006



Número completo

Más información del artículo

Página de la revista en redalyc.org



Sistema de Información Científica Redalyc

Red de Revistas Científicas de América Latina y el Caribe, España y Portugal Proyecto académico sin fines de lucro, desarrollado bajo la iniciativa de acceso abierto



| Vol. 45 | n. 1 | 2020 |

Grain-size mineral analysis of verdete rock coarse and fine aggregates and adjustment to two granulometric distribution models

Aline Amaral Madeira+®

Pontifical Catholic University of Minas Gerais (PUC-MG), 500 Dom José Gaspar Av, Belo Horizonte, Minas Gerais, Brazil

*Corresponding author: Aline Amaral Madeira, phone number +55 31 991807451 email address: madeira.alineamaral@gmail.com


ARTICLE INFO

Article history:

Received: July 21, 2019 Accepted: September 17, 2019 Published: January 1, 2020 Keywords:

- 1. verdete rock
- 2. grain-size analysis
- 3. particle size distribution
- 4. Rosin-Rammler-Bennet model
- 5. Gates-Gaudin-Schuhmann model

ABSTRACT: The supremacy of the mineral industry added to the necessity to supply the world market demand justifies the continuous research efforts for optimizing of the activities of mineral resource utilization. In an approach of mineral characterization, a grain-size analysis study of coarse and fine aggregates of verdete rock was presented in this work. The particle size distribution (PSD) of two samples of aggregates with granulometry < 2.36 mm was experimentally obtained using sieving techniques and adjustment to Rosin-Rammler-Bennet (RRB) and Gates-Gaudin-Schuhmann (GGS) granulometric distribution models. Both RRB and GGS models regressed well to the experimental data, presenting correlation coefficient values were extremely close between them approximately 0.99. The PSD results indicated that 65.97% dry aggregates and 67.68% wet aggregates had a particle size with mean diameter > 0.0050 mm; a similar behavior of the grain-size distributions presented by dry aggregates; and

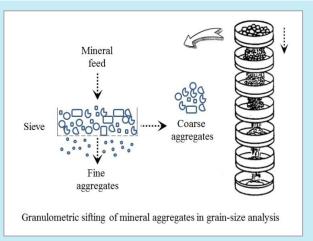

tiny presence of fine particles natural in the analyzed ore sample. The results suggested the suitability of the methodology to predict the grain-size performance the verdete ore beyond to show itself as a contribution to the enriching of the mineral characterization of the studied rock, as a potassium potential source for the mineral processing Brazilian industry.

56

1. Introduction

Technological advancements in processing operations suggest that continuous research efforts are required to minimize energy consumption, optimize resource utilization, and acquire products with the desired size distribution. Size reduction is probably one of the most fundamental and energy-intensive operations in the mineral processing industry, consuming up until 4% of the electrical energy generated worldwide. Comminution operations and grinding fineness determination are important processes employed to fracture coarse mineral aggregates and liberate value-added materials. Estimations on energy consumption in mining operations in the USA indicate that 39% is used for beneficiation and processing operations, 75% of which is consumed in comminution ¹⁻³.

Grain size may be considered a fundamental physical characteristic property of earth materials, being relevant to their classification and geological origin, as well as for its applications in geotechnics, agricultural engineering, and industrial technology. Moreover, particle size distribution (PSD) influences various activities of resource and energy utilization, and industrial processes, such as the granular materials flow characteristics, flotation and leaching processes, compacting and sintering of metallurgical powders, combustion process, settling time of cements, among others processes. Particle size can be determined using several techniques, between them sieving, sedimentation, electrozone sensing,



microscopy techniques, X-ray attenuation, and laser diffraction⁴.

Several models and expressions have been developed to describe the PSD of particulate materials³. These models ranging from the normal and log-normal distributions to the Rosin-Rammler-Bennet (RRB) and Gates-Gaudin-Schuhmann (GGS) models. RRB equation is probably the most well-known distribution in the chemical industries, widely used to analyze all types of materials and GGS equation is another uncomplicated popular model used in the metallic ferrous mining industry⁵. RRB and mathematical models have been widely applied to describe the size distribution of several particles types, such as maize grains²; fenugreek seed⁵; sorghum bagasse⁶; copper tailing⁷; babassu, canola, castor seed and sunflower residual cakes⁸; particle assemblages⁹, and several ores, such as quartz and marble³; iron¹⁰; uranium¹¹; phosphate¹²; apatite¹³; chromite¹⁴; among others. Other numerous granulometric distribution models have also been proposed for greater accuracy in estimating the PSDs, but they have limit applications due to their greater mathematical complexity¹.

In Brazil, one of the most abundant potassium silicates is regionally known as verdete, a metasedimentary rock formed during Neoproterozoic era. Verdete is a greenish and banded rock, which has fine granulometry and clay matrix, and it is composed essentially by glauconite, quartz, and kaolinite minerals and potassium feldspars¹⁵. According to Santos *et al.*¹⁶, the rock occurs in Serra da Saudade, Alto Paranaíba Region (MG), geologically located in the San Francisco Craton. The municipality of Cedro do Abaeté is known to have reasonable reserves of verdete (57.4 million tons)¹⁷. Potassium oxide (K₂O) high contents in the verdete rock were reported in the literature^{15,18-20}. According to Silva and Lana²¹, the Cedro do Abaeté's verdete may contain until 14% of K₂O.

According to the journal Brasil Mineral²², the first mineral project of an industrial processing plant of verdete rock recently was inaugurated in Dores do Indaiá, Minas Gerais State, Brazil. Pioneer in the processing of this potassium rock, the complex of the Kalium Mineração S.A. disposes of a glauconite deposit located in the municipalities of Serra da Saudade and Quartel Geral in Minas Gerais, with total reserves of 218 million tons of ore and an average content of 10.6% K₂O. The mining process certified by Intertek

predicts innovative treatment through an processing techniques of crushing/grinding; acid cure; aqueous lixiviation; liquid-solid separation; thermic decomposition; crystallization; sulfuric acid regeneration. The company mining intended the verdete rock use for the potassium salts production, whose processed products may be applicated as potassium fertilizers, for example, seeking to supply part of great demand of the potassium national market²³.

However, a few previous scientific studies worked with the verdete rock until recently. So far, stand out researches involving chemical, stratigraphic, petrographic and mineralogical characterizations were performed 15,19,24,25, besides other technological studies based on thermal treatment focusing on its reactivity increase 20,26 and its metal availability 21,27-31. No meaningful previous contributions were found that consistently explored the particle size distribution of verdete rock through grain-size analysis and adjustment to RRB and GGS mathematical models.

In this context, based on the relevance of continuous research efforts in mineral processing studies, as well as on the lack of consistent scientific contributions regarding particle size distribution of the verdete rock through the grainsize property, the present article delineates a new study of grain-size of verdete coarse and fine aggregates. For that, this work strives to describe the particle size distribution of such aggregates using sieving techniques and adjustment to Rosin-Rammler-Bennet (RRB) and Gates-Gaudin-Schuhmann (GGS) granulometric distribution models, with the purpose of providing subsidies to a verdete rock characterization as potassium potential source for the mineral processing Brazilian industry.

2. Experimental

Grain-size analysis of verdete rock was realized at environmental conditions at room temperature (298.15 K) under atmospheric pressure (101,325 Pa). Initially, a representative sample of 20 kg of verdete rock from Cedro do Abaeté in Minas Gerais was properly homogenized and ground in a ball mill (Sew-Eurodrive, model FA37B DRE80S4). The grinding product was passed through a 2.36 mm sieve (8 mesh), getting a sample with granulometry < 2.36 mm. Approximately 2.0 kg of verdete rock were weighed on a balance (Urano, model UDC POP).

The sample was subjected to the quartering method of size reduction for homogeneous sampling using a Jones riffle splitter (Gilson Company, model SP-173). In the first step, the quartering method divided the sample into two lots of aggregates of 1.0 kg each. Then, one of the lots was subjected again to riffle splitter for apportioning in two lots of 500 g, and so on; quartering was continued until the obtention of two samples of 250.0 g each (A and B).

Sample A (verdete rock dry aggregates) was directly forwarded grain-size analysis. Sample B (verdete rock wet aggregates) was previously washed before of the granulometric test with deionized water obtained from the purifier Gehaka and dried in a kiln (Infinit, model EMT-200) at

373.15 K by approximately 2 h. The washing procedure exclusively intended to remove possible fine particles natural from the ore. The grain-size analysis consisted of one series montage of granulometric sieves and consecutive vibrating sifting of the sample by 10 min under a frequency of 10 Hz. For that, it was used one kit of seven sieves of Tyler standard screen scale of 4, 8, 28, 35, 48, 100, and 200 mesh (Solotest, model 8X2) and a vibrating sieve shaker (Solotest, model 8X2). Posteriorly, the retained aggregates mass fractions on each sieve were weighed on an analytical balance (Shimadzu, model AW220). Tables 1 and 2 present the grain-size analysis experimental data of dry and wet aggregates of verdete rock.

Table 1. Grain-size analysis data of verdete rock dry aggregates.

Table 1. Grain-size analysis data of verdete fock dry aggregates.										
Tyler Standard Screen Scale / Mesh		Nominal Sieve Opening Size / mm	Nominal Mean Diameter / µm	Nominal Mean Diameter / mm	Mass Retained / g	Percent Retained / %	Cumulative Mass Retained / g	Cumulative Percent Retained / %	Cumulative Mass Passing / g	Cumulative Percent Passing / %
4	+4	4.6990								
8	-4+8	3.3227			0.00	0.00	0.00	0.00	242.02	100.00
28	-8+28	0.5874	1955.05	0.0196	35.04	14.48	35.04	14.48	206.99	85.52
35	-28+35	0.4153	501.35	0.0050	159.67	65.97	194.70	80.45	47.32	19.55
48	-35+48	0.2937	354.50	0.0035	10.94	4.52	205.64	84.97	36.38	15.03
100	-48+100	0.1468	220.25	0.0022	14.10	5.83	219.75	90.80	22.27	9.20
200	-100+200	0.0734	110.10	0.0011	12.18	5.03	231.93	95.83	10.09	4.17
Bottom	-200				9.15	3.78	241.08	99.61	0.94	0.39
					0.94	0.39	242.02	100.00	0.00	0.00
Sum					242.00					

Table 2. Grain-size analysis data of verdete rock wet aggregates.

Tyler Standard Screen Scale / Mesh		Nominal Sieve Opening Size /mm	Nominal Mean Diameter / µm	Nominal Mean Diameter / mm	Mass Retained / g	Percent Retained / %	Cumulative Mass Retained / g	Cumulative Percent Retained / %	Mass	Cumulative Percent Passing / %
4	+4	4.6990								
8	-4+8	3.3227			0.00	0.00	0.00	0.00	239.97	100.00
28	-8+28	0.5874	1955.05	0.0196	33.26	13.86	33.26	13.86	206.71	86.14
35	-28+35	0.4153	501.35	0.0050	162.42	67.68	195.68	81.54	44.29	18.46
48	-35+48	0.2937	354.50	0.0035	9.77	4.07	205.45	85.61	34.52	14.39
100	-48+100	0.1468	220.25	0.0022	11.59	4.83	217.04	90.44	22.93	9.56
200	-100+200	0.0734	110.10	0.0011	14.34	5.97	231.43	96.42	8.60	3.58
Bottom	-200				7.15	2.98	238.52	99.40	1.45	0.60
					1.45	0.60	239.97	100.00	0.00	0.00
Sum					240.00					

Size parameters – number of particles (N, Eq. 1); arithmetic mean diameter (D_A , Eq. 2); volumetric mean diameter (D_V , Eq. 3); surface mean diameter (D_S , Eq. 4); Sauter mean diameter (D_{Sauter} , Eq. 5) – and surface parameters – external surface (S, Eq. 6) and specific surface (S/M, Eq. 7) – of the dry and wet aggregates of verdete rock were measured from experimentally obtained data and presented in Table 3.

$$N = \frac{M}{b \cdot \rho} \sum_{i=1}^{n} \left(\frac{x_i}{D_i^3} \right) \tag{1}$$

where: N = Number of particles (units); M = Total retained mass in the grain-size analysis (g); b = factor assuming cubic format particle = 1; $\rho = \text{verdete rock density} = 2.376 \text{ x } 10^{-3} \text{ g mm}^{-3}$; $x_i = \text{retained weight fraction of a group of particles in the grain-size analysis; } D_i = \text{nominal mean diameter of that group (mm)}$.

$$D_A = \sqrt{\frac{\sum_{i=1}^n \left(\frac{x_i}{D_i^2}\right)}{\sum_{i=1}^n \left(\frac{x_i}{D_i^3}\right)}} \tag{2}$$

where: D_A = Arithmetic mean diameter (mm); x_i = retained weight fraction of a group of particles in the grain-size analysis; D_i = nominal mean diameter of that group (mm).

$$D_V = \sqrt[3]{\frac{1}{\sum_{i=1}^{n} \left(\frac{x_i}{D_i^3}\right)}}$$
 (3)

where: D_V = Volumetric mean diameter (mm); x_i = retained weight fraction of a group of particles in the grain-size analysis; D_i = nominal mean diameter of that group (mm).

$$D_{S} = \sqrt{\frac{\sum_{i=1}^{n} \left(\frac{x_{i}}{D_{i}}\right)}{\sum_{i=1}^{n} \left(\frac{x_{i}}{D_{i}^{3}}\right)}}$$
(4)

where: D_S = Surface mean diameter (mm); x_i = retained weight fraction of a group of particles in the grain-size analysis; D_i = nominal mean diameter of that group (mm).

$$D_{Sauter} = \frac{1}{\sum_{i=1}^{n} \left(\frac{x_i}{D_i}\right)}$$
 (5)

where: D_{Sauter} = Sauter mean diameter (mm); x_i = retained weight fraction of a group of particles in the grain-size analysis; D_i = nominal mean diameter of that group (mm).

$$S = \frac{M*\lambda*\sum_{i=1}^{n} \left(\frac{x_i}{D_i}\right)}{\rho} \tag{6}$$

where: $S = \text{External surface (cm}^2)$; M = Total retained mass in the grain-size analysis (g); $\lambda = \text{factor assuming cubic format particle} = 6$; $x_i = \text{retained weight fraction of a group of particles in the grain-size analysis; <math>D_i = \text{nominal mean diameter of that group (cm)}$; $\rho = \text{verdete rock density} = 2.376 \text{ g cm}^{-3}$.

$$\frac{S}{M} = \frac{\lambda * \sum_{i=1}^{n} \left(\frac{x_i}{D_i}\right)}{\rho} \tag{7}$$

where: S/M = Specific surface (cm² g⁻¹); M = Sum retained mass of sieves 28 to 200 mesh (g) λ = factor assuming cubic format particle = 6; x_i = retained weight fraction of a group of particles in the grain-size analysis; D_i = nominal mean diameter of that group (cm); ρ = verdete rock density = 2.376 g cm⁻³.

Table 3. Size and surface parameters of verdete rock aggregates.

				Mean Diameter			
Sample	Number of Particles / units	External Surface / cm ²	Specific Surface / cm ² g ⁻¹	Surface Diameter / mm	Volumetric Diameter / mm	Arithmetic Diameter / mm	Sauter Diameter / mm
Dry Aggregate	28,430,655	13,685.593	59.007	0.213	0.272	0.169	0.447
Wet Aggregate	31,789,452	13,935.833	60.216	0.203	0.262	0.161	0.435

3. Results and Discussion

Particle size distribution study of verdete rock dry and wet aggregates was developed from the mass values of the different particle size obtained in the sieving operations converted to the cumulative and percent mass fractions. Figure 1 shows the granulometric curves of dry and wet aggregates. By assessing the retained fractions percent values against the sieve sizes, it was observed an increase in percentage weight retained of the 28 mesh sieve (0.5874 mm) for 35 mesh sieve (0.4153 mm) and a retained weight meaningful decrease starting of sieve 35, as a response to the decrease of opening size. So that 65.97% of dry aggregates and 67.68% of wet aggregates were retained on 35 size sieve, suggesting a particle size with 0.0050 < mean diameter < 0.0196 mm.

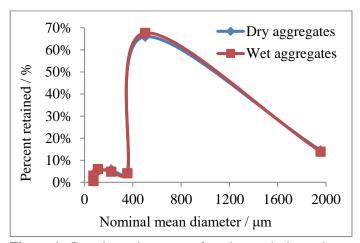


Figure 1. Granulometric curves of verdete rock dry and wet aggregates.

Figure 2 illustrates the grain-size distribution curves of verdete coarse aggregates and Fig. 3 the grain-size distribution curves of verdete fine aggregates. The evolution of the PSD regarding the nominal sieves opening size revealed a distribution with a profile characterized by a decrease of cumulative percent retained in case of the coarse aggregates and an increase of cumulative percent passing of the fine aggregates along of the sieving operations, as expected. The sieving experiments conducted with the wet aggregates (sample B) was previously washed and posteriorly dried intending to remove possible fine particles natural from the ore. It is relevant to emphasize that these particles cannot be confused with fine aggregates with potassium appreciable contents generated by ore

fragmentation processes. As could be seen in Figs. 1, 2 and 3, the granulometric curves of dry and wet aggregates exhibited extremely similar profiles suggesting the hypothesis that the verdete ore mother-sample had not an appreciable amount of natural fine particles sufficient to create a significant differentiation between the granulometric distribution of the A and B samples.

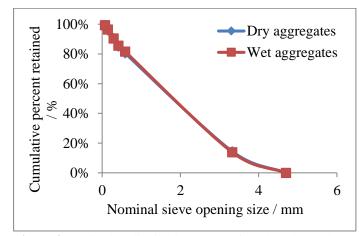


Figure 2. Grain-size distribution curve of verdete dry and wet coarse aggregates.

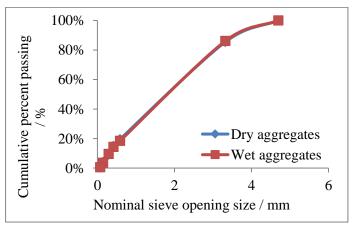


Figure 3. Grain-size distribution curve of verdete dry and wet fine aggregates.

Table 3 lists size and surface parameters of verdete rock's aggregates calculated as defined in equations earlier (Eqs. 1-7) after grain-size analysis via sieve classification. Obtained results for particles number, external and specific surfaces, and mean-diameters showed two particle-populations, the first one composed by dry aggregates and the second population by wet aggregates, with parameters values very similar. Arithmetic, surface, and volumetric mean-diameters obtained values corroborated a particle mean diameter > 0.0050 mm, as foreseen by

granulometric curves results. Sauter mean diameter obtained values expressed a larger mean diameter of the dry particulate matter as compared to the wet particulate matter by taking into account the volume-to-surface area ratio.

Grain-size analysis adjustment of verdete rock aggregates was provided by granulometric distribution models of the Rosin-Rammler-Bennet (RRB) and Gates-Gaudin-Schuhmann (GGS), whose nonlinear and linearized equations were presented in Eqs. 8, 9, 10, and 11, respectively. Table 4 summarizes intrinsic parameters and nonlinear and linear equations of the RRB and GGS models determined from the obtained experimental data and Fig. 4 shows granulometric distribution curves and linearized curves of the RRB and GGS models for verdete rock dry and wet aggregates.

$$X_i = 1 - e^{-\left(\frac{D_i}{D'}\right)^n} \tag{8}$$

where: X_i = passing weight fraction of a group of particles in the grain-size analysis; $\phi = \frac{1}{1-X_i}$; $D_i =$ nominal mean diameter of that group (μ m); n = uniformity coefficient that stands for the width of PSD; D' = characteristic particle diameter (reflecting the particle size of most particles).

$$X_i = \left(\frac{D_i}{k}\right)^m \tag{10}$$

$$ln X_i = m. ln D_i - m. ln k$$
(11)

where: X_i = passing weight fraction of a group of particles in the grain-size analysis; D_i = nominal mean diameter of that group (μ m); k = maximum particle diameter of the distribution (size modulus) that locates the distribution in overall size spectrum (μ m); m = distribution modulus, that measure the broadness of the size distribution.

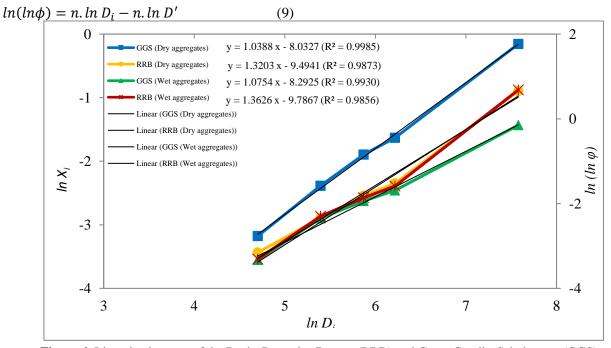


Figure 4. Linearized curves of the Rosin-Rammler-Bennet (RRB) and Gates-Gaudin-Schuhmann (GGS) mathematical models for verdete rock dry and wet aggregates.

Both RRB and GGS granulometric distribution models regressed well to the experimental PSD data, as can be seen in Table 4. The models accuracy was assessed using the correlation coefficient (R^2). The found R^2 values were extremely close between them, all *circa* 0.99, suggesting good quality experimental data. It can be asserted, even if in a tenuous way, that the higher R^2 values of GGS model (nearest 1 unit) suggest a slightly more suitable distribution of Gates-Gaudin-Schuhmann model, as compared to Rosin-Rammler-Bennet model, to represent PSD of verdete rock dry and wet aggregates.

Table 4. Rosin-Rammler-Bennet (RRB) and Gates-Gaudin-Schuhmann (GGS) mathematical model parameters and determined equations.

Sample	Granulometric Distribution Model	Parameters		Nonlinear equation	Linear equation	Correlation Coefficient (R ²)
Dry Aggregate	RRB	n	D'	$\begin{bmatrix} \begin{pmatrix} D_i \end{pmatrix}^{1.3203} \end{bmatrix}$	$ln\left[ln\left(\frac{1}{1-X_i}\right)\right] = 1.3203 \ ln \ D_i$	0.9873
		1.3203	1,327.2517	$X_i = 1 - e^{\left[-\left(\frac{D_i}{1327.2517}\right)^{1.3203}\right]}$	$[(1 - X_i)]$ - 9.4941	
	GGS	k	m	D_i D_i	$ln X_i = 1.0388 ln D_i - 8.0327$	0.9985
		2,281.6915	1.0388	$X_i = \left(\frac{D_i}{2281.6915}\right)^{1.0300}$		
Wet Aggregate	RRB	n	D'	$[(D_i)^{1.3626}]$	$ln\left[ln\left(\frac{1}{1-X_i}\right)\right] = 1.3626 \ ln \ D_i$	0.0076
		1.3626	1,316.0261	$X_i = 1 - e^{\left[-\left(\frac{D_i}{1316.0261}\right)^{1.3626}\right]}$	$[(1 - X_i)]$ - 9.7867	0.9856
	GGS	k	m	$X_i = \left(\frac{D_i}{2232.9620}\right)^{1.0754}$	$\ln X_i = 1.0754 \ln D_i - 8.2925$	0.9930

According to Liu et al. 32, D' and n parameters of RRB distribution model play a dominant role in the determination of the distribution characteristics, in other words, the PSD of any particle system described by using this model can be distinguished with values of D' and n. Lower values of m parameter of GGS distribution model suggest that more fine aggregates, more large particles (coarse aggregates) and fewer particles in the middle range will be produced³³. Comparing the RRB and GGS models parameters obtained for dry and wet aggregates, it was observed a good convergence between the found values, corroborating the hypothesis that the ore mother-sample did not have an amount of fine particles sufficient to create appreciable differentiation between the A and B samples, as foreseen in results obtained by granulometric curves and size and surface parameters.

Due to the lack of studies in the literature dedicated to the description of the particle size distribution of the verdete rock aggregates and its modeling through RRB and GGS models, the work presented here suggests the suitability of the methodology proposed by means of sieving techniques for predicting the grain-size performance the verdete rock beyond enriching its mineral characterization. The developed study could be optimized and enlarged in the purpose to corroborate the described forecasts and to increase of the results representativeness. In this sense, it is recommended to use the method described with other verdete ore granulometry and coming of other mineral reserves, as well as to realize the sieving experiments in triplicate.

4. Conclusions

A grain-size analysis study of verdete rock and adjustments to the Rosin-Rammler-Bennet (RRB) Gates-Gaudin-Schuhmann and (GGS) granulometric distribution models were satisfactorily developed through sieving techniques with sieves of Tyler standard screen scale of 4, 8, 28, 35, 48, 100, and 200 mesh. Both RRB and GGS granulometric models regressed well to the experimental particle size distribution data, presenting correlation coefficient values were extremely close between them approximately 0.99. The PSD results suggested that: 65.97% dry aggregates and 67.68% wet aggregates had a particle size with mean diameter > 0.0050 mm; an extremely similar behavior of the grain-size distributions presented by samples of ore dry and wet aggregates; and a tiny presence of fine particles natural from the analyzed ore sample. The results suggested the suitability of the methodology proposed by work to predict the grain-size performance the verdete ore beyond to show itself as a contribution to the enriching of the mineral characterization of the studied rock, as a potassium potential source for the mineral processing Brazilian industry.

5. References

[1] Ahmed, M. M., A contribution to new measure for evaluation of a particle size distribution, Mineral Processing and Extractive Metallurgy: Transactions of the Institution of Mining and Metallurgy: Section C 116 (4) (2007) 221-230. http://doi.org/10.1179/174328507X198726.

- [2] Bolaji, O. T., Awonorin, S. O., Sanni, L. O., Shittu, T. A., Adewumi, J. K., Modeling of particle size distribution and energy consumption of wet milled maize at varying soaking period and method in the production of Ogi, Particulate Science and Technology 37 (1) (2017) 94-102. https://doi.org/10.1080/02726351.2017.1343882.
- [3] Petrakis, E., Stamboliadis, E., Komnitsas, K., Evaluation of the relationship between energy input and particle size distribution in comminution with the use of piecewise regression analysis, Particulate Science and Technology 35 (4) (2016) 479-489. https://doi.org/10.1080/02726351.2016.1168894.
- [4] Kimura, S., Ito, T., Minagawa, H., Grain-size analysis of fine and coarse non-plastic grains: comparison of different analysis methods, Granular Matter 20 (3) (2018) 1-15. https://doi.org/10.1007/s10035-018-0820-3.
- [5] Savitha, HG., Manohar, B., Studies on grinding and extraction of oil from fenugreek (*Trigonella foenum-graecum*) seed, International Journal of Food Engineering 11 (2) (2015) 275-283. https://doi.org/10.1515/ijfe-2014-0262.
- [6] Miranda, M. R., Cardoso, C. R., Ataíde, C. H., Physical and chemical characterization of sorghum bagasse, Materials Science Forum 727-728 (2012) 1683-1688. https://doi.org/10.4028/www.scientific.net/MSF.727-

728.1683.

- [7] Liu, S., Li, Q., Song, J., Study on the grinding kinetics of copper tailing powder, Powder Technology 330 (2018) 105-113. https://doi.org/10.1016/j.powtec.2018.02.025.
- [8] Castro, A. M., Castilho, L. R., Freire, D. M. G., Characterization of babassu, canola, castor seed and sunflower residual cakes for use as raw materials for fermentation processes, Industrial Crops and Products 83 (2016) 140-148. https://doi.org/10.1016/j.indcrop.2015.12.050.
- [9] Cho, J., Sohn, H. Y., Effects of particle shape and size distribution on the overall fluid-solid reaction rates of particle assemblages, The Canadian Journal of Chemical Engineering 94 (8) (2016) 1516-1523. https://doi.org/10.1002/cjce.22533.
- [10] Singh, M., Kumar, S., Kumar, S., Nandan, G., Gupta, M., Characterization of iron-ore suspension at insitu conditions, Materials today: proceedings 5 (9) (2018) 17845-17851. https://doi.org/10.1016/j.matpr.2018.06.110.

- [11] Kacham, A. R., Suri, A. K., Application of a topochemical reaction model to predict leaching behavior of high carbonate uranium ores in alkaline solutions: an experimental case study, Hydrometallurgy 141 (2014) 67-75. https://doi.org/10.1016/j.hydromet.2013.10.005.
- [12] Xiong, Y., Wu, B., Zhu, J., Fan, X., Cai, P., Wen, J., Liu, X., Preparation of magnesium hydroxide from leachate of dolomitic phosphate ore with dilute waste acid from titanium dioxide production, Hydrometallurgy 142 (2014) 137-144. https://doi.org/10.1016/j.hydromet.2013.11.013.
- [13] Santana, R. C., Ribeiro, J. A., Santos, M. A., Reis, A. S., Ataíde, C. H., Barrozo, M. A. S., Flotation of fine apatitic ore using microbubbles, Separation and Purification Technology 98 (2012) 402-409. https://doi.org/10.1016/j.seppur.2012.06.014.
- [14] Taşdemir, A., Taşdemir, T., Comparative study on PSD models for chromite ores comminuted by different devices. Particle and Particle Systems Characterization 26 (1-2) (2009) 69-79. https://doi.org/10.1002/ppsc.200800035.
- [15] Piza, P. A. T., Bertolino, L. C., Silva, A. A. D., Sampaio, J. A., Luz, A. B., Verdete da região de Cedro de Abaeté (MG) como fonte alternativa para potássio, Geociências 30 (3) (2011) 345-356. https://www.periodicos.rc.biblioteca.unesp.br/index.ph p/geociencias/article/view/5551.
- [16] Santos, W. O., Mattiello, E. M., Costa, L. M., Abrahão, W. A. P., Characterization of verdete rock as a potential source of potassium, Revista Ceres 62 (4) (2015) 392-400. https://doi.org/10.1590/0034-737X201562040009.
- [17] Santos, W. O., Mattiello, E. M., Vergutz, L., Costa, R. F., Production and evaluation of potassium fertilizers from silicate rock, Journal of Plant Nutrition and Soil Science 179 (4) (2016) 547-556. https://doi.org/10.1002/jpln.201500484.
- [18] Guimarães, D., Geologia do Brasil, Rio de Janeiro, 1964.
- [19] Moreira, D. S., Uhlein, A., Fernandes, M. L. S., Mizusaki, A. M., Galéry, R., Delbem, I. D., Estratigrafia, petrografia e mineralização de potássio em siltitos verdes do grupo Bambuí na região de São Gotardo, Minas Gerais, Geociências 35 (2) (2016) 157-171.
- http://www.ppegeo.igc.usp.br/index.php/GEOSP/article/view/9016/8281.

- [20] Silva, A. A. S., Medeiros, M. E., Sampaio, J. A., Garrido, F. M. S., Verdete de Cedro do Abaeté como fonte de potássio: caracterização, tratamento térmico e reação com CaO, Matéria (Rio de Janeiro) 17 (3) (2012) 1062-1074. https://doi.org/10.1590/S1517-70762012000300004.
- [21] Silva, A. A., Lana, R. M. Q., Incubação do verdete com diferentes fontes de ácidos para disponibilização de potássio, cálcio, magnésio do solo, Holos 5 (2015) 73-83. https://doi.org/10.15628/holos.2015.3210.
- [22] Revista Brasil Mineral, Potássio: Projeto da Kalium opera em novembro, 2018. http://www.brasilmineral.com.br/noticias/projeto-da-kalium-opera-em-novembro.
- [23] Kalium Mineração S.A., Projeto Glauconita, KM Kalium Mineração S.A. (2017) 1-41. https://docplayer.com.br/74701318-Km-kalium-mineracao-s-a-projeto-glauconita.html.
- [24] Silva, A. A. S., Medeiros, M. E., Sampaio J. A., Garrido, F. M. S., Caracterização do verdete de Cedro do Abaeté para o desenvolvimento de um material com liberação controlada de potássio, Holos 5 (2012) 42-51. https://doi.org/10.15628/holos.2012.1093.
- [25] Lima, O. N. B., Uhlein, A., Britto, W., Estratigrafia do grupo Bambuí na Serra da Saudade e geologia do depósito fosfático de Cedro do Abaeté, Minas Gerais, Revista Brasileira de Geociências 37 (4, suppl.) (2007) 204-215. https://doi.org/10.25249/0375-7536.200737S4204215.
- [26] Santos, W. O., Mattiello, E. M., Pacheco, A. A., Vergutz, L., Souza-Filho, L. F. S., Abdala, D. B., Thermal treatment of a potassium-rich metamorphic rock in formation of soluble K forms, International Journal of Mineral Processing 159 (2017) 16-21. https://doi.org/10.1016/j.minpro.2016.12.004.
- [27] Eichler, V., Lopes, A. S., Disponibilidade do potássio do Verdete de Abaeté, calcinado com e sem calcário magnesiano, para a cultura do milho (*Zea mays* L.), em solo de textura argilosa, Ciência e Prática 7 (2) (1983) 136-156.
- [28] Leite, P. C., Efeitos de tratamentos térmicos em misturas de verdete de Abaeté, fosfato de Araxá e calcário magnesiano, na disponibilidade de potássio e fósforo. 1985. 146 f. Dissertation (Master's in Agronomy) School of Agriculture of Lavras, Lavras, 1985.
- [29] Martins, V., Gonçalves, A. S. F., Marchi, G., Guilherme, L. R. G., Martins, E. S., Solubilização de potássio em misturas de verdete e calcário tratadas

- termoquimicamente, Pesquisa Agropecuária Tropical 45 (1) (2015) 66-72. https://doi.org/10.1590/1983-40632015v4527917.
- [30] Pereira, A. C., Carvalho, I. S. B., Rocha, S. D. F., Glauconite-bearing rocks as alternative potassium source for fertilizer by thermal processing with additives, Brazilian Applied Science Review 3 (2) (2019) 1455-1467. https://doi.org/10.34115/basrv3n2-050.
- [31] Pereira, A. C., Becheleni, E. M. A., Gomes, M. R. S., Rocha, S. D. F., Fluoride aided potassium extraction from Verdete rock by thermal processing with ferrous sulfate heptahydrate, Brazilian Applied Science Review 3 (2) (2019) 1373-1384. http://www.brjd.com.br/index.php/BASR/article/view/1565.
- [32] Liu, S., Li, Q., Xie, G., Li, L., Xiao, H., Effect of grinding time on the particle characteristics of glass powder, Powder Technology 295 (2016) 133-141. https://doi.org/10.1016/j.powtec.2016.03.030.
- [33] Lu, P., Jefferson, I. F., Rosenbaum, M. S., Smalley, I. J., Fractal characteristics of loess formation: evidence from laboratory experiments, Engineering Geology 69 (3-4) (2003) 287-293. https://doi.org/10.1016/S0013-7952(02)00287-9.