



Polímeros
ISSN: 0104-1428
ISSN: 1678-5169
Associação Brasileira de Polímeros

Polysaccharides of red alga *Gracilaria intermedia*: structure, antioxidant activity and rheological behavior

Castro, Joana Paula Lima de; Costa, Luís Eduardo Castanheira; Pinheiro, Maísa Pessoa; Francisco, Thiago dos Santos; Vasconcelos, Pedro Hermano Menezes de; Funari, Lizandra Mistrello; Daudt, Renata Moschini; Santos, Gustavo Ramalho Cardoso dos; Cardozo, Nilo Sérgio Medeiros; Freitas, Ana Lúcia Ponte

Polysaccharides of red alga *Gracilaria intermedia*: structure, antioxidant activity and rheological behavior

Polímeros, vol. 28, no. 2, 2018

Associação Brasileira de Polímeros

Available in: <http://www.redalyc.org/articulo.oa?id=47058473012>

DOI: 10.1590/0104-1428.013116

Polysaccharides of red alga *Gracilaria intermedia*: structure, antioxidant activity and rheological behavior

Joana Paula Lima de Castro¹

Universidade Federal do Ceará, Brazil

Luís Eduardo Castanheira Costa¹

Universidade Federal do Ceará, Brazil

Maísa Pessoa Pinheiro¹

Universidade Federal do Ceará, Brazil

Thiago dos Santos Francisco²

Universidade Federal do Ceará, Brazil

Pedro Hermano Menezes de Vasconcelos³

Instituto Federal de Educação, Ciência e Tecnologia do Ceará, Brazil

Lizandra Mistrello Funari⁴

Universidade Federal do Rio Grande do Sul, Brazil

Renata Moschini Daudt⁴

Universidade Federal do Rio Grande do Sul, Brazil

Gustavo Ramalho Cardoso dos Santos⁵

Universidade Federal do Rio de Janeiro, Brazil

Nilo Sérgio Medeiros Cardozo^{4*} nilo@enq.ufrgs.br

Universidade Federal do Rio Grande do Sul, Brazil

Ana Lúcia Ponte Freitas¹

Universidade Federal do Ceará, Brazil

Polímeros, vol. 28, no. 2, 2018

Associação Brasileira de Polímeros

Received: 11 October 2016

Revised document received: 13 April 2017

Accepted: 17 June 2017

DOI: 10.1590/0104-1428.013116

CC BY

Abstract: A sulfated polysaccharide fraction from the red alga *Gracilaria intermedia* (PLS) was obtained by papain digestion (60 °C, 30 min). The extract was subjected to colorimetry and turbidimetry analysis, Fourier transform infrared (FTIR) spectroscopy, ¹H, ¹³C and ²D ¹H COSY nuclear magnetic resonance (NMR) and gas chromatography/mass spectrometry analysis. Antioxidant activity tests were performed (chelation of ferrous ion, total antioxidant capacity, and scavenging of DPPH radicals); significant activity of the extract indicated that these polysaccharides may be used as non-synthetic antioxidants. The rheological behavior of aqueous polysaccharide solutions was studied at 25 ± 1 °C using steady-shear and dynamic oscillatory measurements. All the solutions analyzed showed pseudoplastic behavior and potential to act as a thickening agent, as proved through a preliminary comparison with a commercial product used for this application.

Keywords: antioxidant activities, *Gracilaria intermedia*, polysaccharides, rheological behavior, structure.

1. Introduction

Polysaccharides are polymers that show a wide range of properties depending on their monomeric composition and have applications in different types of industries. Applications include the use as a stabilizer, thickener, flocculant, and water-retaining agent in the textile, food, pharmaceutical, and biotechnology industries^[1-4].

Carrageenans and agarans are sulfated polysaccharides obtained from red algae. The industrial applications of these polymers are closely dependent on their rheological properties. Such properties make these two polymers important gelling agents and thickeners, especially in the food industry^[5]. Sulfated polysaccharides also exhibit various biological activities, including antioxidant activities, among others^[6-9]. Therefore, they also have potential application as agents to reduce cellular damage and to prolong the shelf time of foods; these are areas where compounds with antioxidant activity are currently in great demand^[10-12]. Non-synthetic compounds, particularly polysaccharides, with antioxidant potential are currently under investigation by several research groups^[13-18] as an alternative to synthetic antioxidant compounds traditionally used in the food and pharmaceutical industries such as butylated hydroxytoluene (BHT), butylated hydroxyanisole (BHA), and tert-butyl hydroquinone (TBHQ) due to their suspected damage to liver tissue and carcinogenic potential^[9,13,19].

Red algae from the genus *Gracilaria* are economically important in the phycocolloids industry^[20] and are currently the source of about 65% of the 7.5 tons of agar produced annually throughout the world^[21]. Sulfated polysaccharides obtained from species of the genus *Gracilaria* contain 3-linked- β -D-galactopyranose (G unit) and 4-linked-3,6-anhydro- α -L-galactopyranose (LA unit)^[22-25] with substitution of hydroxyl groups by ester sulfate, methyl groups, and pyruvic acid^[23-26] (Figure 1). *Gracilaria* is very common in the Northeast Brazilian coast and its extraction has been pointed as an alternative for the economic inclusion of part of the population of this region^[27].

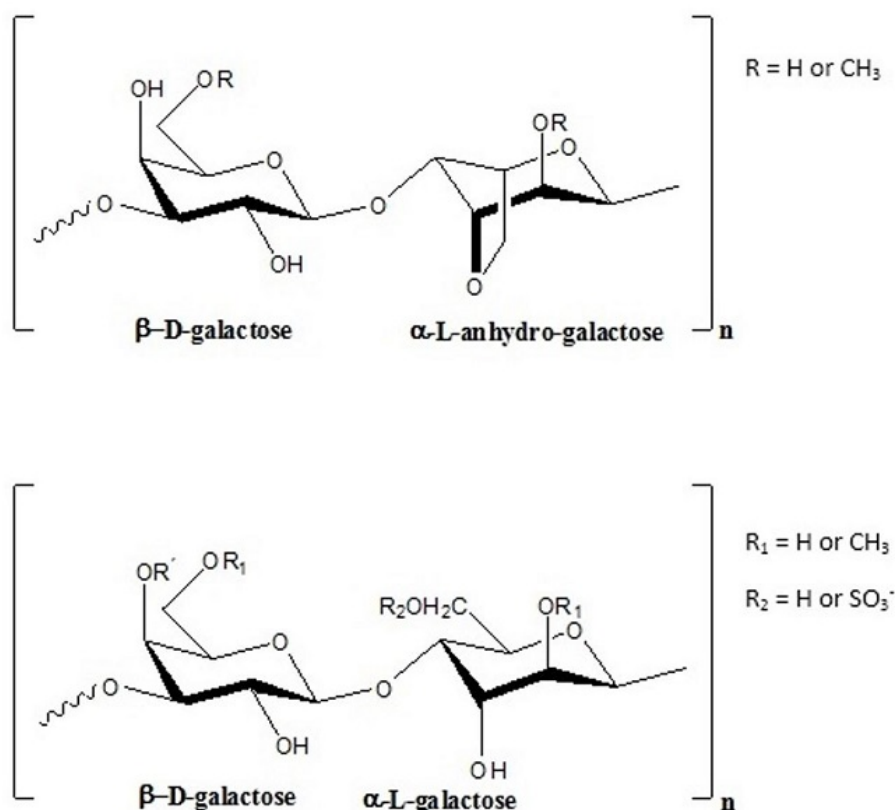


Figure 1.

Chemical structure of agar type molecules with the different types of sugar units and substituents.

Yield of extraction and final properties of agarans depend strongly on the seaweed species, the methodology of extraction of polysaccharides, seasonal variations and the place of origin of the specimens. So the chemical, structural, and rheological characterization of polysaccharides extracted from seaweeds is necessary^[26,28]. In the specific case of the species *Gracilaria intermedia*, the related scientific research *Gracilaria intermedia* is still scarce. To the knowledge of the authors, only studies on its taxonomy^[28-31] and ecological aspects^[32] have been reported.

In this context, the goal of this paper was to characterize sulfated polysaccharides extracted from the red seaweed *Gracilaria intermedia*. This characterization was performed by spectroscopy, turbidimetric and colorimetric methods. The antioxidant activity of the polymer and its rheological behavior in solution were also evaluated.

2. Materials and Methods

2.1 Materials

Papain, cysteine and cetylpyridinium chloride (CPC) were obtained from Vetec (Brazil), ammonium molybdate was purchased from Dinâmica (Brazil) and D-galactose from Acros Organics (USA). Ferrozine, 1, 1-diphenyl-2-picrylhydrazyl (DPPH) and bovine serum albumin (BSA)

were purchased from Sigma–Aldrich (USA). Ascorbic acid was obtained from Synth (Brazil) and Carboxymethyl cellulose was obtained from Mix (Brazil). All other solvents and chemicals were of analytical grade.

2.2 Extraction of sulfate polysaccharides

Specimens of *G. intermedia* were collected in April 2013 on the Atlantic coast of Brazil (Taiba beach, São Gonçalo - Ceará). The collected seaweed were cleaned of epiphytes, washed with distilled water, and stored at -20 °C. A voucher specimen (n° 2386) was deposited in the phycological Herbarium of the Laboratory of Marine Sciences, Universidade Federal do Ceará, Brazil.

The enzymatic extraction of polysaccharides was performed according to the methodology of Farias et al.^[33], with some modifications. The dried tissue (5 g) was suspended in 250 mL of 0.1 mol.L⁻¹ sodium acetate buffer (pH 5.0), containing 1 g of papain, 5×10⁻³ mol.L⁻¹ EDTA, and 5×10⁻³ mol.L⁻¹ cysteine, and incubated at 60 °C for 30 min. The incubation solution was then filtered through a nylon membrane, and the homogenate was retained. The polysaccharides in solution were precipitated with 16 mL of 10% cetylpyridinium chloride (CPC) solution. After 24 h at room temperature (25 °C), the mixture was centrifuged at 2,560 × *g* for 20 min at 20 °C. The polysaccharides were washed with 500 mL of 0.05% CPC solution, dissolved with 100 mL of a 2 mol.L⁻¹ NaCl-ethanol (100:15, v/v) mixture, and the excess of salts was removed by precipitation and wash with 200 mL of absolute ethanol. After 24 h at 4 °C, the precipitate was collected by centrifugation (2,560 × *g* for 20 min at 20 °C), washed extensively with ethanol-80%, then absolute ethanol. After this, the polysaccharides (PLS) were washed with acetone, which was followed by hot air drying (60 °C) until all the acetone was removed.

2.3 Chemical analysis

Sulfate content of PLS was determined by the barium-gelatin method^[34] after hydrolysis of the sample in 1 mol.L⁻¹ HCl (5 h, 105 °C) using sodium sulfate (Na₂SO₄) as standard. To measure the amount of total neutral carbohydrates the phenol-sulfuric method was performed^[35] with a standard curve prepared with D-galactose. The protein content was measured by the Bradford method^[36] using bovine serum albumin (BSA) as standard.

2.4 Monosaccharide composition

Samples of the polysaccharides extracted from *G. intermedia* (5 mg) were hydrolyzed with 5 mol.L⁻¹ trifluoroacetic acid for 4 h at 100 °C, reduced with borohydride, and the alditols were acetylated with

acetic anhydride:pyridine (1:1, v/v). The alditols acetates were dissolved in chloroform and analyzed in a gas-liquid chromatograph/mass spectrometer (GCMS-QP2010 Shimadzu, Japan) with a DB-5ms column (Agilent) [37].

2.5 Infrared spectroscopy

The Fourier transform infrared spectra (FTIR) were obtained with a Shimadzu IR spectrophotometer (FTLA 2000, ABB-BOMEM, Canada) with measurements in the wavenumber range of 400-4000 cm^{-1} using 20 scans. The samples were analyzed as KBr pellets.

2.6 Nuclear magnetic resonance (NMR) spectroscopy

The spectroscopic technique of nuclear magnetic resonance (NMR) is a method commonly used for structural characterization of seaweed polysaccharides [38-41].

^1H , ^{13}C and 2D ^1H COSY NMR spectra in D_2O were recorded at 353 K on a Fourier transform spectrometer (Bruker Avance DRX 500, USA) with an inverse multinuclear gradient probe-head equipped with z-shielded gradient coils.

2.7 Determination of antioxidant activity

2.7.1 Total antioxidant capacity

The total antioxidant capacity test, based on the reduction of Mo^{6+} to Mo^{5+} , was performed by the methodology proposed by Prieto, Pineda & Aguilar [42]. Aliquots of the polysaccharide solution (0.1 mL) of different concentrations (0.1% to 1.5%) were mixed with 1 mL of the reagent solution (0.6 mol.L^{-1} sulfuric acid, 28×10^{-3} mol.L^{-1} sodium phosphate, and 4×10^{-3} mol.L^{-1} ammonium molybdate). This step was followed by incubation at 95 °C for 90 min. Subsequently, absorbance was read at 695 nm. A standard curve under the same conditions was prepared with solutions of ascorbic acid. Thus, the results are presented as equivalence of ascorbic acid (mg/g EAAsc).

2.7.2 Iron (Fe^{2+}) chelating activity

The iron ion is associated with lipid peroxidation due to the Fenton reaction. This process is related to a series of diseases [43-45]. The antioxidants form a complex with this ion, thus preventing cell damage [46]. The ferrous ion chelation activity of PLS was investigated according to the methodology used by Zhang et al. [18]. Aliquots of 1 mL of the polysaccharide solution at different concentrations (0.1% to 1.5%) were

mixed with 0.05 mL of FeCl_2 ($2 \times 10^{-3} \text{ mol.L}^{-1}$), 0.2 mL of ferrozine ($5 \times 10^{-3} \text{ mol.L}^{-1}$), and 2.75 mL of water. The solution was agitated and incubated at room temperature for 10 min. Absorbance of the solution at 562 nm was measured. The chelating activity was calculated using the following Equation 1 :

where A_0 is the absorbance of the blank, A_1 is the absorbance of the test solution, and A_2 is the absorbance of a solution identical to A_1 with the substitution of FeCl_2 for the same aliquot of water. Ascorbic acid was used as the positive control.

2.7.3 Scavenging of DPPH radicals

The 1,1-diphenyl-2-picrylhydrazyl free radical (DPPH) scavenging activity of PLS was measured using the method used by Wu et al.^[16]. Ascorbic acid was used as a positive control. The inhibition (%) was calculated using the following Equation 2 :

where A_0 and A_1 are the absorbance of the blank and sample, respectively.

2.8 Rheological behavior

Rheological measurements were carried out in a rotational rheometer (Ares, TA Instruments, New Castle, DE, USA), using cone-plate geometry (50 mm diameter, cone angle of 0.0399 rad, gap of 0.0553 mm). All measurements were run at $25 \pm 1^\circ\text{C}$.

Dynamic tests were performed to evaluate the behavior of storage (G') and loss (G'') moduli as a function of frequency. The frequency sweep tests were performed in the linear viscoelastic region (LVR), determined through strain sweep tests. Three samples containing the extracted sulfated PLS (1.0%, 1.25%, and 1.5%) were analyzed.

Flow curves were obtained by recording shear stress values when shearing the samples at an increasing shear rate from 0.1 to 100 s^{-1} with increment of 4 s^{-1} and then reducing it through the same path. This test was performed for samples containing PLS in different concentrations (1.0%, 1.25%, and 1.5%). Additionally, for testing the potential of PLS as thickening agent, solutions containing carboxymethylcellulose (CMC), a well-known thickening agent, and blends of CMC and PLS were also analyzed. The concentrations of the referred CMC solutions were of 0.75% of CMC and 1.5%. In the case of the blends, two formulations were prepared, one containing 1.0% of PLS and 0.5% of CMC and another containing 0.75% of PLS and 0.75% of CMC.

The data of the flow curves were fitted using the Ostwald-de Waele model (power-law), Equation 3 :

where: η is the shear viscosity (Pa.s), K is the consistency index (Pa.s); $\dot{\gamma}$ is the shear rate (s^{-1}), n is the power-law index (dimensionless) and K is the consistency index (Pa.s). The estimation of the parameters K and n

was performed using the least-square method, in the software Microsoft Excel.

3. Results and Discussions

3.1 Yield and chemical analysis

The yield of polysaccharides by mass of seaweed *Gracilaria intermedia* was $17.0 \pm 1.18\%$. Studies which extraction took place by enzymatic digestion of seaweed *Gracilaria cornea* (Brazil) achieved yields of 18.0% ^[28] and 11.0 to 21.4% ^[47]. Souza et al.^[12] in Brazil obtained a polysaccharide yield of 27.2% for the seaweed *Gracilaria birdeae* while Freile-Pelegrin and Robledo^[48], on a seasonal study in Mexico, obtained yield from 25.0 to 39.3% for *Gracilaria cervicornis*. In extraction performed at room temperature, in Brazil, Maciel et al.^[23] were able to yield 6.5% of polysaccharides from seaweed *Gracilaria birdeae*. Making the extraction of polysaccharides with autoclave in India, yields of 14.8% for *Gracilaria debilis* and 15.2% for *Gracilaria Salicornia*^[49] were achieved.

Polysaccharides from *Gracilaria intermedia* (PLS) exhibited $6.60 \pm 0.13\%$ of sulfate, which is within the range of sulfate polysaccharides content from the other *Gracilaria* species (2.30 - 8.90%)^[23]. More recent studies indicate that this interval is actually wider, since percentages of sulphate of $0.76 \pm 0.08\%$ (*Gracilaria debilis*, India)^[49], $1.00 \pm 0.05\%$ (*Gracilaria caudata*, Brazil)^[26], and 15.66% (*Gracilaria cornea*, Brazil)^[28] have already been reported.

The carbohydrate content was $54.64 \pm 1.19\%$, consistent with the percentage value of D - galactose found in other *Gracilaria* species. Amorin et al.^[50] performed the test sulfuric phenol in different fractions of *Gracilaria ornata*, Brazil, and found levels of sugars ranging between 33.14 and 62.20% . In polysaccharide fractions of seaweed *Gracilaria birdeae*, Brazil, sugar content between 30.8 and 68.2% ^[51] were found.

Proteins were not detected in the polysaccharide fraction obtained from seaweed *Gracilaria intermedia*.

3.2 Monosaccharide composition

The monosaccharide composition of the polysaccharide extracted from *G.intermedia* was determined based on gas chromatography/mass spectrometry analysis of the alditol acetates formed after acid hydrolysis. The major monosaccharide detected was galactose. This finding is in agreement with results presented by Pomin & Mourão^[52] who describe the presence of sulfated galactans in red algae. No other sugar was detected up to a limit of $< 2\%$ as % of dry weight, ensuring the purity of the material.

3.3 Infrared spectroscopy

Figure 2 shows the FTIR spectrum of the extracted polysaccharide fraction, expanded in the region between 1400 and 700 cm^{-1} to better identify the sulfate groups bands. The bands found at 1375 and 1258 cm^{-1} may be attributed to sulfate ester groups^[51,52], the band at 1075 cm^{-1} corresponds to galactan^[53,54], and the band at 892 cm^{-1} corresponds to the agar-specific band^[55]. The band at 931 cm^{-1} corresponds to the C-O-O group present in the 3,6 -anhydrogalactose, and the bands between 820 and 860 cm^{-1} indicate the presence of sulfate groups^[53-57].

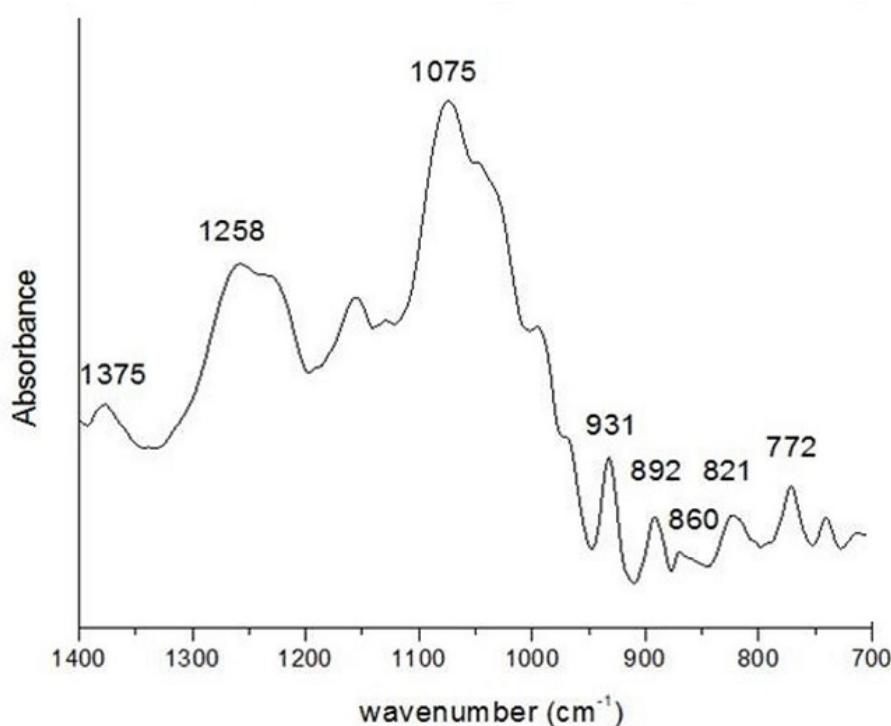


Figure 2.
The IR spectra of the PLSs were determined using a Fourier transform infrared spectrometer (FTIR).

3.4 NMR spectroscopy

Figures 3 and 4 show, respectively, the 1D (^1H and ^{13}C) and 2D NMR spectra of the polysaccharide fraction extracted from *G.intermedia*. The ^1H NMR spectrum is somewhat complex due to overlap and enlargement of the signs (Figure 3 a). It shows the signals from the α -anomeric proton at δ 5.62, 5.14 and 4.69 (assigned, respectively, to 3,6- α -L-anhydrogalactose linked to β -D-galactose, α -L-galactose-6-sulfate linked to β -D-galactose and β -D-galactose linked to 3,6- α -L-anhydrogalactose), and from the H-1 of β -D-galactose linked to 3,6- α -L-anhydrogalactose with a signal at δ 4.69^[23,26,38-41,58]. However, the H-1 β -D-galactose linked to α -L-galactose-6-sulfate was not detected, probably due to the signal

overlap. Others studies state that when this unit is linked with α -3,6-anhydrogalactose and L- α -L-galactose-6-sulfate, there are minor chemical variations in the region of 4.65-3.90 ppm. Therefore, its identification is difficult^[23,26,58,59].

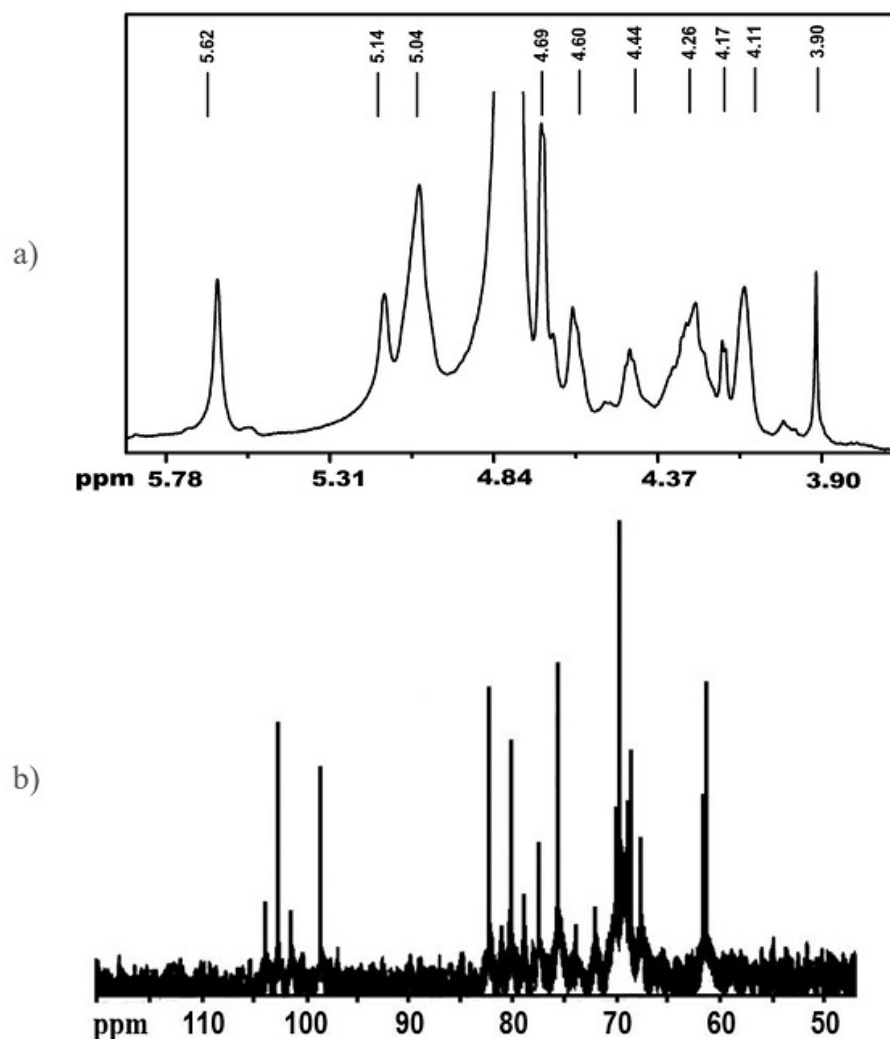


Figure 3.
¹H NMR (a) and ¹³C NMR (b) spectra of the PLSs
extracted from *Gracilaria intermedia* in D₂O solution.

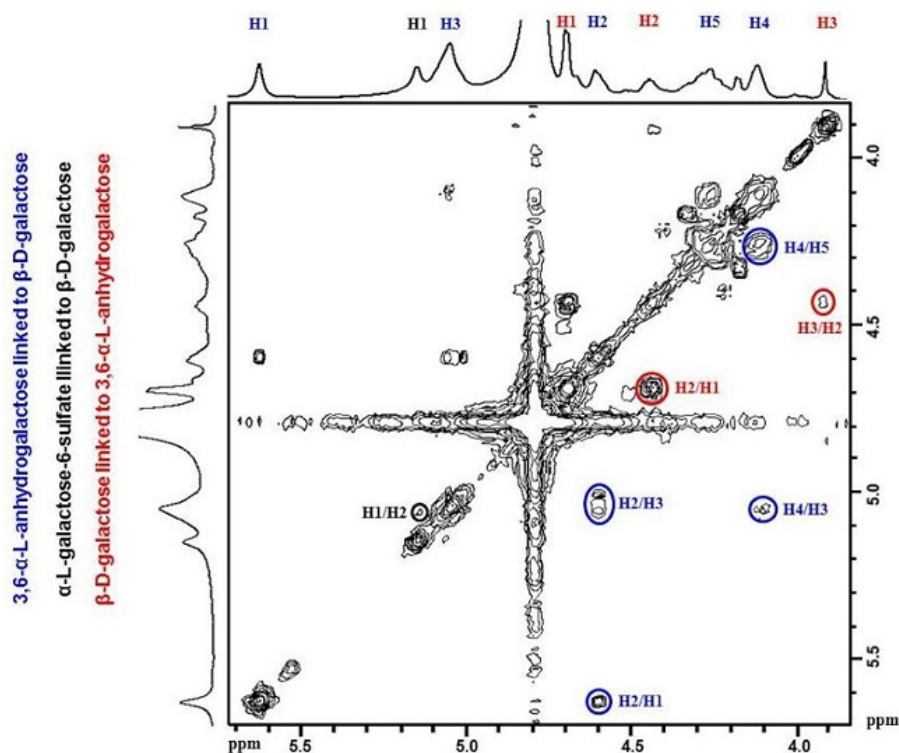


Figure 4.

2D COSY spectrum of PLSs from *Gracilaria intermedia* in D₂O.

The anomeric region of ¹³C NMR (90-110 ppm) shows four main signals (Figure 3 b), which were assigned based on the literature data^[23,26,38-41,58,60,61], just like the other carbons observed in the region of 59 – 85 ppm (Table 1). The C-1 of β-D-galactose linked to α-L-galactose-6-sulfato at δ 103.7; C-1 of β-D-galactose linked to 3,6-α-L-anhydrogalactose at δ 102.5; C-1 of α-L-galactose-6-sulfato linked to β-D-galactose at δ 101.25 and C-1 of 3,6-α-L-anhydrogalactose linked to β-D-galactose at δ 98.4.

Table 1.

¹H and ¹³C NMR chemical shifts for residues of *G. intermedia* polysaccharide.

Residue	¹ H chemical shift (ppm)					
	H-1	H-2	H-3	H-4	H-5	H-6
3,6-α-L-anhydrogalactose linked to β-D-galactose	5.62	4.60	5.04	4.11	4.26	nd*
β-D-galactose linked to 3,6-α-L-anhydrogalactose	4.69	4.44	3.91	nd*	nd*	nd*
α-L-galactose-6-sulfato linked to β-D-galactose	5.14	5.05	nd*	nd*	nd*	nd*
Residue	¹³ C chemical shift (ppm)					
	C-1	C-2	C-3	C-4	C-5	C-6
3,6-α-L-anhydrogalactose linked to β-D-galactose	98.4	nd*	81.2	77.5	nd*	69.5
β-D-galactose linked to 3,6-α-L-anhydrogalactose	102.5	nd*	82.1	68.7	73.8	61.5
α-L-galactose linked to β-D-galactose	101.25	nd*	nd*	78.75	71.9	67.5
β-D-galactose linked to α-L-galactose-6-sulfato	103.7	70.5	80.2	69.3	75.6	61.8

2D COSY was used to determine the proton resonance sequence (Figure 4). Regarding the dimer formed by 3,6-α-L-anhydrogalactose linked to β-D-galactose five couplings relating the 3,6-α-L-anhydrogalactose u and two couplings assigned

β -D-galactose are observed. The protons that are coupled are H-1 (3,6- α -L-anhydrogalactose)/H-2 (3,6- α -L-anhydrogalactose) at δ 5.62/4.60; H-2 (3,6- α -L-anhydrogalactose)/H-3 (3,6- α -L-anhydrogalactose) at δ 4.60/5.04; H-3 (3,6- α -L-anhydrogalactose)/H-4 (3,6- α -L-anhydrogalactose) at δ 5.04/4.11; H-4 (3,6- α -L-anhydrogalactose)/H-5 (3,6- α -L-anhydrogalactose) at δ 4.11/4.26; H-1 (β -D-galactose)/H-2 (β -D-galactose) at δ 4.69/4.44 and H-2 (β -D-galactose)/H-3 (β -D-galactose) at δ 4.44/3.91. For the α -L-galactose-6-sulfate dimer linked to β -D-galactose a coupling is observed for the H-1 (α -L-galactose-6-sulfato)/H-2 (α -L-galactose-6-sulfato) at δ 5.14/5.05. Although other engagements can be observed, it is not possible to identify the sequence of hydrogens because the one-dimensional ^1H spectrum overlap them.

3.5 Determination of antioxidant activity

The total antioxidant capacity was determined by forming a phosphomolybdenum complex when Mo^{6+} is reduced to Mo^{5+} ; PLS showed activity with 28.98 ± 1.86 mg/g EAAsc. In studies performed by Costa et al.^[62] the amount of ascorbic acid in the seaweeds *Codium isthmocladum* and *Spatoglossum schroederi* were (9.2 mg/g EAAsc) and (14.4 mg/g EAAsc) respectively. These values are inferior amount to the ones exhibited by the polysaccharides extracted from *G. intermedia*.

The ability of the PLS to chelate iron (II) ions was dose-dependent. Even though PLS led to higher chelation percentage than the ones obtained from ascorbic acid (Figure 5 a), its activity is low if compared to other polysaccharides extracted from seaweeds. The values for PLS were $11.64 \pm 0.83\%$ (PLS 0.1%) and $2819 \pm 0.97\%$ (PLS 1.5%). Costa et al.^[62] found a value of 40.2% of iron (III) chelation in solutions of 1.5 mg.mL^{-1} of polysaccharides from *Gracilaria caudata*. Wang et al.^[63] studied different polysaccharide fractions from *Laminaria japonica* and found a value of 29.48% for quelation in a 1.17 mg.mL^{-1} solution.

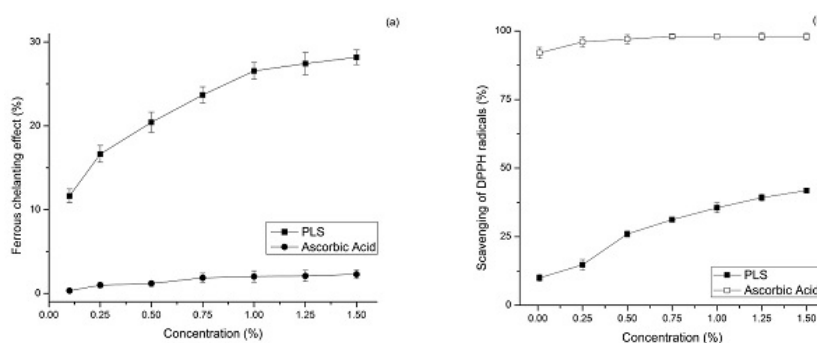


Figure 5.

Antioxidant activity of the PLSs extracted from *Gracilaria intermedia*.

- (a) Chelating activity of Fe^{2+} with ascorbic acid used as a positive control.
 (b) DPPH radical scavenging activity. Values are means \pm SD ($n = 3$).

The DPPH radical scavenging capacity of PLS was also dose-dependent, with a blockage varying from $9.89 \pm 1.32\%$ (at a concentration of 0.1%) to $41.83 \pm 0.97\%$ (at a concentration of 1.5%). Although significant, the DPPH radical scavenging capacity of PLS was lower than that ascorbic acid over the concentration range tested (Figure 5 b) and also lower than the activity of other polysaccharides from seaweeds. Dore et al. [14], with polysaccharides from *Sargassum vulgare*, found values of $10.0 \pm 0.7\%$ a $22.0 \pm 0.6\%$ in solutions that varied from 0.15 to 3.0 mg.mL⁻¹

3.6 Rheological characterization

Based on the strain sweep tests performed to determine the region linear viscoelastic behavior of the samples in the dynamic oscillatory tests, the frequency sweep (FS) tests were carried out at 8% of a deformation. The results of the FS tests are presented in Figure 6, where it can be seen that the values of loss modulus (G'') were higher than those of the storage modulus (G') at all concentrations and frequencies tested. These results indicate that the extracted polysaccharide fraction does not lead to gel-like solutions. This behavior can be attributed to the elevated amount of sulfate that was observed in the polysaccharide obtained by papain digestion. The structure of agarans is strongly influenced by the presence of charged groups that participate in intermolecular hydrogen bonds^[48]; the strength of this polymer gel is inversely proportional to the amount of sulfate present in its structure^[64].




Figure 6.
Effect of the concentration of PLS extracted from *Gracilaria intermedia* on the storage and loss moduli measured during frequency sweeps.

The predominantly viscous response reflected in the dynamic and steady state tests suggest that a potential use for the polysaccharides extracted from the red seaweed *Gracilaria intermedia* is as a thickening agent, especially for applications where antioxidant activity and absence of color and odor are mandatory requirements. To check this hypothesis, the flow curves at 25 ± 1 °C of solutions of the extracted polysaccharides, either pure or in mixture with carboxymethylcellulose (CMC), were compared to those of two solutions containing pure CMC. The concentrations of the pure CMC solutions were of 0.5% and 1.5%, corresponding, respectively, to the lower and upper limit of the range of concentrations typically used in commercial applications of CMC as thickening agent. In the mixtures of CMC with the extracted

polysaccharides, the total concentration of thickening agents was 1.5%. The obtained flow curves are presented in Figure 7.

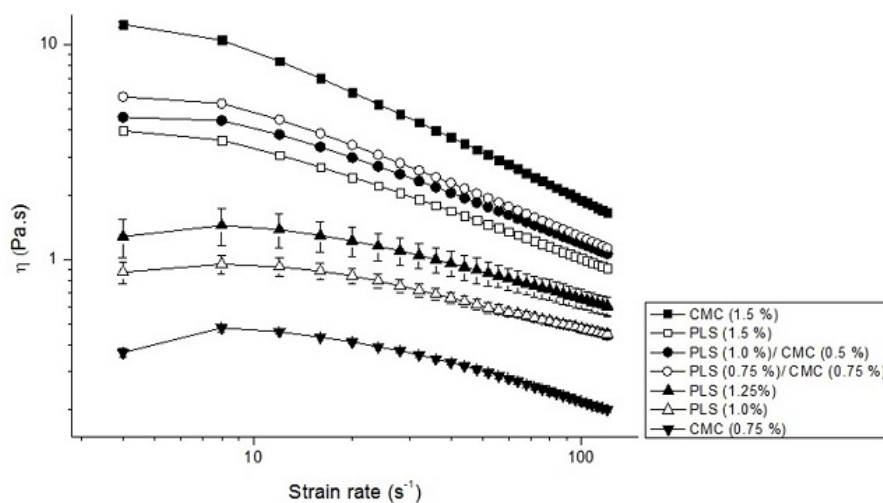


Figure 7.

Flow curves of the PLSs extracted from *Gracilaria intermedia* and of CMC at $25 \pm 1^\circ\text{C}$.

Figure 7 shows that all the tested solutions presented pseudoplastic behavior, since an increase in shear rate led to a decrease in viscosity. Besides, for all samples, the upward and downward (not shown) curves of shear stress vs. shear rate were identical, with no observed hysteresis behavior. Therefore, the extracted polysaccharide fraction solutions, as well as the two solutions with pure CMC, showed no thixotropy in the range of concentrations tested.

In the case of the extracted polysaccharide fraction solution, the pseudoplastic behavior is likely due to the rupture of the double helix structure present in agarans^[65]. Additionally, the fact that this rupture only occurs above a certain value of tension (τ_{crit})^[65] is in agreement with the two-region pattern observed in the flow curves, with constant viscosity at low shear rates (Newtonian plateau) and shear-thinning behavior at higher ones. The higher the polysaccharide concentration, the lower the upper limit of the Newtonian plateau because an increase in viscosity causes τ_{crit} be reached at lower values of shear rate.

Additionally, the data corresponding to the shear thinning region of all flow curves presented in Figure 7 were fitted to power-law model. The obtained values of consistency index (K) and power-law index (n) are presented in Table 2. It is observed that increase of the polysaccharide concentration in the PLS solutions led to increase of the consistency index and reduction of the power-law index. Taking into account that the consistency index is related to the resistance of a fluid to the flow and power-law index indicates how quickly the viscosity is reduced with an increase in the shear rate, the increase of K and reduction of n with the increase of the concentration of PLS in the solution can be explained in terms of the increase in the level of interaction among polysaccharide molecules resulting from the increase in the concentration. As observed in Figure 7, although pure CMC led to the highest viscosity, both pure

PLS and the PLS/CMC blends were able to produce a significant increase of viscosity. Actually, all over the range of strain rates studied, pure PLS and the PLS/CMC blends provided viscosity values closer to the that obtained with the CMC solution of 1.5% than to those obtained with 0.5%. These results confirm the potential of the extracted sulfated PLS to be used as thickening agent.

Table 2.

Power index (n) and consistency index (K) values for PLS, CMC solutions, and blends of both samples.

Sample	Concentration (%)	n	K (Pa.s)
PLS <i>G. intermedia</i>	1.0	0.67	2.31
	1.25	0.62	5.76
	1.5	0.47	11.64
CMC	0.75	0.60	1.44
	1.5	0.29	47.23
PLS + CMC	1.0 PLS + 0.5 CMC	0.43	15.83
	0.75 PLS + 0.75 CMC	0.39	10.11

4. Conclusions

In this study, a water-soluble polysaccharide was successfully extracted from the red seaweed *Gracilaria intermedia*. The data obtained by spectroscopic methods suggest that the extracted polymeric material is rich in agaran. In vitro studies showed that PLS had antioxidant activity, which may be used for cellular protection against free radicals and to increase the viability of products. The rheological characteristics of PLS indicate that it can be used as a viscosity modifier in industrial processes. The antioxidant characteristics and rheological behavior combined with the organoleptic properties observed (absence of color and odor) make polysaccharides from the seaweed *Gracilaria intermedia* a promising agent to be used in manufacturing processes of food and pharmaceuticals.

5. References

- 1 Bafana, A. (2013). Characterization and optimization of production of exopolysaccharide from *Chlamydomonas reinhardtii*. *Carbohydrate Polymers*, 95(2), 746-752. PMID:23648037. <http://dx.doi.org/10.1016/j.carbpol.2013.02.016>.
- 2 Raza, W., Yang, W., Jun, Y., Shakoor, F., Huang, Q., & Shen, Q. (2012). Optimization and characterization of a polysaccharide produced by *Pseudomonas fluorescens* WR-1 and its antioxidant

- activity. *Carbohydrate Polymers*, 90(2), 921-929. PMID:22840021. <http://dx.doi.org/10.1016/j.carbpol.2012.06.021>.
- 3 Sutherland, I. W. (1999). Polysaccharases for microbial exopolysaccharides. *Carbohydrate Polymers*, 38(4), 319-328. [http://dx.doi.org/10.1016/S0144-8617\(98\)00114-3](http://dx.doi.org/10.1016/S0144-8617(98)00114-3).
- 4 Ngah, W. S. W., Teong, L. C., & Hanafiah, M. A. K. M. (2011). Adsorption of dyes and heavy metal ions by chitosan composites: A review. *Carbohydrate Polymers*, 83(4), 1446-1456. <http://dx.doi.org/10.1016/j.carbpol.2010.11.004>.
- 5 Jiao, G., Yu, G., Zhang, J., & Ewart, S. H. (2011). Chemical structures and bioactivities of sulfated polysaccharides from marine algae. *Marine Drugs*, 9(2), 196-223. PMID:21566795. <http://dx.doi.org/10.3390/md9020196>.
- 6 Godard, M., Décordé, K., Ventura, E., Soteras, G., Baccou, J.-C., Cristol, J.-P., & Rouanet, J.-M. (2009). Polysaccharides from the green alga *Ulva rigida* improve the antioxidant status and prevent fatty streak lesions in the high cholesterol fed hamster, an animal model of nutritionally-induced atherosclerosis. *Food Chemistry*, 115(1), 176-180. <http://dx.doi.org/10.1016/j.foodchem.2008.11.084>.
- 7 Qi, H., Huang, L., Liu, X., Liu, D., Zhang, Q., & Liu, S. (2012). Antihyperlipidemic activity of high sulfate content derivative of polysaccharide extracted from *Ulva pertusa* (Chlorophyta). *Carbohydrate Polymers*, 87(2), 1637-1640. <http://dx.doi.org/10.1016/j.carbpol.2011.09.073>.
- 8 Shao, P., Chen, M., Pei, Y., & Sun, P. (2013). In vitro antioxidant activities of different sulfated polysaccharides from chlorophytan seaweeds *Ulva fasciata*. *International Journal of Biological Macromolecules*, 59, 295-300. PMID:23643973. <http://dx.doi.org/10.1016/j.ijbiomac.2013.04.048>.
- 9 Souza, B. W. S., Cerqueira, M. A., Martins, J. T., Quintas, M. A. C., Ferreira, A. C. S., Teixeira, J. A., & Vicente, A. A. (2011). Antioxidant potential of two red seaweeds from the Brazilian coasts. *Journal of Agricultural and Food Chemistry*, 59(10), 5589-5594. PMID:21491929. <http://dx.doi.org/10.1021/jf200999n>.
- 10 Domenech, S., Louaifi, A., Guinault, A., & Baumberger, S. (2013). Potential of Lignins as Antioxidant Additive in Active Biodegradable Packaging Materials. *Journal of Polymers and the Environment*, 21(3), 692-701. <http://dx.doi.org/10.1007/s10924-013-0570-6>.
- 11 Schreiber, S. B., Bozell, J. J., Hayes, D. G., & Zivanovic, S. (2013). Introduction of primary antioxidant activity to chitosan for application as a multifunctional food packaging material. *Food Hydrocolloids*, 33(2), 207-214. <http://dx.doi.org/10.1016/j.foodhyd.2013.03.006>.
- 12 Souza, B. W. S., Cerqueira, M. A., Bourbon, A. I., Pinheiro, A. C., Martins, J. T., Teixeira, J. A., Coimbra, M. A., & Vicente, A. A. (2012). Chemical characterization and antioxidant activity of sulfated polysaccharide from the red seaweed *Gracilaria birdiae*. *Food Hydrocolloids*, 27(2), 287-292. <http://dx.doi.org/10.1016/j.foodhyd.2011.10.005>.
- 13 Cheng, H., Feng, S., Shen, S., Zhang, L., Yang, R., Zhou, Y., & Ding, C. (2013). Extraction, antioxidant and antimicrobial activities of *Epimedium acuminatum* Franch. polysaccharide. *Carbohydrate*

- Polymers*, 96(1), 101-108. PMID:23688459. <http://dx.doi.org/10.1016/j.carbpol.2013.03.072>.
- 14 Dore, C. M. P. G., Alves, M. G. C. F., Will, L. S. E. P., Costa, T. G., Sabry, D. A., Rêgo, L. A. R. S., Accardo, C. M., Rocha, H. A. O., Filgueira, L. G. A., & Leite, E. L. (2013). A sulfated polysaccharide, fucans, isolated from brown algae *Sargassum vulgare* with anticoagulant, antithrombotic, antioxidant and anti-inflammatory effects. *Carbohydrate Polymers*, 91(1), 467-475. PMID:23044157. <http://dx.doi.org/10.1016/j.carbpol.2012.07.075>.
 - 15 Liu, X., Sun, Z., Zhang, M., Meng, X., Xia, X., Yuan, W., Xue, F., & Liu, C. (2012). Antioxidant and antihyperlipidemic activities of polysaccharides from sea cucumber *Apostichopus japonicus*. *Carbohydrate Polymers*, 90(4), 1664-1670. PMID:22944431. <http://dx.doi.org/10.1016/j.carbpol.2012.07.047>.
 - 16 Wu, M., Wu, Y., Qu, M., Li, W., & Yan, X. (2013). Evaluation of antioxidant activities of water-soluble polysaccharides from brown alga *Hizikia fusiformis*. *International Journal of Biological Macromolecules*, 56, 28-33. PMID:23396065. <http://dx.doi.org/10.1016/j.ijbiomac.2013.01.017>.
 - 17 Yang, X., Yang, S., Guo, Y., Jiao, Y., & Zhao, Y. (2013). Compositional characterisation of soluble apple polysaccharides, and their antioxidant and hepatoprotective effects on acute CCl₄-caused liver damage in mice. *Food Chemistry*, 138(2-3), 1256-1264. PMID:23411241. <http://dx.doi.org/10.1016/j.foodchem.2012.10.030>.
 - 18 Zhang, Z., Wang, F., Wang, M., Ma, L., & Zeng, X. (2012). Extraction optimisation and antioxidant activities in vitro of polysaccharides from *Allium macrostemon* Bunge. *International Journal of Food Science & Technology*, 47(4), 723-730. <http://dx.doi.org/10.1111/j.1365-2621.2011.02899.x>.
 - 19 Kumar, K. S., Ganesan, K., & Rao, P. V. S. (2008). Antioxidant potential of solvent extracts of *Kappaphycus alvarezii* (Doty) Doty – An edible seaweed. *Food Chemistry*, 107(1), 289-295. <http://dx.doi.org/10.1016/j.foodchem.2007.08.016>.
 - 20 Martín, L. A., Rodríguez, M. C., Matulewicz, M. C., Fissore, E. N., Gerschenson, L. N., & Leonardi, P. I. (2013). Seasonal variation in agar composition and properties from *Gracilaria gracilis* (Gracilariales, Rhodophyta) of the Patagonian coast of Argentina. *Phycological Research*, 61(3), 163-171. <http://dx.doi.org/10.1111/pre.12000>.
 - 21 Niu, J., Xu, M., Wang, G., Zhang, K., & Peng, G. (2013). Comprehensive Extraction of Agar and R-Phycoerythrin from *Gracilaria lemaneiformis* (Bangiales, Rhodophyta). *Indian Journal Geo-Marine Science*, 42, 21-28.
 - 22 Rodríguez-Montesinos, Y. E., Arvizu-Higuera, D. L., Hernández-Carmona, G., Muñoz-Ochoa, M., & Murillo-Álvarez, J. I. (2013). Seasonal variation of the agar quality and chemical composition of *Gracilaria veleroae* and *Gracilaria vermiculophylla* (Rhodophyceae, Gracilariaceae) from Baja California Sur, Mexico. *Phycological Research*, 61(2), 116-123. <http://dx.doi.org/10.1111/pre.12008>.
 - 23 Maciel, J. S., Chaves, L. S., Souza, B. W. S., Teixeira, D. I. A., Freitas, A. L. P., Feitosa, J. P. A., & Paula, R. C. M. (2008). Structural characterization of cold extracted fraction of soluble sulfated polysaccharide from red seaweed *Gracilaria birdiae*. *Carbohydrate Polymers*, 71(4), 559-565. <http://dx.doi.org/10.1016/j.carbpol.2007.06.026>.

- 24 Lahaye, M., & Yaphe, W. (1988). Effects of seasons on the chemical structure and gel strength of *Gracilaria pseudoverrucosa* agar (Gracilariaceae, rhodophyta). *Carbohydrate Polymers*, 8(4), 285-301. [http://dx.doi.org/10.1016/0144-8617\(88\)90067-7](http://dx.doi.org/10.1016/0144-8617(88)90067-7).
- 25 Araki, C. (1966). Some recent studies on the polysaccharides of agarophytes. In *Proceedings of the Fifth International Seaweed Symposium* (pp. 3-17). Halifax, Canada: Pergamon Press.
- 26 Barros, F. C. N., Silva, D. C., Sombra, V. G., Maciel, J. S., Feitosa, J. P. A., Freitas, A. L. P., & Paula, R. C. M. (2013). Structural characterization of polysaccharide obtained from red seaweed *Gracilaria caudata* (J Agardh). *Carbohydrate Polymers*, 92(1), 598-603. PMID:23218341. <http://dx.doi.org/10.1016/j.carbpol.2012.09.009>.
- 27 Vidotti, E. C., & Rollemberg, M. C. E. (2004). Algas: da economia nos ambientes aquáticos à bioremediação e à química analítica. *Química Nova*, 27(1), 139-145. <http://dx.doi.org/10.1590/S0100-40422004000100024>.
- 28 Coura, C. O., Araújo, I. W. F., Vanderlei, E. S. O., Rodrigues, J. A. G., Quinderé, A. L. G., Fontes, B. P., Queiroz, I. N. L., Menezes, D. B., Bezerra, M. M., Silva, A. A. R., Chaves, H. V., Jorge, R. J. B., Evangelista, J. S. A. M., & Benevides, N. M. B. (2012). Antinociceptive and anti-inflammatory activities of sulphated polysaccharides from the Red Seaweed *Gracilaria cornea*. *Basic & Clinical Pharmacology & Toxicology*, 110(4), 335-341. PMID:21985563. <http://dx.doi.org/10.1111/j.1742-7843.2011.00811.x>.
- 29 Solé, M., & Barrios, J. (2009). Catálogo de las macroalgas marinas del golfo de Paria y delta del Orinoco, Venezuela. *Memoria de la Fundación La Salle de Ciencias Naturales*, 171, 99-112.
- 30 Kim, M.-S., Yang, E. C., & Boo, S. M. (2006). Taxonomy and phylogeny of flattened species of *Gracilaria* (Gracilariaceae, Rhodophyta) from Korea based on morphology and protein-coding plastid *rbcL* and *psbA* sequences. *Phycologia*, 45(5), 520-528. <http://dx.doi.org/10.2216/05-38.1>.
- 31 Gurgel, C. F. D., Fredericq, S., Norris, J. N., & Yoneshigue-Valentin, Y. (2008). Two New Flat Species of *Gracilaria* (Gracilariales, Rhodophyta) From Brazil: *G. Abyssalis* sp. nov. and *G. Brasiliensis* sp. nov. *Phycologia*, 47(3), 249-264. <http://dx.doi.org/10.2216/PH06-59.1>.
- 32 Lyra, M. G., Nunes, J. M. C., Jesus, P. B., Lázaro, J. L., & Assis, J. G. A. (2011). Aspectos ecológicos de *Gracilaria* Grev. (Gracilariales, Rhodophyta) em uma praia tropical brasileira. *Revista Gestão Costeira Integrada*, 11(4), 451-457. <http://dx.doi.org/10.5894/rgci273>.
- 33 Farias, W. R., Valente, A. P., Pereira, M. S., & Mourão, P. A. (2000). Structure and Anticoagulant Activity of Sulfated Galactans Isolation of a unique sulfated galactan from the red algae *Botryocladia occidentalis* and comparison of its anticoagulant action with that of sulfated galactans from invertebrates. *The Journal of Biological Chemistry*, 275(38), 29299-29307. PMID:10882718. <http://dx.doi.org/10.1074/jbc.M002422200>.
- 34 Dodgson, K. S., & Price, R. G. (1962). A note on the determination of the ester sulphate content of sulphated polysaccharides. *The Biochemical Journal*, 84(1), 106-110. PMID:13886865. <http://dx.doi.org/10.1042/bj0840106>.

- 35 DuBois, M., Gilles, K. A., Hamilton, J. K., Rebers, P. A., & Smith, F. (1956). Colorimetric method for determination of sugars and related substances. *Analytical Chemistry*, 28(3), 350-356. <http://dx.doi.org/10.1021/ac60111a017>.
- 36 Bradford, M. M. (1976). A rapid and sensitive method for the quantitation of microgram quantities of protein utilizing the principle of protein-dye binding. *Analytical Biochemistry*, 72(1), 248-254. PMID:942051. [http://dx.doi.org/10.1016/0003-2697\(76\)90527-3](http://dx.doi.org/10.1016/0003-2697(76)90527-3).
- 37 Kircher, H. W. (1960). Gas-liquid partition chromatography of methylated sugars. *Analytical Chemistry*, 32(9), 1103-1106. <http://dx.doi.org/10.1021/ac60165a016>.
- 38 Lahaye, M., Yaphe, W., Viet, M. T. P., & Rochas, C. (1989). ¹³C-n.m.r. spectroscopic investigation of methylated and charged agarose oligosaccharides and polysaccharides. *Carbohydrate Research*, 190(2), 249-265. [http://dx.doi.org/10.1016/0008-6215\(89\)84129-1](http://dx.doi.org/10.1016/0008-6215(89)84129-1).
- 39 Miller, I. J., & Furneaux, R. H. (1997). The Structural Determination of the Agaroid Polysaccharides from Four New Zealand Algae in the Order Ceramiales by Means of ¹³CNMR Spectroscopy. *Botanica Marina*, 40(1-6), 333-340. <http://dx.doi.org/10.1515/botm.1997.40.1-6.333>.
- 40 Usov, A. I., Yarotsky, S. V., & Shashkov, A. S. (1980). ¹³C-nmr spectroscopy of red algal galactans. *Biopolymers*, 19(5), 977-990. <http://dx.doi.org/10.1002/bip.1980.360190504>.
- 41 Valiente, O., Fernandez, L. E., Perez, R. M., Marquina, G., & Velez, H. (1992). Agar Polysaccharides from the Red Seaweeds *Gracilaria domingensis* Sonder ex Kützting and *Gracilaria mammillaris* (Montagne) Howe. *Botanica Marina*, 35(2), 77-82. <http://dx.doi.org/10.1515/botm.1992.35.2.77>.
- 42 Prieto, P., Pineda, M., & Aguilar, M. (1999). Spectrophotometric Quantitation of Antioxidant Capacity through the Formation of a Phosphomolybdenum Complex: Specific Application to the Determination of Vitamin E. *Analytical Biochemistry*, 269(2), 337-341. PMID:10222007. <http://dx.doi.org/10.1006/abio.1999.4019>.
- 43 Chun-hui, L., Chang-hai, W., Zhi-liang, X., & Yi, W. (2007). Isolation, chemical characterization and antioxidant activities of two polysaccharides from the gel and the skin of *Aloe barbadensis* Miller irrigated with sea water. *Process Biochemistry*, 42(6), 961-970. <http://dx.doi.org/10.1016/j.procbio.2007.03.004>.
- 44 Qi, H., Zhang, Q., Zhao, T., Chen, R., Zhang, H., Niu, X., & Li, Z. (2005). Antioxidant activity of different sulfate content derivatives of polysaccharide extracted from *Ulva pertusa* (Chlorophyta) in vitro. *International Journal of Biological Macromolecules*, 37(4), 195-199. PMID:16310843. <http://dx.doi.org/10.1016/j.ijbiomac.2005.10.008>.
- 45 Zhang, Z., Wang, X., Zhang, J., & Zhao, M. (2011). Potential antioxidant activities in vitro of polysaccharides extracted from ginger (*Zingiber officinale*). *Carbohydrate Polymers*, 86(2), 448-452. <http://dx.doi.org/10.1016/j.carbpol.2011.04.062>.
- 46 Murugan, K., & Iyer, V. V. (2013). Differential growth inhibition of cancer cell lines and antioxidant activity of extracts of red, brown, and green marine algae. *In Vitro Cellular & Developmental Biology*.

- Animal*, 49(5), 324-334. PMid:23645467. <http://dx.doi.org/10.1007/s11626-013-9603-7>.
- 47 Melo, M. R. S., Feitosa, J. P. A., Freitas, A. L. P., & Paula, R. C. M. (2002). Isolation and characterization of soluble sulfated polysaccharide from the red seaweed *Gracilaria cornea*. *Carbohydrate Polymers*, 49(4), 491-498. [http://dx.doi.org/10.1016/S0144-8617\(02\)00006-1](http://dx.doi.org/10.1016/S0144-8617(02)00006-1).
- 48 Freile-Pelegrín, Y., & Robledo, D. (1997). Influence of alkali treatment on agar from *Gracilaria cornea* from Yucatán, México. *Journal of Applied Phycology*, 9(6), 533-539. <http://dx.doi.org/10.1023/A:1007989931915>.
- 49 Mehta, G. K., Meena, R., Prasad, K., Ganesan, M., & Siddhanta, A. K. (2010). Preparation of galactans from *Gracilaria debilis* and *Gracilaria salicornia* (Gracilariales, Rhodophyta) of Indian waters. *Journal of Applied Phycology*, 22(5), 623-627. <http://dx.doi.org/10.1007/s10811-010-9502-1>.
- 50 Amorim, R. N. S., Rodrigues, J. A. G., Holanda, M. L., Quinderé, A. L. G., Paula, R. C. M., Melo, V. M. M., & Benevides, N. M. B. (2012). Antimicrobial effect of a crude sulfated polysaccharide from the red seaweed *Gracilaria ornata*. *Brazilian Archives of Biology and Technology*, 55(2), 171-181. <http://dx.doi.org/10.1590/S1516-89132012000200001>.
- 51 Vanderlei, E. S. O., Araújo, I. W. F., Quinderé, A. L. G., Fontes, B. P., Eloy, Y. R. G., Rodrigues, J. A. G., Silva, A. A. R., Chaves, H. V., Jorge, R. J. B., Menezes, D. B., Evangelista, J. S. A. M., Bezerra, M. M., & Benevides, N. M. B. (2011). The involvement of the HO-1 pathway in the anti-inflammatory action of a sulfated polysaccharide isolated from the red seaweed *Gracilaria birdiae*. *Inflammation Research*, 60(12), 1121-1130. PMid:21879365. <http://dx.doi.org/10.1007/s00011-011-0376-8>.
- 52 Pomin, V. H., & Mourão, P. A. (2008). Structure, biology, evolution, and medical importance of sulfated fucans and galactans. *Glycobiology*, 18(12), 1016-1027. PMid:18796647. <http://dx.doi.org/10.1093/glycob/cwn085>.
- 53 Prado-Fernández, J., Rodríguez-Vázquez, J. A., Tojo, E., & Andrade, J. M. (2003). Quantitation of κ -, ι - and λ -carrageenans by mid-infrared spectroscopy and PLS regression. *Analytica Chimica Acta*, 480(1), 23-37. [http://dx.doi.org/10.1016/S0003-2670\(02\)01592-1](http://dx.doi.org/10.1016/S0003-2670(02)01592-1).
- 54 Rochas, C., Lahaye, M., & Yaphe, W. (1986). Sulfate Content of Carrageenan and Agar Determined by Infrared Spectroscopy. *Botanica Marina*, 29(4), 335-340. <http://dx.doi.org/10.1515/botm.1986.29.4.335>.
- 55 Mollet, J.-C., Rahaoui, A., & Lemoine, Y. (1998). Yield, chemical composition and gel strength of agarocolloids of *Gracilaria gracilis*, *Gracilariopsis longissima* and the newly reported *Gracilaria cf. vermiculophylla* from Roscoff (Brittany, France). *Journal of Applied Phycology*, 10(1), 59-66. <http://dx.doi.org/10.1023/A:1008051528443>.
- 56 Chopin, T., & Whalen, E. (1993). A new and rapid method for carrageenan identification by FT IR diffuse reflectance spectroscopy directly on dried, ground algal material. *Carbohydrate Research*, 246(1), 51-59. [http://dx.doi.org/10.1016/0008-6215\(93\)84023-Y](http://dx.doi.org/10.1016/0008-6215(93)84023-Y).
- 57 Parekh, R. G., Doshi, Y. A., Rao, V. D., & Chauhan, V. D. (1987). Studies on a phycocolloid from red alga *Halymenia venusta* Boergesen. *Indian Journal of Geo-Marine Sciences*, 16, 274-276.

- 58 Batista, J. A., Dias, E. G. N., Brito, T. V., Prudêncio, R. S., Silva, R. O., Ribeiro, R. A., Souza, M. H., Paula, R. C., Feitosa, J. P., Chaves, L. S., Melo, M. R., Freitas, A. L., Medeiros, J. V., & Barbosa, A. L. (2014). Polysaccharide isolated from *Agardhiella ramosissima*: Chemical structure and anti-inflammation activity. *Carbohydrate Polymers*, 99(1), 59-67. PMID:24274479. <http://dx.doi.org/10.1016/j.carbpol.2013.08.071>.
- 59 Mazumder, S., Ghosal, P. K., Pujol, C. A., Carlucci, M. J., Damonte, E. B., & Ray, B. (2002). Isolation, chemical investigation and antiviral activity of polysaccharides from *Gracilaria corticata* (Gracilariaceae, Rhodophyta). *International Journal of Biological Macromolecules*, 31(1-3), 87-95. PMID:12559431. [http://dx.doi.org/10.1016/S0141-8130\(02\)00070-3](http://dx.doi.org/10.1016/S0141-8130(02)00070-3).
- 60 Wang, L., Yao, Y., Sang, W., Yang, X., & Ren, G. (2015). Structural features and immunostimulating effects of three acidic polysaccharides isolated from *Panax quinquefolius*. *International Journal of Biological Macromolecules*, 80, 77-86. PMID:26056990. <http://dx.doi.org/10.1016/j.ijbiomac.2015.06.007>.
- 61 Xia, Y.-G., Liang, J., Yang, B.-Y., Wang, Q.-H., & Kuang, H.-X. (2015). Structural studies of an arabinan from the stems of *Ephedra sinica* by methylation analysis and 1D and 2D NMR spectroscopy. *Carbohydrate Polymers*, 121, 449-456. PMID:25659720. <http://dx.doi.org/10.1016/j.carbpol.2014.12.058>.
- 62 Costa, L. S., Fidelis, G. P., Cordeiro, S. L., Oliveira, R. M., Sabry, D. A., Câmara, R. B. G., Nobre, L. T. D. B., Costa, M. S. S. P., Almeida-Lima, J., Farias, E. H. C., Leite, E. L., & Rocha, H. A. O. (2010). Biological activities of sulfated polysaccharides from tropical seaweeds. *Biomedicine and Pharmacotherapy*, 64(1), 21-28. PMID:19766438. <http://dx.doi.org/10.1016/j.biopha.2009.03.005>.
- 63 Wang, J., Zhang, Q., Zhang, Z., & Li, Z. (2008). Antioxidant activity of sulfated polysaccharide fractions extracted from *Laminaria japonica*. *International Journal of Biological Macromolecules*, 42(2), 127-132. PMID:18023861. <http://dx.doi.org/10.1016/j.ijbiomac.2007.10.003>.
- 64 Cosson, J., Deslandes, E., Zinoun, M., & Mouradi-Givernaud, A. (1995). Carrageenans and agars, red algal polysaccharides. In: F. E. Round & D. J. Chapman (Eds.), *Progress in phycological research* (pp. 269-324). Bristol: Biopress Ltd.
- 65 Grant, C. A., Twigg, P. C., Savage, M. D., Woon, W. H., & Greig, D. (2012). Mechanical investigations on agar gels using atomic force microscopy: effect of deuteration. *Macromolecular Materials and Engineering*, 297(3), 214-218. <http://dx.doi.org/10.1002/mame.201100164>.

Author notes

*

nilo@enq.ufrgs.br