



Journal of applied research and technology

ISSN: 1665-6423

UNAM, Centro de Ciencias Aplicadas y Desarrollo
Tecnológico

Camacho, J.N.; Romero, R.; Galván Muciño, G. E.;
Martínez-Vargas, S.L.; Pérez-Alonso, C.; Natividad, R.
Kinetic modeling of canola oil transesterification catalyzed by quicklime
Journal of applied research and technology, vol.
16, no. 6, 2018, November-December, pp. 446-454
UNAM, Centro de Ciencias Aplicadas y Desarrollo Tecnológico

DOI: <https://doi.org/10.22201/icat.16656423.2018.16.6.743>

Available in: <https://www.redalyc.org/articulo.oa?id=47471640001>

- ▶ How to cite
- ▶ Complete issue
- ▶ More information about this article
- ▶ Journal's webpage in redalyc.org



Journal of Applied Research and Technology

www.jart.ccadet.unam.mx
Journal of Applied Research and Technology 16 (2018) 446-454

Original

Kinetic modeling of canola oil transesterification catalyzed by quicklime

J.N. Camacho ^a, R. Romero ^{a,*}, G. E. Galván Muciño ^a, S.L. Martínez-Vargas ^b, C. Pérez-Alonso ^b, R. Natividad ^a

^a *Chemical Engineering Lab., Centro Conjunto de Investigación en Química Sustentable UAEM-UNAM, Universidad Autónoma del Estado de México, Carretera Toluca-Atlacomulco Km 14.5, Unidad San Cayetano, Toluca Estado de México, 50200, México*

^b *Faculty of Chemistry, Universidad Autónoma del Estado de México, Paseo Colón esq. Paseo Tollocan s/n 50120 Toluca, Estado de México, México.*

Received dd mm aaaa; accepted dd mm aaaa
Available online dd mm aaaa

Abstract: This work aimed to study and model the kinetics of transesterification of canola oil with methanol catalyzed by calcined quicklime ($\text{CaO} + \text{MgO}$). The influence of three main variables was studied at 328 K: reagents order addition (has a negligible effect on the reaction), methanol-oil molar ratio (has minor effect on reaction rate after 1.5 h of reaction) and catalyst loading (high effect on reaction rate) to achieve at least a triglycerides conversion of 96.5% in concordance with norm EN 14103. A kinetic model based on an Eley-Rideal mechanism was found to well fit ($R^2 = 0.9886$) the experimental data. Thus, it was concluded that for the quicklime catalyzed transesterification of canola oil with methanol to occur, first the methanol must be chemisorbed and the resulting methoxy species react with triglycerides in the interface liquid-solid. The whole process is limited by this step since methanol readily adsorbs onto the catalytic surface.

Keywords: Methyl Esters; Alcoholysis; CaO; MgO; Biodiesel; Kinetic modelling

1. INTRODUCTION

Biodiesel, an alternative to fossil fuels, is basically a mixture of Fatty Acids Alkyl Esters obtained from renewable sources, mainly by transesterification of either vegetable oils or animal fats. Transesterification is a chemical reaction between large branched triglycerides (TGs) or fatty acids and an alcohol (most often methanol) under the presence of a catalyst and temperature to produce alkyl (most often methyl) esters and glycerol.

Transesterification implies a sequence of reversible and consecutive reactions: (1) TGs react with methanol (M) and are converted into diglycerides (DGs), (2) DGs are further converted into monoglycerides (MGs) and (3) MGs are finally transformed into glycerol (G). In each step an ester is produced and therefore three molecules of ester (E) are produced for every reacted molecule of TG. Since reaction proceeds too slow at standard conditions, a catalyst is used in order to accelerate it; being the recommended catalysts either base or acid. When the transesterification of oils with low free fatty acids (FFA) content is to be conducted, solid base catalysts are preferred (Lee & Wilson, 2015). Among these catalysts, CaO-based catalysts have been extensively studied and

* Corresponding author.

E-mail address: rromeror@uaemex.mx, rnatividadr@uaemex.mx

(R. Romero, R. Natividad, J.N. Camacho).

Peer Review under the responsibility of Universidad Nacional Autónoma de México.
<http://>

recognized as promising catalysts to conduct the transesterification of vegetable oils at industrial scale (Alba-Rubio et al., 2010; Arzamendi, Arguiñarena, Campo, Zabala, & Gandía, 2008; Boey, Ganesan, Maniam, & Khairuddean, 2012; Khemthong et al., 2012; Viola et al., 2012). This is due to CaO exhibiting low solubility in organic compounds, high basicity, no toxicity, easy handling, long useful life, human exposure benign, reusability and low cost and natural availability of precursors, i.e. limestone (Alba-Rubio et al., 2010; Arzamendi et al., 2008; Khemthong et al., 2012). CaO has been demonstrated to be an excellent catalyst not only for pure oils but also for waste oil (Boey et al., 2012; Viola et al., 2012). Also, in the vast existing literature on transesterification catalyzed by CaO, it has been demonstrated that not only the methanol:oil ratio, catalyst loading, temperature, doping, type of alcohol and feedstock impact the attained yield of fatty acids alkyls esters but also the CaO precursor does (Tang, Yan, Shen, Li, & Jeje, 2016). It has been found (Tang et al., 2016) that CaO from calcium carbonate exhibits more active sites and larger surface areas than the oxide from other precursors (acetate, hydroxide and oxalate). CaO catalytic performance is also affected by its combination with other oxides like MgO (Ilgen, 2011; Ilgen & Akin, 2012), ZnO (Alba-Rubio et al., 2010; Lukic et al., 2014; Ngamcharussrivichai, Totarat, & Bunyakiat, 2008) or Al₂O₃ (Marinković et al., 2017) and doping with metals like Li (Alonso, Mariscal, Granados, & Maireles-Torres, 2009), Zn (Banković-Ilić, Miladinović, Stamenković, & Veljković, 2017) and Na compounds (Luz Martínez et al., 2011). In most of the cases, CaO reagent grade has been used. For the sake of sustainability and economical viability, however, other sources of CaO have been explored. Within these alternatives, eggshells (Risso, Ferraz, Meireles, Fonseca, & Vital, 2018), sea sand (Muciño et al., 2014) and quicklime (Camacho et al., 2016; Miladinović, Krstić, Tasić, Stamenković, & Veljković, 2014) can be found. Quicklime has been recognized as a rather low cost source of CaO and has already been successfully applied in the methanolysis of safflower oil (Camacho et al., 2016), sunflower oil (Miladinović et al., 2014) and rapeseed oil (Masato, Jyu-suke, Yoshiya, & Haruhiko, 2009). The higher activity of quicklime compared to CaO (Camacho et al., 2016) reagent grade and to Li/CaO (Alonso et al., 2009) has already been demonstrated, with safflower and sunflower oil,

respectively, though. In this work, quicklime was used to catalyze the transesterification of canola oil and the main objective was to establish a kinetic model that allows not only to attain a further insight into this reaction but also to be able to further design and scale a process involving, both, quicklime and canola oil. It is worth noticing that the quicklime used in this work has also some content of MgO and this has been previously reported (Camacho et al., 2016). Although canola oil is an edible oil, its use as feedstock in biodiesel production is preferred due to its high oil content and its use may increase due to a recent study that demonstrates the production of free glycerol biodiesel from canola oil (Tang et al., 2016). Furthermore, this oil, due to its chain of 18 carbon atoms and an unsaturated bond results in biodiesel with a superior cold flow property (Ilgen, 2012a).

In the context of biodiesel production by canola oil methanolysis, kinetic models have been obtained when dolomite (Ilgen, 2012a) and nanopowder reagent grade CaO (Zhao, Qiu, & Stagg-Williams, 2013) have been used as catalysts. In the former, it was concluded that triglycerides are not chemisorbed and in the latter the best model was concluded to be the one assuming both compounds, methanol and triglycerides, chemisorbed onto the catalytic surface (Langmuir-Hinshelwood-Hougen-Watson approach). Although the quicklime used in this work is basically CaO (Camacho et al., 2016), the textural and basicity properties are different to those of the catalysts assessed in previous works (Zhao et al., 2013). Thus, from the understanding and process design point of view is rather important to establish whether or not both reagents are chemisorbed onto the surface and to establish the kinetic and adsorption parameters when canola oil methanolysis is catalyzed by quicklime, which is a rather low cost heterogeneous catalyst that may help to increase economical viability of biodiesel production process. In order to achieve this aim, different models based on Eley-Rideal (ER) or Langmuir-Hinshelwood-Hougen-Watson (LHHW) mechanisms were assessed in this work based on previous kinetic studies with other catalysts or feedstock (Ilgen, 2012a; Miladinović et al., 2014; Zhao et al., 2013).

2. MATERIALS AND METHODS

2.1 MATERIALS

Food-grade Canola oil was used as raw material and it was purchased from a local grocery store. Its fatty acid

composition consisted of palmitic acid (3.5%), stearic acid (1.5%), oleic acid (60.1%), linoleic acid (20.1%), and others (14.8%). Quicklime was purchased from a rural market and characterized in a previous paper (Camacho et al., 2016). Anhydrous methanol (99.96%) was supplied by J.T. Baker. Methanol (99.9%) and heptane (HPLC grade) was purchased from Fermont Co. The gas chromatography reference standard for fatty acid methyl esters was purchased in Supelco. Methyl heptadecanoate was purchased in Sigma Aldrich (puriss. p.a., standard for GC, ≥99.7%) and was used for quantifying total methyl esters.

2.2 CATALYST PREPARATION AND CHARACTERIZATION

Quicklime was triturated, meshed and recovered between 0.12 mm and 0.84 mm mesh, then calcined at 900 °C for 8 h. This temperature was established by a TGA analysis to be the one at which all CaCO₃ is converted and surface water is desorbed. Relatively large exposure to air was avoided in order to prevent contamination. The main crystalline phase of the calcined catalyst was found by XRD to be CaO; however, MgO was also identified. The basicity and base strength were determined by Hammett method (Hammett & Deyrup, 1932) to be 0.228 mmol/g and 9.8>H₁₅, respectively. The details of the catalyst characterization have already been reported in (Camacho et al., 2016) and therefore are not repeated here.

2.3 REACTION PROCEDURE

Transesterification reactions were carried out in a 250 mL glass stirred tank reactor with a condenser, baffles and heating and stirring plate. The reaction volume was 100 mL. The assessed variables in this work were the catalyst loading, methanol-to-oil molar ratio and the addition order of raw materials. The response variable at all cases was the FAME content.

When not being the variable under study, the stirring rate, methanol-oil molar ratio, catalyst loading, order of reagents addition, raw materials source and temperature were kept constant at all experiments. The stirring rate was 1000 rpm. Experiments were performed with a methanol-oil molar ratio of 6:1, 9:1 and 12:1. The studied catalyst loading was 2, 3, 6 and 8% (w/w) with respect to the reaction mixture weight, and the reaction time was 5 h at all experiments. The maximum reaction temperature was set at 328 K in order to reduce methanol evaporation

without compromising much the energy provided to activate the catalyst and the reaction. It is worth pointing out that the boiling point of methanol is reduced at the atmospheric pressure (558 mmHg) of the place where this research was conducted. The reaction conditions for each experiment are summarized in Table 1. Each experiment was conducted by duplicate. Upon reaction completion, catalyst was separated from the products (glycerol and methyl esters) by centrifugation. Residual methanol was evaporated in a rotavapor (R-215 Buchi Switzerland) under vacuum.

Table 1. Reaction conditions: a summary.

Code	Molar ratio (Oil: Methanol)	Addition Order	Catalyst loading (w/w)%	Temperature (K)
1	(1:6)	Methanol-Catalyst	6%	328
2	(1:9)	Methanol-Catalyst	6%	328
3	(1:6)	Methanol-Catalyst	8%	328
4	(1:9)	Methanol-Catalyst	8%	328
5	(1:12)	Methanol-Catalyst	8%	328
6	(1:6)	Oil-Catalyst	6%	328
7	(1:9)	Oil-Catalyst	8%	328
8	(1:6)	Oil-Catalyst	8%	328
9	(1:12)	Methanol-Catalyst	6%	328
10	(1:6)	Methanol-Catalyst	3%	328
11	(1:6)	Methanol-Catalyst	2%	328

2.4 BIODIESEL CHARACTERIZATION

Samples (1.5 mL) were withdrawn every hour from reaction mixture. Samples were cooled down and the catalyst was separated from the products and reactants by centrifugation at 10,000 rpm during 10 min. Then, the residual methanol was evaporated by heating samples. These samples were analysed using a Varian CP-3800 gas chromatograph with flame ionization detector (FID).

To quantify the methyl esters content in concordance with norm EN 14103, a capillary column Agilent HP-Innowax column (30 m × 0.32 mm. × 0.25 µm) was used. To measure glycerides the EN-14105 standard was followed (with modification of the injection conditions due to the high initial concentration of glycerides) with a HP-DB5-HT capillary column (15 m x 0.320 mm x 0.10 µm). Helium was used as carrier gas in both analyses.

A Varian 720-ES Series ICP Optica Emission Spectrometer was employed to quantify the amount of Ca and Mg in the resulting biodiesel in the experiments where the methanol:oil ratio was investigated.

2.5 KINETIC MODELING

As it is produced in batch mode, the FAME production rate is given by equation 1,

$$\frac{dn_{FAME}}{dt} = r'W \quad (1)$$

$$\text{Where } r' [=] \frac{n_{FAME}}{\text{min} * K_{cat}} \quad (2)$$

where n_{FAME} is the number of produced moles of methyl esters (FAME), W is the catalyst mass and r' is the FAME production rate per mass of catalyst.

In order to establish the kinetic model that best represents the transesterification of canola oil catalyzed by calcined quicklime, two mechanistic approaches were assessed, i.e. Langmuir-Hinshelwood and Eley-Rideal.

In both approaches the following assumptions were made,

A. The reaction mixture is perfectly mixed so the reagents distribution and concentration are uniform in the whole reaction volume.

B. At first, the reaction mixture contains only 3 species (methanol, oil and calcined quicklime), two of them are immiscible phases: methanol and oil. As reaction continues, other species like monoglycerides, diglycerides, glycerol and FAMEs are produced, but the concentration of diglycerides and monoglycerides in the liquid phase of the reaction mixture does not present a significant change compared to triglycerides and methyl esters with reaction time, because once they are formed they react quickly with adsorbed methanol onto the catalytic surface until be transformed into methyl esters, so their consumption rates are much faster than that of triglycerides. Thus, the concentrations of monoglycerides and diglycerides are too small and they can be neglected from the kinetic modelling (Galván Muciño et al., 2016).

C. The contribution to the reaction due to the homogeneously catalyzed methanolysis due to the leached calcium is considered negligible if the catalyst loading is ≥1% (w/w) based on the oil mass. This is the case in this paper.

For each mechanism, several rate equations were deduced depending on the assumed rate-determining step.

The LHHW mechanism was established by assuming that both, methanol (M) and triglycerides (T) are adsorbed onto common active sites and react to produce adsorbed glycerol (G) and adsorbed methyl esters (E). Finally, glycerol and adsorbed methyl esters are desorbed from the catalytic surface. All these steps are reversible. Thus, the rate determining elementary steps and the accordingly established models are presented in Table 2.

Table 2. Kinetic models based on LHHW mechanism.

Rate limiting step	Model	Simplified Model
$M + * \xrightleftharpoons[k_2]{k_1} M *$	$r_1 = \frac{k_1 M - \frac{k_2 k_4 k_6 k_8 k_{10} GE}{k_3 k_5 k_7 k_9 T}}{1 + \frac{k_4 k_6 k_8 k_{10} GE}{k_3 k_5 k_7 k_9 T} + \frac{k_8}{k_7} G + \frac{k_3}{k_4} T + \frac{k_{10}}{k_9} E}$	$r_1 = \frac{K_1 M - K_2 GE/T}{1 + K_3 GE/T + K_4 G + K_5 T + K_6 E}$
$T + * \xrightleftharpoons[k_4]{k_3} T *$	$r_2 = \frac{k_3 T - \frac{k_2 k_4 k_6 k_8 k_{10} GE}{k_1 k_5 k_7 k_9 T}}{1 + \frac{k_1}{k_2} M + \frac{k_2 k_6 k_8 k_{10} GE}{k_1 k_5 k_7 k_9 T} + \frac{k_8}{k_7} G + \frac{k_{10}}{k_9} E}$	$r_2 = \frac{K_1 T - K_2 GE/T}{1 + K_3 M + K_4 GE/T + K_5 G + K_6 E}$
$M * + T * \xrightleftharpoons[k_6]{k_5} G * + E *$	$r_3 = \frac{\frac{k_1 k_3 k_5 MT}{k_2 k_4} - \frac{k_6 k_8 k_{10} GE}{k_7 k_9}}{\left(1 + \frac{k_1}{k_2} M + \frac{k_3}{k_4} T + \frac{k_8}{k_7} G + \frac{k_{10}}{k_9} E\right)^2}$	$r_3 = \frac{K_1 MT - K_2 GE}{(1 + K_3 M + K_4 T + K_5 G + K_6 E)^2}$
$G * \xrightleftharpoons[k_8]{k_7} G + *$	$r_4 = \frac{\frac{k_1 k_3 k_5 k_7 k_9 MT}{k_2 k_4 k_{10} E} - k_9 G}{1 + \frac{k_1}{k_2} Me + \frac{k_3}{k_4} T + \frac{k_{10}}{k_9} E + \frac{k_1 k_3 k_5 k_7 MeT}{k_2 k_4 k_{10} E}}$	$r_4 = \frac{K_4 MT/E - K_2 G}{1 + K_3 M + K_4 T + K_5 E + K_6 MT/E}$
$E * \xrightleftharpoons[k_{10}]{k_9} E + *$	$r_5 = \frac{\frac{k_1 k_2 k_5 k_7 k_9 MT}{k_2 k_4 k_8 G} - k_{10} E}{1 + \frac{k_1}{k_2} M + \frac{k_3}{k_4} T + \frac{k_8}{k_7} G + \frac{k_1 k_3 k_5 k_7 MeT}{k_2 k_4 k_8 G}}$	$r_5 = \frac{K_4 MT/E - K_2 E}{1 + K_3 M + K_4 T + K_5 G + K_6 MT/G}$

The ER mechanism based models assume the adsorption of methanol (M) on the catalytic surface and then the surface reaction between triglycerides (T) with adsorbed methanol (M) proceeds to form adsorbed glycerol (G) and free methyl esters (E). Finally, adsorbed glycerol is desorbed from the catalytic surface. All these steps are considered reversible. The rate determining elementary steps and the accordingly established models are presented in Table 3.

In addition, two other set of kinetic models based on LHHW and ER mechanisms were assessed and these are summarized in tables 4 and 5, respectively. The difference between the models presented in tables 4 and 5 and the ones presented in tables 2 and 3, is that the glycerol adsorption term is assumed small compared to the other adsorption terms.

Although glycerol has the property of attaching to the catalyst and form species known as calcium diglyceroxide $\text{CH}_3\text{-O-Ca-O(OH)}_2\text{C}_3\text{H}_5$, this may not deactivate the active sites in catalyst; in fact this specie has been proven to exhibit catalytic activity on the transesterification reaction (Kouzu, Fujimori, Suzuki, Koshi, & Moriyasu, 2017).

Contrast between the different kinetic models was performed considering the physical significance of the estimated parameters and models were discarded if no consistency with experimental data was shown or kinetic parameters with erroneous values, i.e., negative values, too high values or not significantly different from zero at the 95% confidence level. To perform the minimization of the objective function the software POLYMATH 5.1 applying the Levenberg–Marquardt algorithm was utilized.

Table 3. Kinetic models based on ER mechanism.

Rate limiting step	Model	Simplified Model
$M + * \xrightleftharpoons[k_2]{k_1} M *$	$r_1 = \frac{k_1 M - \frac{k_2 k_4 k_6 GE}{k_3 k_5 T}}{1 + \frac{k_4 k_6 GE}{k_3 k_5 T} + \frac{k_6}{k_5} G}$	$r_1 = \frac{K_1 M - K_2 GE/T}{1 + K_3 GE/T + K_4 G}$
$T + M * \xrightleftharpoons[k_4]{k_3} G * + E$	$r_2 = \frac{\frac{k_1 k_3}{k_2} TM - \frac{k_4 k_6}{k_5} EG}{1 + \frac{k_1}{k_2} M + \frac{k_6}{k_5} G}$	$r_2 = \frac{K_1 TM - K_2 EG}{1 + K_3 M + K_4 G}$
$G * \xrightleftharpoons[k_6]{k_5} G + *$	$r_3 = \frac{\frac{k_1 k_3 k_5}{k_4 k_2} TM - k_6 G}{1 + \frac{k_1}{k_2} M + \frac{k_1 k_3}{k_4 k_2} TM}$	$r_3 = \frac{K_1 TM/E - K_2 G}{1 + K_3 M + K_4 TM/E}$

Table 4. Kinetic models based on LHHW mechanism with weak adsorption of products.

Rate limiting step	Model	Simplified Model
$M + * \xrightleftharpoons[k_2]{k_1} M *$	$r_1 = \frac{k_1 M - \frac{k_2 k_4 k_6 k_8 k_{10} GE}{k_3 k_5 k_7 k_9 T}}{1 + \frac{k_4 k_6 k_8 k_{10} GE}{k_3 k_5 k_7 k_9 T} + \frac{k_3}{k_4} T + \frac{k_{10}}{k_9} E}$	$r_1 = \frac{K_1 M - K_2 GE/T}{1 + K_3 GE/T + K_5 T + K_6 E}$
when, $\frac{k_6}{k_5} G \ll \frac{k_4 k_6 k_8 k_{10} GE}{k_3 k_5 k_7 k_9 T} + \frac{k_3}{k_4} T + \frac{k_{10}}{k_9} E$	$r_2 = \frac{k_3 T - \frac{k_2 k_4 k_6 k_8 k_{10} GE}{k_1 k_5 k_7 k_9 T}}{1 + \frac{k_1}{k_2} M + \frac{k_2 k_6 k_8 k_{10} GE}{k_1 k_5 k_7 k_9 T} + \frac{k_{10}}{k_9} E}$	$r_2 = \frac{K_1 T - K_2 GE/T}{1 + K_3 M + K_4 GE/T + K_6 E}$
$T + * \xrightleftharpoons[k_7]{k_4} T *$	$r_3 = \frac{\frac{k_1 k_3 k_5}{k_2 k_4} MT - \frac{k_6 k_8 k_{10} GE}{k_7 k_9}}{\left(1 + \frac{k_1}{k_2} M + \frac{k_3}{k_4} T + \frac{k_{10}}{k_9} E\right)^2}$	$r_3 = \frac{K_1 MT - K_2 GE}{(1 + K_3 M + K_4 T + K_5 E)^2}$
when, $\frac{k_6}{k_5} G \ll \frac{k_1}{k_2} M + \frac{k_3}{k_4} T + \frac{k_{10}}{k_9} E$	—	—
$G * \xrightleftharpoons[k_8]{k_5} G + *$	$r_5 = \frac{\frac{k_1 k_3 k_5 k_7 k_9 MT}{k_2 k_4 k_8 G} - k_{10} E}{1 + \frac{k_1}{k_2} M + \frac{k_3}{k_4} T + \frac{k_8}{k_7} + \frac{k_1 k_3 k_5 k_7 MT}{k_2 k_4 k_8 G}}$	$r_5 = \frac{K_4 MT/E - K_2 E}{1 + K_3 M + K_4 T + K_5 MT/G}$
when, $\frac{k_6}{k_5} G \ll \frac{k_1}{k_2} M + \frac{k_3}{k_4} T + \frac{k_1 k_3 k_5 k_7 MT}{k_2 k_4 k_8 G}$		

Table 5. Kinetic models based on ER mechanism with weak glycerol adsorption.

Rate limiting step		Model	Simplified Model
$M + * \xrightleftharpoons[k_2]{k_1} M *$	when, $\frac{k_6}{k_5} G \ll \frac{k_4 k_6 G E}{k_3 k_5 T}$	$r_1 = \frac{k_1 M - \frac{k_2 k_4 k_6 G E}{k_3 k_5 T}}{1 + \frac{k_4 k_6 G E}{k_3 k_5 T}}$	$r_1 = \frac{K_1 M - K_2 G E / T}{1 + K_3 G E / T}$
$T + M * \xrightleftharpoons[k_4]{k_3} G * + E$	when, $\frac{k_6}{k_5} G \ll \frac{k_1}{k_2} M$	$r_2 = \frac{\frac{k_1 k_3}{k_2} T M - \frac{k_4 k_6}{k_5} E G}{1 + \frac{k_1}{k_2} M}$	$r_2 = \frac{K_1 T M - K_2 E G}{K_3 M}$
$G * \xrightleftharpoons[k_6]{k_5} G + *$		—	—

3. RESULTS AND DISCUSSION

3.1 TRANSESTERIFICATION OF CANOLA OIL

Reaction experiments described in section 2.3 were performed by duplicate and FAME profiles as function of time were established. By comparing the FAME profiles of experiments 1, 3 and 4 (methanol-catalyst mixed at first) versus 6, 7 and 8 (oil-catalyst mixed first) in Figure 1, it can be concluded that the reagents order of addition does not affect the time at which equilibrium is reached (about 5 h). Initial production rate (given by the slope of each profile at zero time) is found to be not significantly dependent on reagents order addition. This suggests canola oil transesterification catalyzed by quicklime may not follow the methanol adsorption as the rate-determining step as observed in the transesterification of safflower oil catalyzed by K_2O/NaX [15].

By contrasting the produced profiles in experiments in Figure 2, it can be concluded that the effect of methanol-oil molar ratio has a minor effect on reaction rate at all reaction times. This was an unexpected result and can be attributed to the fact that the reactor was equipped with baffles that promote mixing of methanol with oil and the catalyst thus avoiding mass transfer limitation at these molar ratios. Thus, a kinetic modelling is plausible to be conducted. It is also worth noticing that when studying this variable, the amount of Ca and Mg in the produced biodiesel was determined to be 145 and 2.0 mg/L, respectively. This analysis was conducted by ICP spectrometry as mentioned in section 2.4. Significant differences in the aforementioned values were not found among experiments. This indicates that the amount of catalyst available for homogeneous catalysis, Ca and Mg ions in the reaction mixture, was similar at all experiments when studying the effect of methanol-oil molar ratio. It is worth pointing out that these measurements were

conducted at the end of the reaction time so these values could follow a different evolution with time but at the end of reaction the amount of leached ions is rather similar.

Figure 3 shows evidence of the importance of catalyst loading. It can be observed that increasing the catalyst loading increases reaction rate and with the lowest catalyst loading of 2% presents a sigmoidal profile. This can be ascribed to the lack of active sites to readily transesterify the canola oil.

3.2 KINETIC MODELLING

The aforementioned experimental data were used to test the models proposed in section 2.5 (Tables 2, 3, 4 and 5). Based on the estimated parameters, confidence intervals and regression coefficients for all models, it can be concluded that the model that best fits the experimental data is the one with the Eley-Rideal mechanism and surface reaction as determining step with the assumption of $\frac{k_6}{k_5} G \ll \frac{k_1}{k_2} M$ in accordance with section 2.5, i.e. glycerol adsorption is weak (table 5). The Eley-Rideal kinetic model is consistent with the surface reaction step that becomes rate determining when a high basicity catalyst is used, such as BaO, CaO or SrO (Ilgen, 2012b). It can also be concluded that the LHHW mechanism based models fail to represent the experimental data. These models were found to be less precise, estimated parameters were negative and/or the confidence intervals were rather large. The ER model is shown in equation 3 with its estimated parameters and statistics in Table 6.

$$r = \frac{K_1 T M - K_2 E G}{K_3 M} \quad (3)$$

It is worth noticing that the adsorption equilibrium constant of methanol (K_3) in the selected model, is several orders of magnitude greater than the surface reaction constants (K_1 and K_2), this is coherent with the

assumption of the model, i.e the adsorption of methanol is faster than the surface reaction, which can be considered the controlling step of the reaction. Besides, it can be seen that the value of K_2 is lower than K_1 , indicating that the reaction can be considered as irreversible. This is consistent with the use of an excess of methanol.

The r' calculated with equation 3 was plotted versus the r' obtained from experimental data. This parity plot is shown in Figure 4.

Table 6. Estimated parameters and statistics.

Parameter	Value	95% confidence	Units
K_1	19.013546	0.4281062	$\frac{mol\ E \cdot L}{mol\ T \cdot mol\ M \cdot min \cdot Kg}$
K_2	0.2187906	0.1902954	$\frac{L}{mol\ G \cdot min \cdot kg}$
K_3	316.11977	7.1536297	$\frac{L}{mol\ M}$
Statistics			
R^2		0.9886145	
R_{adj}^2		0.9881498	
R_{msd}		0.0462578	
σ^2		0.1180812	

The selected model is coherent with the mechanism reported by Peng-Lim *et al.* (Peng-Lim Boey, Maniam, & Hamid, 2011) using CaO (with other oil though) and also includes the proposal of Kouzu *et al.* (Masato Kouzu, Hidaka, Wakabayashi, & Tsunomori, 2010). According to the former, methanol is dissociated upon adsorption onto the catalytic surface to mainly form calcium methoxide, partial negative charge over the oxygen in this specie attacks a carbonile group, as a consequence a stable diglyceride and one FAME molecule is obtained and CaO is recovered. This may also be occurring over the existent MgO. The same cycle will follow but now the diglyceride will be transformed to monoglyceride, and finally the monoglyceride will be transformed into glycerol and three molecules of FAME's will be obtained. In addition and according to the validated model, once glycerol is formed some will desorb and some other will remain attached to the surface as glyceroxide (Sharma, Singh, & Korstad, 2011) and this specie can also promote the methoxide formation. Then, the active site that is occupied by this specie can still promote the reaction and thus reaction rate is not really altered. Thus, instead of adding this step, desorption can still be assumed to be fast enough compared to the other steps (this means it cannot be the rate determining elementary step) and adsorption of glycerol to the active site is assumed to be relatively weak ($\frac{k_{irreversible}}{k_{reversible}}G \ll \text{other adsorbed species}$).

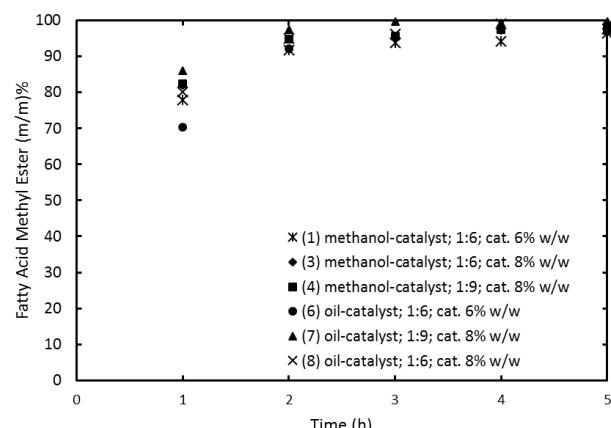


Fig. 1. Effect of reagents order addition on Fatty-Acid Methyl Ester Content profile. Reaction conditions: $T = 328\ K$, rpm = 1000, $W_{\text{catalyst}} = 6$ and 8 % w/w.

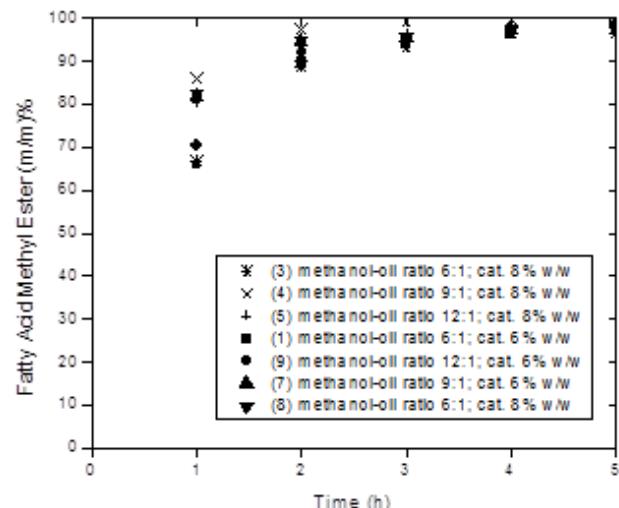


Fig. 2. Effect of methanol-oil molar ratio and catalyst loading on fatty acid methyl esters content. Reaction conditions: methanol-catalyst mixed at first (1, 9, 3, 4 and 5) and methanol-oil mixed at first (7 and 8), $T = 328\ K$, rpm = 1000, $W_{\text{catalyst}} = 6-8$ % w/w.

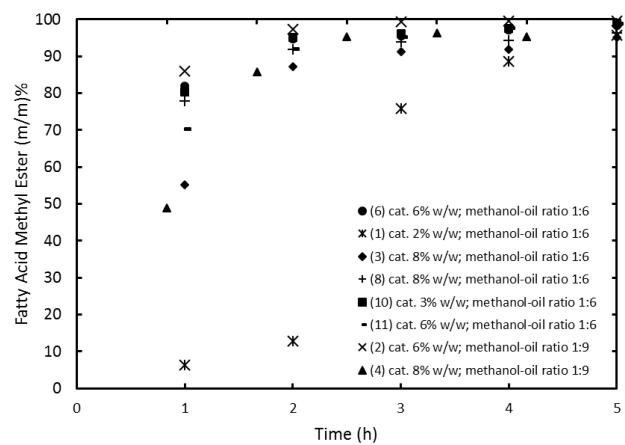


Fig. 3. Effect of catalyst loading ratio on Fatty Acid Methyl Esters evolution with time. Reaction conditions: methanol-catalyst mixed at first (1, 2, 3, 4, 10, 11) and methanol-oil mixed at first (6 and 8), $T = 328\ K$, rpm = 1000.

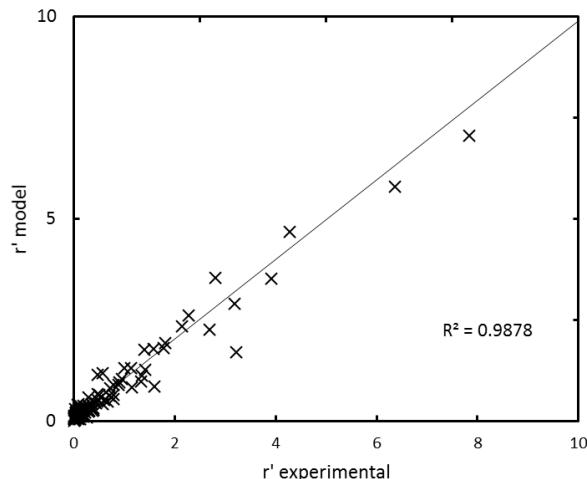


Fig. 4. FAME production rates parity plot.

4. CONCLUSIONS

Biodiesel fulfilling the norm EN 14103 in terms of methyl esters content was produced from the transesterification of canola oil catalyzed by quicklime. This is a relatively low cost catalyst that can be successfully applied in the transesterification of vegetable oils. It was also concluded that none of the assessed methanol-oil molar ratio (6:1, 9:1 or 12:1) exerted a significant effect on reaction rate or final FAME content.

Regarding the kinetic modelling, it can be concluded that Langmuir-Hinshelwood-Hougen-Watson approaches are not adequate to reproduce FAME concentration profiles generated during the quicklime catalyzed canola oil transesterification.

A kinetic model based on Eley-Rideal mechanism with surface reaction as limiting step and weak adsorption of glycerol, for the transesterification of canola oil and methanol in the presence of quicklime as catalyst was concluded to best fit experimental results. The established equation can be applied to predict the methyl esters content with time and for process design purposes.

It can also be concluded that during the assessed process, triglycerides are not adsorbed onto the catalyst surface and due to the rapid adsorption of methanol the order of addition of reactants does not affect the reaction rate with this catalyst.

ACKNOWLEDGEMENTS

The financial support of Universidad Autónoma del Estado de México through Project 3685/2014 CIB is acknowledged. N. Camacho wishes to thank Consejo

Nacional de Ciencia y Tecnología (CONACYT) for scholarship No. 383423 to conduct postgraduate studies. CONACYT financial support through project 269093 is also acknowledged. Uvaldo Balderas Hernández and Citlalit Martínez Soto are acknowledged for technical support.

CONFLICT OF INTEREST

The authors have no conflicts of interest to declare.

REFERENCES

- Alba-Rubio, A. C., Santamaría-González, J., Mérida-Robles, J. M., Moreno-Tost, R., Martín-Alonso, D., Jiménez-López, A., & Maireles-Torres, P. (2010). Heterogeneous transesterification processes by using CaO supported on zinc oxide as basic catalysts. *Catalysis Today*, 149(3–4). <https://doi.org/10.1016/j.cattod.2009.06.024>
- Alonso, D. M., Mariscal, R., Granados, M. L., & Maireles-Torres, P. (2009). Biodiesel preparation using Li/CaO catalysts: Activation process and homogeneous contribution. *Catalysis Today*. <https://doi.org/10.1016/j.cattod.2008.09.021>
- Arzamendi, G., Arguiñarena, E., Campo, I., Zabala, S., & Gandía, L. M. (2008). Alkaline and alkaline-earth metals compounds as catalysts for the methanolysis of sunflower oil. *Catalysis Today*, 133–135(1–4). <https://doi.org/10.1016/j.cattod.2007.11.029>
- Banković-Ilić, I. B., Miladinović, M. R., Stamenković, O. S., & Veljković, V. B. (2017). Application of nano CaO-based catalysts in biodiesel synthesis. *Renewable and Sustainable Energy Reviews*. <https://doi.org/10.1016/j.rser.2017.01.076>
- Boey, P.-L., Ganesan, S., Maniam, G. P., & Khairuddeen, M. (2012). Catalysts derived from waste sources in the production of biodiesel using waste cooking oil. *Catalysis Today*, 190(1). <https://doi.org/10.1016/j.cattod.2011.11.027>
- Boey, P.-L., Maniam, G. P., & Hamid, S. A. (2011). Performance of calcium oxide as a heterogeneous catalyst in biodiesel production: A review. *Chemical Engineering Journal*, 168(1), 15–22. <https://doi.org/10.1016/j.cej.2011.01.009>
- Camacho, J. N., Natividad, R., Galván Muciño, G. E., García-Orozco, I., Baeza, R., & Romero, R. (2016). Comparative Study of Quick Lime and CaO as Catalysts of Safflower Oil Transesterification. *International Journal of Chemical Reactor Engineering*, 14(4). <https://doi.org/10.1515/ijcre-2015-0144>
- Galván Muciño, G. E., Romero, R., Ramírez, A., Ramos, M. J., Baeza-Jiménez, R., & Natividad, R. (2016). Kinetics of transesterification of safflower oil to obtain biodiesel using heterogeneous catalysis. *International Journal of Chemical Reactor Engineering*, 14(4). <https://doi.org/10.1515/ijcre-2015-0108>

- Hammett, L. P., & Deyrup, A. J. (1932). A series of simple basic indicators. I. The acidity functions of mixtures of sulfuric and perchloric acids with water. *Journal of the American Chemical Society*, 54(7). <https://doi.org/10.1021/ja01346a015>
- Ilgen, O. (2011). Dolomite as a heterogeneous catalyst for transesterification of canola oil. *Fuel Processing Technology*, 92(3), 452–455. <https://doi.org/10.1016/j.fuproc.2010.10.009>
- Ilgen, O. (2012a). Reaction kinetics of dolomite catalyzed transesterification of canola oil and methanol. *Fuel Processing Technology*, 95, 62–66. <https://doi.org/10.1016/j.fuproc.2011.11.015>
- Ilgen, O. (2012b). Reaction kinetics of dolomite catalyzed transesterification of canola oil and methanol. *Fuel Processing Technology*, 95, 62–66. <https://doi.org/10.1016/j.fuproc.2011.11.015>
- Ilgen, O., & Akin, A. N. (2012). Determination of reaction orders for the transesterification of canola oil with methanol by using KOH/MgO as a heterogeneous catalyst. *Applied Catalysis B: Environmental*, 126, 342–346. <https://doi.org/10.1016/j.apcatb.2012.07.034>
- Khemthong, P., Luadthong, C., Nualpaeng, W., Changsuwan, P., Tongprem, P., Viriya-Empikul, N., & Faungnawakij, K. (2012). Industrial eggshell wastes as the heterogeneous catalysts for microwave-assisted biodiesel production. *Catalysis Today*, 190(1). <https://doi.org/10.1016/j.cattod.2011.12.024>
- Kouzu, M., Fujimori, A., Suzuki, T., Koshi, K., & Moriyasu, H. (2017). Industrial feasibility of powdery CaO catalyst for production of biodiesel. *Fuel Processing Technology*, 165. <https://doi.org/10.1016/j.fuproc.2017.05.014>
- Kouzu, M., Hidaka, J., Wakabayashi, K., & Tsunomori, M. (2010). Solid base catalysis of calcium glyceroxide for a reaction to convert vegetable oil into its methyl esters. *Applied Catalysis A: General*, 390(1–2), 11–18. <https://doi.org/10.1016/j.apcata.2010.09.029>
- Lee, A. F., & Wilson, K. (2015). Recent developments in heterogeneous catalysis for the sustainable production of biodiesel. *Catalysis Today*. <https://doi.org/10.1016/j.cattod.2014.03.072>
- Lukic, I., Kesic, Z., Maksimovic, S., Zdujic, M., Krstic, J., & Skala, D. (2014). Kinetics of heterogeneous methanolysis of sunflower oil with CaO·ZnO catalyst: Influence of different hydrodynamic conditions. *Chemical Industry and Chemical Engineering Quarterly*, 20(3), 425–439. <https://doi.org/10.2298/CICEQ130514025L>
- Luz Martínez, S., Romero, R., López, J. C., Romero, A., Sánchez Mendieta, V., & Natividad, R. (2011). Preparation and characterization of CaO nanoparticles/NaX zeolite catalysts for the transesterification of sunflower oil. In *Industrial and Engineering Chemistry Research* (Vol. 50, pp. 2665–2670).
- Marinković, D. M., Avramović, J. M., Stanković, M. V., Stamenković, O. S., Jovanović, D. M., & Veljković, V. B. (2017). Synthesis and characterization of spherically-shaped CaO/γ-Al₂O₃ catalyst and its application in biodiesel production. *Energy Conversion and Management*. <https://doi.org/10.1016/j.enconman.2017.04.079>
- Masato, K., Jyu-suke, H., Yoshiya, K., & Haruhiko, N. (2009). A process to transesterify vegetable oil with methanol in the presence of quick lime bit functioning as solid base catalyst. *Fuel*, 88(10), 1983–1990.
- Miladinović, M. R., Krstić, J. B., Tasić, M. B., Stamenković, O. S., & Veljković, V. B. (2014). A kinetic study of quicklime-catalyzed sunflower oil methanolysis. *Chemical Engineering Research and Design*, 92(9), 1740–1752. <https://doi.org/10.1016/j.cherd.2013.11.023>
- Muciño, G. G., Romero, R., Ramírez, A., Martínez, S. L., Baeza-Jiménez, R., & Natividad, R. (2014). Biodiesel production from used cooking oil and sea sand as heterogeneous catalyst. In *Fuel* (Vol. 138, pp. 143–148). <https://doi.org/10.1016/j.fuel.2014.07.053>
- Ngamcharussrivichai, C., Totarat, P., & Bunyakiat, K. (2008). Ca and Zn mixed oxide as a heterogeneous base catalyst for transesterification of palm kernel oil. *Applied Catalysis A: General*. <https://doi.org/10.1016/j.apcata.2008.02.020>
- Risso, R., Ferraz, P., Meireles, S., Fonseca, I., & Vital, J. (2018). Highly active CaO catalysts from waste shells of egg, oyster and clam for biodiesel production. *Applied Catalysis A: General*, 567(September), 56–64. <https://doi.org/10.1016/j.apcata.2018.09.003>
- Sharma, Y. C., Singh, B., & Korstad, J. (2011). Latest developments on application of heterogenous basic catalysts for an efficient and eco friendly synthesis of biodiesel: A review. *Fuel*, 90(4), 1309–1324. <https://doi.org/10.1016/j.fuel.2010.10.015>
- Tang, Y., Yan, T., Shen, B., Li, H., & Jeje, A. (2016). Synthesis of no-glycerol biodiesel through transesterification catalyzed by CaO from different precursors. *The Canadian Journal of Chemical Engineering*, 94(8), 1466–1471. <https://doi.org/10.1002/cjce.22543>
- Viola, E., Blasi, A., Valerio, V., Guidi, I., Zimbardi, F., Braccio, G., & Giordano, G. (2012). Biodiesel from fried vegetable oils via transesterification by heterogeneous catalysis. *Catalysis Today*, 179(1). <https://doi.org/10.1016/j.cattod.2011.08.050>
- Zhao, L., Qiu, Z., & Stagg-Williams, S. M. (2013). Transesterification of canola oil catalyzed by nanopowder calcium oxide. *Fuel Processing Technology*, 114, 154–162. <https://doi.org/10.1016/j.fuproc.2013.03.027>