



Maderas. Ciencia y tecnología

ISSN: 0718-221X

Universidad del Bío-Bío

Couto da Silva, Bruno; Trevisan, Henrique; Garcia, Rosilei Aparecida
Effect of the thermal modification and nano-ZnO impregnation on the deterioration of Caribbean pine wood
Maderas. Ciencia y tecnología, vol. 22, no. 4, 2020, pp. 569-576
Universidad del Bío-Bío

Available in: <http://www.redalyc.org/articulo.oa?id=48565177015>

- How to cite
- Complete issue
- More information about this article
- Journal's webpage in redalyc.org

UDEM  redalyc.org

Scientific Information System Redalyc

Network of Scientific Journals from Latin America and the Caribbean, Spain and Portugal

Project academic non-profit, developed under the open access initiative

EFFECT OF THE THERMAL MODIFICATION AND NANO-ZNO IMPREGNATION ON THE DETERIORATION OF CARIBBEAN PINE WOOD

Bruno Couto da Silva¹, Henrique Trevisan^{2,}, Rosilei Aparecida Garcia²*

ABSTRACT

This study aimed to investigate the effect of thermal modification and nano-zinc oxide (nano-ZnO) particle impregnation on the deterioration of Caribbean pine wood under field conditions. Samples were thermally-modified at various temperature levels (control, 180 °C, 200 °C, and 220 °C). Nano-ZnO impregnation was done with an aqueous solution at 1,5 % in an autoclave under two-steps of pressure and vacuum. Unmodified and thermally-modified, non-impregnated and nano-ZnO impregnated samples were exposed to deterioration for five months in field tests. A deterioration index was used to evaluate the health condition of the samples. The mass loss and occurrence of termite tunnels in percentage were also determined. The nano-ZnO impregnation improved the resistance of unmodified wood to field-deterioration. The thermal modification at 180°C, and 200°C increased the wood deterioration and nano-ZnO impregnation did not improve their resistance. Unmodified and 220 °C modified samples had a lower mass loss by xylophages than other thermal treatments regardless of the nanoparticle impregnation. The nano-ZnO impregnation decreases the occurrence of termite tunnels in unmodified, 200 °C and 220 °C-modified samples.

Keywords: Deterioration index, mass loss, nano-zinc oxide particle, termite tunnels, wood deterioration.

INTRODUCTION

Wood is an organic material subject to the action of biotic and abiotic deterioration. Therefore, it is necessary to use products and processes that increase its resistance to deterioration in order to optimize its use, especially when the environmental conditions as in Brazil favor the action of xylophage agents. The biological resistance of wood can be improved through treatments that add characteristics that hinder or inhibit the action of these xylophage organisms (Vidal *et al.* 2015). Among the treatments used for wood preservation, the most noteworthy are the chemical products (Valle *et al.* 2013, Vidal *et al.* 2015) and thermal modification (Salman *et al.* 2017, Sivrikaya *et al.* 2015, Tripathi *et al.* 2014).

CCA (Chromium Copper Arsenate) is the most well-known and most used chemical in the wood preservation industry and accounts for more than 90 % of chemically-treated wood in Brazil (Vidal *et al.* 2015). Actually, in Brazil, there is no restriction on the use of CCA for the preservation of wood. However, in North America and Europe, its use, mainly due to the arsenic component, has been restricted due to environmental and human health issues, being limited to certain classes of exposure to biological risks that do not involve direct contact with the being such as domestic use. Therefore, the wood preservation sector has been searching for methods that can replace the use of CCA, mainly in applications where the product has been banned.

¹Postgraduate program in Environmental and Forest Sciences, Department of Forest Products, Forest Institute, Federal Rural University of Rio de Janeiro. Seropédica, Brazil.

²Professor, Department of Forest Products, Forest Institute, Federal Rural University of Rio de Janeiro. Seropédica, Brazil.

*Corresponding author: hentrevisan@gmail.com

Received: 07.05.2019 Accepted: 05.08.2020

Thermal modification and nanoparticles (e.g. zinc oxide, zinc-borate, silver, copper, and copper-borate) treatments have emerged as alternative treatments to improve biological resistance to wood (Bak and Németh 2018, Lykidis *et al.* 2016, Marzbani *et al.* 2015, Taghiyari *et al.* 2015, Mantanis *et al.* 2014, Clausen *et al.* 2011). Several works have reported an increase on decay resistance of wood following thermal modification (Salman *et al.* 2017, Sivrikaya *et al.* 2015, Tripathi *et al.* 2014) but a decrease on the resistance to termite attacks (Trevisan *et al.* 2014, Salman *et al.* 2017). Moreover, the literature reports contradictory results about the effect of thermal modification on the resistance of wood to the attack of these insects in laboratory tests (Paes *et al.* 2015, Pessoa *et al.* 2006). Previous works also have shown an important effect of nano-ZnO on biological resistance. For example, Clausen *et al.* (2011) reported an increase of termite mortality (*Reticulitermes flavipes* Kollar) and a decrease in wood consumption in nano-ZnO-treated Southern yellow pine (*Pinus echinata* Mill.) wood in laboratory tests. According to Mantanis *et al.* (2014), nano-ZnO and Boron association inhibited the action of termite species *Coptotermes formosanus* and the decomposition by xylophagous fungus *Trametes versicolor* in pine wood. Lykidis *et al.* (2018) also observed that wood species *Fagus sylvatica* impregnated with nano-ZnO has shown increased resistance to the termite species *Reticulitermes grassei*. However, it is not clear whether this also occurs in field conditions or other termite species. In these environments, the biotic and abiotic deteriorating agents interact with each other in the form of synergies and antagonisms which are difficult to reproduce under laboratory conditions. According to Lykidis *et al.* (2013), nano-ZnO has great potential to be used in wood preservatives, although they emphasize the need of carrying out tests under field conditions. This same reasoning should also be done when considering thermal modification as a process to increase the biological resistance of the wood.

Therefore, this study aimed to investigate the effect of thermal modification and nano-ZnO impregnation on the deterioration of Caribbean pine wood in field tests.

MATERIAL AND METHODS

Material and thermal modification

Free-defect samples of 150 x 75 x 20 mm³ (length x width x thickness) were prepared from a twenty-five-years-old Caribbean pine tree harvested from a plantation located in Seropédica city of Rio de Janeiro State, Brazil (Latitude: -22° 44' 38" S, Longitude: -43° 42' 27" W). Samples were conditioned in a climate chamber at 20 °C and 65 % relative humidity (RH) until mass equilibrium.

Thermal modification treatments were performed in a laboratory muffle furnace from Linn Elektro Therm of 600 x 600 x 700 mm³ at three temperature levels (180 °C, 200 °C, and 220 °C). Four steps were used for the thermal treatment: (1) heating up to 100 °C for 2 h, (2) heat increasing from 100 °C to final temperature (180 °C, 200 °C, and 220 °C) for 30 min, (3) thermal modification at the final temperature for 2 h, and (4) cooling for approximately 24 h. The initial moisture content of the samples (before thermal modification) was approximately 12 % (based on the oven-dry weight). Thermally-modified samples were then stored at 20 °C and 65 % RH until mass equilibrium. Afterward, thermally-modified woods were separated into two matched groups and one from them was used to nanoparticle impregnation.

Nanoparticle impregnation treatment

A compact impregnation plant T10 with 453 l of capacity from Wood Treatment Technology (WTT) company was used to nanoparticle treatment. Commercial nano-ZnO particles denominated VP AdNano® ZnO 20, hydrophilic version, with dimensions varying from 20 to 25 nm, from Evonik Industries AG (Essen, Germany) were used for impregnation treatment. A nano-ZnO aqueous solution at 1,5 % was prepared and homogenized with a CanLab mechanical stirrer. This concentration was chosen due to the high cost of nanoparticles. Moreover, low concentrations decrease the viscosity of the solution, which facilitates the impregnation of the nanoparticles in the wood. The sample impregnation was done in a storage tank placed below the autoclave under two steps of pressure and vacuum: (1) application of vacuum at 0,005 Mpa for 10 min, and (2) application of pressure at 0,4 MPa for 15 min. The nano-ZnO-impregnated samples were dried at 40 °C for 24 h and then stored at 20 °C and 65 % RH until mass equilibrium. The weight of the samples was taken at this condition.

An experimental design with four temperature levels of thermal modification (ambient or control, 180 °C, 200 °C, and 220 °C) and two impregnation groups (non-impregnated and nano-ZnO-impregnated) were used, resulting in eight treatments.

Field tests

Wood samples of 150 x 20 x 20 mm³ (length x width x thickness) were installed in a field trial using the randomized complete block design (RDBD) with eight replicates per treatment. Samples were planted until half of its length, remaining exposed to the process of deterioration during five months, from April to September 2017. Inspections were monthly performed to record termite colonization, evidenced by the construction of tunnels along the length of the sample. After five months of exposure in the decay-field, the samples were transported to the laboratory where they were cleaned and then the deterioration level was evaluated according to the criteria shown in Table 1. Afterward, samples were conditioned at 20 °C and 65 % UR until constant mass. The sample masses were measured at the initial condition (before field test) and after exposure in the field test. The mass losses of the samples were then calculated in percentage.

Table 1: Classification criteria of deterioration levels of wood samples in field tests according to Lepage (1970).

Health condition	Deterioration index
Breakage, almost total loss of resistance	0
Severe decay or internal attack of termites	40
Moderate attack of decay or termites	70
Slight or superficial attack of decay or termites	90
Healthy, no evidence of the attack	100

The analysis of the mass loss data was performed in the BioEstat software, version 5.0 (Ayres *et al.* 2007). The normality of the data was verified by the Lillefors test, followed by an analysis of variances and the comparison of the means by the Tukey’s test at the 0,05 probability level.

RESULTS AND DISCUSSION

The means of the index deterioration and density of the thermally-modified Caribbean pine wood, non-impregnated, and nano-ZnO-impregnated, after five months in the field test, are shown in Table 2. All samples from all treatments showed evidence of deterioration but at different levels depending on the treatment condition (Figure 1). The 180 °C-modified samples, regardless of the nanoparticle treatment, showed a high deterioration with an average index of 23 and 7 for non-impregnated and nano-ZnO-impregnated samples. On the other side, the action of the xylophages was less intense in the 200 °C-modified samples (non-impregnated and nano-ZnO-impregnated). The nanoparticle treatment provided an index that indicates lower deterioration in the unmodified samples, compared to the other treatments, being, therefore, the most expressive result in this experiment. It is important to emphasize that all treatments presented ruptured samples in the border region between the buried and aerial parts, evidenced by the zero indexes in the minimum value, except in the non-impregnated-220 °C-modified and the nano-ZnO-impregnated-unmodified samples (Figure 1). These results, in addition to the previous observations, show that these two treatment conditions were actually the ones that improved the resistance to deterioration because no sample was completely broken by the action of the deterioration processes.

Table 2: Mean, maximum, and minimum deterioration index (\pm standard deviation) and density of the thermally-modified pine wood, non-impregnated and nano-ZnO impregnated, after five months in field tests.

Nanoparticle treatment	Temperature (°C)	Deterioration index			Density (kg/m ³)
		Mean	Maximum	Minimum	
Non-impregnated	Control	43 \pm 26	70	0	700
	180	23 \pm 36	70	0	760
	200	30 \pm 35	70	0	740
	220	45 \pm 12	70	40	610
nano-ZnO impregnated	Control	68 \pm 16	90	40	710
	180	7 \pm 16	40	0	710
	200	37 \pm 31	70	0	730
	220	47 \pm 41	100	0	660

The analysis of the mass loss caused mainly by termites is an important variable to verify the improvement or not of biological resistance to the wood by the treatment. In this sense, it was observed that the nano-ZnO-impregnated-unmodified samples and the non-impregnated-220 °C-modified samples had lower mass losses (Figure 2). The mass loss assessment must be carried out together with that of the wood density in order to avoid misinterpretations. The temperature at 200 °C decreased the density of the wood, (Table 2) and when a non-toxic substrate has a lower density, the termites may remove a similar amount of biomass as a denser substrate, however, the lesions caused by this removal may be more significant. This may explain the similar mass loss recorded for the nano-ZnO-impregnated-unmodified and 220 °C-modified samples.

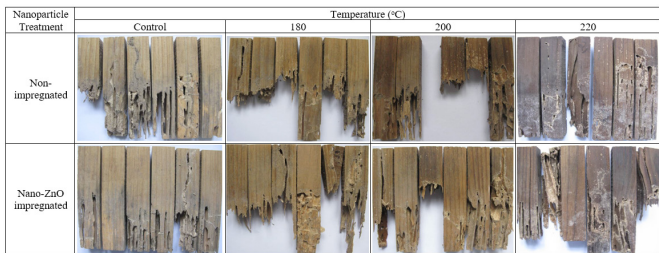


Figure 1: Deterioration of the thermally-modified pine wood, non-impregnated and nano-ZnO impregnated, after five months in field tests.

This fact is evident when the mass loss of the wood is analyzed together with the deterioration index, which is a value that expresses, among other attributes, the lesions provided by the xylophagous organisms in the wood. Thus, although the mass losses were equivalent in the nano-ZnO-impregnated-unmodified and 220 °C-modified samples, the deterioration index shows that the thermally-modified samples had higher wear caused by xylophages, compared to the nano-ZnO-impregnated-unmodified samples (Table 2).

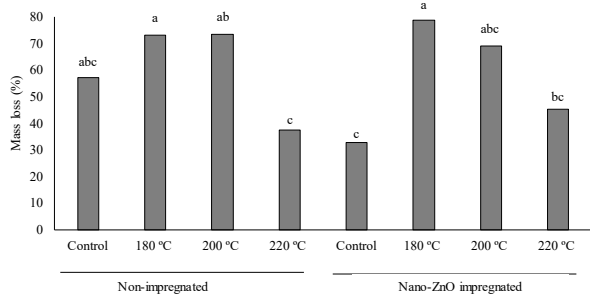


Figure 2: Relative mass loss of the thermally-modified pine wood, non-impregnated and nano-ZnO impregnated, after five months in field tests.

Means with the same letter are not significantly different from each other by Tukey’s test at the 0,05 probability level.

Therefore, the nano-ZnO impregnation in the natural pine wood is more efficient to improve biological resistance than when added to thermally-modified wood at 220 °C, which exhibited more evident lesions provided by xylophages. A study realized by Clausen *et al.* (2009) reported the effectiveness of nano-ZnO treatment to prevent the consumption of wood by termites, regardless of the size of the nanoparticles. These authors also reported significant mortality of termites at a nano-ZnO concentration of 1 %. However, it must be considerate that they performed laboratory trials that promote constant conditions and the termites have no preference choice.

It is important to consider other factors that influence the deterioration of wood by xylophages in field tests, including abiotic factors such as pH. The pH of the soil may influence the properties of the nanoparticles, which can be solubilized at very acid or very basic pH. Thus, the high mortality of termites observed in other studies (Clausen *et al.* 2011), may not occur under conditions that favor the solubility of the nanoparticles as in field conditions. In addition, the presence of water and the acidic pH of the wood could promote the dissolution of the nano-ZnO (Silva 2018). Therefore, in field tests, soil moisture and precipitation may favor leaching. Clausen *et al.* (2010) evaluated the leach resistance of the Southern pine samples vacuum-treated with nano-ZnO. In laboratory tests, no leaching occurred in nano-ZnO-treated samples even at the highest retention of 12,96 % kg/m³ with a concentration of 5 %. However, in the field experiments, the authors found a loss of nano-ZnO by leaching of 65 % in concentrations of 2,5 % and 58 % in the concentration of 5 %. Low concentrations of nano-ZnO (1 %) showed almost no leaching, however, these authors did not report the pH in which the samples were tested. Lykidis *et al.* (2018) assessed wood species *Fagus sylvatica* impregnated with nano-ZnO, at the concentrations of 0,5 %, 1 %, 2 %, and observed that all treatments increased its resistance to the action of termite species *Reticulitermes grassei*; leaching by water did not significantly change this result.

Our results show that, even with these assumptions, the nano-ZnO impregnation improved biological resistance to natural pine wood at low concentration. Clausen *et al.* (2011) used an aqueous dispersion containing three nano-ZnO concentrations (1,0 %; 2,5 % and 5,0 %) to treat Southern yellow pine and assess the termite mortality in laboratory tests. Their results showed that termite (*Reticulitermes flavipes*) consumed less than 10 % and exhibited from 93 % to 100 % mortality for all treatment concentrations. Thus, it is possible to assume that, under field conditions, higher concentrations could result in less mass loss and greater resistance to xylophages. According to Mantanis *et al.* (2014), nano-ZnO has shown reduced leaching when it was incorporated, in association with acrylic emulsion, to pine wood. Thus, this type of emulsion can be an interesting strategy to reduce the leaching of these nanoparticles under field conditions.

The size of nanoparticles also can be an important factor for the efficacy of the treatment. Kartal *et al.* (2009) reported good efficiency of nano-ZnO treatment of Southern yellow pine wood against Eastern subterranean termites (*Reticulitermes flavipes*) and decay fungi using nanoparticles from 40 nm to 100 nm. Németh *et al.* (2013) also reported good performance of nano-ZnO of 20-40 nm in the resistance of some softwoods and hardwoods (spruce (*Picea abies* L.), Scots pine sapwood (*Pinus sylvestris* L.), poplar (*Populus x euramericana* cv. *Pannonia*), and beech (*Fagus sylvatica* L.) species using concentration of 5 %. On the other hand, Lykidis *et al.* (2016) evaluated the resistance of Scots pine wood treated with nano-ZnO of 60-80 nm against the brown-rot fungi (*Daedalea quercina* L. and *Poria placenta* (Fr.) Cooke) and dry rot fungus (*Serpula lacrymans* (Wulfen) J. Schröt.). The nano-ZnO treatment improved the wood resistance to *Serpula lacrymans* but not against the *Poria placenta* fungus. Clausen *et al.* (2011) used nano-ZnO of 30 nm and 70 nm, but they did not evaluate its efficacy against fungi. Furthermore, these studies show that nano-ZnO efficacy also depends on the wood and the xylophage species.

Also, the efficiency of nano-ZnO was observed for wood-based composites. Marzbani *et al.* (2015) also studied the effect of nano-ZnO added to the adhesive urea-formaldehyde used in the manufacture of particleboard against the white-rot (*Trametes versicolor* (L.) Lloyd) and the brown-rot (*Coniophora puteana* (Schumach.) P. Karst.) fungi. The authors added 5 %, 10 % and 15 % of nano-ZnO (based on the dry weight of the adhesive). Their results showed an improvement of particleboard against fungi decay, principally at 15% nano-ZnO. Taghiyari *et al.* (2015) observed that wood species *Paulownia* subjected to heat treatment at 150 °C, in association with nano-ZnO impregnation under laboratory conductions, significantly inhibited the growth of fungus species *Trametes versicolor* and the loss of mass.

In order to evaluate the efficiency of a product and/or process to preserve wood against the action of xylophagous organisms, mainly termites, several parameters should be considered and not only the mass loss. The foraging and tunneling pattern of termites can provide important information about the influence of these treatments on the biological resistance and consequently on their preservative efficiency in the wood. Therefore, the occurrence of tunnels in the aerial part of the samples caused by two subterranean termite

species: *Coptotermes gestroi* (Wasmann) and *Heterotermes tenuis* (Hagen) was registered monthly during the five months in the field conditions (Figure 3). According to Guadalupe-Rojas and Morales-Ramos (2001), the food preference of *Coptotermes formosanus* Shiraki is determined by the nutritional value of the resource. Considering that this is the same for other termite species, tunnel construction time, analyzed together with the mass loss and the lesions caused in the samples, may reveal relevant information to evaluate the efficiency of wood preservation techniques. Therefore, termites choose their food according to nutritional needs, and for this choice to take place, it is necessary to construct tunnels to locate suitable food resources (Grace and Campora 2005). Food is only accepted after arduous inspection by fodder since not all sources are accepted (Lima 2014). This inspection occurs by foraging the substrate, which occurs when the termite constructs the tunnels on the substrate.

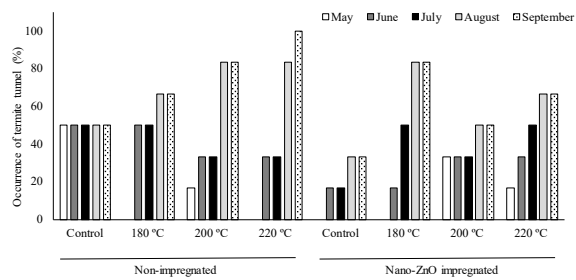


Figure 3: Percentage occurrence of termite tunnels in thermally-modified pine wood, non-impregnated and nano-ZnO impregnated, after five months in field tests.

Our results showed that the majority of the non-impregnated samples had a greater occurrence of tunnels in the external part of the sample (Figure 3). This fact could suggest that biomass consumption was higher in these samples. However, the external tunneling of the samples only shows that the resource is being foraged and not effectively consumed by the termites. Lima (2014) explains the importance of analyzing the tunneling pattern together with the biomass values consumed as well as associating them with the lesions caused by the insects in the samples. In our study, the occurrence of tunnels was evaluated by the system of grades attributed to wear by the termite (Table 1). All the non-impregnated-220 °C-modified samples presented the occurrence of tunnels at the final of the experiment (Figure 3), however, they exhibited low mass loss, together with the nano-ZnO-impregnated-unmodified samples (Figure 2). This suggests that the non-impregnated-220 °C-modified samples, although the higher occurrence of tunnels, had only foraging by termites, not consumption effectively. Hence, the thermal modification at 220 °C can add characteristics that make the wood little palatable to these insects and not necessarily toxic. This could justify the greater presence of tunnels in these samples, which would be more difficult to produce if the substrate were toxic. On the other hand, the nano-ZnO-impregnated-unmodified samples were discarded at the beginning and consequently had lower occurrence tunnels to the end of the experiment (Figure 3), indicating the toxic effect of the nanoparticles. These results corroborate to those found by Clausen *et al.* (2011), which showed high mortality and low mass consumption by *Reticulitermes flavipes* termite in nano-ZnO-treated samples.

Considering these data, we found that the thermal modification at 180 °C and 200 °C, even with the nano-ZnO treatment, made the wood more attractive and consumed by termites. Nevertheless, the temperature of 220 °C made the wood attractive but less consumed by the termites. The nano-ZnO incorporation to unmodified wood was the most efficient treatment for wood preservation since these samples were the least tunneled and less consumed by termites. However, the nano-ZnO incorporation to the thermally-modified wood was not efficient to improve the deterioration resistance under the conditions of the field test.

CONCLUSIONS

The nano-ZnO impregnation increase the degradation resistance in unmodified Caribbean pine wood, however, it does not improve the degradation resistance of 180 °C and 200 °C-modified samples.

The 220 °C-modified Caribbean pine samples were more resistant to xylophage organisms, regardless of the nano-ZnO impregnation, compared to unmodified, 180 °C and 200 °C-modified samples.

Pinus wood impregnated with nano-ZnO has shown decreased tunneling by termites under natural conditions, which indicated anti-feeding effect on these organisms.

Nano-ZnO impregnation in pine wood is a promising treatment to add biological resistance to this material under field conditions. It is necessary to conduct further studies to assess the efficiency of this technique in other forest species, as well as to investigate its application in association with other procedures that also aim at protecting this material from biological deterioration processes.

ACKNOWLEDGMENTS

This work was conducted during a scholarship supported by CAPES - Brazilian Federal Agency for Support and Evaluation of Graduate Education within the Ministry of Education of Brazil. The authors are grateful to Professor Dr. Bernard Riedl of the Laval University of Canada for his valuable guidance on the treatment of nanoparticles.

REFERENCES

- Ayres, M.; Ayres, M.; Ayres, D.L.; Santos, A.A.A. 2007.** BioEstat 5.0. Aplicações Estatísticas nas Áreas das Ciências Biológicas e Médicas. Tefê: Sociedade Civil Mamirauá.Brazil.
- Bak, M.; Németh, R. 2018.** Effect of different nanoparticle treatments on the decay resistance of wood. *BioResources* 13(4): 7886-7899. https://ojs.cnr.ncsu.edu/index.php/BioRes/article/view/BioRes_13_4_7886_Bak_Nanoparticle_Decay_Resistance_Wood.
- Clausen, C.A.; Green, F.; Nami Kartal, S. 2010.** Weatherability and leach resistance of wood impregnated with nano-zinc oxide. *Nanoscale Res Lett* 5(9): 1464-1467. <https://doi.org/10.1007/s11671-010-9662-6>
- Clausen, C.A.; Kartal, S.N.; Arango, R.A.; Green, F. 2011.** The role of particle size of particulate nano-zinc oxide wood preservatives on termite mortality and leach resistance. *Nanoscale Res Lett* 6: 427. <https://doi.org/10.1186/1556-276X-6-427>
- Clausen, C.A.; Yang, V.W.; Arango, R. A.; Green, F. 2009.** Feasibility of nanozinc oxide as a wood preservative. In Proceedings of American Wood Protection Association 105: 255-260. <https://naldc.nal.usda.gov/download/41044/PDF>
- Grace, J.K.; Campora, C.E. 2005.** Food location and discrimination by subterranean termites (Isoptera: Rhinotermitidae). In Proceedings of International Conference on Urban Pests 437-441
- Guadalupe-Rojas, M.; Morales-Ramos, J.A. 2001.** Bait matrix for delivery of chitin synthesis inhibitors to the Formosan subterranean termite (Isoptera: Rhinotermitidae). *J Econ Entomol* 94(2): 506-510. <https://doi.org/10.1603/0022-0493-94.2.506>
- Kartal, S.N.; Green III, F.; Clausen, C.A. 2009.** Do the unique properties of nanometals affect leachability or efficacy against fungi and termites? *Inter Biodeter Biodegr* 63(4): 490-495. <https://doi.org/10.1016/j.ibiod.2009.01.007>
- Lepage, E.S. 1970.** Método Sugerido pela IUFRO para ensaios de campo com estacas de madeira. *Preservação de madeiras* 1: 205-216
- Lima, J.T.; Costa-Leonardo, A.M. 2014.** Foraging in subterranean termites (Isoptera: Rhinotermitidae): how do *Heterotermes tenuis* and *Coptotermes gestroi* behave when they locate equivalent food resources? *B Entomol Res* 10(4): 525-533. <https://doi.org/10.1017/S0007485314000297>
- Lykidis, C.; Bak, M.; Mantanis, G.; Németh, R. 2016.** Biological resistance of pine wood treated with nano-sized zinc oxide and zinc borate against brown-rot fungi. *Eur J Wood Wood Prod* 74(6): 909-911. <https://doi.org/10.1007/s00107-016-1093-3>
- Lykidis, C.; Mantanis, G.; Adamopoulos, S.; Kalafata, K. 2013.** Arabatzis, I. Effects of nano-sized zinc oxide and zinc borate impregnation on brown rot resistance of black pine (*Pinus nigra* L.) wood. *Wood Mater*

Sci Eng 8(4): 242-244. <https://doi.org/10.1080/17480272.2013.834969>

Lykidis, C.; Troyab, T. De.; Condeb, M.; Galvanc, J.; Mantanisd, G. 2018. Termite resistance of beech wood treated with zinc oxide and zinc borate nanocompounds. *Wood Mater Sci Eng* 13(1): 45-49. <https://doi.org/10.1080/17480272.2016.1257651>

Mantanis, G.; Terzi, E.; Kartal, S.N.; Papadopoulos, A.N. 2014. Evaluation of mold, decay and termite resistance of pine wood treated with zinc- and copper-based nanocompounds. *Int Biodeter Biodegr* 90: 140-144. <https://doi.org/10.1016/j.ibiod.2014.02.010>

Marzbani, P.; Afrouzi, Y.; Omidvar, A. 2015. The effect of nano-zinc oxide on particleboard decay resistance. *Maderas-Cienc Tecnol* 17(1): 63-68. <http://dx.doi.org/10.4067/S0718-221X2015005000007>

Németh, R.; Bak, M.; Yimmou, B.M.; Csupor, K.; Molnár, S.; Csóka, L. 2013. Nano-zink as an agent against wood destroying fungi. In *Wood the Best Material for Mankind*. Kúdela, J.; Babiak, M. (eds). Arbora Publishers, Zvolen, Slovakia. <https://iaws-web.org/files/file/Zborn%C3%ADk%202012.pdf>

Paes, J.B.; Segundinho, P.G.A.; Euflosino, A.E.R.S.; Oliveira, J.G.L. 2015. Resistance of thermally treated woods to *Nasutitermes corniger* in a food preference test. *Madera Bosques* 21(1): 157-164. <https://doi.org/10.21829/myb.2015.211439>

Pessoa, A.M.C.; Berti Filho, E.; Brito, J.O. 2006. Evaluation of the *Eucalyptus grandis* thermorectified wood submitted to the drywood termite attack, *Cryptotermes brevis*. *Sci For* 72: 11-16. <https://www.ipef.br/publicacoes/scientia/nr72/cap01.pdf>

Salman, S.; Thévenon, M.F.; Pétrissans, A.; Dumarçay, S.; Candelier, K.; Gérardin, P. 2017. Improvement of the durability of heat-treated wood against termites. *Maderas-Cienc Tecnol* 19(3): 317-328. <http://dx.doi.org/10.4067/S0718-221X2017005000027>

Silva, B. C. 2018. Efeitos da modificação térmica e da impregnação de nanopartículas na molhabilidade da superfície, composição química e na deterioração da madeira de pinus. Ph.D Thesis, Federal Rural University of Rio de Janeiro, UFRRJ. Rio de Janeiro, Brazil (not published)

Sivrikaya, H.; Can, A.; Troya, T.; Conde, M. 2015. Comparative biological resistance of differently thermal modified wood species against decay fungi, *Reticulitermes grassei* and *Hylotrues bajulus*. *Maderas-Cienc Tecnol* 17(3): 559-570. <http://dx.doi.org/10.4067/S0718-221X2015005000050>

Taghiyari, H.R.; Kalantari, A.; Ghorbani, M.; Bavaneghi, F.; Akhtari, M. 2015. Effects of fungal exposure on air and liquid permeability of nanosilver and nanozinc oxide-impregnated *Paulownia* wood. *Int Biodeter Biodegr* 105: 51-57. <https://doi.org/10.1016/j.ibiod.2015.08.014>

Trevisan, H.; Latorraca, J.V.F.; Santos, A.L.P.; Teixeira, J.G.; Carvalho, A.G. 2014. Analysis of rigidity and deterioration from exposure in a decay test field of thermorectified *Eucalyptus grandis* wood. *Maderas-Cienc Tecnol* 16(22): 217-226. <http://dx.doi.org/10.4067/S0718-221X2014005000017>

Tripathi, S.; Pant, H.; Kashyap, A.K. 2014. Decay resistance against Basidiomycetes fungi of heat-treated *Pinus roxburghii* and *Mangifera indica* wood. *J Trop For Sci* 26(2): 203-207. <https://www.jstor.org/stable/23723905?seq=1>

Valle, M.L.A.; Silva, J.C.; Della Lucia, R.M.; Evangelista, W.V. 2013. Retention and penetration of CCA in wood of first and second rotation of *Eucalyptus urophylla* S.T. Blake. *Cienc Florest* 23(2): 481-490. <https://doi.org/10.5902/198050989292>

Vidal, J.M.; Evangelista, W.V.; Silva, J.C.; Jankowsky, I.P. 2015. Preservação de madeiras no Brasil: histórico, cenário atual e tendências. *Cienc Florest* 25(1): 257-271. https://www.scielo.br/scielo.php?pid=S1980-50982015000100257&script=sci_arttext&tlng=pt