



DYNA

ISSN: 0012-7353

Universidad Nacional de Colombia

Schwantes-Cezario, Nicole; Peres, Maria Vânia Nogueira do Nascimento; Fruet, Thomas Kehrwald; Nogueira, Geovana Souza Ferreira; Toralles, Berenice Martins; Cezario, Davi De Souza  
Crack filling in concrete by addition of *Bacillus subtilis* spores - Preliminary study  
DYNA, vol. 85, no. 205, 2018, April-June, pp. 132-139  
Universidad Nacional de Colombia

DOI: <https://doi.org/10.15446/dyna.v85n205.68591>

Available in: <https://www.redalyc.org/articulo.oa?id=49657889017>

- How to cite
- Complete issue
- More information about this article
- Journal's webpage in redalyc.org

UNEN 

Scientific Information System Redalyc  
Network of Scientific Journals from Latin America and the Caribbean, Spain and Portugal

Project academic non-profit, developed under the open access initiative

## Crack filling in concrete by addition of *Bacillus subtilis* spores – Preliminary study

Nicole Schwantes-Cezario <sup>a</sup>, Maria Vânia Nogueira do Nascimento Peres <sup>b</sup>, Thomas Kehrwald Fruet <sup>b</sup>,  
Geovana Souza Ferreira Nogueira <sup>a</sup>, Berenice Martins Toralles <sup>a</sup> & Davi De Souza Cezario <sup>c</sup>

<sup>a</sup> State University of Londrina, Londrina, Brazil. [nicoleschwantes@hotmail.com](mailto:nicoleschwantes@hotmail.com); [geovanasouzanogueira@gmail.com](mailto:geovanasouzanogueira@gmail.com), [betoralles@gmail.com](mailto:betoralles@gmail.com)

<sup>b</sup> FAG University, Cascavel, Brazil. [vaniaperes@gmail.com](mailto:vaniaperes@gmail.com); [thomas@fag.edu.br](mailto:thomas@fag.edu.br)

<sup>c</sup> State University of São Paulo, Ilha Solteira, Brazil. [davi.scezario@gmail.com](mailto:davi.scezario@gmail.com)

Received: October 30<sup>th</sup>, 2017. Received in revised form: March 16<sup>th</sup>, 2018. Accepted: April 4<sup>th</sup>, 2018.

### Abstract

This study aimed to analyze the performance of two concrete mixtures with the addition of *B. subtilis* spores regarding their capacity of filling cracks during the curing time, evaluating whether the addition can influence the compressive strength of the concrete. For so, six concrete mixtures were studied divided in two mix compositions: 1:1:2 and 1:2:3 (cement: sand: gravel) with w/c of 0.33 and 0.45, respectively. For each composition were added concentrations of 0, 0.3x10<sup>8</sup> or 1.2x10<sup>8</sup> of *B. subtilis* spores/mL. The results showed that all the samples with spores addition presented crystals precipitation, possibly calcium carbonate, that visually filled the cracks. However, more studies of microstructural analysis should be conducted to prove that the cracks were closed. The compressive strength presented satisfactory results, because the addition of 1.2x10<sup>8</sup> spores/mL did not present significant differences in compressive strength at probability level of 5%, when compared to the reference concrete.

**Keywords:** bioconcrete; concrete with addition of spores; *Bacillus subtilis*; crack filling; cracks.

## Relleno de fisuras en concreto por la adición de esporas de *Bacilos subtilis* - Estudio preliminar

### Resumen

Este estudio tiene como objetivo analizar el desempeño de dos composiciones de hormigón con adición de esporas de *B. subtilis* con relación a su capacidad de relleno de fisuras durante el periodo de cura, evaluando la influencia de la adición en la resistencia a compresión. Para ello han sido estudiadas seis composiciones de hormigón, divididas en dos dosificaciones: 1:1:2 y 1:2:3 (cemento: árido fino: grava) en peso, con relación a/c de 0,33 y 0,45. Para cada una de las mezclas se utilizaron concentraciones de 0, 0.3x10<sup>8</sup> or 1.2x10<sup>8</sup> de esporas de *B. subtilis*/mL. Los resultados obtenidos han demostrado que todas las muestras con adición de esporas presentaron precipitación de cristales, posiblemente carbonato de calcio, que fue visualizado en las fisuras. Más estudios microestructurales deberán ser realizados para comprobar que de hecho ocurrió el relleno de las fisuras. La resistencia a compresión presentó resultados satisfactorios, pues no hubo diferencias significativas en relación al hormigón de referencia, a nivel de 5% de probabilidad.

**Palabras clave:** biohormigón; hormigón con adición de esporas; *Bacilos subtilis*; relleno de fisuras; fisuras.

### 1. Introduction

Concrete is the main material used in construction, as other materials are limited compared to it, by either cost, ease of execution, durability or flexibility to adapt to various geometric shapes [1]. However, concrete is subject to pathological

manifestations, which compromise its integrity and durability [2]. Among these manifestations, cracking is a frequent problem, which in addition to an aesthetic damage, can cause leakage and may compromise the entire structure [3].

Moreover, in environmental terms, the production of concrete is unsustainable [4], for the manufacture of the main

**How to cite:** Schwantes-Cezario, N., Peres, M.V.N.doN., Fruet, T.K., Nogueira, G.S.F., Toralles, B.M. and Cezario, D.deS., Crack filling in concrete by addition of *Bacillus subtilis* spores – Preliminary study. DYNA, 85(205), pp. 132-139, June, 2018.

component, Portland cement, is a major global carbon dioxide emitter [5]. The emission of CO<sub>2</sub> from the calcination process of limestone and from the combustion in the furnace of the cement industry accounts for about 7% of global CO<sub>2</sub> emissions, making it an important sector for mitigation strategies concerning this pollutant gas [6].



In view of these problems and the need to make concrete a more durable and sustainable material, researches are being conducted on the addition of different materials that provide healing of concrete cracks [7].

In this context, there arises a technological innovation that seeks to minimize the problem of cracks in concrete structures, the bioconcrete. The incorporation of bacteria to the concrete matrix has been used from the bio-precipitation of minerals, with the goal of closing pores and cracks. Thus, the bacteria are considered a self-healing agent of concrete cracks, because they have the ability to precipitate minerals that close the cracks autonomously [8].

However, obtaining a greater understanding of the basic mechanisms and principles of materials that are able to close concrete cracks is still a challenging goal. If this goal is achieved, it will undoubtedly lead to the development of a new generation of self-healing materials [7].

The mineral precipitated by the bacteria in cement materials is from calcium carbonate (CaCO<sub>3</sub>), which can be precipitated by microorganisms from several mechanisms. The precipitation of CaCO<sub>3</sub> promoted by bacteria is classified as a Biologically Induced Mineralization (BIM) [9]. This process will result in minerals formed from three possible ways: enzymatic hydrolysis of urea, dissimilation of nitrates and aerobic metabolic conversion of calcium salts [10]. This last one results in minerals that are formed from an involuntary metabolic activity [11].

After investigation about equations that could summarize possible ways for CaCO<sub>3</sub> bioprecipitations, researchers found three main results (Eqs. 1-3) for these biochemical reactions in which the cell surface works as a nucleation site [12].



This bioprecipitations happen as the bacteria finds a calcium source such as limestone rocks or cements. This source, due its negativity, tends to approach the cell wall of the bacteria forming a complex. This complex precipitates calcium carbonate due to the reaction with ion CO<sub>3</sub> (Eq. 1). The carbonate and bicarbonate ions dissolved in solutions are formed mainly from the CO<sub>2</sub> produced during the microbial respiration (Eq. 2 and 3) [12].

Some bacteria that produce minerals by BIM have been used to repair limestone monuments [13-16] and to fill pores and cracks in concrete and other cementitious materials [17-22].

The success of the use of bacteria to close pores in cement materials is directly related to their ability to form spores [8]. The pH of the concrete is highly alkaline, has no nutrients and there is oxygen only in its open pores and on its surface,

tending to restrict bacterial growth [19].

Thus, this research aims at evaluating the crack filling and the compressive strength of two concrete mixtures with addition of *B. subtilis* spores isolated in Brazil [23] at different concentrations.

## 2. Microorganisms and growth conditions

### 2.1. Materials

This study was conducted with *B. subtilis* AP91, isolated in Brazil from leaves of long grain rice. This bacterium has the potential to bioprecipitate CaCO<sub>3</sub> according previous researches [23]. Initially the bacteria was reproduced from two culture medium: Mueller Hinton (MH) (Sigma-Aldrich, USA) and Trypton Soy Broth (TS) (Sigma-Aldrich, USA). These two culture medium were tested to verify in which one the bacteria have the more effectively reproduction ability. From the analysis of this tests, it was select the best culture medium, which provided the highest bacterial growth, enabling to obtain the experiment.

The culture media (MH and TS) were formulated to 500 mL and autoclaved for 15 minutes at 121°C and 1 atm. After sterilization, the bacteria were inoculated in the culture medium and samples were placed in shaker TE 400 (Tecnal) for 66 hours at an average temperature of 29.1°C to induce bacterial growth.

After the stir period, the solution with the bacteria was washed in order to remove the culture medium and to obtain a more concentrated solution of bacteria. For this, the culture media was centrifuged in Falcon tubes for 20 minutes at 3600 rpm spin, the supernatant was removed and replaced with 0.85% saline solution [1177]. The experiment was repeated twice (n = 2).

Then, the solution containing bacteria was stored for two days at the temperature of 8°C to induce spore formation. It is important to mention that spores formation are fundamental for the survival of the bacteria in the cementitious materials.

### 2.2. Quantification of bacteria

Quantification of the bacteria grown in MH and TS were performed with the spectrophotometer UV340GX (Gehaka), with reading at 600 nm. For this test, three samples were used: the control with 0.85% of saline solution, the bacteria grown in MH dissolved in 0.85% saline solution and the bacteria grown in ST dissolved in 0.85% saline solution. To calculate the concentration of bacteria in the medium through the absorbance, Equation 4 was applied [17].

$$Y = 8.59 * 10^7 * X^{1.3627} \quad (4)$$

Where:

- X = absorbance (A);
- Y = Spore concentration per mL.

After complete this stage, the culture medium that resulted in the highest cell growth was identified and then the procedure was repeated with this medium to obtain the required concentrations in the experiment, which are 0.3x10<sup>8</sup>

and  $1.2 \times 10^8$  spores/mL according to previous experiment with the bacteria *B. pasteurii* and *Pseudomonas aeruginosa* [17].

### 2.3. Concrete mixture proportions

For the production of concrete mix, the following materials were used: Portland cement, high early strength (CPV ARI, Brazilian denomination); fine aggregate: medium quartz sand; coarse aggregate: gravel 19 mm of basalt, water and *B. subtilis* spores dissolved in 0.85% of saline solution. The aggregates were characterized according to Brazilian standard [24].

The cement specifications and the requirements of NBR 5733 (Brazilian standard) [25] are presented in Table 1.

Mixture proportions are presented in Table 2. The mix proportions used were 1:1:2 and 1:2:3 (cement: sand: gravel), in mass, with water to cement ratio of 0.33 and 0.45, respectively. For each composition used, two treatments were made with the addition of *B. subtilis* spores to the mixing water in the concentration of  $0.3 \times 10^8$  and  $1.2 \times 10^8$  spores/mL. Besides, in the mixing water it was added 0.85% saline solution to maintain the medium isotonic for the bacteria.

The concrete mixture was performed in a vertical shaft mixer and bacteria concentrations were added to the mixing water.

For each treatment, six cylindrical specimens (100x200 mm) were made, being three for visual analysis of crack filling ( $n=3$ ) over the curing time and the other three for the compressive strength test at 28 days ( $n=3$ ). It should be noted that, for each mix compositions, reference specimens were made without bacterial spores, with 0.85% sodium chloride to ensure the same conditions as the specimens with spores.

Specimens were molded in 100x200 mm cylindrical samples according to NBR 5738/2015 (Brazilian standard) [26]. The specimens were demolded after 24 hours and stored in a dripping wet chamber at  $20^\circ\text{C} \pm 2^\circ\text{C}$  and relative humidity

Table 1.

Characteristics of cement CPV ARI (Brazilian denomination) and the requirements of NBR 5733 (1991).

Ages	Compressive strength (MPa)				Blaine( $\text{cm}^2/\text{g}$ )	Cement setting	
	24 hours	3 days	7 days	28 days		Start (min)	End (min)
NBR 5733*	$\geq 14$	$\geq 24$	$\geq 34$	-	$\geq 3000$	$\geq 60$	$\geq 600$
CPV ARI	27	37	42	48	5330	160	265

Source: Brazilian standard [25].

Table 2.

Mixture proportions.

Mix proportions	w/c	Cement (g)	Sand (g)	Gravel (g)	Water (g)	NaCl (g)	Treatment (spores/mL)
1:1:2	0.33	5.750	5.750	11.500	1.900	16.15	0
							$0.3 \times 10^8$
1:2:3	0.45	3.860	7.710	11.560	1.740	14.79	0
							$1.2 \times 10^8$

Source: The authors.

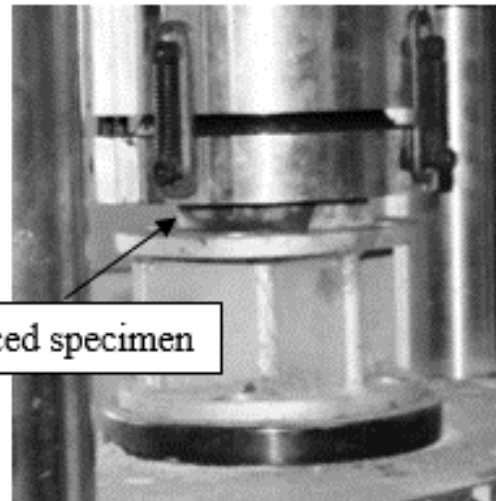


Figure 1. Cracking simulation.

Source: The authors.

greater than 95% until the test ages, which was 7 days for cracking, 8, 15, 22, 29, 36 and 43 days for the monitoring visual of crack filling, and 28 days for the compressive strength test.

### 2.4. Simulation and analysis of cracks

In order to evaluate the cracks filling by spores addition compared to reference, a 2 centimeters slice was extracted from each concrete ( $n=3$ ). These slices were sent to the hydraulic press on the seventh day of healing to apply a strength to simulate a crack, as shown in Fig. 1.

The visual monitoring of cracks during the curing period, at 8, 15, 22, 29, 36 and 43 days, was conducted by images taken from an optical microscope with an attached camera (Olympus), with magnification of 100x. To ensure that the analysis was always held in the same position of the crack, it was demarcated. It is worth mentioning that from this method of cracking simulation it was not possible control its thickness.

### 2.5. Compressive strength

The compressive strength test was performed with non cracked specimens of 100x200mm at the age of 28 days ( $n = 3$ ) according to a NBR 5739/2007 (Brazilian denomination) [27].

### 2.6. Statistical design

A statistical analysis was performed only for the evaluation of compressive strength, from a completely randomized design experiment (CRD), in a  $2 \times 3$  factorial scheme, consisting of two concrete mixtures (1:1:2 and 1:2:3) and three bacteria content (0,  $0.3 \times 10^8$  and  $1.2 \times 10^8$ ). In this statistical scheme, the two concrete mixtures were evaluated with all bacterial contents, with three replications.

For the statistical analysis, the software Sisvar was used to perform an analysis of variance [28].

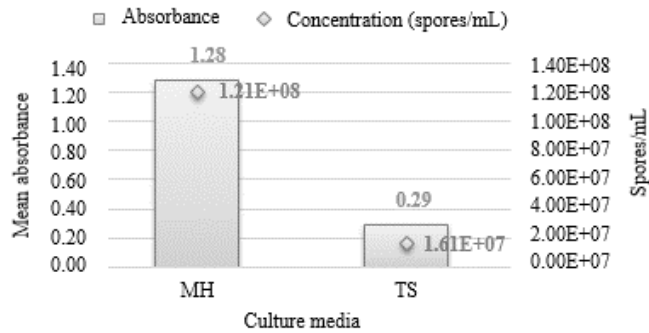


Figure 2. Mean absorbance and concentration of bacteria in each culture medium.

Source: The authors.

### 3. Results and discussion

#### 3.1. Quantification of spores

From the two culture medium used in the experiment, the spores quantification of each medium was performed in accordance with Eq. 1., Fig. 2 shows the results of absorbance and concentration of spores/mL of culture media MH and TS.

Through the analysis of Fig. 3, it was observed a higher absorbance values and concentration of spores in the medium MH, of 1.28 and  $1.21 \times 10^8$  spores/mL, respectively, while under the same conditions, the medium TS presented, respectively, 0.29 and  $1.61 \times 10^7$  spores/mL. From this result, only the culture medium MH was selected for this experiment.

The reproduction procedure was repeated only with the medium MH, which presented the highest concentration of spores/mL, until it reached the concentrations of  $1.2 \times 10^8$  and  $0.3 \times 10^8$  spores/mL, which was quantified by spectrophotometer.

#### 3.2. Characterization of aggregates

Sand was performed by Particle size analysis [24]. The results of these test were presented in Fig. 3.

The fine aggregate used was a medium sand. The particle size analysis is shown in Fig. 3. It was found that the grading curve is inside the limits established by NBR 7211/2009 (Brazilian standard) [29]. Analyzing the grading curve it should be noted that it has a continuous particle size, with desirable characteristic for use in cementitious materials due to the better packaging of the grains in the structure of the material. For the grading curve, it were calculated the maximum size, specific mass and unit mass. The values found were 2.36 mm,  $2.62 \text{ g/cm}^3$  and  $1.57 \text{ g/cm}^3$ , respectively. Besides that, the gravel has maximum size of 19 mm.

#### 3.3. Crack filling visual analysis

The visual analysis of crack filling was performed with one crack per specimen until 43 days of curing, being that three specimens of each concrete were analyzed ( $n=3$ ). The images obtained from an optical microscope with attached camera are shown in Figs. 3 and 4.

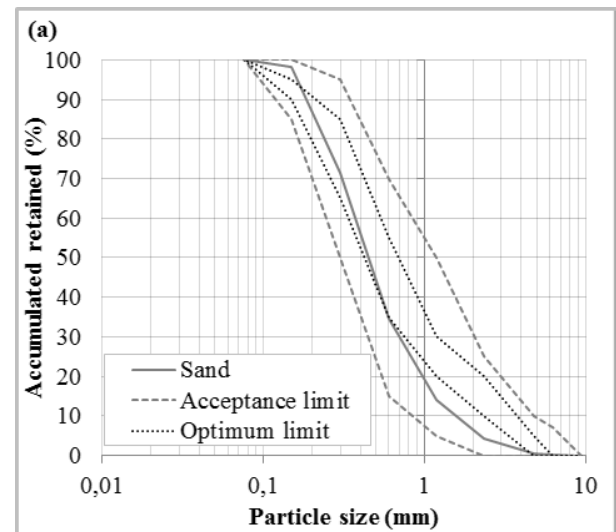


Figure 3. Particle size analysis of sand.

Source: The authors.

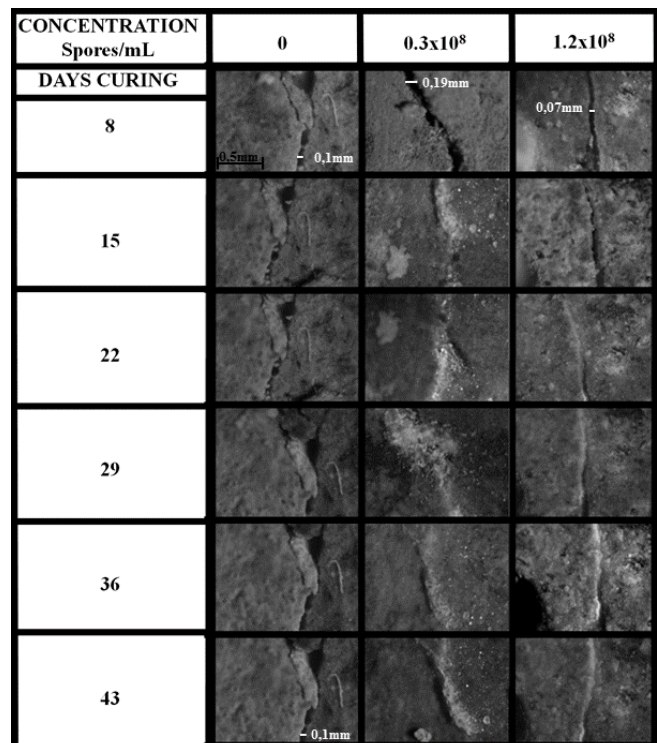


Figure 4. Visual monitoring of crack filling in the specimens of composition 1:1:2.

Source: The authors.

It can be seen that in all the compositions in which bacteria were added, there was a crystal precipitation from the 15th day on, possibly calcium carbonate ( $\text{CaCO}_3$ ) according to literature [20,22,30-35]. Besides that, the same strain was used in another study [23] that performed an analysis in vitro of the bioprecipitation of calcium carbonate by pH change during biofilm formation. The authors found that the *B. subtilis* AP91 were able to precipitate crystals of  $\text{CaCO}_3$  with the same morphology as other researches [11,36-40].



CONCENTRATION Spores/mL	0	$0.3 \times 10^8$	$1.2 \times 10^8$
DAYS CURING			
8		 0.19mm	 ~0.04mm
15	 0.5mm	 0.15mm	
22			
29			
36			
43	 0.15mm		

Figure 5. Monitoring the crack filling in the specimens of composition 1:2:3. Source: The authors.

Other investigators conducted the studies in the same way, first studying whether the bacterium has the ability to precipitate  $\text{CaCO}_3$  and in the sequence analyzing how that addition would behave in the cement matrix [9,41].

The filling of cracks up to 0.19 mm were visible in concretes with addition of spores of *B. subtilis*. However, in the samples without spores addition, precipitated material was not visible and the crack remained with the same feature throughout the curing period analyzed.

Although the cracks have different thickness sizes, it was visually found that in the concretes with addition of *B. subtilis* spores there was filling of the cracks by precipitation of crystals, even if the crack were of greater thickness compared to the reference concrete, without spores. Besides, in the reference concretes this filling was not visualized in this analysis. It is noteworthy that this analysis was just visual. To a better detailing a microstructural analysis would be necessary.

Fig. 6 shows the crystals formed by calcium carbonate precipitation promoted by the bacterium *B. alkalinitrilicus* added with a nutrient source and curing totally submerged under water for the healing regime [3]. It was observed that there was closure of the cracks from 0.13 to 0.40 mm thickness after 100 days of curing. Similar results were found in this research. Besides the above referenced authors, similar results using the bacterium *B. sphaericus* have been presented [18].

Thus, it was observed that the crystals precipitation promoted by the addition of *B. subtilis* spores under the conditions analyzed was visually satisfactory in crack filling. However, for more specific studies a microstructural analysis would be required.

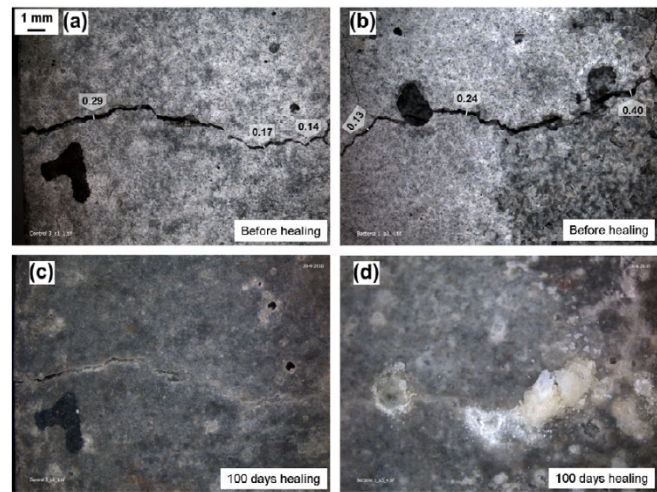


Figure 6. Stereomicroscopic images of crack-healing process in control mortar specimen before (a) and after 100 days healing (c), in bio-chemical agent-based specimen before (b) and after 100 days healing (d). Source: [3].

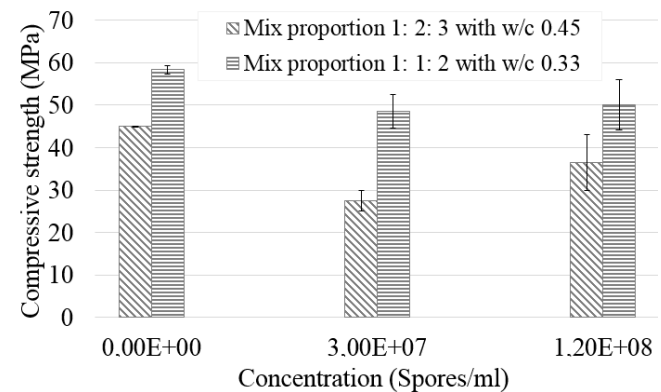


Figure 7. Compressive strength of concretes.

Source: The authors.

### 3.4. Compressive strength

The compressive strength test was performed on the 28th day of curing and the results are shown in Fig. 7. There was a difference in resistance between the compositions due to the proportions of materials used and the water/cement ratio (w/c), with higher resistance for the mix proportion 1:1:2 compared to w/c of 0.33 and without addition of bacteria, and the lowest resistance for the mix proportion 1:2:3 with w/c of 0.45.

Through the analysis of the results, it was noted that there was a decrease in the mean resistance of samples with added spores when compared to the reference. This decrease in the mix proportion 1:1:2 was of 20.06 and 16.58% for the treatments  $0.3 \times 10^8$  and  $1.2 \times 10^8$  spores/mL, respectively. For the mix proportion 1:2:3, the difference was greater, corresponding to 63.63 and 23.28% for the treatments  $0.3 \times 10^8$  and  $1.2 \times 10^8$  spores/mL.

There was an increase in the resistance of the samples with  $1.2 \times 10^8$  spores/mL compared to the ones with  $3.0 \times 10^7$  spores/mL in both mix proportions, demonstrating that the

amount of bacteria added to concrete influences the compression strength. However, it is necessary to test a larger number of bacteria concentrations for a better understanding. According to the literature [31], calcium hydroxide ( $\text{Ca}(\text{OH})_2$ ) is the most important source of calcium for concrete, but it does not alter mechanical resistance. On the other hand, calcium carbonate ( $\text{CaCO}_3$ ) contributes to increase this resistance, which makes the bioprecipitation a positive contribution [31]. It should be noted that the crystals precipitated by bacteria in cementitious materials, calcium carbonate stand out [12, 20, 22-23, 30-35]. But, to confirm that the crystal precipitated by *B. subtilis* was calcium carbonate more studies need to be conducted, since this research is a preliminary test.

#### 3.4.1. Statistical analysis

The statistical analysis was performed in Sisvar [28] and the results of analysis of variance are shown in Table 3. The sources of variation were the mix proportions of concrete and concentration of added spores, as well as the interaction of these two sources of variation.

There was a significant difference ( $P < 0.05$ ) at 5% probability, for the parameter compressive strength in the variation of Mix proportion (M) and Spores Concentration (C), indicating that there are variations to compressive strength according to the concentration of spores added and to the mix proportion analyzed.

Table 4 presents the tests of means performed for the parameter compressive strength with variation of Mix proportion (M) and Table 5 present the test of means for the parameter Spores Concentration (C).

Table 3.  
Mean squares and summary of the Analysis of Variance (ANOVA).

Sources of variation	Mean squares
Spores Concentration (C)	189.00 *
Mix proportion (M)	768.00 *
Interaction (C x M)	19.51 ns
Residue	33.84

\* Significant at 5% probability by the Fisher test; ns: non-significant  
Source: The authors.

Table 4.  
Tukey test for compressive strength with variation in mix proportion.

Mix proportion	Mean Square
1:2:3	38.050 a
1:1:2	43.275 b
DMS	8.218
CV (%)	13.120

Source: The authors.

Table 5.  
Tukey test for compressive strength with the addition of *B. subtilis* spores

Spores concentration (spores/mL)	Mean Square
$0.3 \times 10^8$	38.050 a
$1.2 \times 10^8$	43.275 ab
0	51.675 b
DMS	12.617
CV (%)	13.120

Source: The authors.

It was noted that there were significant differences in compressive strength by varying both the concentration of spores added and the mix proportion. A significant difference between the compressive strengths of the two mix compositions were expected, since the w/c ratio is a factor directly related to it [6].

Regarding the addition of bacterial spores, it was observed that the lowest concentration of spores resulted in a minor compressive strength, significantly differing from the reference (without addition of spores). The concentration of  $1.2 \times 10^8$  spores/mL presented minor compressive strength than the reference; however, there was no significant difference between them.

Based on this analysis (Tukey test), it's possible that the addition of spores of *B. subtilis* could be used in concretes with these specific mix proportions without significant influences in compressive strength, nevertheless it is necessary more investigations about the use of this kind of material, since this study is a preliminary analysis.

#### 4. Conclusion

From the experimental results, it was verified that there was a visual crack filling when the *B. subtilis* spores were added in two studied concentrations ( $0.3 \times 10^8$  and  $1.2 \times 10^8$  spores/mL). However the analysis by microscope with attached camera is just a visual analysis. To confirm that there was a closure of cracks a microstructural analysis would be necessary.

The addition of  $0.3 \times 10^8$  spores/mL resulted in a statistically significant decrease (at 5% probability) of the compressive strength of the specimens, while the addition of  $1.2 \times 10^8$  spores/mL did not present statistically significant differences when compared to the reference concrete. It possible happened because the highest concentration of spores was capable to produce more crystals that could increase the strength. Although further analysis need to be performed to confirm this theory.

Thus, these preliminary study has shown that the addition of *B. subtilis* spores isolated in Brazil to unarmored concrete could be beneficial and this practice should be developed in order to obtain a material capable of self-healing and consequently increase its lifetime. For this, further studies on the concentration of addition of these spores are required, as well as on the adding procedure, curing process and microstructural analysis.

#### Acknowledgements

The authors are grateful to Assis Gurgacz College, State University of Londrina and CNPQ for all financial support.

#### References

- [1] Carmona Filho, A. and Carmona, T.G., Fissuração nas estruturas de concreto. Asociación Latinoamericana de Control de Calidad, Patología y Recuperación de la Construcción, Boletim Técnico. Revista ALCONPAT, 3, 2013.
- [2] Koch, G.H., Brongers, M.P., Thompson, N.G., Virmani, Y.P. and Payer, J.H., Corrosion cost and preventive strategies in the United States (No. FHWA-RD-01-156), 2002.

- [3] Wiktor, V. and Jonkers, H.M., Quantification of crack-healing in novel bacteria-based self-healing concrete. *Cement & Concrete Composites*, 33, pp. 763-770, 2011. DOI: 10.1016/j.cemconcomp.2011.03.012
- [4] Gerilla, G.P., Teknomo, K. and Hokao, K., An environmental assessment of wood and steel reinforced concrete housing construction. *Building and Environment*, 42(7), pp. 2778-2784, 2007. DOI: 10.1016/j.buildenv.2006.07.021
- [5] Worrell, E., Price, L., Martin, N., Hendriks, C. and Meida, L.O., Carbon dioxide emissions from the global cement industry. *Energy Environ*, 26(1), pp. 303-329. DOI: 10.1146/annurev.energy.26.1.303
- [6] Mehta, P.K. and Monteiro, P.J.M., *Concrete: microstructure, properties and materials*. 2nd ed. Ibracon, São Paulo; 2014.
- [7] Van Tittelboom, K., Gruyaert, E., Rahier, H. and De Belie, N., Influence of mix composition on the extent of autogenous crack healing by continued hydration or calcium carbonate formation. *Construction and Building Materials*, 37, pp. 349-359, 2012. DOI: 10.1016/j.conbuildmat.2012.07.026
- [8] Jonkers, H.M., Thijssen, A., Muyzer, G., Copuroglu, O. and Schlangen, E., Application of bacteria as self-healing agent for the development of sustainable concrete. *Ecological Engineering*, 36(2), pp. 230-235, 2010. DOI: 10.1016/j.ecoleng.2008.12.036
- [9] Barabesi, C., Galizzi, A., Mastromei, G., Rossi, M., Tamburini, E. and Perito, B., *Bacillus subtilis* gene cluster involved in calcium carbonate biomineralization. *Journal of bacteriology*, 189, pp. 228-235, 2007. DOI: 10.1128/JB.01450-06
- [10] Alazhari, M., Sharma, T., Heath, A., Cooper, R. and Paine, K., Application of expanded perlite encapsulated bacteria and growth media for self-healing concrete. *Construction and Building Materials*, 160, pp. 610-619, 2018. DOI: 10.1016/j.conbuildmat.2017.11.086
- [11] Park, S.J., Park, J.M., Kim, W.J. and Ghim, S.Y., Application of *Bacillus subtilis* 168 as a multifunctional agent for improvement of the durability of cement mortar. *Journal of Microbiology and Biotechnology*, 22, pp. 1568-1574, 2012.
- [12] Stocks-Fischer, S., Galinat, J.K. and Bang, S.S., Microbiological precipitation of  $\text{CaCO}_3$ . *Soil Biol. Biochem.* 31(11), pp. 1563-1571, 1999. DOI: 10.1016/S0038-0717(99)00082-6.
- [13] Bang, S.S., Galinat, J.K. and Ramakrishnan, V., Calcite precipitation induced by polyurethane-immobilized *Bacillus pasteurii*. *Enzyme and microbial technology*, 28(4), pp. 404-409, 2001. DOI: 10.1016/S0141-0229(00)00348-3
- [14] Bachmeier, K.L., Williams, A.E., Warmington, J.R. and Bang, S.S. Urease activity in microbiologically-induced calcite precipitation. *Journal of Biotechnology*, 93(2), pp. 171-181, 2002. DOI: 10.1016/S0168-1656(01)00393-5
- [15] Dick, J., De Windt, W., De Graef, B., Saveyn, H., Van Der Meeren, P., De Belie, N. and Verstraete, W., Bio-deposition of a calcium carbonate layer on degraded limestone by *Bacillus* species. *Biodegradation*, 17(4), pp. 357-367, 2006. DOI: 10.1007/s10532-005-9006-x
- [16] Rodriguez-Navarro, C., Rodriguez-Gallego, M., Bencheikroun, K. and Gonzalez-Munoz, M.T., Conservation of ornamental stone by *Myxococcus xanthus*-induced carbonate biomineralization. *Applied and Environmental Microbiology*, 69(4), pp. 2182-2193, 2003. DOI: 10.1128/AEM.69.4.2182-2193.2003
- [17] Ramachandran, S.K., Ramakrishnan, V. and Bang, S.S., Remediation of concrete using microorganisms. *ACI Materials Journal-American Concrete Institute*, 98(1), pp. 3-9, 2001. DOI: 10.14359/10154
- [18] De Muynck, W., Debrouwer, D., De Belie, N. and Verstraete, W., Bacterial carbonate precipitation improves the durability of cementitious materials. *Cement and Concrete Research*, 38(7), pp. 1005-1014, 2008. DOI: 10.1016/j.cemconres.2008.03.005
- [19] Van Tittelboom, K., De Belie, N., De Muynck, W. and Verstraete, W., Use of bacteria to repair cracks in concrete. *Cement and Concrete Research*, 40, pp. 157-166, 2010. DOI: 10.1016/j.cemconres.2009.08.025
- [20] Xu, J. and Yao, W., Multiscale mechanical quantification of self-healing concrete incorporating non-ureolytic bacteria-based healing agent. *Cement and Concrete Research*, 64, pp. 1-10, 2014. DOI: 10.1016/j.cemconres.2014.06.003
- [21] De Koster, S.A.L., Mors, R.M., Nugteren, H.W., Jonkers, H.M., Meesters, G.M.H. and Van Ommen, J.R., Geopolymer coating of bacteria-containing granules for use in self-healing concrete. *Procedia Engineering*, 102, pp. 475-484, 2015. DOI: 10.1016/j.proeng.2015.01.193
- [22] Luo, M., Qian, C.X. and Li, R.Y., Factors affecting crack repairing capacity of bacteria-based self-healing concrete. *Construction and Building Materials*, 87, pp. 1-7, 2015. DOI: 10.1016/j.conbuildmat.2015.03.117
- [23] Schwantes-Cezario, N., Meideiros, L.P., De Oliveira Jr. A.G., Nakazato, G., Kobayashi, R.K.T. and Toralles, B.M., Bioprecipitation of calcium carbonate induced by *Bacillus subtilis* isolated in Brazil. *International Biodeterioration & Biodegradation*, 123, pp. 200-205, 2017. DOI: 10.1016/j.ibiod.2017.06.021
- [24] Brazilian Standards NBR NM 248 – Agregados: determinação da composição granulométrica. ABNT, 2003.
- [25] \_\_\_\_\_. NBR 5733 – Cimento Portland de alta resistência inicial. Rio de Janeiro: ABNT, 1991.
- [26] \_\_\_\_\_. NBR 5738 – Concreto: procedimento para moldagem e cura de corpos de prova. ABNT, 2015.
- [27] \_\_\_\_\_. NBR 5739 – Concreto: ensaio de compressão de corpos de prova cilíndricos. São Paulo: ABNT, 2007.
- [28] Ferreira, D.F., Programa de análises estatísticas (Statistical analysis software) e planejamento de experimentos. Universidade Federal de Lavras, Brasil, 2003.
- [29] Brazilian Standards NBR 7211 – Agregados para concreto – Especificação. Rio de Janeiro: ABNT, 2009.
- [30] Abo-El-Enen, S.A., Ali, A.H., Talkhan, F.N. and Abdel-Gawwad, H.A., Application of microbial biocementation to improve the physico-mechanical properties of cement mortar. *HBRC Journal*, 9, pp. 36-40, 2013. DOI: 10.1016/j.hbrcj.2012.10.004
- [31] Pei, R., Liu, J., Wang, S. and Yang, M., Use of bacterial cell walls to improve the mechanical performance of concrete. *Cement and Concrete Composites*, 39, pp. 122-130, 2013. DOI: 10.1016/j.cemconcomp.2013.03.024
- [32] Schlangen, E. and Sangadji, S., Addressing infrastructure durability and sustainability by self healing mechanisms-Recent advances in self healing concrete and asphalt. *Procedia Engineering*, 54, pp. 39-57, 2013. DOI: 10.1016/j.proeng.2013.03.005
- [33] Achal, V., Mukerjee, A. and Reddy, M.S., Biogenic treatment improves the durability and remediates the cracks of concrete structures. *Construction and Building Materials*, 48, pp. 1-5, 2013. DOI: 10.1016/j.conbuildmat.2013.06.061
- [34] Chahal, N. and Siddique, R., Permeation properties of concrete made with fly ash and silica fume: influence of Ureolytic bacteria. *Construction and Building Materials*, 49, pp. 161-174, 2013. DOI: 10.1016/j.conbuildmat.2013.08.023
- [35] Krishnapriya, S., Venkatesh-Babu, D.L. and Prince-Arulraj, G., Isolation and identification of bacteria to improve the strength of concrete. *Microbiological Research*, 174, pp. 48-55, 2015. DOI: 10.1016/j.micres.2015.03.009
- [36] Schwantes-Cezario, N., Nogueira, G.S.F. and Toralles, B.M., Biocimentação de compostos cimentícios mediante adição de esporos de *B. subtilis* AP91, 2017. *Revista de Engenharia Civil IMED*, 4(2), pp. 142-158. DOI: 10.18256/2358-6508.2017.v4i2.2072
- [37] Hammes, F., Boon, N., De Villiers, J., Verstraete, W. and Siciliano, S.D., Strainspecific ureolytic microbial calcium carbonate precipitation. *Appl. Environ. Microbiol.* 69(8), pp. 4901-4909, 2003. DOI: 10.1128/AEM.69.8.4901-4909.2003.
- [38] Braissant, O., Cailleau, G., Dupraz, C. and Verrecchia, E.P., Bacterially induced mineralization of calcium carbonate in terrestrial environments: the role of exopolysaccharides and amino acids. *Journal of Sedimentary Research*, 73(3), pp. 485-490, 2003. DOI: 10.1306/111302730485.
- [39] Dupraz, S., Parmentier, M., Ménez, B. and Guyot, F., Experimental and numerical modeling of bacterially induced pH increase and calcite precipitation in saline aquifers. *Chemical Geology*, 265(1), pp. 44-53, 2009. DOI: 10.1016/j.chemgeo.2009.05.003.
- [40] Daskalakis, M.I., Rigas, F., Bakolas, A., Magoulas, A., Kotoulas, G., Katsikis, I. and Mavridou, A., Vaterite bio-precipitation induced by *Bacillus pumilus* isolated from a solutional cave in Paiania, Athens, Greece. *International Biodeterioration & Biodegradation*, 99, pp. 73-84, 2015. DOI: 10.1016/j.ibiod.2014.12.005.
- [41] Perito, B., Marvasi, M., Barabesi, C., Mastromei, G., Bracci, S.,



Vendrell, M. and Tiano, P., A *Bacillus subtilis* cell fraction (BCF) inducing calcium carbonate precipitation: biotechnological perspectives for monumental stone reinforcement. *Journal of Cultural Heritage*, 15(4), pp. 345-351, 2014. DOI: 10.1016/j.culher.2013.10.001

**N. Schwantes-Cezario**, received the BSc. in Civil Engineering in 2015, the MSc. degree in Building Engineering and Sanitation in State University of Londrina, Brazil in 2016, and is a PhD student in Civil Engineering at State University of Londrina, Brazil.  
ORCID: 0000-0002-3254-6396

**M.V.N.N. Peres**, received the BSc. in Civil Engineering in 2004, the MSc. degree in Structures in Federal University of Rio Grande do Sul, Brazil in 2008, and is a PhD. student in Structures by Federal University at Rio Grande do Sul, Brazil. Currently is a professor at Centro Universitário Fundação Assis Gurgacz (FAG), Brazil.  
ORCID: 0000-0002-3986-3503

**T.K. Fruet**, received the degree in Biological Sciences in 2010, the MSc. degree in Conservation and management of natural resources in State University of Western Paraná in 2013 and is a PhD student in Biology at State University of Maringá, Brazil. Currently is a professor at Centro Universitário Fundação Assis Gurgacz (FAG), Brazil.  
ORCID: 0000-0002-3521-600X

**G.S.F. Nogueira**, graduated in Civil Engineering in 2016 at the State University of Londrina, and is a MSc. degree student in Civil Engineering at State University of Londrina, Brazil.  
ORCID: 0000-0002-7059-257X

**B.M. Toralles**, received the BSc. in Civil Engineering in 1982, the MSc. degree in Civil Engineering in Federal University of Rio Grande do Sul, Brazil in 1986, and the PhD degree in Engenharia de Camins Canals i Ports - Universitat Politècnica de Catalunya - Barcelona Tech, Spain, in 1996 and PhD. in Universitat Politècnica de Catalunya, Spain, in 2013. Currently is an associate professor at the State University of Londrina, Brazil.  
ORCID: 0000-0001-8828-7250

**D.S. Cezario**, received the BSc. in Mechanical Engineering in 2014 at the State University of São Paulo and post graduated in Labor Safety at the State University of Maringá, Brazil in 2017.  
ORCID: 0000-0001-6137-731X



UNIVERSIDAD NACIONAL DE COLOMBIA

SEDE MEDELLÍN  
FACULTAD DE MINAS

Área Curricular de Ingeniería Civil

Oferta de Posgrados

Especialización en Vías y Transportes  
Especialización en Estructuras  
Maestría en Ingeniería - Infraestructura y Sistemas  
de Transporte  
Maestría en Ingeniería - Geotecnia  
Doctorado en Ingeniería - Ingeniería Civil

Mayor información:

E-mail: asisacic\_med@unal.edu.co  
Teléfono: (57-4) 425 5172