



DYNA

ISSN: 0012-7353

Universidad Nacional de Colombia

Martínez, Maby Mool; Ocampo-Cardona, Rogelio; Aguirre-Cortés, Jhon Mauricio; Giraldo, Oscar; Ríos-Vásquez, Luz Amalia
Palladium nanoparticles from a surfactant-modified hydroxysalt exchanged with tetrachloropalladate
DYNA, vol. 85, no. 206, 2018, July-September, pp. 142-147
Universidad Nacional de Colombia

DOI: <https://doi.org/10.15446/dyna.v85n206.68132>

Available in: <https://www.redalyc.org/articulo.oa?id=49659032017>

- How to cite
- Complete issue
- More information about this article
- Journal's webpage in [redalyc.org](https://www.redalyc.org)

UNEN [redalyc.org](https://www.redalyc.org)

Scientific Information System Redalyc
Network of Scientific Journals from Latin America and the Caribbean, Spain and
Portugal

Project academic non-profit, developed under the open access initiative

Palladium nanoparticles from a surfactant-modified hydroxysalt exchanged with tetrachloropalladate

Maby Mool Martínez ^a, Rogelio Ocampo-Cardona ^a, Jhon Mauricio Aguirre-Cortés ^{a,b,c}, Oscar Giraldo ^{b,c}
& Luz Amalia Ríos-Vásquez ^a

^a Facultad de Ciencias Exactas y Naturales, Universidad de Caldas, Manizales, Colombia. maby.martinez@ucaldas.edu.co,
rogelio.ocampo@ucaldas.edu.co, jhon.aguirre@ucaldas.edu.co, amalia.rios@ucaldas.edu.co

^b Departamento de Física y Química, Universidad Nacional de Colombia, sede Manizales, Manizales, Colombia. ohgiraldo@unal.edu.co

^c Laboratorio de Materiales Nanoestructurados y Funcionales, Universidad Nacional de Colombia, sede Manizales, Manizales, Colombia

Received: October 04th, 2017. Received in revised form: June 22nd, 2018. Accepted: July 18nd, 2018.

Abstract

Palladium nanoparticles supported in the interlayer space of hydroxysalts were obtained from zinc hydroxychloride via a prior intercalation of the anionic surfactant sodium dodecyl sulfate (DS), followed by an exchange with potassium tetrachloropalladate and its final reduction to metallic palladium by ethanol. The final materials and their intermediates were characterized by several instrumental techniques such as PXRD, N₂ adsorption, SEM, and TEM. The comparative analyses revealed clearly visible changes on structure, specific surface area and morphology of the reduced material with respect to the starting precursors. The analyses demonstrated that, upon modification of the starting material with the surfactant, the resulting material had a significantly enhanced interlayer space and BET area, which were fairly maintained until the reduced palladium-containing hydroxysalt was obtained.

Keywords: surfactant-modified zinc hydroxychloride; palladium nanoparticles; tetrachloropalladate; anionic clays

Nanopartículas de paladio a partir de una hidroxisal modificada con surfactante intercambiada con tetracloropaladato

Resumen

Se obtuvieron nanopartículas de paladio soportadas en el espacio interlamilar de hidroxisales obtenidas a partir de hidroxiclورو de zinc, mediante la intercalación previa del surfactante aniónico dodecil sulfato de sodio (DS), seguida por intercambio con tetracloropaladato de potasio y la reducción final a paladio metálico mediante etanol. Los materiales finales e intermediarios fueron caracterizados mediante varias técnicas instrumentales tales como PXRD, adsorción de N₂, SEM y TEM. Los análisis comparativos revelaron cambios claramente observables en la estructura, área superficial específica y morfología del material reducido con respecto a los precursores de partida. Los análisis demostraron que, tras la modificación del material de partida con el surfactante, en el material resultante se incrementó el espacio interlamilar y el área BET, los cuales se conservaron considerablemente hasta la obtención de la hidroxisal que contenía nanopartículas de paladio reducido.

Palabras clave: hidroxiclورو de zinc modificado con surfactante; nanopartículas de paladio; tetracloropaladato; arcillas aniónicas


1. Introduction

Clays are interesting materials which have been extensively used for a number of industrial applications, for example, they are applicable in the preparation of nanocomposites [1], controlled-release pharmaceutical

systems [2,3], catalytic supports [4,5], and other purposes. A category of clays, layered double hydroxides (LDH), are useful materials because it is possible to modulate several of their physical-chemical properties by proper modification of the preparation method and their chemical composition [6-10]. LDH consist of positively charged layers of metallic


How to cite: Martínez, M.M., Ocampo-Cardona, R., Aguirre-Cortés, J.M., Giraldo, O. and Ríos-Vásquez, L.A., Palladium nanoparticles from a surfactant-modified hydroxysalt exchanged with tetrachloropalladate. DYNA, 85(206), pp. 142-147, September, 2018.

hydroxides containing water molecules and anions in the interlayer spaces that compensate the charge of the laminae. The positive charge on the layers comes from the substitution of divalent cations by trivalent ones on some octahedral positions, giving rise to structures that are represented according to equation (1):



Where M may be a divalent or trivalent metal, x corresponds to the molar ratio $M(II)/(M(II)+M(III))$, and A^{n-} is the interlayer chemical species with charge n , while m is the hydration extent [11,12]. These materials have successfully been used for immobilization of metallic nanoparticles based on Au, Pt, Ni or Pd [13-15], useful as heterogeneous catalysts for organic reactions such as alcohol oxidations, hydrogenations, carbon-carbon couplings and others [16-18].

Another kind of clays is constituted by metallic hydroxysalts, which are represented by equation (2):



Unlike in LDH, the M in hydroxysalts corresponds to only one kind of metal, but similarly to the LDH structure, metals in hydroxysalts occupy not only octahedral positions (*oct*) inside the layers but also tetrahedral positions (*tet*) which are differentiated. About one-fourth of octahedral sites are empty (*vac*)^{oct} and they are compensated by tetrahedral arrangements up and down in that particular point of the layer. As in LDH, this structural feature gives rise to a charge excess that promotes the intercalation of hosted anionic species in the interlayer space [19,20].

Conventionally, laminar hydroxysalts are solid structures resulting from the reaction of a metal oxide and a salt, promoting in one side the metal species that form the laminar inorganic structure and the interspace anion which confers its stability [19, 21-22]. A particularly useful hydroxysalt is zinc hydroxychloride ($Zn_5(OH)_8Cl_2 \cdot H_2O$: simonkolleite: ZHC) [22] which has advantages as a supporting material for catalytic systems in comparison to other frequently used materials, especially regarding their easy preparation and modification. Some authors have reported the synthesis of zinc hydroxychloride by adjusting pH around 6 units by the addition of NaOH [22], and others have prepared hydroxysalts hosting nitrate anion in the interspace, through a two-day reaction of zinc oxide and zinc nitrate at temperatures above 60 °C, but a shorter methodology to prepare ZHC would be welcome, so we prepared a highly crystalline material in a shorter reaction time.

On the other hand, there are reports in the literature [6-10] about chemical modification of clays by inserting hosting molecules in the interlayer space resulting in materials with modulated properties, especially for catalysts. Taking into account the above, we decided to insert a surfactant into the interlayer space of ZHC to generate lipophilicity inside the material, and then it was exchanged with a palladate complex anion and reduced to metal palladium. It would be expected

for this new material to be a promising heterogeneous catalysts for C-C coupling reactions [1,2].

This work illustrates the arrangement of palladium nanoparticles on zinc hydroxychloride which was previously exchanged with a surfactant aiming to take advantage of the wide interspace distances which might positively affect the distribution of palladium nanoparticles. The physical-chemical characterization of the intermediate and target materials and their properties such as morphology, textural analysis, crystallinity and particle size are being presented and discussed as well.

2. Materials and methods

2.1. Starting materials

Analytical grade reagents were used: ZnO (Sigma-Aldrich, 99+%), $ZnCl_2$ (Merck, 98%), $CH_3(CH_2)_{11}OSO_3Na$ (DS) (Carlo Erba, 92%), Na_2PdCl_4 (Aldrich, 99,99%). Distilled water was deionized previously in our laboratories. All materials were dried at room temperature and atmospheric pressure without the use of drying solvents.

2.2. Physical-chemical characterization of the materials

All materials (ZHC, ZHC-DS, ZHC-DS-PdCl, and ZHC-DS-Pd⁰) were characterized by X-Ray diffraction (PXRD), Scanning Electronic Microscopy (SEM), Transmission Electronic Microscopy (TEM), surface area and pore distribution were measured at the temperature of liquid nitrogen (-196 °C).

PXRD analyses were carried out on a Rigaku Miniflex II instrument (30 kV and 15 mA) that uses copper as the radiation source ($Cu K\alpha$) with a scan rate of 2° per minute in normal environmental conditions. The crystal size of Pd in the ZHC- Pd⁰ was estimated from its diffraction pattern by the Debye-Scherrer's method [25].

Micrograph images were run on a Scanning Electron Microscope SEM, model QUANTA 250 of FEI, while Transmission Electronic Microscopy TEM analyses were run in a JEOL 1200 EX instrument.

Nitrogen adsorption-desorption isotherms and the textural properties of the materials were determined by nitrogen adsorption on a Micromeritics instrument ASAP 2020, using samples of about 0.100 g. Specific surface areas were estimated from the adsorption isotherms by applying the BET method [26].

2.3. Experimental methods

Precursor preparation (ZHC). Zinc hydroxychloride was obtained in an aqueous phase using the reported procedure [27], but in our case, we did not use an autoclave. ZnO (3.5 g) was added to 100 mL of an aqueous solution containing 136 g of $ZnCl_2$. The resulting suspension was shaken at room temperature under a nitrogen atmosphere for 6 hours, and a white precipitate was obtained by centrifugation, and then it was washed several times with distilled deionized water (DDW). The material was dried at room temperature.

Surfactant-modified, ZHC-DS. To a 100 mL of a 0.05M solution of sodium dodecyl sulfate, 1.3 g of ZHC was added.

The entire suspension was shaken at room temperature for 22 hours. A white precipitate was obtained by filtration, and then it was washed several times with distilled deionized water (DDW) and dried at room temperature.

Tetrachloropalladate-exchanged, ZHC-DS-PdCl. The surfactant in ZHC-DS was exchanged with the tetrachloropalladate anion. 1.5 g of Na_2PdCl_4 was added to 50 mL of an aqueous suspension containing 0.3 g of ZHC-DS. The resulting suspension was shaken at room temperature for 5 hours, and a brown precipitate was obtained by filtration. Then, it was washed several times with distilled deionized water (DDW) and dried at room temperature for 12 hours.

Nanoparticles of Pd in surfactant-modified, ZHC-DS-Pd⁰. The target material was obtained by reduction of ZHC-DS-PdCl. 72 mg of ZHC-DS-PdCl were suspended in 5.0 mL of $\text{CH}_3\text{CH}_2\text{OH}$ and shaken for 2 hours at room temperature. A black precipitate was obtained by centrifugation and it was washed seven times with 3.0 mL of $\text{CH}_3\text{CH}_2\text{OH}$ each.

3. Results and discussion

Zinc oxide and zinc chloride were combined to form the respective ZHC, a white material that was used as the starting precursor to assemble the palladium nanoparticles inside the ZHC. The target material was obtained through a step-by-step sequence that involved: (1) synthesis of the hydroxysalt (ZHC) according to the standard procedure [19]; (2) intercalation of dodecyl sulfate anion in the interlayer space of the ZHC precursor (ZHC-DS); (3) exchange of dodecyl sulfate by tetrachloropalladate anion (ZHC-DS-PdCl); (4) reduction of the palladium species retained inside the ZHC to be converted into metallic palladium nanoparticles ZHC-DS-Pd⁰. Visible qualitative changes in the appearance of the materials upon going successively from precursors to intermediates and to the final product are strong suggestions that modifications were occurring properly, and such transformations were confirmed by instrumental analysis as discussed ahead. Our first piece of evidence comes from X-ray diffraction (PXRD patterns) of the materials (Fig. 1), exhibiting the typical lines corresponding to laminar structures.

For the ZHC precursor, Fig. 1a suggests the presence of the expected typical pattern of this kind of materials [28] and shows the crystallographic planes (003), (006), (110) and (0012) corresponding to 2θ values of 11.2, 22.5, 28.1 and 46.0° respectively, and a basal spacing of 7.8 Å. Fig. 1b-d exhibits substantial differences of the surfactant-modified hydroxysalt (ZHC-DS, Fig. 1b) and the subsequent materials (ZHC-DS-PdCl, Fig. 1c, and ZHC-DS-Pd⁰, Fig. 1d) with respect to the precursor ZHC (Fig. 1a). The disappearing of the characteristic zinc hydroxychloride peaks evidences the transformation of the laminar phase into a new one, with the surfactant molecules being intercalated in the interlayer space, giving rise to an ordered bilayer structure, where the longitudinal axis of the surfactant molecules turns out to be approximately perpendicular to the precursor laminae [29]. In Fig. 1b, two peaks at low 2θ values are observed, which correspond to two phases with d-spacing of 32.3 Å and 26.2 Å for the main phase. The first value closely resembles the

reported data of 31.5 Å for a nitrate-based hydroxysalt that was exchanged with DS in methanol in a theoretical and experimental study [29], which concluded that external variables such as solvent and temperature of the system exert some influence on the structural arrangement of surfactant in the interlayer space. According to it, we believe that in our case the presence of the second phase which is absent in the materials studied by Demel *et al.* [29], may be the result of the use of water instead of methanol as the solvent. In turn, as observed in Fig. 1c for ZHC-DS-PdCl, as a consequence of the intercalation of a PdCl_4^{2-} anion in the interlayer space, a decreased basal spacing is observed. As such, the surfactant-containing material (ZHC-DS) with original basal spacing's of 32.3 Å and 26.2 Å is changed for a material (ZHC-DS-PdCl) with a lowered basal spacing of 25.6 Å and 22.7 Å for the primary phase (Fig. 1c). These data are consistent with an expected diminution in the content of surfactant that induces a bilayer structural change in such way that a decrease in the basal spacing takes place, as reported [29].

Finally, in this sequence, Fig. 1d corresponds to the PXRD pattern of the material resulting from the reduction of the PdCl_4^{2-} anion exchanged ZHC to form palladium nanoparticles (this final material was labeled ZHC-DS-Pd⁰). Comparing Fig. 1c and 1d, there are substantial changes in the PXRD pattern and morphology (as shown later in Fig. 3d) of the laminar material upon reduction. As expected, palladium is reduced to metallic palladium with a consequent loss of the structural ordering which is due to the size and distribution of the resulting nanoparticles and the subsequent delamination of the ZHC-DS-PdCl material, so that the characteristic peaks of the clay are not visible anymore.

According to a previous report [21,30], palladium nanoparticles formation is suggested by the diffraction peak at about 40° in 2θ , which is consistent with our result, and it was also confirmed by TEM images (see ahead in Fig. 3e and 3f). Based on this PXRD peak, palladium nanoparticles size was estimated in about 4 nm by using the Debye-Scherrer's method [25].

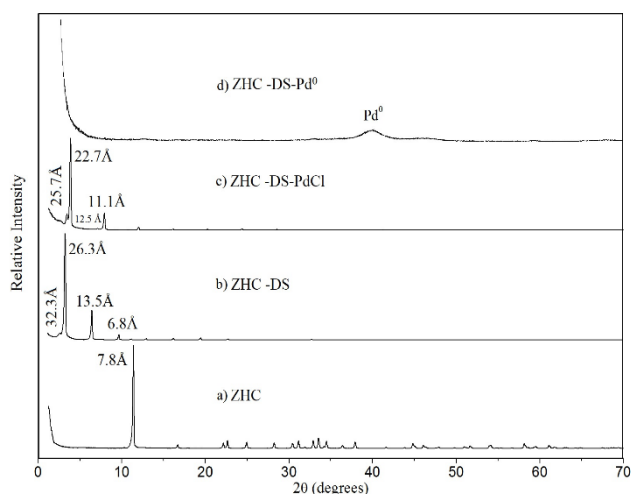


Figure 1. PXRD patterns: (a) ZHC, (b) ZHC -DS (c) ZHC -DS-PdCl, (d) ZHC -DS-Pd⁰.

Source: The authors

Table 1.
Textural properties of hydroxysalts materials

Material	BET surface area ($\text{m}^2\cdot\text{g}^{-1}$)	Pore volume ($\text{cm}^3\cdot\text{g}^{-1}$)	Average pore size (nm)
ZHC	1.07	0.002	8.19
ZHC-DS	11.66	0.040	13.65
ZHC-DS-PdCl	6.79	0.019	11.14
ZHC-DS-Pd ⁰	70.11	0.23	13.19

Source: The authors

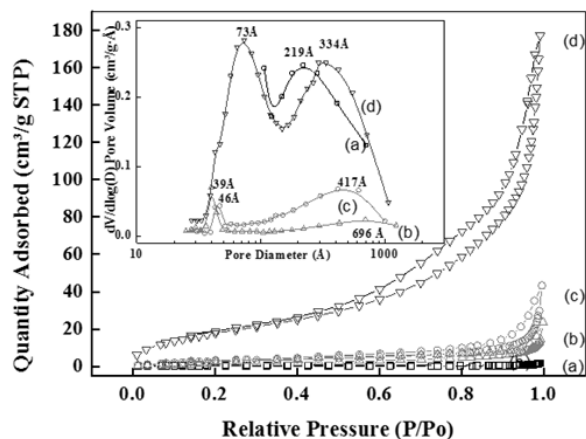


Figure 2. N₂ adsorption-desorption isotherms for (a) ZHC, (b) ZHC-DS, (c) ZHC-DS-PdCl, (d) ZHC-DS-Pd⁰. Inset. Mesopore distribution by BJH method for (a) ZHC, (b) ZHC-DS (c) ZHC-DS-PdCl, (d) ZHC-DS-Pd⁰. Source: The authors

Our second piece of evidence of structural changes from precursors to intermediates and to the final material comes from adsorption-desorption isotherms at liquid N₂ temperature (Fig. 2) while the respective analysis of the physical chemical features is summarized in Table 1.

According to IUPAC classification, these are isotherms type II (Fig. 2), typical of materials with big pores, characterized by hysteresis type H2 and H3 of materials with slit-shaped pores. The surfactant-modified hydroxysalt (ZHC-DS) register a slight adsorption enhancement, likely because of the electrostatic attraction between the sulfate groups of surfactant molecules and the positive charges of the ZHC, and also because of the hydrophobic interactions of the surfactant, as other authors have reported [31].

It is important to note that ZHC pore diameter distribution is characterized by a heterogeneous distribution with diameters centered mainly at 219 Å (Fig. 2a), while the surfactant-modified ZHC (ZHC-DS) (Fig. 2b) exhibits a significant diameter decrease (39 Å), probably because the insertion of surfactant forms mesopores. Upon exchange with the PdCl₄²⁻ anions, pore diameters of the resulting material (ZHC-DS-PdCl, Fig. 2c) increase again due to a possible reconfiguration of the interlayer space as explained before. After the reduction to form a palladium-containing surfactant-modified ZHC (ZHC-DS-Pd⁰, Fig. 2d), a heterogeneous pore diameter distribution is observed. In Fig. 2d, the first peak suggests the presence of 73 Å-mesopores, and the second peak indicates the occurrence of pores diameters centered at around 334 Å. The first maximum

might be the result of palladium nanoparticles being incorporated possibly in the interlayer space, while the second one indicates an increase of the mesopore diameters that are formed in the material due to the incorporation of bigger palladium nanoparticles and mesopores that could be formed between the particles of the material.

According to the trends observed in Table 1, the precursor material ZHC is characterized by a low BET surface area ($1.07 \text{ m}^2\text{g}^{-1}$) which is significantly increased to $11.6 \text{ m}^2\text{g}^{-1}$ when DS is intercalated into the material, and is in turn diminished back to $6.79 \text{ m}^2\text{g}^{-1}$ when the PdCl₄²⁻ anion entered into the material. This latter effect might be the result of a reconfiguration of the interlayer surfactant molecules because of the insertion of the PdCl₄²⁻ in some of the pores, in agreement with a previous literature report [32]. Furthermore, by comparison of BET surface areas for these materials, a drastic increase from $6.79 \text{ m}^2\text{g}^{-1}$ (in ZHC-DS-PdCl) to $70.11 \text{ m}^2\text{g}^{-1}$ (in ZHC-DS-Pd⁰) was observed, and this should be the result of the formation of palladium nanoparticles that generate mesopores with the consequent substantial increase of the pore volume, which finally results in the loss of the ordered structure in the material (consistent with Fig. 1d).

To study the morphology of the materials, SEM analyses were run for each of them, and the respective microographies are shown in Fig. 3.

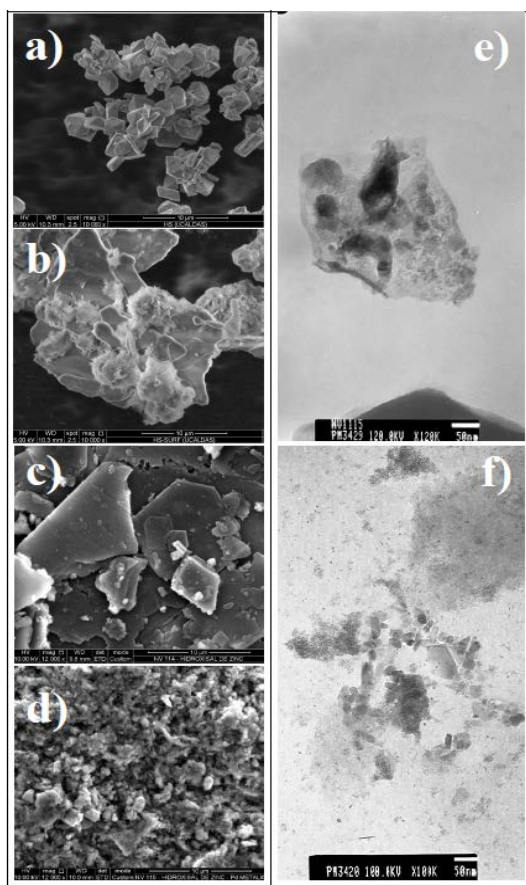


Figure 3. SEM microographies: (a) ZHC (10.000x), (b) ZHC-DS (10.000x), (c) ZHC-DS-PdCl (12.000x), (d) ZHC-DS-Pd⁰ (12.000x). (e) and (f) TEM microographies of the reduced material ZHC-DS-Pd⁰.

Source: The authors

The first image corresponds to the initial hydroxysalt (ZHC), where a crystalline material is observed, and some octahedral crystals with sizes of around 2-3 μm can be distinguished (Fig. 3a). In contrast, the morphology of the surfactant-modified hydroxysalt (ZHC-DS) is characterized by platelets of irregular thickness and irregular aggregates of flakes (Fig. 3b), which suggest the presence of two phases. This drastic change in the morphology of the materials illustrates that a DS intercalation effectively took place.

On the other hand, and according to Fig. 3c, after intercalation of the PdCl_4^{2-} anions, irregularly-shaped laminae are visualized in the resulting material ZHC-DS- PdCl , which upon treatment with refluxing ethanol, changes its morphology to clusters of sub-micrometric particles (see Fig. 3d for ZHC-DS- Pd^0). Additionally, TEM images were run for the material containing reduced palladium (ZHC-DS- Pd^0), Fig. 3e and 3f, where it is possible to differentiate particles with sizes varying approximately from 4-7 nm up to bigger aggregates and even particles of 100 nm in size. Both, TEM images (Fig. 3e and 3f) and PXRD patterns (Fig. 1d) confirm the successful generation of metal palladium particles with nanometric sizes. These particles are characterized by irregular shapes and are heterogeneously dispersed throughout the material.

4. Conclusions

The physical chemical characterization of materials proved that changes were occurring from the structural, textural and morphological point of view, upon going step by step from the ZHC precursor to intermediates and to the final material. PXRD patterns confirm that an intercalation of surfactant into the interlayer space of the hydroxysalt took place, giving rise to an interstratified material (32.3 Å and 26.3 Å). Then, the exchange reaction with a PdCl_4^{2-} anion promotes a decrease in the content of surfactant, which was evidenced by the PXRD analysis (basal spacing changes to 25.7 Å and 22.7 Å). Subsequently, the respective reduced material is constituted by palladium nanoparticles into the surfactant-containing material, and this fact was confirmed by both their PXRD patterns and TEM images.

The possibility of a surfactant-guided preparation of palladium nanoparticles into a hydroxysalt has been demonstrated. The significant increase of BET surface area of the reduced material is closely related to the palladium nanoparticles formation and the laminar material exfoliation. The adsorption of surfactant into a hydroxysalt makes possible to introduce a slight lipophilic character into this highly hydrophilic material, which may be taken advantage of in organic reactions, as suggested by Liu *et al* [33] who reported that a catalyzed Suzuki C-C coupling reaction with palladium nanoparticles supported on a LDH was favored by intercalation of dodecyl sulfate anion.

In order to have some idea about the likely catalytic potential of the new material, a preliminary catalytic test with our reduced material in a Suzuki C-C coupling reaction was performed, starting from iodobenzene and phenylboronic acid, which gave rise to about 90% yield of a white solid, which was not spectroscopically characterized but exhibited identical physical properties than an authentic biphenyl sample.

Acknowledgements

The authors thankfully acknowledge Universidad de Caldas, Vicerrectoría de Investigaciones y Postgrados, for the financial support of this project (code number 0526312) and to the laboratory of scanning electron microscopy (in the Stratigraphy Research Institute) at Universidad de Caldas. We also acknowledge Universidad del Cauca for the TEM analyses.

References

- [1] Carmo, D. M., Oliveira, M. G. and Soares, B. G. Effect of the dispersive method in the preparation of the polyurethane/hydrotalcite nanocomposites by in situ polymerization. *Applied Clay Science*, 101, pp. 128-135, 2014. <http://dx.doi.org/10.1016/j.clay.2014.07.027>
- [2] Ambrogio, V., Peroli, L., Ricci, M., Pulcini, L., Nocchetti, M., Giovagnoli, S. and Rossi, C. Eudragit® and hydrotalcite-like anionic clay composite system for diclofenac colonic delivery. *Microporous and Mesoporous Materials*, 115 (3), pp. 405-415, 2008. <http://dx.doi.org/10.1016/j.micromeso.2008.02.014>
- [3] Monteiro, M., Lunz, J., Veiga, Sebastião, P. and Tavares, M. Evaluation of Nevirapine Release Kinetics from Polycaprolactone Hybrids. *Materials Sciences and Applications*, 7 (11), pp. 680-701, 2016. <http://dx.doi.org/10.4236/msa.2016.711055>
- [4] An, Z., Zhang, W., Shi, H. and He, J. An effective heterogeneous L-proline catalyst for the asymmetric aldol reaction using anionic clays as intercalated support. *Journal of Catalysis*, 241 (2), pp. 319-327, 2006. <http://dx.doi.org/10.1016/j.jcat.2006.04.035>
- [5] Burrueco, M. I., Mora, M., Jiménez-Sanchidrián, C. and Ruiz, J. R. Hydrotalcite-supported palladium nanoparticles as catalysts for the Suzuki reaction of aryl halides in water. *Applied Catalysis A: General*, 485, pp. 196-201, 2014. <http://dx.doi.org/10.1016/j.apcata.2014.07.031>
- [6] Chen, X., Mi, F., Zhang, H. and Zhang H. Facile synthesis of a novel magnetic core-shell hierarchical composite submicrospheres $\text{Fe}_3\text{O}_4/\text{CuNiAl-LDH}$ under ambient conditions. *Materials Letters*, 69, pp. 48-51, 2012. <http://dx.doi.org/10.1016/j.matlet.2011.11.052>
- [7] Diao, Z., Zhang, Y., Hao, X., Wen, Z. Facile synthesis of $\text{CoAl-LDH}/\text{MnO}_2$ hierarchical nanocomposites for high-performance supercapacitors. *Ceramics International*, 40 (1), pp. 2115-2120, 2014. <http://dx.doi.org/10.1016/j.ceramint.2013.07.127>
- [8] Xie, L., Sun, G., Xie, L., Su, F., Li, X., Liu, Z., Kong, Q., Lu, C., Li, K. and Chen, C. A high energy density asymmetric supercapacitor based on a CoNi -layered double hydroxide and activated carbon. *New Carbon Materials*, 31 (1), pp. 37-45, 2016. [http://dx.doi.org/10.1016/S1872-5805\(16\)60003-3](http://dx.doi.org/10.1016/S1872-5805(16)60003-3)
- [9] Ma, J., Ding, J., Li, L., Zou, J., Kong, Y. and Komamene, S. In situ reduction for synthesis of nano-sized Cu_2O particles on MgCuAl-LDH layers for degradation of orange II under visible light. *Ceramics International*, 41 (2), pp. 3191-3196, 2014. <http://dx.doi.org/10.1016/j.ceramint.2014.10.172>
- [10] Hoessle, F., Plank, J. and Leroux, F. Intercalation of sulfonated melamine formaldehyde polycondensates into a hydrocalumite LDH structure. *Journal of Physics and Chemistry of Solids*, 80, pp. 112-117, 2015. <http://dx.doi.org/10.1016/j.jpcs.2015.01.008>
- [11] Chakraborty, S., Kumar, M., Suresh, K. and Pugazhenth, G. Influence of organically modified NiAl layered double hydroxide (LDH) loading on the rheological properties of poly (methyl methacrylate) (PMMA)/LDH blend solution. *Powder Technology*, 256, pp. 196-203, 2014. <http://dx.doi.org/10.1016/j.powtec.2014.02.035>
- [12] Zhou, J., Xu, Z. P., Qiao, S., Liu, Q., Xu, Y. and Qian, G. Enhanced removal of triphosphate by MgCaFe-Cl-LDH : Synergism of precipitation with intercalation and surface uptake. *Journal of Hazardous Materials*, 189 (1-2), pp. 586-594, 2011. <http://dx.doi.org/10.1016/j.jhazmat.2011.02.078>
- [13] Lakshmi Kantam, M., Parsharamulu, T. and Manorama, S. V. Layered double hydroxides supported nano palladium: An efficient catalyst for the chemoselective hydrogenation of olefinic bonds. *Journal of*

- Molecular Catalysis A: Chemical, 365, pp.115-119, 2012. <http://dx.doi.org/10.1016/j.molcata.2012.08.017>
- [14] de Rezende, S. M., Franchini, C. A., Dieuzeide, M. L., Duarte de Farias, A. M., Amadeo, N. and Fraga, M. A. Glycerol steam reforming over layered double hydroxide-supported Pt catalysts. *Chemical Engineering Journal*, 272, pp.108-118, 2015. <http://dx.doi.org/10.1016/j.cej.2015.03.033>
- [15] Li, Z., Xi, W. and Lu, C. Hydrotalcite-supported gold nanoparticle catalysts as a low temperature cataluminescence sensing platform. *Sensors and Actuators B: Chemical*, 219, pp. 354-360, 2015. <http://dx.doi.org/10.1016/j.snb.2015.05.030>
- [16] Huang, L., Zhou, J., Hsu, A.T. and Chen, R. Catalytic partial oxidation of n-butanol for hydrogen production over LDH-derived Ni-based catalysts. *International Journal of Hydrogen Energy*, 38 (34), pp. 14550-14558, 2013. <http://dx.doi.org/10.1016/j.ijhydene.2013.09.068>
- [17] Sahoo, M. and Parida, K. M. Pd(II) loaded on diamine functionalized LDH for oxidation of primary alcohol using water as solvent. *Applied Catalysis A: general*, 460-461, pp. 36-45, 2013. <http://dx.doi.org/10.1016/j.apcata.2013.04.003>
- [18] Saber, O., Goraba, H. M. and Jaafari, A. A. Catalytic activity and surface characteristics of layered Zn-Al-Si materials supported platinum. *Applied Clay Science*, 53, pp. 317-325, 2011. <http://dx.doi.org/10.1016/j.clay.2010.12.026>
- [19] Cavani, F., Trifirò, F. and Vaccari, A. Hydrotalcite-type anionic clays: preparation, properties and applications. *Catalysis Today*, 11 (2), pp. 173-301, 1991. [http://dx.doi.org/10.1016/0920-5861\(91\)80068-K](http://dx.doi.org/10.1016/0920-5861(91)80068-K)
- [20] Ahmed, I. M. and Gasser, M. S. Adsorption study of anionic reactive dye from aqueous solution to Mg-Fe-CO₃ layered double hydroxide (LDH). *Applied Surface Science*, 259, pp. 650-656. 2012. <http://dx.doi.org/10.1016/j.apsusc.2012.07.092>
- [21] Nityashree, N. and Rajamathi, M. Interstratified composite of the anionic clays, Zn₅(OH)₈(NO₃)₂·2H₂O and Ni₃Zn₂(OH)₈(NO₃)₂·2H₂O, by delamination-costacking. *Journal of Physics and Chemistry of Solids*, 74 (8) pp. 1164-1168, 2013. <http://dx.doi.org/10.1016/j.jpcs.2013.03.015>
- [22] Khamlich, S., Abdullaeva, Z., Kennedy, J. V. and Maaza, M. High performance symmetric supercapacitor based on zinc hydroxychloride nanosheets and 3D graphene-nickel foam composite. *Applied Surface Science*, 405, pp. 329-336, 2017. <http://dx.doi.org/10.1016/j.apsusc.2017.02.095>
- [23] Li, B., Wang, C., Chen, G., and Zhang, Z. Palladium-phosphinous acid complexes catalyzed Suzuki cross-coupling reaction of heteroaryl bromides with phenylboronic acid in water/alcoholic solvents. *Journal of Environmental Sciences*, 25 (6), pp. 1083-1088, 2013. [http://dx.doi.org/10.1016/S1001-0742\(12\)60132-6](http://dx.doi.org/10.1016/S1001-0742(12)60132-6)
- [24] Negishi, E. I. Palladium- or nickel-catalyzed cross coupling. A new selective method for carbon-carbon bond formation. *Acc. Chem. Res.*, 15, pp. 340-348, 1982. <http://dx.doi.org/10.1021/ar00083a001>
- [25] Moore, D. M. and Reynolds, R. C., Jr. X-ray diffraction and the identification and analysis of clay minerals, 2nd ed. Oxford: University Press, 1998.
- [26] Chui, S. S.-Y., Lo, S. M.-F., Charmant, J. P. H., Orpen, A. G. and Williams, I. D. A chemically functionalizable nanoporous material [Cu₃(TMA)₂(H₂O)₃]_n. *Science*, 283 (5405), pp. 1148-1150, 1999. <http://dx.doi.org/10.1126/science.283.5405.1148>
- [27] Tanaka, H., Futouy, A., Fujioka, A., Kandori, K. and Ishikawa, T. Influence of Ti(IV) on the structure and properties of zinc hydroxychloride. *Corrosion Science*, 50 (11), pp. 3154-3159, 2008. <http://dx.doi.org/10.1016/j.corsci.2008.08.022>
- [28] Tanaka, H., Tashima, K., Kandori, K., Ishikawa, T. and Nakayama, T. Structure and properties of Ti (IV)-doped zinc hydroxychloride rusts formed at various temperatures. *Corrosion Science*, 53 (2), pp. 696-702, 2011. <http://doi.org/10.1016/j.corsci.2010.10.018>
- [29] Demel, J., Hynek, J., Kovář, P., Dai, Y., Taviot-Guého, C., Demel, O., Pospíšil, M. and Lang, K. Insight into the Structure of Layered Zinc Hydroxide Salts Intercalated with Dodecyl Sulfate Anions. *Journal of Physical Chemistry C*, 118 (46), pp. 27131-27141, 2014. <http://dx.doi.org/10.1021/jp508499g>
- [30] Papp, S., Szűcs, A. and Dékány, I. Preparation of PdO nanoparticles stabilized by polymers and layered silicate. *Applied Clay Science*, 19 (1-6), pp. 155-172, 2001. [http://dx.doi.org/10.1016/S0169-1317\(01\)00048-5](http://dx.doi.org/10.1016/S0169-1317(01)00048-5)
- [31] Pavan, P. C., Gomes, G. de A. and Valim, J. B. Adsorption of sodium dodecyl sulfate on layered double hydroxides. *Microporous and Mesoporous Materials*, 21 (4-6), pp. 659-665, 1998. [https://doi.org/10.1016/S1387-1811\(98\)00054-7](https://doi.org/10.1016/S1387-1811(98)00054-7)
- [32] Wibulswas, R., White, D. A. and Rautiu, R. Adsorption of Phenolic Compounds from Water by Surfactant-Modified Pillared Clays. *Process Safety and Environmental Protection*, 77 (2), pp. 88-92, 1999. <http://dx.doi.org/10.1205/095758299529857>
- [33] Liu, S., Zhou, Q., Jin, Z., Jiang, H. and Jiang, X. Dodecylsulfate Anion Embedded Layered Double Hydroxide Supported Nanopalladium Catalyst for the Suzuki Reaction, *Chinese Journal of Catalysis*, 31 (5), pp. 557-561, 2010. [http://dx.doi.org/10.1016/S1872-2067\(09\)60072-3](http://dx.doi.org/10.1016/S1872-2067(09)60072-3)

M.M. Martínez, received her BS. Education degree in Biology and Chemistry in 2005 and the M.Sc. Chemistry in 2010, both degrees obtained from Universidad de Caldas, Manizales, Colombia. She currently works in the Department of Chemistry at Universidad de Caldas. Her present research is developed mainly in heterogeneous organic catalysis using nanostructured materials and in the study of medicinal plants. Contact information: maby.martinez@ucaldas.edu.co
ORCID: orcid.org/0000-0002-7509-9610

R. Ocampo-Cardona, received his BS. Education degree in Biology and Chemistry in 1984 from Universidad de Caldas, Colombia, and the M.Sc. degree in Chemistry in 1997, and the Ph.D. degree in Chemistry in 1997, from Universidad del Valle, Cali, Colombia. Currently, he is a full professor in the Department of Chemistry at Universidad de Caldas. His present research is mainly developed in organic synthesis, particularly synthesis of molecules with medicinal interest. His research is also focused to heterogeneous organic catalysis using nanostructured materials. Contact information: rogelio.ocampo@ucaldas.edu.co
ORCID: orcid.org/0000-0002-3375-6352

J.M. Aguirre-Cortes, Graduated as Chemical Engineer and Master in Engineering in 2005 and 2008 respectively from the National University of Colombia. He has worked as a professor at the University of Caldas in areas of basic chemistry. His research interests include the synthesis and characterization of nanostructured materials. Contact information: jhon.aguirre@ucaldas.edu.co
ORCID: orcid.org/0000-0002-9700-3544

O. Giraldo, completed his BSc. in Chemistry in 1992, at Universidad del Valle, Cali, Colombia, and his Ph.D. degree in Chemistry in 2000, at the University of Connecticut, USA. He is a full professor in the Physics and Chemistry Department, Universidad Nacional de Colombia, Manizales Colombia. His research interests include: nanostructured functional materials, solid state chemistry, heterogeneous catalysis, hybrid materials, biomaterials, biopolymer-based nanocomposite materials and applications of material chemistry. Contact information: ohgiraldo@unal.edu.co
ORCID: orcid.org/0000-0002-9213-6348

L.A. Ríos-Vásquez, received her BS. Education degree in Biology and Chemistry in 1987 from Universidad de Caldas, Colombia, and the M.Sc. degree in Chemistry in 1992, and the Ph.D. degree in Chemistry in 1998, from Universidad del Valle, Cali, Colombia. Currently, she is a full professor in the Department of Chemistry at Universidad de Caldas. Her present research is mainly developed in organic synthesis, particularly synthesis of molecules with medicinal interest. Contact information: amalia.rios@ucaldas.edu.co
ORCID: orcid.org/0000-0002-4510-7771