



REVISTA DE INGENIERIA DE LA FACULTAD DE INGENIERIA - UNIVERSIDAD NACIONAL DE COLOMBIA - BOGOTÁ

DYNA

ISSN: 0012-7353

ISSN: 2346-2183

Universidad Nacional de Colombia

Quintero-Giraldo, Leidy Johana; Cruz-Riaño, Luis Javier; García-Guzmán, Jaime Alexis; Alcaraz-Zapata, Alejandro; González-Castrillón, Eugenia del Socorro; Osorio-Saraz, Jairo Alexander
Incidence of mercerization treatment in the mechanical properties of bamboo fibre bundles "Guadua Angustifolia Kunth" from colombian origin
DYNA, vol. 86, no. 210, 2019, July-September, pp. 156-163
Universidad Nacional de Colombia

DOI: <https://doi.org/10.15446/dyna.v86n210.71782>

Available in: <https://www.redalyc.org/articulo.oa?id=49662789020>

- How to cite
- Complete issue
- More information about this article
- Journal's webpage in redalyc.org

UNEN
redalyc.org

Scientific Information System Redalyc
Network of Scientific Journals from Latin America and the Caribbean, Spain and Portugal

Project academic non-profit, developed under the open access initiative

Incidence of mercerization treatment in the mechanical properties of bamboo fibre bundles "Guadua Angustifolia Kunth" from colombian origin

Leidy Johana Quintero-Giraldo ^a, Luis Javier Cruz-Riaño ^a, Jaime Alexis García-Guzmán ^a, Alejandro Alcaraz-Zapata ^a, Eugenia del Socorro González-Castrillón ^b & Jairo Alexander Osorio-Saraz ^b

^a Mechanical Engineering Faculty, Universidad Pontificia Bolivariana, Medellín, Colombia. leidyqg@gmail.com, luis.cruz@upb.edu.co, alexis.garcia@upb.edu.co, alejandro.alcaraz@upb.edu.co

^b Department of Agricultural Engineering and Food, Universidad Nacional de Colombia, Medellín, Colombia. egcastril@unal.edu.co, aosorio@unal.edu.co

Received: April 18th, 2018. Received in revised form: March 11th, 2019. Accepted: June 15th, 2019.

Abstract

In this article, bamboo fibre bundles of "Guadua Angustifolia Kunth" specie were isolated from different locations of the basa zone: upper, middle and lower, through mechanical extraction method. The elastic modulus and the tensile strength were obtained with preliminary tensile tests. Applying the statistical analysis known as ANOVA, it was determined that the mechanical properties are similar in all the extension of the basa zone. From there, fibre bundles were extracted randomly, and a part of the fibre bundles was treated with NaOH (mercerization). Later, tensile tests with different calibration lengths were made for calculate the elastic modulus and the tensile strength of the treated and untreated fibre bundles. Best results belonged to the treated fibre bundles. A good correspondence between the results obtained in this work and the results reported in the literature was concluded.

Keywords: natural fibres; bamboo; alkaline treatment; extraction of fibres; mechanical properties.

Incidencia del tratamiento de mercerización en las propiedades mecánicas de haces de fibras de bambú "Guadua Angustifolia Kunth" de origen colombiano

Resumen

En este artículo se empleó el método de extracción mecánica para aislar haces de fibra de bambú de la especie GAK desde las zonas superior, central e inferior de la parte de la planta llamada basa. Se hicieron ensayos preliminares de tensión, obteniéndose el módulo elástico y la resistencia a la tensión. Se determinó por medio de un análisis estadístico ANOVA que las propiedades mecánicas eran similares en toda la zona de la basa. De ahí, se extrajeron haces de fibras de forma aleatoria y una parte fue tratada con NaOH (mercerización). Posteriormente, se realizaron ensayos de tensión variando la longitud de calibración y, se calculó la resistencia a la tensión y el módulo elástico de los haces de fibras no tratados y tratados. Los mejores resultados pertenecieron a los haces de fibras tratados. Se concluye una buena correspondencia entre los resultados obtenidos y los reportados en la literatura.


Palabras clave: fibras naturales; bambú; tratamiento alcalino; extracción de fibras; propiedades mecánicas.

1. Introduction

Since the start of our civilization, natural fibers have been used in basic elements such as baskets, ropes, fabrics, floors, and

roofs [1]. However, as the global energy crisis and ecological risks increase, interest has arisen in the research and development of biodegradable and high-performance products [2]. In recent years, natural fibers such as hemp, linen, jute, kenaf, oil palm, and

How to cite: Quintero-Giraldo, L.J., Cruz-Riaño, L.J., García-Guzmán, J.A., Alcaraz-Zapata, A., González-Castrillón, E.S. and Osorio-Saraz, J.A., incidence of mercerization treatment in the mechanical properties of bamboo fibre bundles "Guadua Angustifolia Kunth" from colombian origin. DYNA, 86(210), pp. 156-163, July - September, 2019.

© The author; licensee Universidad Nacional de Colombia. 
Revista DYNA, 86(210), pp. 156-163, July - September, 2019, ISSN 0012-7353
DOI: <http://doi.org/10.15446/dyna.v86n210.71782>

bamboo have been considered in several applications such as automobiles, furniture, packaging, and construction. This is a result of the superior advantages they possess over synthetic fibers in terms of their relative low cost, low weight, less damage to processing equipment, better surface finish in molded parts compounds, and adequate specific mechanical properties.

The aforesaid fosters the consideration of using natural fibers for various applications and under different loading conditions [3].

In industrial applications, synthetic fibers such as fibers of glass, carbon, and kevlar are highly used [4]. However, this type of material generates high environmental pollution and its disposal after the finalization of its lifecycle is difficult. The use of these fibers, such as fiberglass, in the case of being incorporated into automotive spare parts, due to their density, increases the use of petroleum-derived fuels, which contribute to the increase in environmental problems generated by the large amount of CO₂ emissions, which for the year 2013, was around 4,996 metric tons per capita worldwide [5].

A natural fiber is understood as a fibrous material that can be extracted from animals, minerals, and vegetables. The vegetal fibers that we address in this article are composed mainly of cellulose, hemicellulose, and lignin. Further, they possess additional components in less proportion, as shown in Table 1. Cellulose imposes mechanical strength to the fibers (resistance and rigidity), lignin is the hydrophobic part, and hemicellulose, the most amorphous component, improves water absorption and mechanically facilitates elasticity. These vegetable fibers present highly dispersed mechanical properties and are dependent on their chemical composition and the conditions in which they are found, mainly of their degree of humidity, their cultivation processes, and extraction methods [10]. However, Table 2 shows that the specific mechanical properties of these natural fibers are similar or even superior to those presented by synthetic fibers such as fiberglass [7,8,12].

The bundles of natural bamboo fibers from the "*Guadua Angustifolia Kunth* (GAK)" species can be a good alternative for industrial applications as they possess adequate mechanical properties, as well as additional advantages such as low density and low cost. Moreover, they exhibit rapid growth and are classified as a renewable resource [12,13].

The bamboo is divided into six zones: rhizome, bottom, middle, top, stick, and leader, as shown in Fig. 1 [14], and according to literature, the fiber bundles with superior mechanical properties are found in the middle zone. [15].

It is important to point out the importance of choosing a good extraction method, as it is difficult to separate the fibrous bundles from the plants. When lignin and other components are removed, the cellulose microfibrils are also affected, which may increase the fragility of the bundles and decrease their mechanical properties [15]. Therefore, different extraction methods and chemical, physical, and biological surface treatments have been applied, with which significant differences have been obtained in terms of mechanical properties [14,16]. One of the most widely used surface treatments is mercerization or basic hydrolysis. As part of this treatment, the natural fiber is first impregnated with an alkali solution (caustic soda). Then, tension is applied

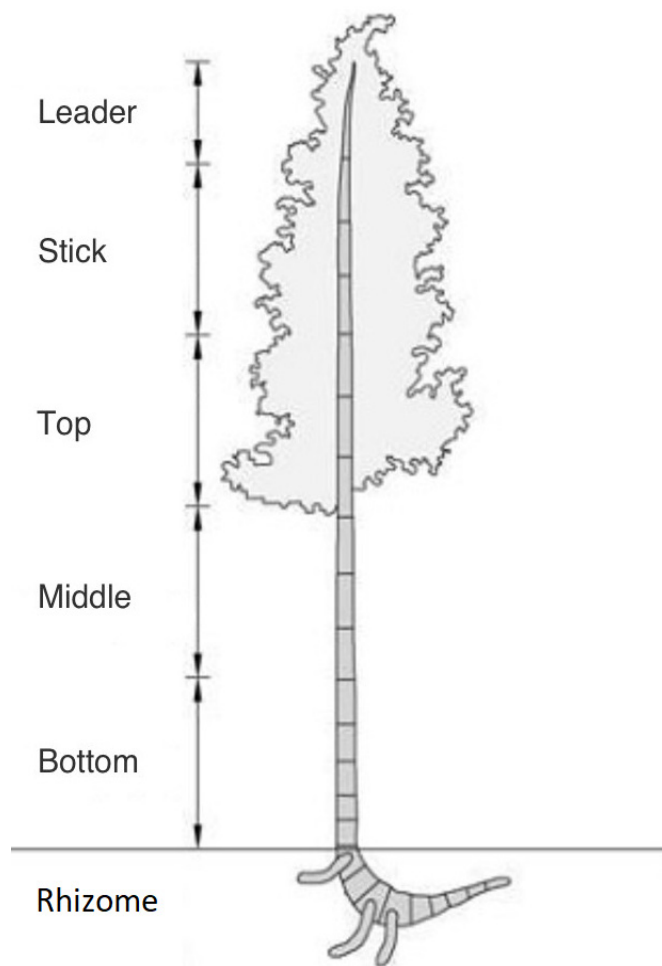


Figure 1. Parts of a bamboo plant.
Source: [14]

while it is rinsed to eliminate caustic soda, thus improving the luster and facilitating the handling of natural fiber in later processes and the removal of lignin and hemicellulose.

Given the above, the objective of this work was to determine the mechanical properties, specifically the elastic modulus and tensile strength at different calibration lengths, of *Guadua Angustifolia Kunth* bamboo fiber bundles obtained from the middle zone, after being isolated by mechanical extraction and having applied a mercerization treatment.

2. Materials and methods

2.1. Materials

Untreated GAK bamboo stalks or culms, with an average age of 4 years, from the municipality of Santa Fe de Antioquia (Colombia) provided by the National University of Colombia at Medellin were used as raw materials. This region is located at an altitude of 625 meters above sea level and its average temperature is 27°C [17]. For the mercerization treatment, analytical grade sodium hydroxide was used at a concentration of 5% w/v.

2.2. Mechanical characterization of GAK

2.2.1. Obtaining GAK fiber bundles through mechanical extraction

The GAK fiber bundles were isolated using an IMOCOM milling machine.

In this first stage, GAK culms were randomly selected from the middle region, which was divided into three zones: upper, middle, and lower. Subsequently, the fiber bundles of the different zones were extracted through the mechanical extraction method.

The GAK culms were cut at an approximate height of 15 cm (internode) and placed on a milling machine. Next, a tungsten beading mill with a working angle of 90°, a speed of 1050 rpm, and a cutting depth of 0.3 mm was used. This assembly is depicted in Fig. 2.

After the initial experimentation, through a statistical analysis from an ANOVA table, it was determined that the mechanical properties in all the middle zones (upper, middle, and lower) were similar. Therefore, in the second stage, the fiber bundles were mechanically removed in random manner before a chemical surface treatment was applied on their surfaces to remove non-cellulosic components.

2.2.2. Chemical surface treatment

The fiber bundles were treated with an alkaline 5% w/v sodium hydroxide solution at a constant temperature of 30°C for a period of 30 min. A ratio of 20 g of fiber bundles per liter of alkaline solution was used. Subsequently, the treated fiber bundles were washed with abundant distilled water until obtaining a neutral pH and were dried in a DIES oven at a temperature of $100.0 \pm 0.1^\circ \text{C}$ for 12 h.

Table 1.
Chemical composition of different natural vegetable fibers.

Fiber	Cellulose (%)	Hemicellulose (%)	Lignin (%)	Pectin (%)	Waxes (%)	Ashes (%)
Cotton	82.7	5.7	28.2	5.7	0.6	ND
Jute	64.4	12.0	0.2	11.8	0.5	0.5-2.1
Linen	64.1	16.7	2.0	1.8	1.5	13.1
Ramie	68.6	13.1	0.6	1.9	0.3	ND
Sisal	65.8	12.0	9.9	0.8	0.3	4.2
Bamboo	48.2-73.8	12.5-73.3	10.2-21.4	0.37	ND	2.3
Hemp	55-80.2	12-22.4	2.6-13	0.9-3.0	0.2	0.5-0.8
Kenaf	37-49	18-24	15-21	8.9	0.5	2.4-5.1
Abaca	56-63	15-17	7-9	0.3	0.1	3.2
Henequen	77.6	4-8	13.1	ND	ND	ND
Oil palm	42.7-65	17.1-33.5	13.2-25.3	ND	0.6	1.3-6.0
Areca	35-64.8	29-33.1	13-26	9.2-15.4	0.5-0.7	1.1-2.1
Sugarcane Bagasse	28.3-55	20-36.3	21.2-24	ND	0.9	1-4
Coconut	19.9-36.7	11.9-15.4	32.7-53.3	4.7-7.0	ND	ND
Pineapple	57.5-74.3	80.7	4.4-10.1	1.1	3.3	0.9-4.7

Source: Adapted from [6]

Table 2.
Mechanical properties of different vegetable and synthetic fibers.

	Density (g/cm ³)	Tensile strength (MPa)	Modulus of elasticity (GPa)	Specific tensile strength (MPa/g/cm ³)	Specific modulus of elasticity (GPa/g/cm ³)	Elongation (%)
Linen	1.4	800-1500	60-80	571.43-1071.43	42.86-57.14	1.2-1.6
Hemp	1.48	550-900	70	371.62-608.11	47.30	1.6
Kenaf	1.45	930	53	641.38	36.55	1.6
Jute	1.46	400-800	10-30	273.97-547.94	6.85-20.55	1.8
Ramie	1.5	500	44	333.33	29.33	2
Coconut	1.25	220	6	176	4.8	15-25
Sisal	1.33	600-700	38	451.13-526.32	28.57	2-3
Cotton	1.55	400	12	258.06	7.74	3-10
Sugarcane Bagasse	1.2	20-290	19.7-27.1	16.67-241.67	16.42-22.58	1.1
Henequen	1.4	430-580	-	307.14-414.29	-	3-4.7
Pineapple	1.5	170-1627	82	113.33-1084.67	54.67	1-3
Banana	1.35	355	33.8	262.96	25.04	5.3
Bamboo	1.1	391-713	18-55	355.45-648.18	16.36-50	-
E-glass	2.5	2000-3500	70	800-1400	28	2.8
Aramid (Std)	1.4	3000-3150	63-67	2142.86-2250	45-47.86	3.3-3.7
Carbon (Std PAN)	1.4	4000	230-240	2857.14	164.29-171.43	1.4-1.8

Source: Adapted from [7-9]

2.2.3. Test Tube preparation for tensile tests

The treated and untreated bundles of extracted GAK fibers were separated manually. Subsequently, the test tubes were prepared for mechanical tests under the ASTM D3822-14 standard, as shown in Fig. 3 [18]. The calibration lengths used in the first and second experimentation stages were 10 mm and 15 mm, respectively. The apparent diameter of each fiber bundle was calculated by the projected profile technique [1] using a LEICA microscope at a magnification of 50 \times , supported by the IQMATERIALS software.

Afterwards, these samples were conditioned for 12 h before testing at a relative ambient humidity of 69% \pm 1% and a temperature of 21.0 \pm 0.1 $^{\circ}$ C, as per the ASTM D1776-15 standard [19].

Fig. 4 denotes a flowchart of the extraction process and chemical surface treatment of the fiber bundles.

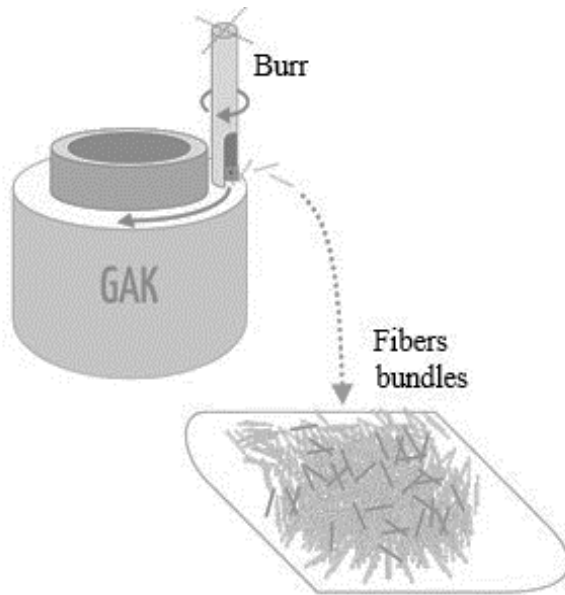


Figure 2. Assembly of the GAK culm in the milling machine.
Source: The Authors.

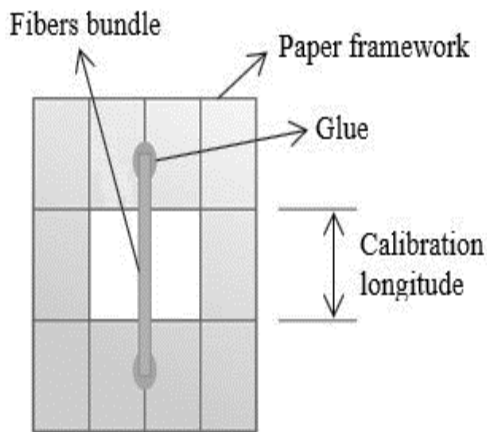


Figure 3. Test tube for tensile tests.
Source: The Authors.

Table 3.
Parameters used in tensile tests

Parameter	Value	Units
Velocity before the test	3	mm/min
Test velocity	1.2	mm/min
Displacement scale	1	mm

Source: The Authors.

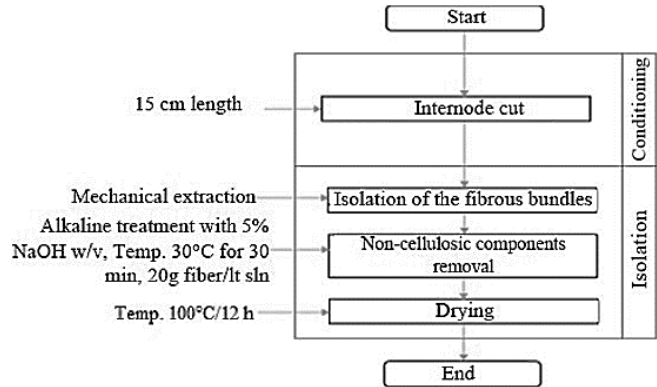


Figure 4. Flow chart of the extraction process and chemical surface treatment of the GAK fiber bundles.
Source: The Authors.

2.2.4. Mechanical characterization of GAK fibers bundles

About 320 tensile tests were performed using a TAXT Plus texturometer from the Agroindustrial Research Group-GRAIN laboratory at the Universidad Pontificia Bolivariana at Medellin.

A 50 Kgf load cell was used and the data were analyzed by the Exponent software. The parameters used in these tensile tests are shown in Table 3.

Based on the ASTM D3822-14 standard and using the calibration lengths mentioned in the first and second stages, some of the mechanical properties were calculated, specifically the tensile strength and the elastic modulus [18].

3. Results and discussion

The results obtained in the different mechanical tests were analyzed using the Statgraphics software [20].

3.1. First stage: mechanical characterization of GAK fibers from the middle area

According to the statistical analysis made from the ANOVA table, it can be determined that the "middle zone" factor, divided into upper, middle, and lower, does not present a statistically significant difference in its mechanical properties (elastic modulus and tensile strength), since the F-ratio is very small (inter-group and intra-group quotient estimates) and the P-Value is greater than 0.05, as may be observed in Tables 4 and 5.

Additionally, from the multiple range tests, it was concluded that there is only one homogeneous group, which means that the fiber bundles from the different middle zones have similar mechanical properties, as shown in Tables 6 and 7. This is confirmed in the Mean charts, where the results overlap, as evidenced in Figs. 5 and 6.

Table 4.

ANOVA Statistical analysis for the elastic modulus

Middle zone modulus of elasticity ANOVA table					
Source	Sum of Squares	D F	Mean Squares	F-Ratio	P-Value
Between groups	0.64	2	0.32	0.35	0.71
Within groups	8.33	9	0.92		
Total (Corr.)	8.97	11			

Source: The Authors.

Table 5.

ANOVA Statistical analysis for tensile strength.

Middle zone tensile strength ANOVA test					
Source	Sum of Squares	DF	Mean Squares	F-Ratio	P-Value
Between groups	4672.15	2	2336.07	1.46	0.28
Within groups	14429.60	9	1603.29		
Total (Corr.)	19101.70	11			

Source: The Authors.

Table 6.

Multiple range test for the elastic modulus.

Middle zone modulus of elasticity multiple range tests			
Method: 95.0 LSD percentage			
Middle zone	Cases	Mean (GPa)	Homogeneous Groups
Middle	4	4.73	X
Upper	4	5.26	X
Lower	4	5.16	X

Source: The Authors.

Table 7.

Multiple Range Test for Tensile Strength.

Middle zone tensile strength multiple range tests			
Method: 95.0 LSD percentage			
Middle zone	Cases	Mean (GPa)	Homogeneous Groups
Middle	4	163.25	X
Upper	4	210.83	X
Lower	4	194.39	X

Source: The Authors.

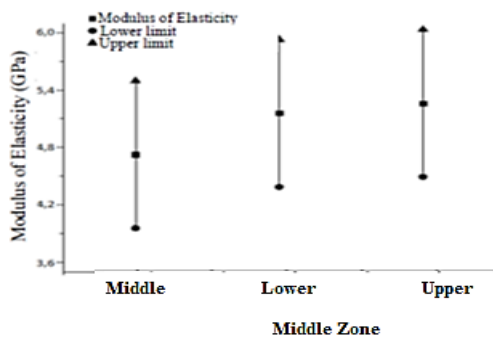


Figure 5. Mean chart for the elastic modulus.

Source: The Authors.

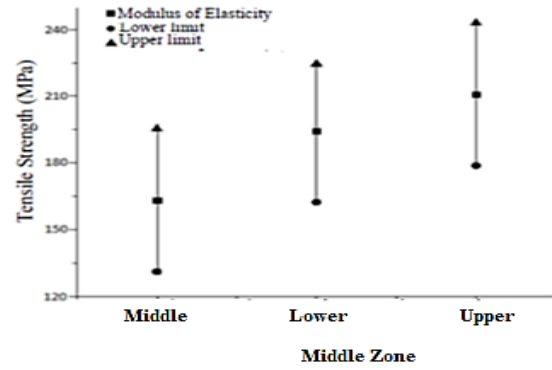


Figure 6. Mean chart for tensile strength.

Source: The Authors.

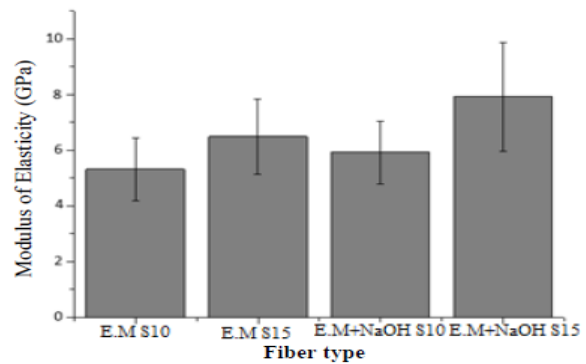


Figure 7. Elastic modulus obtained before and after the chemical surface treatment.

Source: The Authors.

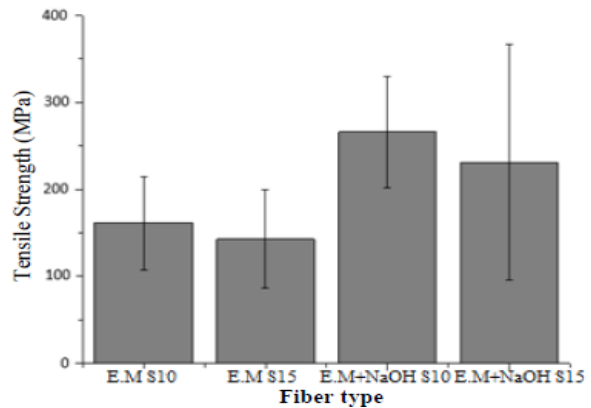


Figure 8. Tensile strength obtained before and after the chemical surface treatment.

Source: The Authors.

3.2. Second stage: mechanical extraction and chemical surface treatment

In Figs. 7 and 8, we can observe the high standard deviations from elastic modulus and tensile strength properties, originated by the high heterogeneity in shape and size of the fiber bundles. In addition, these bundles evidence

Table 8.

Natural fibers with inferior mechanical properties compared to what is found in this research.

Natural fiber	Tensile strength (MPa)	Modulus of elasticity (GPa)
Coconut	175	4-6
Oil palm	80-248	0.5-3.2
Piassava	134-143	1.07-4.59
GAK S10 (For this experiment)	161.36-265.98	5.31-5.92
GAK S15 (For this experiment)	142.55-230.97	6.49-7.92

Source: Adapted from [11,27]

high diameter variability, which is a fundamental tensile strength parameter. In addition, the results are very sensitive to variables, such as the processing method, cultivation conditions, type of surface treatment, and percentage of humidity, which determine the final characteristics of this type of natural material [21-24]. Moreover, the best results for both the elastic modulus and the tensile strength are presented after the surface treatment with NaOH for both calibration lengths (span 10 and 15). The aforementioned is due to the fact that the mechanical extraction by itself does not remove non-cellulose components such as lignin and hemicellulose, which have an amorphous structure that significantly affects the mechanical strength of the fiber bundles, thus contributing a greater quantity of microdefects within them and counteracting the crystalline structure of the cellulose component [25]. Given the above, when applying a surface treatment with NaOH to these fiber bundles, the abovementioned components are removed, which improves the mechanical properties of these materials [26]. Furthermore, the best elastic modulus values were obtained at a 15 mm span, since this property improves as the number of bonds aligned in the direction of the applied force increases, which is consistent with the results reported in the literature [24].

However, the results obtained for the tensile strength are quite different. Here, the best results are achieved with 10 mm span since at greater lengths, there is a higher probability of finding defects and/or irregularities. These defects become stress concentrators, and therefore, facilitate the fracture of the fiber bundle [14,24]. Finally, the results obtained in this research study, with respect to other natural fibers, present better mechanical properties, as shown in Table 8.

4. Conclusions

The preliminary mechanical characterization tests and the statistical analysis corroborate the similarity of the mechanical properties existing along the middle zone in the GAK bamboo culm.

Regarding the extraction of GAK fiber bundles, a better yield could be observed when the surfaces are treated with NaOH, since this treatment removes components such as lignin and hemicellulose, thus improving the mechanical properties of the fiber bundles.

In term of calibration lengths, a better tensile strength is obtained when using a span of 10 mm, since there is a smaller number of defects and/or irregularities that can generate

fractures in the fiber bundle. Otherwise, for the elastic modulus, the best result is reported when using a 15 mm span because there is a greater number of bonds aligned in the direction of the applied force, which plays an important role in this property.

Although the mechanical properties of untreated GAK fiber bundles are inferior compared with those of treated GAK fiber bundles, they can be used in applications where fiber bundles do not require a high mechanical performance.

The abovementioned results demonstrate the potential of using natural fibers in industrial applications where synthetic fibers have been traditionally implemented.

Acknowledgments

The authors thank the GRAIN Agroindustrial Research Group and the Unitary Operations laboratory of the Universidad Pontificia Bolivariana at Medellin for their support in the equipment and laboratories required to conduct this research study. Likewise, the authors wish to thank the Research Center for Development and Innovation-CIDI of the Universidad Pontificia Bolivariana at Medellin, which under the UPB INNOVA 2015 program, financed this research project. Finally, the authors also express their gratitude to the GTG Guadua Working Group for the Forestry product laboratory, as well as to the Direction of Agrarian Stations CEAGRO of the School of Agrarian Sciences at the Universidad Nacional de Colombia at Medellin for facilitating the raw materials for this study.

References

- [1] Monteiro, S.N., Satyanarayana, K.G., Ferreira, A.S., Nascimento, D.C.O., Lopes, F.P.D., Silva, I.L.A., Bevilotti, A.B., Inácio, W.P., Bravo, J. and Portela, T.G., Selection of high strength natural fibers. *Revista Matéria*, 15(4), pp. 488-505, 2011. DOI: 10.1590/S1517-70762010000400002
- [2] Mora, W.J., Ramon, B.A. y Ramon, F., Desarrollo de materiales biocompuestos reforzados con fibras naturales colombianas. *Revista Ambiental. Agua, aire y suelo*, [online]. 4(2), pp. 1-7, 2013. Available at: http://revistas.unipamplona.edu.co/ojs_viceinves/index.php/RA/article/view/507
- [3] Omrani, E., Menezes, P.L. and Rohatgi, P.K., State of the art on tribological behavior of polymer matrix composites reinforced with natural fibers in the green materials world. *Engineering Science and Technology, an International Journal*, 19(2), pp. 717-736, 2016. DOI: 10.1016/j.jestech.2015.10.007
- [4] Gonzáles, C., Del Campo, J., Cardín, P., Fernández, J.O. y García, P., Relaciones composición-propiedades en materiales compuestos de matriz poliolefínica reforzados con fibras de celulosa, Congreso Nacional de Materiales Compuestos, (MATCOMP'03), Saragoza, España, [en línea]. 2003. Disponible en: <http://www.aemac.org/wp/wp-content/uploads/2015/05/MATCOMP03.pdf>
- [5] Banco Mundial, Emisiones de CO₂ (toneladas métricas per cápita), Centro de análisis de información sobre Dióxido de Carbono, División de Ciencias Ambientales del Laboratorio Nacional de Oak Ridge, Tennessee, Estados Unidos, [Online]. 2013. [Accessed: March 10th, 2017]. Available at: <http://datos.bancomundial.org/indicador/EN.ATM.CO2E.PC>
- [6] Nirmal, U., Hashim, J. and Megat-Ahmad, M.M.H., A review on tribological performance of natural fibre polymeric composites. *Tribology International*, 83, pp. 77-104, 2015. DOI: 10.1016/j.triboint.2014.11.003
- [7] Ku, H., Wang, H., Pattarachaiyakoo, N. and Trada, M., A review on the tensile properties of natural fibre reinforced polymer composites.

- Composites: Part B, 42(4), pp. 856-873, 2011. DOI: 10.1016/j.compositesb.2011.01.010
- [8] Jawaaid, M. and Abdul-Khalil, H.P.S., Cellulosic/synthetic fibre reinforced polymer hybrid composites: a review. *Carbohydrate Polymers*, 86(1), pp. 1-18, 2011. DOI: 10.1016/j.carbpol.2011.04.043
- [9] Osorio, L., Trujillo, E., Van Vuure, A.W. and Verpoest I., Morphological aspects and mechanical properties of single bamboo fibers and flexural characterization of bamboo/epoxy composites. *Journal of Reinforced Plastics & Composites*, 30(5), pp. 396-408, 2011. DOI: 10.1177/0731684410397683
- [10] Azwa, Z.N., Yousif B.F., Manalo, A.C. and Karunasena W., A review on the degradability of polymeric composites based on natural fibres. *Materials and Design*, 47, pp. 424-442, 2013. DOI: 10.1016/j.matdes.2012.11.025
- [11] Abdul-Khalil, H.P.S., Alwani, M.S., Islam, M.N., Suhaily, S.S., Dungani, R., H'ng, Y.M. and Jawaaid, M., The use of bamboo fibres as reinforcements in composites, in: Faruk, O. and Sain, M., Eds., *Biofiber Reinforcements in Composite Materials*, 2015, pp. 488-524. DOI: 10.1533/9781782421276.4.488
- [12] Li, H. and Shen, S., The mechanical properties of bamboo and vascular bundles. *Journal of Materials Research*, 26(21), pp. 2749-2756, 2011. DOI: 10.1557/jmr.2011.314
- [13] Zakikhani, P., Zahari, R., Sultan, M.T.H. and Majid, D.L., Extraction and preparation of bamboo fibre-reinforced composites. *Materials and Design*, 63, pp. 820-828, 2014. DOI: 10.1016/j.matdes.2014.06.058
- [14] Estrada, M. y Ramírez, F., Extracción y caracterización mecánica de las fibras de bambú (*Guadua Angustifolia*) para su uso potencial como refuerzo de materiales compuestos, Tesis MSc., Departamento de Ingeniería Civil y Ambiental, Universidad de los Andes, Bogotá, Colombia, 2010
- [15] Osorio, J., Vélez, J. and Ciro, H., Internal structure of *Guadua* and its incidence in the mechanical properties. *DYNA*, [Online].74(153), 2007. [Date of reference: October 20th, of 2017]. Available at: http://www.scielo.org.co/scielo.php?script=sci_arttext&pid=S0012-73532007000300009
- [16] George, M., Chae, M. and Bressler, D.C., Composite materials with bast fibres: structural, technical and environmental properties. *Progress in materials Science*, 83, pp. 1-23, 2016. DOI: 10.1016/j.pmatsci.2016.04.002
- [17] Estaciones Agrarias, Facultad de Ciencias Agrarias de la Universidad Nacional de Colombia, Medellín, Colombia, [Online] 2016. [Accessed: June 5th, 2017]. Available at: <https://cienciasagrarias.medellin.unal.edu.co/la-facultad/estaciones-agrarias.html>
- [18] American Society for Testing and Materials (ASTM). Standard test method for tensile properties of single textile fibers. D3822M-14. ASTM Annual Book of Standards. West Conshohocken, Pa, 2015.
- [19] American Society for Testing and Materials (ASTM). Standard practice for conditioning and testing textiles. D1776M-15. ASTM Annual Book of Standards. West Conshohocken, Pa, 2004.
- [20] Statgraphics net. [Online]. [Accessed: October 08th, 2016]. Available at: <http://www.statgraphics.net>
- [21] Andersons, J., Sparnins, E., Joffe, R. and Wallstrom, L., Strength distribution of elementary flax fibres. *Composites Science and Technology*, 65(3-4), pp. 693-702, 2005. DOI: 10.1016/j.compscitech.2004.10.001
- [22] Garcia, L., Radial and longitudinal variation of the mechanical properties of bamboo. Thesis, Department of Materials Science and Engineering, Massachusetts Institute of Technology, Massachusetts, U.S.A, 2011.
- [23] Faruk, O., Bledzki, A.K., Fink, H. and Sain, M., Biocomposites reinforced with natural fibers: 2000-2010. *Progress in Polymer Science*, 37(11), pp. 1552-1596, 2012. DOI: 10.1016/j.progpolymsci.2012.04.003
- [24] Muñoz, M.F., Hidalgo, M.A. y Mina, J.H., Fibras de fique una alternativa para el reforzamiento de plásticos. Influencia de la modificación superficial. *Bioteconología en el Sector Agropecuario y Agroindustrial*, [Online], 12(2), pp.60-70, 2014. [Date of reference: October 20th, 2017]. Available at: http://www.scielo.org.co/scielo.php?script=sci_abstract&pid=S1692-35612014000200007&lng=en&nrm=iso&tlng=es
- [25] Johar, N., Ahmad, I. and Dufresne, A., Extraction, preparation and characterization of cellulose fibres and nanocrystals from rice husk. *Industrial Crops and Products*, 37, pp. 93-99, 2012. DOI: 10.1016/j.indcrop.2011.12.016
- [26] Manalo, A., Wani, E., Zukarnain, N.A., Karunasena, W. and Lau, K., Effects of alkali treatment and elevated temperature on the mechanical properties of bamboo fibre-polyester composites. *Composites Part B: Engineering*, 80, pp. 73-83, 2015. DOI: 10.1016/j.compositesb.2015.05.033
- [27] Dittenber, D.B. and GangaRao, H.V.S., Critical review of recent publications on use of natural composites in infrastructure. *Composites Part A: applied science and manufacturing*, 43(8), pp. 1419-1429, 2012. DOI: 10.1016/j.compositesa.2011.11.019

L.J. Quintero-Giraldo, received the BSc. Eng in Chemical Engineering in 2013 from the Universidad Nacional de Colombia, Medellín, Colombia. She is MSc. in Engineering with emphasis in New Materials, in 2018 from the Universidad Pontificia Bolivariana, Colombia. From 2015 to 2018, she worked at the New Materials Research Group – GINUMA of the Universidad Pontificia Bolivariana, Colombia. Her research interests include: natural fibers, polymers (thermoplastics and thermosets), developing of polymeric composite materials reinforced with natural fibers, mechanical and thermal characterization of natural fibers and natural composite materials.
ORCID: 0000-0003-2611-9539

L.J. Cruz-Riaño, received the BSc. Eng in Mechanical Engineering in 1985 from the Universidad Pontificia Bolivariana, Colombia. PhD in Industrial Engineering in 2005 from the Polytechnic University of Madrid, Spain. Since 2010, Dr. Cruz is the academic coordinator of postgraduate courses in engineering, new materials area, and he is the manager of the New Materials Research Group – GINUMA of the Universidad Pontificia Bolivariana, Colombia. Besides, Dr. Cruz is a full professor at Mechanical Engineering Faculty of the Universidad Pontificia Bolivariana. His research interests include: materials selection, mechanics of materials, materials properties, processing and mechanics of composites materials.
ORCID: 0000-0001-7650-5441

J.A. García-Guzmán, received the BSc. Eng in Geological Engineering in 2004 from the Universidad Nacional de Colombia, Medellín. PhD degree in Engineering in 2018 from the Universidad Pontificia Bolivariana, Colombia; also is PhD degree in 2017 in Mechanical, Civil and Packaging Engineering from the Université de Reims Champagne-Ardenne, France. Currently, he is a Master (MED) student in Education topics from Universidad de Manizales, Colombia. Since 1999, Dr. García is associate professor at Mechanical Engineering Faculty of the Universidad Pontificia Bolivariana, Colombia. His research interests include: simulation, computational modeling, composite and ceramics materials, natural fibers and manufacturing process.
ORCID: 0000-0003-1650-1451

A. Alcaraz-Zapata, received the BSc. Eng in Mechanical Engineering in 2018 from the Universidad Pontificia Bolivariana, Colombia. Since 2015 to 2018, he was working as a researcher in the New Materials Research Group – GINUMA carrying out research projects related to the development and characterization of polymer matrix composite materials reinforced with natural fibers. Besides, he was focus on the analysis of fiber isolation techniques, the synthesis of the composite materials, surface treatments incorporation, the evaluation of industrial scale applications and the identification of statistical methods for the mechanical properties determination. In addition, Mr. Alcaraz worked in the operation and maintenance area at Empresas Públicas de Medellín - Colombia. Currently, he works as a Project Engineer at GALCO Company.
ORCID: 0000-0002-0166-2191.

E.S. González-Castrillón, received the BSc. Eng in Agricultural Engineering in 1992, from the Universidad Nacional de Colombia, Medellín, is Sp. in Environmental Legislation in 1996 from the Universidad Pontificia Bolivariana, Colombia, MSc. in Regional Urban Studies in 2001, from the Universidad Nacional de Colombia, Medellín, PhD degree in Territory, Environment and Society in 2009, from the Universidad Autónoma de Madrid, Spain. Since 1996, Dr. Gonzales is associate professor attached to

the Department of Agricultural Engineering and Food of the Universidad Nacional de Colombia, Medellin. She has been a manager in different academic and administrative positions. Her research interests include builds, developments and properties of the Guadua.

ORCID: 0000-0003-1101-1250

J.A. Osorio-Saraz, received the BSc. Eng in Agricultural Engineering in 1998, from the Universidad Nacional de Colombia, Medellin, is Sp. in Environmental Legislation in 2001 from the Universidad de Medellin, Colombia, MSc. degree in Materials Engineering in 2006 from the Universidad Nacional de Colombia, Medellin, PhD degree in Agricultural Engineering in 2010, from the Universidade Federal de Viçosa, Brazil. Since 2003 Dr. Osorio is professor at the Universidad Nacional de Colombia, Medellin, teaching and rural constructions, alternative materials, computational modeling for livestock housing, air quality and animal welfare.

ORCID: 0000-0002-4358-3600



UNIVERSIDAD NACIONAL DE COLOMBIA

SEDE MEDELLÍN
FACULTAD DE MINAS

Área Curricular de Ingeniería
Eléctrica e Ingeniería de Control

Oferta de Posgrados

Maestría en Ingeniería - Ingeniería Eléctrica
Maestría en Ingeniería - Automatización
industrial
Especialización en Eco-eficiencia Industrial

Mayor información:

E-mail: ingelcontro_med@unal.edu.co
Teléfono: (57-4) 425 52 64