



DYNA

ISSN: 0012-7353

ISSN: 2346-2183

Universidad Nacional de Colombia

Enriquez-Fuertes, Juliana P.; Molano, William A.; Guerrero-Duymovic, Alejandra I.;
Ramírez-Sanabria, Alfonso E.; Gaona-Jurado, Sonia; Villaquirán-Raigoza, Claudia F.

Synthesis, structural characterization and functional
properties of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{FexO}_6$ ceramic powders

DYNA, vol. 88, no. 218, 2021, July-September, pp. 95-100

Universidad Nacional de Colombia

DOI: <https://doi.org/10.7440/res64.2018.03>

Available in: <https://www.redalyc.org/articulo.oa?id=49671325012>

- How to cite
- Complete issue
- More information about this article
- Journal's webpage in redalyc.org

UNEN 

Scientific Information System Redalyc

Network of Scientific Journals from Latin America and the Caribbean, Spain and
Portugal

Project academic non-profit, developed under the open access initiative

Synthesis, structural characterization and functional properties of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ ceramic powders

Juliana P. Enriquez-Fuertes ^a, William A. Molano ^b, Alejandra I. Guerrero-Duymovic ^c, Alfonso E. Ramírez-Sanabria ^d, Sonia Gaona-Jurado ^c & Claudia F. Villaquirán-Raigoza ^c

^a Departamento de Física – Universidad del Cauca, Colombia. jpenriquez@unicauca.edu.co

^b Grupo de Computação Analógica e Sistemas Dinâmicos CASiD, Centro universitário do Distrito Federal, Distrito Federal Brazil. wallanmolano@gmail.com

^c Grupo de investigación en Ciencia y Tecnología de Materiales Cerámicos (CYTEMAC), Departamento de Física – Universidad del Cauca, Colombia. aiguerrero@unicauca.edu.co, sgaona@unicauca.edu.co, gure@unicauca.edu.co

^d Grupo de investigación Catálisis, Departamento de Química – Universidad del Cauca, Colombia. aramirez@unicauca.edu.co

Received: September 21th, 2020. Received in revised form: May 10th, 2021. Accepted: June 8th, 2021.

Abstract

$\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ (SBNF) ceramic powders for $x=0.00$, $x=0.02$ and $x=0.03$ were synthesized using coprecipitation method. The structure of the SBNF single phase with $x=0.02$ was identified by X-ray diffraction and Rietveld refinement; the morphology and size of the particles were observed by TEM and SEM-EDS microscopy. Electrical characterization showed that Fe doping did not cancel the typical ferroelectric relaxor behavior and magnetic characterization showed a weak ferromagnetic response, which suggest that the samples obtained can be considered as multiferroic.

Keywords: SBNF; coprecipitation method; ferroelectric relaxor; multiferroic.

Síntesis, caracterización estructural y propiedades funcionales de polvos cerámicos de $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$

Resumen

Se sintetizaron polvos cerámicos de $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ (SBNF) para $x=0.00$, $x=0.02$ y $x=0.03$ usando el método de coprecipitación. La estructura de la fase única SBNF con $x=0.02$ se identificó por difracción de rayos X y refinamiento de Rietveld; La morfología y el tamaño de las partículas se observaron mediante microscopía TEM y SEM-EDS. La caracterización eléctrica mostró que el dopaje con Fe no anuló el comportamiento típico del relajante ferroeléctrico y la caracterización magnética mostró una respuesta ferromagnética débil, lo que sugiere que las muestras obtenidas pueden considerarse como multiferroicas.


Palabras claves: SBNF; método coprecipitación; ferroeléctrico relaxor; Multiferroico.

1. Introduction

The $\text{Sr}_y\text{Ba}_{1-y}\text{Nb}_2\text{O}_6$ system was presented in 1960 by Francombe ^[1] as a ferroelectric material in the range of $0.25 < y < 0.75$, with a tetragonal tungsten-bronze (TTB) structure at room temperature. The compound has the form $[(\text{A}_1)_2(\text{A}_2)_4\text{C}_4][(\text{B}_1)_2(\text{B}_2)_8]\text{O}_{30}$ and consists of 10 ordered oxygen octahedrons, forming 3 types of interstitial places (A1, A2 and C) occupied by Sr^{2+} and Ba^{2+} cations ^[2]. The B1

and B2 sites, occupied by Nb, are located inside the octahedron. Researchers found that even if the SBN compound is a ferroelectric material, upon doping it with iron it acquires a ferromagnetic behavior, which does not cancel its ferroelectric behavior ^[3]. Therefore, the doping of SBN compound with iron results in the multiferroic property. Several methods have been proposed for the synthesis and processing of SBN ferroelectric ceramics, including solid-state synthesis, gel citrate, Pechini and controlled

How to cite: Enriquez-Fuertes, J.P., Molano, W.A., Guerrero-Duymovic, A.I., Ramírez-Sanabria, A.E., Gaona-Jurado, S. and Villaquirán-Raigoza, C.F., Synthesis, structural characterization and functional properties of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ ceramic powders. DYNA, 88(218), pp. 95-100, July - September, 2021.

© The author; licensee Universidad Nacional de Colombia. 
Revista DYNA, 88(218), pp. 95-100, July - September, 2021, ISSN 0012-7353
DOI: <https://doi.org/10.15446/dyna.v88n218.90662>

precipitation [4-10]. The controlled precipitation method is based on aqueous media reactions containing stoichiometric predetermined amounts of the precursors (salts). Additionally, Cho et al. [11,12] and Kshirsagar et al. [13] studied the effect of Fe doping on the ferroelectric and ferromagnetic properties of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ prepared by a solid-state reaction method. These groups reported that the synthesized materials maintained the bronze tungsten structure at low Fe values ($x = 0.03$). In addition, a multiferroic response was reported when $x = 0.03$. Few materials with multiferroic properties are known to date; therefore, it is relevant to carry out studies to synthesize these materials and characterize their properties. In this study, we synthesized and characterized $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ powders by the controlled coprecipitation method. Structural characterization showed monophasic powders and electrical and magnetic characterizations showed that Fe incorporation did not suppress the ferroelectric behavior of the samples and generated a ferromagnetic character, this indicates that a multiferroic material was obtained.

2. Experimental conditions

We obtained powders with a stoichiometry corresponding to $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_2\text{O}_6$ (SBN), $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ (SBNF2) and $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.97}\text{Fe}_{0.03}\text{O}_6$ (SBNF3). Strontium carbonate (SrCO_3 , Aldrich 99.9%), Barium carbonate (BaCO_3 , Mallinckrodt 99.9%), Iron II oxalate ($\text{FeC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$, Alfa Aesar 95%) and Niobium pentoxide (Nb_2O_5 , Aldrich 99.9%) were used as precursors. All precursors were previously dissolved one by one in 50 mL of an acidic aqueous solution (1.5 mL nitric acid). Niobium pentoxide was pre-mixed with water for 12 hours. A controlled potentiometric titration was performed on the final solution with a precipitating agent (ammonium hydroxide) to measure the pH as the volume of precipitating agent was added. Two stages were identified as the solution was saturated with the precipitating agent (Fig. 1): the solid phase nucleation and the nuclei growth, determined by the equivalence and saturation pH ($\text{pH}_{\text{eq}} = 7$ and $\text{pH}_{\text{sat}} = 10$, respectively).

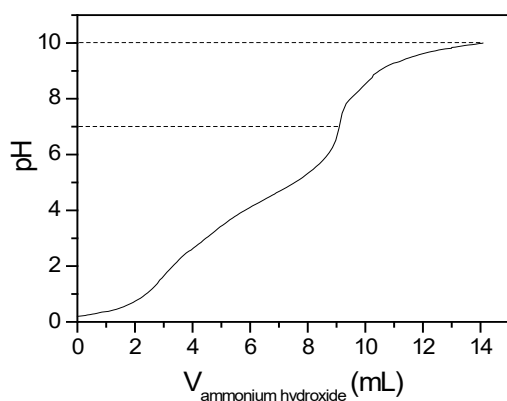


Figure 1. Potentiometric titration curve for $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_2\text{O}_6$. Dotted lines indicate the equivalence and saturation points. $\text{pH}_{\text{eq}}=7$, $\text{pH}_{\text{sat}}=10$. Source: The authors.

The solution was sonicated for 15 min, using an ultrasound equipment (frequency 20kHz) to destroy possible aggregates, dried, macerated to get a powder, and calcined at 1200°C for 4.5-h, and at 1300°C for 4.0-h. The analysis by X-ray diffraction (XRD) was performed using a PANalytical X'Pert Pro diffractometer in continuous mode using $\text{Cu K}\alpha$ (λ 1.5406 Å) with divergence slit width of 0.2 mm. XRD patterns were measured with a steps size of 0.02, time per step of 2.0 s, 2θ range of 20°-80° and analyzed according to diffractogram patterns for X'Pert HighScore Reference Patterns (Barium strontium niobium oxide): 00-039-0265. The morphological general aspect of the particles was observed by transmission electron microscopy (TEM, JEOL – 1200 EX) and scanning electron microscopy (SEM - SM7001 – F JEOL). Because Nb^{+5} and Fe^{+3} cations do not have the same valence, we tested if doping affected the conduction processes inside the material by characterizing the disk-shaped samples prepared at a pressure of 343.2 MPa and synthesized at 1200 °C for 4.5-h with and without doping. The relative permittivity was measured as a function of temperature using an impedance analyzer in the temperature range of 50° C – 300 °C. The measurements of magnetization vs. external magnetic field were obtained with a vibrating sample magnetometer (VSM) with a field in a range of -15 and 15 kOe, at 50 K.

3. Results and discussion

The Fig. 2 shows the XRD diffractogram for $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ samples with $x=0.00$, $x=0.02$ and $x=0.03$, treated at 1200 °C for 4.5-h, and $\text{pH}=7$. The $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_2\text{O}_6$ phase was obtained but the sample also contained Sr and Ba niobates, produced from previous reactions [14]. Upon iron addition, the intensity of the peaks corresponding to the secondary phases decreased. This effect was more noticeable in samples with doping $x=0.02$ and therefore, testing continued with this doping value.

Based on these results, we continued the process of obtaining $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ with the inclusion of a new parameter, the variation of the Sr/Ba stoichiometric ratio. This new parameter was introduced according to previous studies in which barium hexaferrites ($\text{BaFe}_{12}\text{O}_{19}$) were obtained with good results by varying the stoichiometric ratio Fe:Ba [15, 16]. The Figs. 3(a) and 3(b) show the XRD diffractograms to powders, at $T=1300^\circ\text{C}$, varying the Sr:Ba stoichiometric ratio for $\text{pH}=7$ (Fig. 3a) and $\text{pH}=10$ (Fig. 3b).

As observed, the production of monophasic powders depends on pH, since only at $\text{pH}=10$ and $\text{Sr/Ba}=0.5/0.55$ (Fig. 3b), the XRD patterns showed a single phase for $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$. The Fig. 4 shows the diffractogram with Rietveld refinement for the $\text{Sr/Ba}=0.5/0.55$. The Table 1 contains the parameters confirming the monophasic powders. The monophasic sample was obtained at lower temperature and less calcination time than reported by Köferstein [6].

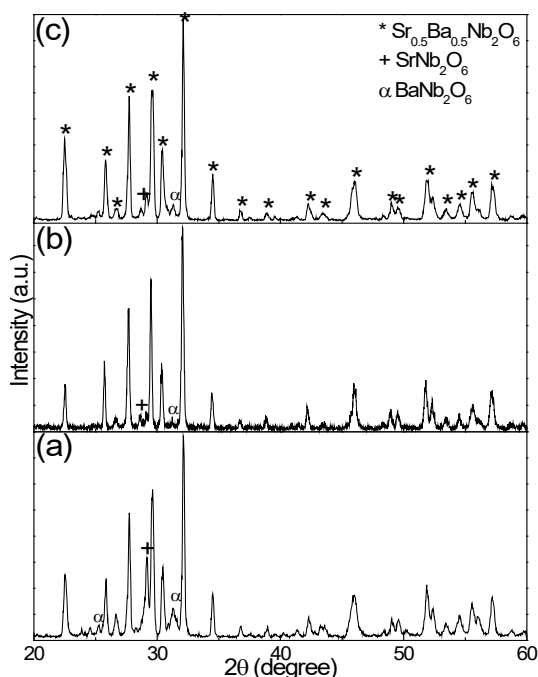


Figure 2. $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ diffractograms at (a) $x=0.00$, (b) $x=0.02$, (c) $x=0.03$.

Source: The authors.

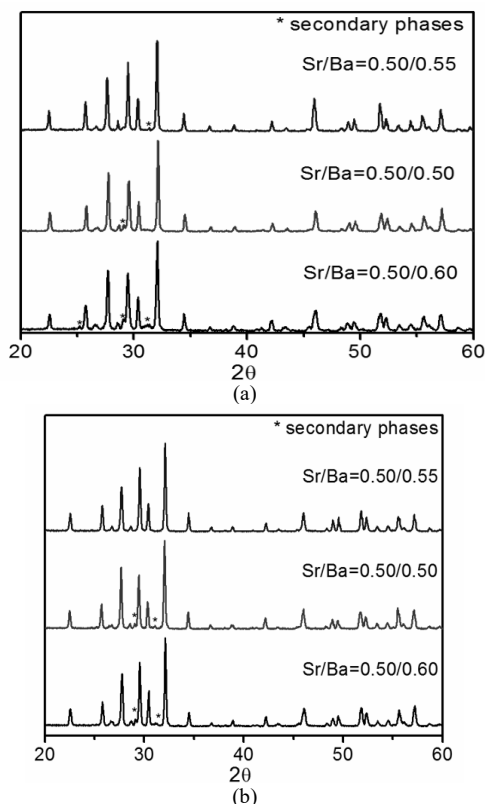


Figure 3. Diffractograms of ceramic powder $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ sample obtained by coprecipitation at $T=1300^\circ\text{C}$, with different Sr/Ba ratios and at (a) $\text{pH}=7$; (b) $\text{pH}=10$.

Source: The authors.

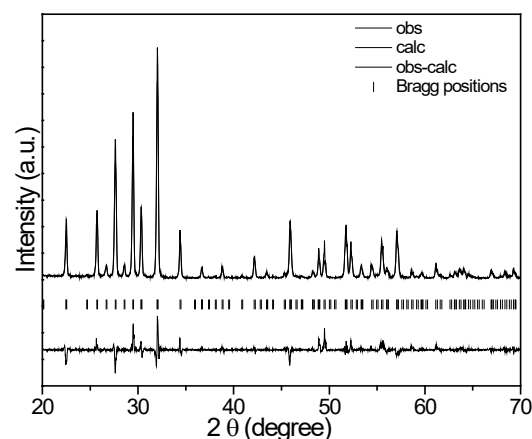


Figure 4. Diffractogram with Rietveld refinement for $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$. Diffractogram corresponds to $\text{Sr}/\text{Ba}=0.5/0.55$ in Fig. 3b.

Source: The authors

Table 1.

Rietveld refinement parameters for $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$.

Refined parameters		$\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$
Spatial group P4bm	a (Å)	12.490
	b (Å)	12.490
	c (Å)	3.953
Volume (Å ³)		616.64
Phase %		100
χ^2		2.29

Source: The authors.

The TEM micrograph for the $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ sample with $\text{Sr}/\text{Ba} = 0.5/0.55$ and $\text{pH}=10$ (Fig. 5) shows uniform morphology and particle size, with a round shape and size around 150 nm.

The EDS analysis was done in a particular area of the material and it required several measurements for acceptable statistics. Fig. 6 shows one of the SEM micrographs and its corresponding EDS analysis. The atomic percentage has the expected proportion of the constituent ions and presents a Ba excess which agrees with the excess used for the synthesis, $\text{Sr}/\text{Ba} = 0.5/0.55$.

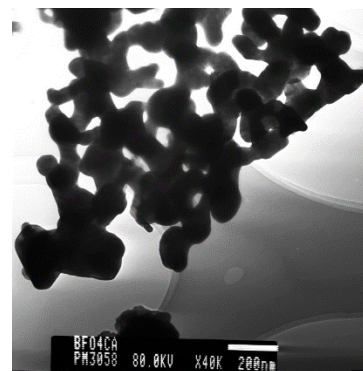


Figure 5. TEM micrographs of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ samples with $\text{Sr}/\text{Ba} = 0.5/0.55$, at $\text{pH}=10$, $T=1300^\circ\text{C}$.

Source: The authors.

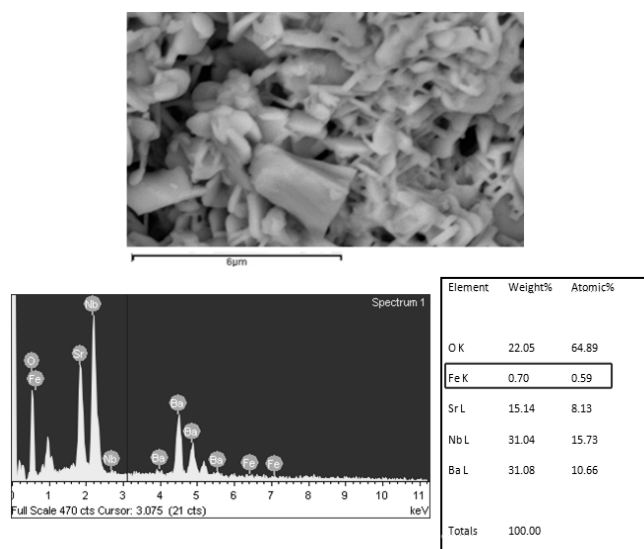


Figure 6. SEM micrograph and EDS spectrum of the $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ samples with $\text{Sr}/\text{Ba} = 0.5/0.55$, at $\text{pH}=10$, $T=1300^\circ\text{C}$. The percentage of Fe is highlighted in the box.

Source: The authors

To analyze the doping effect on the electrical response of the produced material, we measured the dependency of the dielectric constant with the temperature at 50 kHz. The variation of the dielectric permittivity with temperature at two different compositions is shown in Fig. 7a. A broad dielectric peak is observed, characteristic of the relaxor ferroelectric behavior of SBN [16,17]; the temperature of maximum dielectric constant (ϵ'_{max}) shifts to the right when Fe decreases: for $x=0.02$: $T_m=141.7^\circ\text{C}$ and for $x=0$: $T_m=174.0^\circ\text{C}$. This agrees with previous studies reported in the literature [11-13].

The ϵ'_{max} (dielectric constant at T_m) increases when iron doping increases. This is expected because iron introduction should generate new conducting processes, which can be confirmed by the response in the imaginary part of the relative permittivity (ϵ'') vs temperature (Fig. 7b). The imaginary part of the relative permittivity measures the samples conductive behavior, i.e., the smaller the imaginary permittivity values, the more dielectric the sample will be. ϵ'' increases when doping increases; the introduction of iron decreases the materials dielectric response, which can be observed in Fig. 7c, which represents the behavior of the loss tangent $\tan\delta$ for the Fe-doped systems. The Fig. 8 shows the behavior of the magnetization vs the external magnetic field taken at 50K for the sample $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$. Perhaps because of the low magnitude of maximum magnetization and high sensitivity of the VSM a noise may occur. The noise may also occur due to the fineness of the powder used for the test; nevertheless, even with the noise, a small coercivity field, close to 500 Oe is observed, characteristic of a ferromagnetic behavior [13]. The results indicate that iron doping did not inhibit the sample ferroelectric behavior and instead it gave it a ferromagnetic character. Therefore, we can say that the synthesized powders can be catalogued as multiferroic materials.

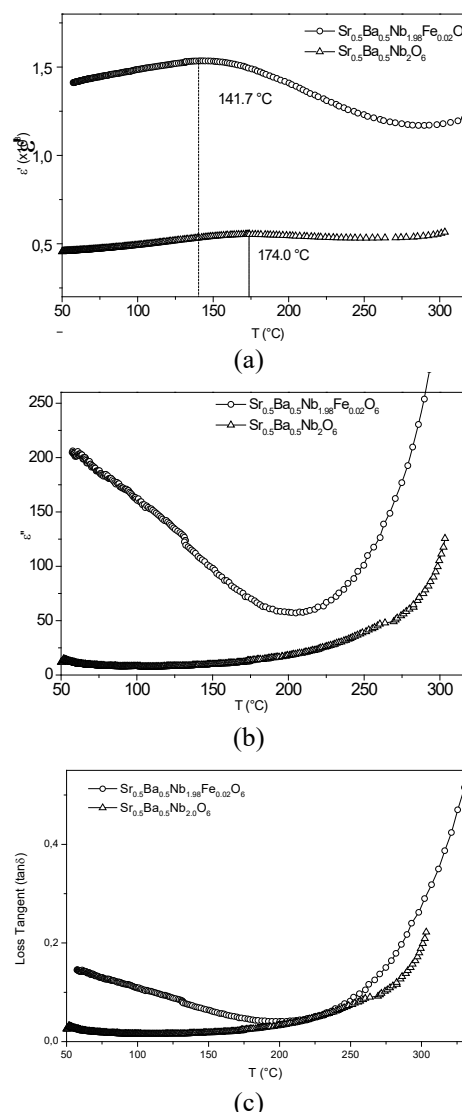


Figure 7. Real and imaginary electrical permittivity measurements and variation of loss tangent vs temperature taken at 50 kHz (a) Real permittivity ϵ' , (b) Imaginary permittivity ϵ'' , (c) loss tangent, $\tan\delta$

Source: The authors

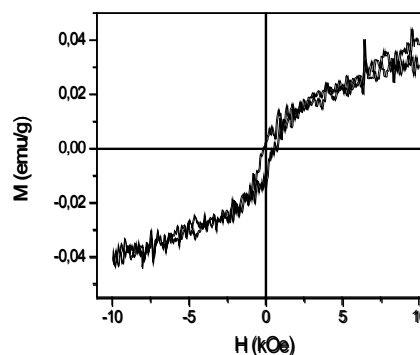


Figure 8. Magnetic hysteresis from $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ powders, $T = 50\text{ K}$.

Source: The authors.

4. Conclusions

Ceramic powders of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ were synthesized with the coprecipitation method, with stoichiometries corresponding to $x=0.00$, $x=0.03$, and $x=0.02$. According to the structural characterization by XRD, samples without doping showed significant presence of secondary phases, which were reduced by the addition of iron. To obtain powders of the $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{1.98}\text{Fe}_{0.02}\text{O}_6$ stoichiometry with single phase, it was necessary to vary the stoichiometry ratio Sr/Ba. A single phase was obtained for Sr/Ba = 0.5/0.55 ratio and was confirmed by Rietveld refinement. The powders showed particles with sizes around 150 nm and uniform morphology. The electrical characterizations showed a relaxor ferroelectric behavior, even for iron-containing samples, which suggests that iron does not change the ferroelectric nature of the system. The permittivity vs temperature graphs showed a shift in the temperature (174°C to 141.7°C) corresponding to the maximum permittivity, which suggests incorporation of iron into the structure. The magnetic measurements showed that iron inclusion gives a small magnetic character, resulting in a hysteresis cycle with a small coercivity field; this means the iron inclusion gives a multiferroic character to the samples.

Acknowledgements

The authors acknowledge the financial support from Universidad del Cauca.

References

- [1] Francombe, M.H. The relation between structure and ferroelectricity in lead barium and barium strontium niobates. *Acta Crystallographica*, 13, pp. 131-140, 1960. DOI 10.1107/S0365110X60000285.
 - [2] Chernaya, T.S., Marychev, M.O., Ivanov, V.A., Ivanov, N.J., Chuprunov, E.V., Ivleva, L.I. and Simonov, V.I., Structural conditionality for the quadratic nonlinear susceptibility of $\text{Sr}_{1-x}\text{Ba}_x\text{Nb}_2\text{O}_6$. *Crystals Crystallography Reports*, 52(6), pp. 1056-1060, 2007. DOI 10.1134/S106377450706020X.
 - [3] Jamieson, P.B., Abrahams, S.C. and Bernstein, J.L., Ferroelectric tungsten bronze type crystal structures. I. Barium Strontium Niobate $\text{Ba}_{0.27}\text{Sr}_{0.73}\text{Nb}_2\text{O}_6$. *The Journal of Chemical Physics*, 48(11), pp. 5048-5057, 1968. DOI 10.1063/1.1668176
 - [4] Kumar, S.N., Kumar, P. and Agrawal, D.K., Structural, dielectric and ferroelectric properties of SBN ceramics synthesized by microwave reactive sintering technique. *Ceramics International*, 38, pp. 5243-5250, 2012. DOI 10.1016/j.ceramint.2012.03.034.
 - [5] Hoyos, J.R., Botero, E.R., Garcia, D. and Kiminami, R.H.G.A., Simultaneous two-phase formation model in synthesized SBN/NFO using the in-situ modified Pechini method. *Ceramics International*, 45, pp. 8593-8599, 2019. DOI 10.1016/j.ceramint.2019.01.178
 - [6] Köferstein, R., Oehler, F. and Ebbinghaus, S.G., Investigations of nano-crystalline $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_2\text{O}_6$ and bulk ceramics synthesized by a polymerization method using PEG400. *Journal of the European Ceramic Society*, 39(4), pp. 1156-1163, 2019. DOI 10.1016/j.jeurceramsoc.2018.11.043
 - [7] Pasricha R. and Ravi, V., Synthesis of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_2\text{O}_6$ by citrate gel method. *Materials Chemistry and Physics*, 94(1), pp. 34-36, 2005. DOI 10.1016/j.matchemphys.2005.04.003.
 - [8] Melo, M., Araujo, E.B., Turygin, A.P., Shur, V.Ya. and Kholkin A.L., Physical properties of strontium barium niobate thin films prepared by polymeric chemical method. *Ferroelectrics*, 496(1), pp. 177-186, 2016. DOI 10.1080/00150193.2016.1155035.
 - [9] Patro, P.K., Kulkarni, A.R., Gupta, S.M. and Harendranath, C.S., Effect of homogeneity on microstructure, dielectric, and ferroelectric properties of strontium barium niobate. *Defence Science Journal*, 57(1), pp. 79-87, 2007. DOI 10.14429/dsj.57.1733.
 - [10] Chen W., Kume S., Duran C. and Watari, K., Preparation of single crystalline $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_2\text{O}_6$ particles. *Journal of the European Ceramic Society*, 26, pp. 647-653, 2006. DOI 10.1016/j.jeurceramsoc.2005.06.010.
 - [11] Cho, S.Y. and Jang M.S., Effect of Fe doping on ferroelectric and ferromagnetic properties of $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ ceramics. *Journal of the Korean Physical Society*, 49, pp. S667-S670, 2006.
 - [12] Kim J.S., Cho, S.Y. and Jang M.S., Ferroelectric and relaxor behavior of Fe-Doped $\text{Sr}_{0.5}\text{Ba}_{0.5}\text{Nb}_{2-x}\text{Fe}_x\text{O}_6$ ceramics with a Tungsten-Bronze structure. *Journal of the Korean Physical Society*, 51(2), pp. 692-696, 2007.
 - [13] Kshirsagar S.H., Jigajeni S.R., Tarale A.N., Salunkhe D.J. and Joshi P.B., Investigations on Fe-doped strontium barium niobate, single phase ferroelectric and magnetodielectric compounds. *Journal of Advanced Dielectrics*, 5(1), art. 1550001, 2015. DOI 10.1142/S2010135X15500010.
 - [14] Gaona, S., Muñoz J.R., Raigoza C.F.V., Ramírez, A. y Caneiro, A., Influencia de parámetros de síntesis sobre las características de los polvos cerámicos nanométricos del compuesto $\text{Sr}_x\text{Ba}_{1-x}\text{Nb}_2\text{O}_6$ (SBN). *Boletín de la Sociedad Española de Cerámica y Vidrio*, 52(6), pp. 291-295, 2013. DOI 10.3989/cyv.362013.
 - [15] Sandoval, D.M., Gaona, J.S. and Caneiro, A., Síntesis y caracterización de hexaferrita de bario por el método de combustión. *Revista Latinoamericana de Metalurgia y Materiales*, 28(1), pp. 29-37, 2008.
 - [16] Jieun, K., Takenaka, H., Qi, Y., Damodaran, A.R., Fernandez, A., Gao, R., McCarter, M.R., Saremi, S., Chung, L., Rappe, A.M. and Martin, L.W. Epitaxial strain control of relaxor ferroelectric phase evolution. *Advanced Materials*, art. 1901060 (pp. 1-10), 2019. DOI 10.1002/adma.201901060.
 - [17] Cheng, Z.-Y., Katiyar, R.S., Yao, X. and Bhalla, A.S., Temperature dependence of the dielectric constant of relaxor ferroelectrics. *Physical Review B*, 57(14), pp. 8166-8177, 1998. DOI 10.1103/PhysRevB.57.8166.
- J.P. Enriquez-Fuertes**, received a BsSc. Eng in Physics Engineering in 2011 from the Universidad del Cauca, Colombia; Currently, she is a Master's student in Environmental science and since 2014, she works at Universidad del Cauca in the Physics Department. Her research interests include: Environmental science and Material science.
ORCID: 0000-0003-1917-1769
- W.A. Molano**, received a BSc. Eng in Physics Engineering in 2010 and a MSc. in Mechatronic in 2016 from the Universidade de Brasilia, Brazil; Currently, he is a PhD. student in Mechatronic and since 2011 he works at Centro Universitário do Distrito Federal, Distrito Federal Brazil. His research interests include: mechatronic, dynamic systems and computation science.
ORCID: 0000-0002-4901-1822.
- A.I. Guerrero-Duymovic**, received a BSc. Eng in Physics Engineering in 2007 from the Universidad del Cauca, Colombia; a MSc. in Physics 2010 from the Universidade Federal de Pernambuco, Brazil and a PhD. in Physics in 2015 from the Universidad Federal de Rio Grande Do Sul, Brazil. Since 2016, she works at Universidad del Cauca in the Physics Department. Her research interests include: material science, using model and statistical mechanics.
ORCID 0000-0001-5582-8807.
- A.E. Ramírez-Sanabria**, received his BSc. Biology and Chemistry Education in 1993, a MSc. in 1998 and a PhD. in Applied Chemistry in 2007. He is a full professor in Chemistry department, Universidad del Cauca since 1999. His research interests include: catalysis and materials.
ORCID: 0000-0002-7557-4047
- S. Gaona-Jurado**, received a BSc. in Physics in 1991 from the Universidad del Valle, Colombia; a MSc. in Physics 1994, and a PhD. in Physics in 1998

from the Universidade Federal de Minas Gerais, Brazil. Since 1999, she works at Universidad del Cauca, currently, she is a full professor in the Physics Department. Her research interests include: material science, multiferroic materials and ceramic materials.

ORCID: 0000-0001-7297-6326

C.F. Villaquirán-Raigoza, received a BSc. in Physics in 1992 from the Universidad del Valle, Colombia; a MSc. in Physics in 2002 from the Universidad de Oriente, Venezuela and a PhD. in Physics in 2008 from the Universidade Federal de Sao Carlos, Brazil. Since 1998, she works at Universidad del Cauca, currently, she is a full professor in the Physics Department. Her research interests include: material science, multiferroic materials and ceramic materials.

ORCID: 0000-0003-0037-534X