



DYNA

ISSN: 0012-7353

ISSN: 2346-2183

Universidad Nacional de Colombia

Ramos-Maldonado, Fabian; Hernández-Montoya, Isabel; Rojas-Reyes, Néstor
Rheological modeling of cellulose gum, xanthan gum, and guar gum mixtures in aqueous solutions
DYNA, vol. 90, no. 229, 2023, October-December, pp. 66-74
Universidad Nacional de Colombia

DOI: <https://doi.org/10.15446/dyna.v90n229.109644>

Available in: <https://www.redalyc.org/articulo.oa?id=49677793004>

- ▶ [How to cite](#)
- ▶ [Complete issue](#)
- ▶ [More information about this article](#)
- ▶ [Journal's webpage in redalyc.org](#)

UNAM 

Scientific Information System Redalyc

Network of Scientific Journals from Latin America and the Caribbean, Spain and Portugal

Project academic non-profit, developed under the open access initiative

Rheological modeling of cellulose gum, xanthan gum, and guar gum mixtures in aqueous solutions

Fabian Ramos-Maldonado ^a, Isabel Hernández-Montoya ^b & Néstor Rojas-Reyes ^c

^a Universidad Nacional de Colombia, sede Medellín, Facultad de Minas, Departamento de Materiales y Minerales, Medellín, Colombia. flramosmal@unal.edu.co

^b Universidad Nacional de Colombia, sede Medellín, Facultad de Minas, Departamento de Procesos y Energía, Medellín, Colombia. maihernandezmo@unal.edu.co

^c Universidad Nacional de Colombia, sede Medellín, Facultad de Minas, Instituto de Minerales CIMEX, Medellín, Colombia. nrrojasr@unal.edu.co

Received: June 21th, 2023. Received in revised form: August 30th, 2023. Accepted: September 29th, 2023.

Abstract

The synergistic effects observed in hydrocolloid mixtures hold significant potential for the discovery of new industrial products and compounds. Through an examination of the rheological behavior of mixtures of cellulose gum, xanthan gum, and guar gum, synergistic viscosity patterns were observed in binary mixtures. Notably, the viscosity of these mixtures exceeded that of the individual components. Binary and ternary systems with high elasticity and minimal temporal variation exhibited low levels of thixotropy and demonstrated stable elastic modulus values across various frequencies. Ternary mixtures containing a high proportion of xanthan gum exhibit enhanced stability in response to temperature fluctuations. This underscores the potential of hydrocolloid mixtures to yield novel functionalities by capitalizing on the distinct rheological behaviors arising from their interactions.

Keywords: synergy; ternary gum mixture; viscoelasticity.

Modelamiento reológico de mezclas de goma de celulosa, goma xantana y goma guar en soluciones acuosas

Resumen

El efecto sinérgico entre las mezclas de hidrocoloides es de gran interés, puesto que se pueden encontrar nuevos productos y compuestos de uso industrial. Mediante el estudio del comportamiento reológico de mezclas de goma de celulosa, goma xantana y goma guar se encontraron comportamientos sinérgicos de viscosidad en mezclas binarias, observando que el valor de la viscosidad de las mezclas es mayor a la viscosidad de los componentes individuales. Se encontraron sistemas binarios y ternarios con alto comportamiento elástico y menor variación en el tiempo, con bajos valores de tixotropía y estabilidad del módulo elástico a diferentes frecuencias. Las mezclas ternarias con altos contenidos de goma xantana presentan un comportamiento más estable frente a cambios de temperatura. Se evidencia que la mezcla de hidrocoloides es una posibilidad de obtención de nuevas funcionalidades a partir de las diferencias en el comportamiento reológico dado por la interacción entre ellas.

Palabras clave: sinergia; mezcla ternaria de gomas; viscoelasticidad.

1. Introduction

Cellulose gum (CG), xanthan gum (XG) and guar gum (GG) are hydrophilic polysaccharides, also called hydrocolloids, used in various industries as stabilizers and rheology modifiers with appealing properties for different uses [1]. Hydrocolloids used in food applications exhibit a viscoelastic rheological behavior. This behavior arises from

the chemical structures of hydrocolloids, which form dispersions in aqueous mediums, allowing them to resist strain as evidenced in solids. However, when the stress applied exceeds the elastic resistance threshold, the material transitions into a flowing state, exhibiting characteristics of a viscous liquid [2]. During this flow phase, hydrocolloid dispersions conform to non-Newtonian shear-thinning fluid behavior. When hydrocolloids are combined to form a

How to cite: Ramos-Maldonado, F., Maldonado, Isabel Hernández-Montoya, I., and Rojas-Reyes, N., Rheological modeling of cellulose gum, xanthan gum, and guar gum mixtures in aqueous solutions. DYNA, 90(229), pp. 66-74, October - December, 2023.

solution in aqueous media, the gum structures interact with each other, leading to alterations in viscoelastic behavior (formation of gels or high-viscosity solutions). Importantly, the changes in shearing often do not follow a proportional pattern in the mixture, but instead lead to an amplification of specific effects. This phenomenon is commonly referred to as a synergistic effect [3].

CG, also known as sodium carboxymethyl cellulose, is a polysaccharide consisting of cellulosic structures linked by an ether group to an ionic carboxylic radical, which is produced by the reaction of cellulose with sodium hydroxide (generating the basic form of cellulose) and subsequently reacting with chloroacetic acid [4]. CG is derived from cellulose and is widely used due to its solubility in water, which imparts it with the characteristic properties of being a hydrocolloid, making it valuable as a thickening agent, viscosifier, suspension agent, stabilizer, and film former. It can be used in detergents, food, textiles, paints and inks, glues, pharmaceuticals, cosmetics, ceramics, paper, and in the oil industry, among others [5]. For its use in the food industry, manufactured CG has a minimum degree of purity of 99.5%, with impurities being those of sodium chloride and sodium glycolate. Cellulose gum is used in dressings and sauces, honeys and syrups, ice cream and creams, diet foods, ready-to-drink beverages, powdered drinks, and bakery and confectionery products, among others. XG is an extracellular hydrophilic anionic polysaccharide of high molecular weight produced by several species of *Xanthomonas*, with *Xanthomonas Xampestris B-1459* as the bacterium commercially used for its synthesis [6,7]. The backbone of the polysaccharide chain is composed of β -D-glucose units linked through the first and fourth positions. In the third position of the main chain, trisaccharide chains consisting of two mannose groups and a glucuronic acid are alternately linked. Around half of the terminal mannose units have a pyruvic acid group attached to their fourth and sixth positions. The mannose units attached to the main chain have an acetyl group at the sixth position [3]. XG is a non-gelling biopolymer formed in aqueous media with an ordered rigid chain formation; it is highly soluble both in hot and cold water and can form high viscosity solutions, even at low concentrations [8]. Due to its temperature and pH stability, it is widely accepted in the industry [9]. XG aqueous solutions undergo a conformational transition with increasing temperature, which is associated with a change from a rigid and ordered structure to a more flexible and disordered structure at high temperatures. This conformational change was first noticed by the sigmoidal variation of viscosity with temperature [8]. CG is obtained from the seed endosperm of *Cyamopsis tetragonolobus*, a plant belonging to the legume family that grows in arid or semi-arid areas of India, Pakistan and specific areas of Texas and Arkansas [10]. GG is a polysaccharide consisting of a straight chain of mannose units linked on the sides with single galactose units at a 2:1 ratio (mannose:galactose) [11]. An important property of GG is its ability to hydrate quickly in cold water and to produce highly viscous solutions. The viscosity GG imparts to a solution depends on various factors including time, temperature, concentration, pH, ionic strength, and the type of agitation [2,3,11].

The synergistic properties arising from hydrocolloid mixtures hold great promise for the development of new products and compounds for various industrial applications, characterized by their ability to exhibit high viscosities and enhanced stability under diverse operating conditions [1,9]. These conditions may encompass saline, acidic, or alkaline environments, with varying concentrations of solids, and a range of usage temperatures, among other factors. For some industrial applications, the CG produced in the Colombian industry lacks the necessary properties to serve as a suitable rheological additive in food applications such as powdered soft drinks, industrially processed fruit drinks, sauces, dairy products, bakery products, and some non-food applications such as coatings or paints used in construction or even drilling fluids for the oil industry. This is primarily attributed to the requirement of attaining precise viscosity levels and specific rheological behavior within specified dosage limits. For instance, in some food applications, such as sauces and dairy products, there are restrictions on the maximum allowable dosage of hydrocolloids [12] and CG may not be the sole product capable of meeting the expected performance. To address this limitation, other hydrocolloids are used, including XG and GG, are employed to contribute to the application of the desired effect sought with rheological additives. In most cases, particularly in the above-mentioned applications, a combination of the gum options gum mixtures are used, rather than relying on a single gum product alone.

An analysis of research related to hydrocolloid synergies, such as natural gums, thickeners, and rheology conformers, reveals studies exploring synergistic interactions among various components, including GG, CG, carob bean gum, alginates, and pectin, under specific conditions [9,13-15]. However, there is little research on Colombian-produced CG mixtures. Thus, from a technical and economic standpoint, the study of hydrocolloid mixtures is of great interest, since it can offer information about the rheological properties of individual products and their applications. This can provide insights into how to reduce costs by using less active material per component, especially with high-cost gums that are difficult to obtain. Similarly, given the numerous applications where gums serve as thickeners and stabilizers in different temperature-dependent media [16], this study is of great utility in examining rheological behavior across various aqueous medium conditions.

2. Materials and Methods

2.1 Materials

The following raw materials were used in this study: cellulose gum (CG) commercial brand Gelycel® of Amtex S.A. produced in Colombia; xanthan gum (XG) produced in China by Deosen Biochemical Ltd.; and guar gum (GG) produced in India by Durga Enterprises.

2.2 Gum characterization

To assess the conformity and initial characteristics of CG, XG, and GG, the hydrocolloids were analyzed for the

following physicochemical parameters: moisture content, purity, Brookfield LV viscosity, and pH in solution at 1%.

2.3 Gum preparation

To prepare the samples prior to dissolution, specific amounts of each gum were weighed according to the proportion of the mixture, totaling 50g in weight. Subsequently, 500 g of distilled water was added to each sample and stirred until complete dissolution, ensuring that the temperature did not exceed 25°C. After complete dissolution, stirring is stopped, and the sample is left to settle for one minute. This process yielded three single-component mixtures, twelve binary composition mixtures, and six ternary composition mixtures, as indicated in Table 1.

2.4 Rheological analysis

Regarding gum characterization, viscosity determination was carried out using a Brookfield LV rheometer following the manufacturer's recommended parameters [17] and in accordance with the ASTM D-1439 standard [18].

Anton Paar MCR-301® rheometer with denominated geometry CP-50 1° with 50 mm in diameter and 1° with the following conditions depending on the type of analysis:

Flow curve: Flow curve experiments were conducted within a shear rate range of 0.1 and 100 s⁻¹ in 300 s, and at a temperature of 25°C. The rheometer software provides the shear rate, the shear stress, and the apparent viscosity. Experimental flow curves were fitted using two models: the Cross model given by Eq. (1):

$$\frac{\eta - \eta_{\infty}}{\eta_0 - \eta_{\infty}} = \frac{1}{1 + [K_{Cr}\dot{\gamma}]^m} \quad (1)$$

Dynamic rheological tests were performed using an where η is the apparent viscosity; η_0 is the Newtonian viscosity measured at low shear rates; η_{∞} is the Newtonian

Table 1. Compositions of the mixtures evaluated (in mass fraction)

Mix number	CG	XG	GG
1	0.00	1.00	0.00
2	0.00	0.00	1.00
3	1.00	0.00	0.00
4	0.33	0.33	0.33
5	0.00	0.60	0.40
6	0.40	0.00	0.60
7	0.60	0.40	0.00
8	0.20	0.20	0.60
9	0.20	0.80	0.00
10	0.20	0.00	0.80
11	0.80	0.20	0.00
12	0.60	0.00	0.40
13	0.00	0.40	0.60
14	0.00	0.80	0.20
15	0.00	0.20	0.80
16	0.20	0.60	0.20
17	0.40	0.60	0.00
18	0.80	0.00	0.20
19	0.60	0.20	0.20
20	0.40	0.20	0.40
21	0.40	0.40	0.20

Source: the authors.

viscosity measured at high shear rates; K_{Cr} is the Cross model constant (measured in time units); and m is a dimensionless constant. The second model is the power law model given by Eq. (2):

$$\eta = \frac{\tau}{\dot{\gamma}} = K\dot{\gamma}^{n-1} \quad (2)$$

where η is the apparent viscosity; τ the shear stress; $\dot{\gamma}$ the shear rate; K the coefficient of consistency, and n the flow performance index ($n-1 < 0$ corresponds to a shear-thinning behavior, $n-1 > 0$ corresponds to a shear-thickening behavior, and $n = 1$ corresponds to a Newtonian behavior).

Thixotropy curve: Thixotropy curves were generated at a constant temperature of 25°C involving a sequence of shear rate variations: an ascending shear rate slope of 1 to 100 s⁻¹ over 300 s, a constant rate of 100 s⁻¹ for 300 s, and a descending slope from 100 to 1 s⁻¹ over 300 s. Using the rheometer software, graph depicting the relationship between shear stress and shear rate was used to calculate both the area of the upward curve and the area of hysteresis.

Oscillatory tests: The amplitude sweep was conducted at 25°C, covering a strain range (γ) from 0.05 to 1000%, and a constant frequency (f) of 1 Hz. The frequency sweep was conducted at 25°C at a frequency range (f) from 100 to 1 Hz and a constant strain (γ) of 0.5%. The temperature sweep was conducted within a range from 10 to 70°C (3°C/min) and at a constant strain and frequency of 0.5% and 10 Hz, respectively. The rheometer software yielded the elastic modulus (G'), the viscous modulus (G''), the phase angle (δ), and complex viscosity (η^*).

The dependence of viscosity and, in general, of the rheological parameters on temperature was determined by modeling using the Arrhenius Eq. (3) [2,19]:

$$B = Ae^{\left(\frac{Ea}{RT}\right)} \quad (3)$$

where A is the pre-exponential factor, Ea is the activation energy (J·mol⁻¹), R is the universal gas constant (J·mol⁻¹·K⁻¹), and T is the absolute temperature (°K) [20]. The parameter B can be any rheological parameter of interest to be analyzed as a function of temperature, such as the dynamic viscosity when performing rotational tests [21], complex viscosity or the elastic, viscous, or complex moduli resulting from oscillatory tests.

2.5 Experimental design and statistical analysis

Experimental analysis followed a simplex-lattice mixture design of 3 components (CG, XG, and GG), of order 5 and with central points, resulting in 21 points as shown in Table 1.

Data analysis for the respective mixture designs was carried out using Minitab® software with the Design of Experiments (DOE) tool, within the mixture design section. The computational model selected to analyze the response variables (viscosity, thixotropy, elastic modulus, viscous modulus, phase angle, and complex viscosity) in the different mixture designs employed a full cubic order model (see Eq.

(4)). This approach enables the design to be adjusted to a first, second, or third order model allowing the modeling of extreme response changes as the proportion of one or more components approaches its limit [22]:

$$E(y) = \sum_{i=1}^q \beta_i x_i + \sum_{i<j} \sum_{j=2}^q \beta_{ij} x_i x_j + \sum_{i<j} \sum_{i<k} \sum_{k=3}^q \beta_{ijk} x_i x_j x_k \quad (4)$$

where $E(y)$ is the expected or adjusted value of the response variable according to experimental data, β corresponds to the adjustment factors of the model, and x_i , x_j and x_k correspond to the compositions or mass fractions of the gums [23]. The type of model selected is adjusted to a 0.95 level of confidence and verified by the correlation coefficient R^2 for each case.

Furthermore, non-linear regression analysis was performed using a statistical tool. This involved inputting the model equation, and the software automatically calculated the constants within the equation, generated data balancing graphics, and determined the standard error (S) of the model regression with a 95% confidence level.

3. Results and discussion

3.1 Gum characterization

Table 2 shows the main properties of each gum used in the study. The purity of CG falls within the parameters suitable for use in food according to the US FDA guidelines, which establish a minimum purity of 99.5% [24]. XG and GG also meet the specifications suitable for consumption in food applications according to FAO parameters, which specify a minimum purity for XG of 91% [25] and for GG of at least 80% [26].

Table 2. Physicochemical analysis of gum.

Parameter	Gum		
	CG	XG	GG
Moisture [%]	6.6	10.6	10.5
Purity or Gum Content [%]	99.7	91.5*	84.2*
Brookfield Viscosity LV, 25°C, [mPa·s]	5060	2924	6280
pH, 1% solution	7.20	6.91	5.80

* Data obtained from the manufacturer's certificate of analysis. Source: the authors.

3.2 Rheological analysis

3.2.1 Apparent viscosity

The apparent viscosity behavior (measured with the Brookfield LV at 30 rpm) for the CG – XG – GG system mixtures is illustrated in Figure 1 across 3 stages: immediate (0 h), at 4 hours, and at 24 hours at rest.

Notably, the highest system viscosities (dark green) are found in the binary interactions CG-GG at a 20:80 ratio, reaching viscosity values above 8000 mPa·s without variation over time. The synergistic interaction of high viscosity between CG-GG is maintained up to ratios of 40:60. Beyond this composition with an increased proportion of CG, viscosity decreases.

The Brookfield viscosity model at 30 rpm and 0 hours is presented in Eq. (5) as a function of the gum compositions, and it exhibits a coefficient of determination R^2 of 0.971.

$$\eta_{ap} [mPa \cdot s] = 5096x_{CG} + 3277x_{XG} + 6382x_{GG} - 7419x_{CG}x_{XG} + 9600x_{CG}x_{GG} + 5707x_{XG}x_{GG} + 6582x_{CG}x_{XG}x_{GG} \quad (5)$$

3.2.2 Viscosity model

The observed unphysical values may be attributed to the software used for nonlinear regression, potentially leading to biased fits or local minima rather than global minima [27]. As indicated in Table 3, the power law model exhibits lower error variances, making it the most suitable choice for compositions where XG and GG are predominant, and CG is present in smaller proportions. This behavior is probably due to the high pseudoplasticity of the system generated by the synergies between XG and GG. In such mixtures, the flow performance index n in the power law model tends to be below 0.40, indicating a rapid decrease in viscosity with minor changes in shear rate. This evinces high pseudoplasticity, indicating the absence of a Newtonian region at low shear rates and rendering the Cross model unsuitable for said compositions. Numerically, it is apparent that the viscosity value at near-zero shear rates (η_0) in the Cross model tends to be high and while viscosity to high shear rates (η_∞) tends to small or even negative. Fig. 2 illustrates the data points analyzed within the experimental design and showcases the viscosity model that best aligns with the different compositions.

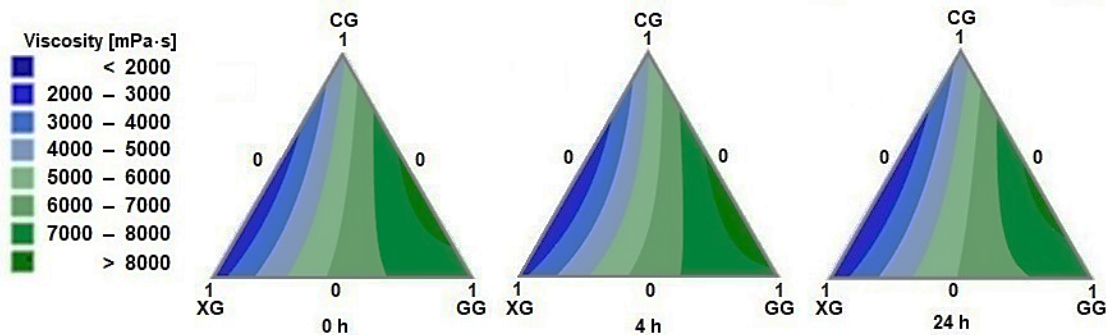


Figure 1. Contour plots for viscosity, CG: cellulose gum, XG: xanthan gum and GG: guar gum. Source: the authors.

Table 3. Parameters of the mixtures according to the Cross Model and Power Law Model.

Mixture No.	Cross				Power law			
	η_0 [Pa·s]	η_∞ [Pa·s]	K_{Cr} [Pa·sm]	m [Adim]	Standard error (S) [Pa·s]	K [Pa·sn]	n [Adim]	Standard error (S) [Pa·s]
1	*	*	*	0.000	-	14.04	0.181	0.2947
2	49.53	0.045	1.96	0.807	0.0982	15.25	0.556	1.8972
3	19.43	0.063	1.20	0.689	0.0589	7.86	0.652	0.8829
4	108.91	0.005	5.73	0.792	0.1828	15.99	0.426	1.3437
5	*	*	*	0.154	-	20.92	0.224	0.4082
6	77.88	0.192	2.43	0.803	0.1590	21.25	0.533	2.4244
7	13.24	*	1.91	0.603	-	4.17	0.630	0.3611
8	*	*	*	0.755	-	32.37	0.373	2.7273
9	*	18.05	0.784	-0.037	-	9.26	0.257	0.2952
10	86.79	0.543	2.47	0.881	0.3169	23.83	0.515	2.9783
11	14.97	0.024	1.37	0.654	0.0452	5.68	0.648	0.5828
12	53.90	0.168	2.12	0.772	0.1299	16.00	0.561	1.7908
13	*	*	*	0.218	-	26.11	0.325	1.8033
14	*	*	*	0.159	-	20.72	0.210	0.5925
15	*	*	*	0.194	-	28.48	0.381	1.9545
16	*	*	*	0.107	-	11.29	0.351	1.0578
17	30.46	*	7.27	0.545	-	3.53	0.539	0.1506
18	34.10	0.119	1.71	0.735	0.0794	11.43	0.598	1.2685
19	37.93	0.478	2.05	0.885	0.1668	11.78	0.545	1.4771
20	92.36	0.550	3.16	0.943	0.2566	21.93	0.465	2.8086
21	38.93	0.326	3.13	0.847	0.1775	9.28	0.499	0.9826

* Values unphysical. Source: the authors.

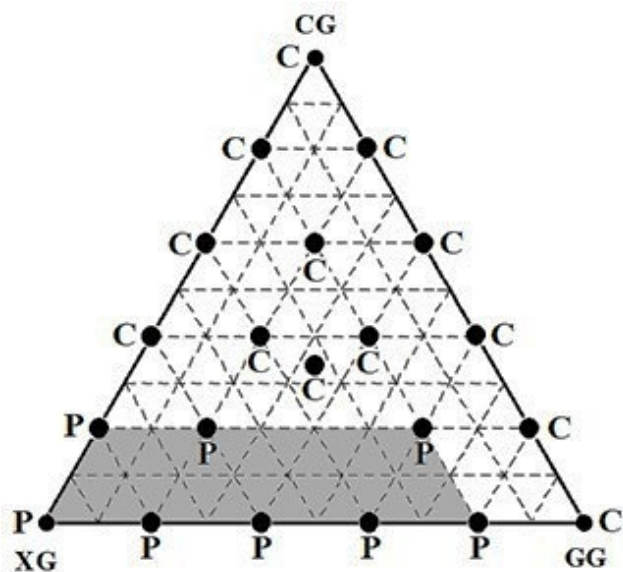


Figure 2. Viscosity model with the best adjustment to mixture points. C: points modeled with the Cross Equation; P: points modeled with the Power Law Equation. Source: the authors.

3.2.1 Thixotropic behavior

The thixotropy percentage in the ternary system CG – XG – GG was calculated by measuring the hysteresis between the ascent curve and the descent curve for each prepared mixture. The adjustment model was created with the thixotropy data within the ternary composition diagram (Fig. 3). It is evident that GG is the component that primarily influences

thixotropic behavior. As the ternary system contains a higher proportion of a specific gum, the synergy in terms of thixotropy percentage is amplified. Thixotropic behavior can also be observed in binary mixtures of CG and CG, which present thixotropies between 5 and 6%.

The equation that links thixotropy (T [%]) as a function of the gum compositions with a correlation coefficient R² of 0.931 is shown in Eq. (6).

$$T [\%] = 0.61x_{CG} + 0.58x_{XG} + 4.36x_{GG} + 16.8x_{CG}x_{XG} - 7.9x_{CG}x_{GG} + 2.3x_{XG}x_{GG} - 140x_{CG}^2x_{XG}x_{GG} - 403x_{CG}x_{XG}^2x_{GG} + 690x_{CG}x_{XG}x_{GG}^2 \quad (6)$$

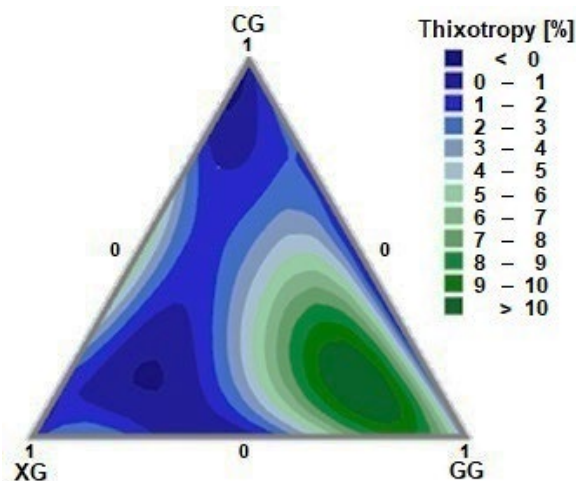


Figure 3. Thixotropy of the ternary system; CG: cellulose gum, XG: xanthan gum and GG: guar gum. Source: the authors.

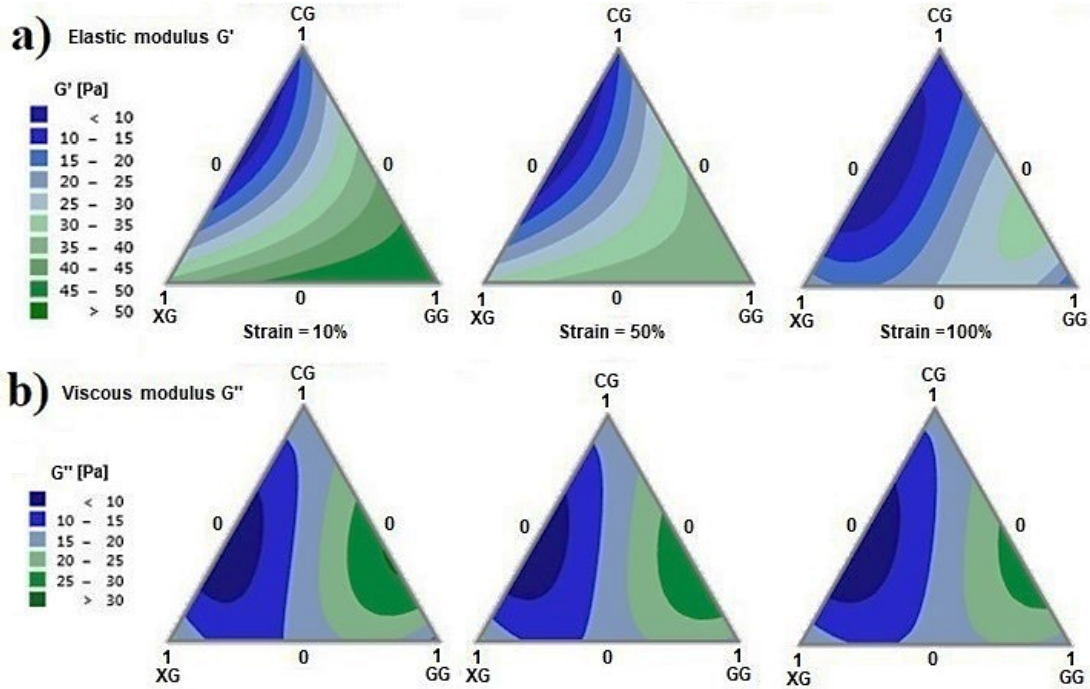


Figure 4. Plots of dynamic moduli of CG–XG–GG ternary mixtures at three strains (10, 50 and 100%). a) Elastic modulus (G'); b) Viscous modulus (G''). Source: the authors.

3.2.1 Viscoelastic behavior

The viscoelastic behavior, as determined through oscillatory rheology, reveals two important phenomena that merit identification: a) At very low strain levels, it becomes possible to discern the type of structure within the ternary system CG – XG – GG. This helps elucidate the behavior of the internal structure comprising the gum system in aqueous solutions. b) Oscillatory measurements help to assess the stability of the formation of the internal structure over time. In the former case, the internal structure exhibits either elastic solid or viscous fluid behavior, which can be observed through oscillatory amplitude tests. In the latter case, where the stability of viscoelastic structures over time is assessed in mixtures, the characteristics of the internal structure are determined through frequency tests [28,29].

3.2.4.1 Oscillatory Amplitude Tests

Amplitude tests enable the characterization of the elastic modulus (G') and the viscous modulus (G'') of the ternary system. Row a) in Fig. 4 illustrates the behavior of G' at a strain of 10% (located within the viscoelastic linear region), 50% (elastic solid to viscous fluid transition region) and 100% (strain at which most mixtures are in the melt flow region). High values of G' with a greater presence of GG, medium values of G' with a greater presence of XG, and low values of G' with a greater presence of CG are all obtained at low strain values. As the strain increases (50 and 100%), the values of G' decrease. At a high strain, the largest G' is obtained with the binary mixture GG-CG. Row b) in Fig. 4 shows the behavior of G'' for strains at 10, 50, and 100%. The gum mixtures that evince high values of G'' are found in binary mixtures of GG-CG, and low values of G'' are found in binary mixtures of XG-CG. Values of G'' remain

unaffected by the increase in strain.

Furthermore, the relationship between G' and G'' can be established through the phase angle defined as $\tan \delta = G''/G'$. Fig. 5 shows the phase angle (δ) of the viscoelastic linear region (10% strain) for the fabricated mixtures. The areas with the lowest phase angles correspond to those areas where behavioral dominance is more rigid (blue regions); this is mainly due to the presence of XG. Whereas the region with phase angles of around 45° (dark green areas) correspond to the mixture systems where behavior tends to be more fluid; that is, with a predominance of CG in the mixture. Generally, the ternary mixtures of these gums behave as viscous fluids ($G'' > G'$).

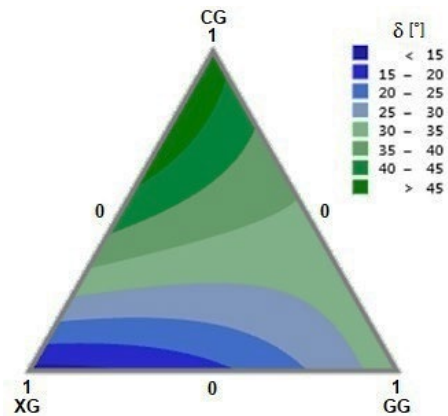


Figure 5. Plot of phase angle at the viscoelastic limit (VEL) of CG–XG–GG ternary mixtures at 10% strain. Source: the authors.

The phase angle adjustment model (δ) in relation to the composition of the ternary system is shown in Eq. (7) with a correlation coefficient R^2 of 0.958.

$$\delta [^\circ] = 47.9x_{CG} + 13.2x_{XG} + 33.3x_{GG} + 49.3x_{CG}x_{XG} - 24.8x_{CG}x_{GG} - 19.0x_{XG}x_{GG} \quad (7)$$

3.2.4.2 Oscillatory Frequency Tests

Frequency tests are used to determine the stability of the suspension with respect to its structural conformation in certain time periods. High frequencies will indicate stability in short time periods, whereas low frequencies will correspond to longer time periods. Fig. 6 a) shows the values of G' in the ternary diagram CG–XG–GG for a frequency sweep of 10, 1, and 0.1 Hz. As we can see, G' is modified in different magnitudes depending on the composition of the gum mixtures. In general, G' diminishes as the frequency also decreases. This indicates that, in large time intervals, the system exposed to constant strain tends to flow. Nevertheless, the mixture intervals that showed higher values of G' in the amplitude tests are the ones that now show the greatest variations in G' as frequency decreases.

In contrast, binary mixtures of XG and CG with lower values of G' at high frequencies resist variations as the frequency decreases. This is evident, for example, in mixtures with a high GG content, where G' is high, but where there is an accelerated decrease as frequency diminishes, indicating that material rigidity is unstable over long time periods. Mixtures with a high XG content have low G' , but a decrease in frequency has a small impact on them, which is why these systems are more stable over time.

Fig. 6 b) shows the gum mixtures that are affected to a greater or lesser extent over time with respect to viscoelastic

behavior; that is, the phase angle (δ). In general, the presence of XG affects the suspension by providing a more solid structure over a long time period (high frequencies).

3.2.4.3 Oscillatory Temperature Tests

The effect of temperature on the behavior of the ternary system CG-XG-GG can be described by the evolution of G' depending on the temperature (Fig. 7). The regions with lower G' values comprise regions of the binary mixture CG-XG, while the regions with higher G' values correspond to the mixture CG-GG. It is also noted that the gum mixtures with higher G' values are more sensitive to an increase in temperature. Although the G' value describes the rigidity of the material, a complex viscosity analysis can also appropriately describe the relationship between the elastic and viscous component. Complex viscosity is a term describing the response to oscillatory shear stress and associates the elastic and viscous components of the structure in terms of dynamic viscosity.

By analyzing the system using complex viscosity and applying the Arrhenius equation, we obtain the activation energy for each mixture point. Fig. 8 shows the activation energy values for each mixture point. Mixtures with a high XG content have regions with low activation energies (dark blue); and mixtures with high CG and GG contents have regions with high activation energies (dark green). Low activation energies are associated with a lower sensitivity of the analyzed rheological property (in this case, complex viscosity) with respect to temperature [20]. On the other hand, high activation energies indicate more rapid changes in viscosity [30].

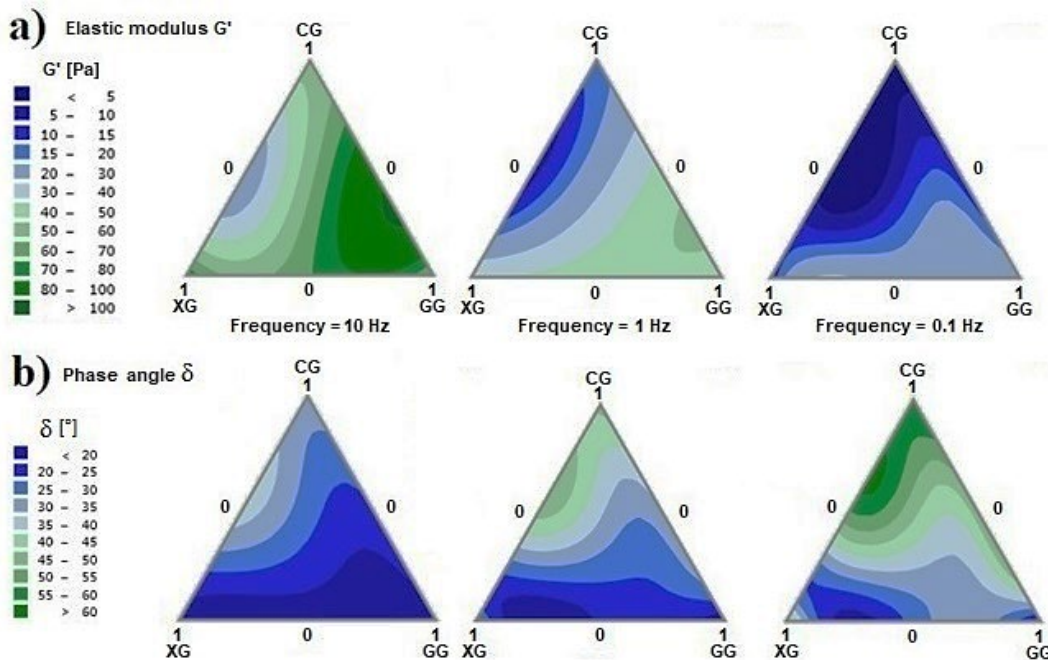


Figure 6. Plots of dynamic moduli of CG–XG–GG ternary mixtures at three frequencies (10, 1 and 0.1 Hz). a) Elastic modulus (G'); b) Phase angle (δ). Source: the authors.

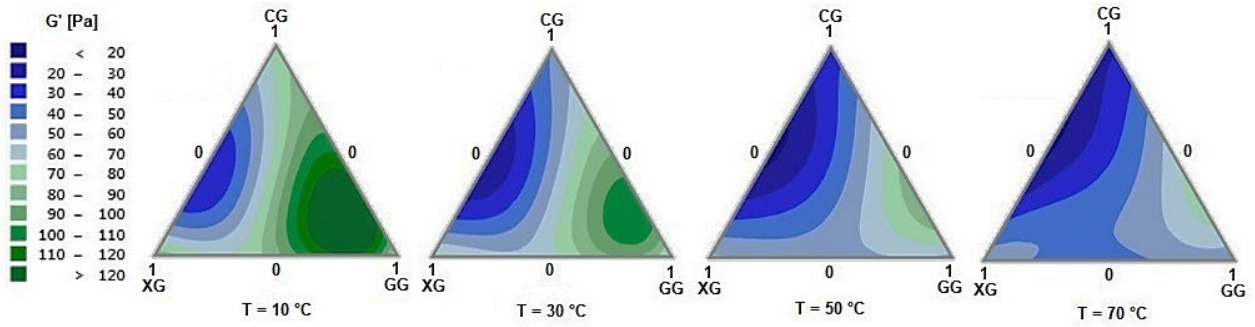


Figure 7. Plots of elastic moduli of CG–XG–GG ternary mixtures at different temperatures (10, 30, 50, and 70°C). Source: the authors.

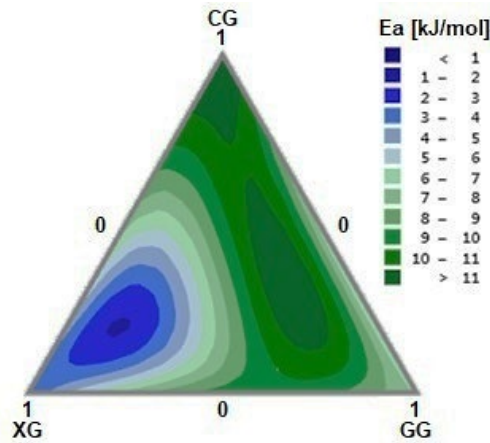


Figure 8. Plots of activation energy of CG–XG–GG ternary mixtures. Source: the authors.

By looking at the combined results of Fig. 7 and 8, it is evident that at a lower value of the modulus G' , the gum mixture improves temperature stability. A more solid behavior requires more energy for molecules to move, but once mobilized, it loses its structure and becomes more viscous with small temperature changes. The observation that XG exhibits lower activation energy values compared to GG and CG aligns with the findings in [19], who reports that the higher the pseudoplastic behavior, the lower the temperature dependency. Mixtures of CG-GG are highly temperature sensitive. By incorporating XG into a mixture, more resistant suspensions can be manufactured, such as the mixtures CG-XG that are stable to temperature changes but have low elasticity.

The model for activation energy adjustment as a function of system compositions is shown in Eq. (8) with a correlation coefficient R^2 of 0.929.

$$Ea \left[\frac{kJ}{mol} \right] = 12.90x_{CG} + 2.97x_{XG} + 6.87x_{GG} - 1.65x_{CG}x_{XG} - 14.15x_{CG}x_{GG} + 18.31x_{XG}x_{GG} + 169x_{CG}^2x_{XG}x_{GG} - 513x_{CG}x_{XG}^2x_{GG} + 377x_{CG}x_{XG}x_{GG}^2 \quad (8)$$

1. Conclusions

In general, synergistic behaviors have been observed in XG-GG and CG-GG systems, noting that the viscosity value

and different rheological parameters, such as shear behavior (pseudoplasticity), in time (thixotropy), and the viscoelastic phenomena of the mixtures is different from the results obtained with the individual components. A direct relationship was found between the results of the Brookfield viscosity and the consistency value (K) of the power law model. For the ternary system CG–XG–GG, pseudoplastic fluid behavior occurs with flow rates (n) greater than 0.60, as well as systems with high pseudoplasticity with flow rates lower than 0.20. It is concluded that the rheological Cross model is a better fit for systems with flow rates greater than 0.40, while the power law model presents the best fit for the experimental flow curves in systems with flow rates lower than 0.40.

With respect to dynamic rheology, binary XG-GG (maximum 50% XG) and ternary (maximum 50% XG and CG greater than 20%) systems have regions with higher elastic behavior that correspond with regions where rheological behavior is less affected over time, with low thixotropy values and stability of the elastic modulus G' at different frequencies. This can be used to manufacture ternary mixtures with high consistency and low pseudoplasticity. Ternary mixtures with high XG contents are more stable against temperature changes, which is reflected in lower activation energy values.

References

- [1] Yaseen, E., Herald, T., Aramouni, F. and Alavi, S., Rheological properties of selected gum solutions. *Food Research International*, 38, pp. 111-119, 2005. DOI: <https://doi.org/10.1016/j.foodres.2004.01.013>.6/j.hydromet.2018.05.022
- [2] Lapasin, R. and Priel, S., *Rheology of Industrial Polysaccharides: Theory and Applications*, Glasgow: Blackie Academic and Professional. Springer New York, 1995. DOI: <https://doi.org/10.1007/978-1-4615-2185-3>
- [3] Philips, G. and Williams, P., *Handbook of Hydrocolloids*. Cambridge: Woodhead Publishing, CRP Press [Online]. 2009. Available at: <https://www.sciencedirect.com/book/9781845694142/handbook-of-hydrocolloids>
- [4] Haleema, N., Arshada, M., Shahidb, M. and Tahir, M.A., Synthesis of carboxymethyl cellulose from waste of cotton ginning industry. *Carbohydrate Polymers*, 113, pp. 249-255, 2014. DOI: <http://dx.doi.org/10.1016/j.carbpol.2014.07.023>
- [5] Salmi, T., Damlin, P., Mikkola, J.P. and Kangas, M., Modelling and experimental verification of cellulose substitution kinetics. *Chemical Engineering Science*, 66(2), pp. 171-182, 2011. <https://doi.org/10.1016/j.ces.2010.10.013>

- [6] Katzbauer, B., Properties and applications of xanthan gum. *Polymer Degradation and Stability*, 59(1-3) pp. 81-84, 1998. DOI: [https://doi.org/10.1016/S0141-3910\(97\)00180-8](https://doi.org/10.1016/S0141-3910(97)00180-8)
- [7] Song, K., Kim, Y. and Chang, G., Rheology of concentrated xanthan gum solutions: steady shear flow behavior. *Fibers and Polymers*, 7(2), pp. 129-138, 2006. DOI: <https://doi.org/10.1007/BF02908257>
- [8] Jeanes, A., Pittsley, J. and Senti, F., Polysaccharide B-1459: A new hydrocolloid polyelectrolyte produced from glucose by bacterial fermentation. *Journal of Applied Polymer Science*, 5(17), pp. 519-526, 1961. DOI: <https://doi.org/10.1002/app.1961.070051704>
- [9] Tipvarakarnkoon, T. and Senge, B., Rheological behaviour of gum solutions and their interactions after mixing. *Annual Transactions of the Nordic Rheology Society* [Online]. 16, pp. 1-8, 2008. Available at: <https://nordicrheology.org/Content/Transactions/2008/Oral%20presentations/Rheology%20of%20Food%20Hydrocolloids/Tipvarakarnkoon.pdf>
- [10] Nikaedo, P., Amaral, F. and Penna, A.L., Caracterização tecnológica de sobremesas lácteas achocolatadas cremosas elaboradas com concentrado protéico de soro e misturas de gomas carragena e guar. *Revista Brasileira de Ciências Farmacêuticas*, 40(3), pp. 397-404, 2004. DOI: <https://doi.org/10.1590/S1516-93322004000300016>
- [11] BeMiller, J., *Carbohydrate Chemistry for Food Scientists*. Woodhead Publishing and AACC International Press, 2019. DOI: <https://doi.org/10.1016/C2016-0-01960-5>
- [12] Ospina, K., Estudio de la interacción de hidrocoloides empleados en alimentos y su efecto en las propiedades reológicas y de textura sensorial e instrumental. Bogotá: Universidad Nacional de Colombia, Tesis de Maestría [Online]. 2016. Available at: <https://repositorio.unal.edu.co/handle/unal/59273>
- [13] Ospina, M., Sepúlveda, J., Restrepo, D., Cabrera, K. and Suarez, H., Influencia de goma xantán y goma guar sobre las propiedades reológicas de leche saborizada con cocoa. *Biotecnología en el Sector Agropecuario y Agroindustrial* [Online]. 10(1), pp. 51-59, 2012. Available at: http://www.scielo.org.co/scielo.php?script=sci_arttext&pid=S1692-35612012000100007
- [14] Gómez, D. and Navaza, J., Rheology of aqueous solutions of food additives: Effect of concentration, temperature and blending. *Journal of Food Engineering*, 56(4), pp. 387-392, 2003. DOI: [https://doi.org/10.1016/S0260-8774\(02\)00211-X](https://doi.org/10.1016/S0260-8774(02)00211-X)
- [15] Hayati, I., Ching, C. and Helmi, M., Flow properties of o/w emulsions as affected by xanthan gum, guar gum and carboxymethyl cellulose interactions studied by a mixture regression modelling. *Food Hydrocolloids*, 53, pp. 199-208, 2016. DOI: <https://doi.org/10.1016/j.foodhyd.2015.04.032>
- [16] Fagioli, L., Pavoni, L., Logrippo, S., Pelucchini, C., Rampoldi, L., Cespi, M., Bonacina, G. and Casettari, L., Linear viscoelastic properties of selected polysaccharide gums as function of concentration, pH, and temperature. *Journal of Food Science*, 84(1), pp. 65-72, 2018. DOI: <https://doi.org/10.1111/1750-3841.14407>
- [17] Brookfield Engineering Laboratories Inc., More solutions to sticky problems. Middleboro, MA: Brookfield [Online]. 2017. Available at: <https://www.brookfieldengineering.com/-/media/ametekbrookfield/tech%20sheets/more%20solutions%202017.pdf?la=en>
- [18] ASTM International, D1439-15: Standard Test Methods for sodium carboxymethylcellulose. West Conshohocken: ASTM [Online]. 2015. Available at: <https://celluloseether.com/wp-content/uploads/2018/04/ASTM-D1439-03.pdf>
- [19] Razavi, S.M.A. and Irani, M., *Rheology of Food Gum. Bioactive Molecules in Food. Reference Series in Phytochemistry*, Springer, Cham, 2019. DOI: https://doi.org/10.1007/978-3-319-78030-6_20
- [20] Razavi, S., *Emerging Natural Hydrocolloids: Rheology and Functions*. John Wiley & Sons, Inc. [Online]. 1, 2019. Available at: <https://www.wiley.com/en-us/Emerging+Natural+Hydrocolloids%3A+Rheology+and+Functions-p-9781119418542>
- [21] Moraes, I., Fasolin, L., Cunha, R. and Menegalli, F., Dynamic and steady-shear rheological properties of xanthan and guar gums dispersed in yellow passion fruit pulps. *Brazilian Journal of Chemical Engineering*, 28(3), pp. 483-494, 2011. DOI: <https://doi.org/10.1590/S0104-66322011000300014>
- [22] Minitab® Support. Models, the terms that they fit, and the type of blending that they model. Minitab® Support [Online]. 2020. Available at: <https://support.minitab.com/en-us/minitab/20/help-and-how-to/statistical-modeling/doc/supporting-topics/mixture-designs/models-terms-and-blending/>
- [23] Montgomery, D.C., *Design and analysis of experiments*. John Wiley & Sons, Inc. [Online]. 8, 2005. Available at: <https://mip.faperta.unri.ac.id/file/bahanajar/58219-2013-8ed-Montgomery-Design-and-Analysis-of-Experiments.pdf>
- [24] U.S. Food and Drugs Administration. Code of Federal Regulations Title 21: 21CFR182.1745 [Online]. 2019. Available at: <https://www.accessdata.fda.gov/scripts/cdrh/cfdocs/cfcfr/CFRSearch.cfm?fr=182.1745>
- [25] Food and Agriculture Organization of the United Nations. Xanthan Gum [Online]. 1999. Available at: http://www.fao.org/fileadmin/user_upload/jecfa_additives/docs/Monograph1/Additive-487.pdf
- [26] Food and Agriculture Organization of the United Nations. Guar Gum, chemical and technical assessment [Online]. 2008. Available at: http://www.fao.org/fileadmin/templates/agns/pdf/jecfa/cta/69/Guar_gum.pdf
- [27] Escudier, M.P., Gouldson, I.W., Pereira, A.S., Pinho, F.T. and Poole, R.J., On the reproducibility of the rheology of shear-thinning liquids. *Journal of Non-Newtonian Fluid Mechanics*, 97(2-3), pp. 99-124, 2001. DOI: [https://doi.org/10.1016/S0377-0257\(00\)00178-6](https://doi.org/10.1016/S0377-0257(00)00178-6)
- [28] Choi, S.J., Chun, S.Y. and Yoo, B., Dynamic rheological comparison of selected gum solutions. *Food Science and Biotechnology* [Online]. 15(3), pp. 474-477, 2006. Available at: <https://koreascience.kr/article/JAKO200609905843557.pdf>
- [29] Gunasekaran, S. and Ak, M.M., Dynamic oscillatory shear testing of foods selected applications. *Trends in Food Science & Technology*, 11, pp. 115-127, 2000. DOI: [https://doi.org/10.1016/S0924-2244\(00\)00058-3](https://doi.org/10.1016/S0924-2244(00)00058-3)
- [30] Miao, Q., Jiang, H., Gao, L., Cheng, Y., Xu, J., Fu, X. and Gao, X., Rheological properties of five plant gums. *American Journal of Analytical Chemistry*, 9, pp. 210-223, 2018. DOI: <https://doi.org/10.4236/ajac.2018>

F. Ramos-Maldonado, holds a BSc. Eng. in Chemical Engineering, completed a postgraduate course in Business Management, and earned an MSc. in Engineering with a specialization in Materials and Processes from Universidad Nacional de Colombia. He currently serves as the R&D coordinator at Amtex. His research focuses on the rheology characterization of materials, with a particular expertise in hydrocolloids and cellulose derivatives, and their applications in various industries, including food, paints, coatings, and other related products.
ORCID: 0000-0002-3464-4395

I. Hernández-Montoya, holds a BSc. Eng. in Chemical Engineering from Universidad Nacional de Colombia. She has also completed a diploma course in analytical quality control and validation of physicochemical methods from the same university. Isabel has gained valuable experience as a researcher in the GIEM group at Universidad de Antioquia and currently serves as the R&D leader at Amtex. Her research interests encompass rheology characterization of materials, the development of innovative products and analytical methods, and the scale-up of industrial processes.
ORCID: 0000-0002-4591-4653

N. Rojas-Reyes, holds a BSc. Eng. in Metallurgy Engineering from Universidad Pedagógica y Tecnológica de Colombia. He earned his MSc. in Sciences of Engineering with a specialization in Extractive Metallurgy from the Universidad de Concepción in Chile and completed his DSc. in Engineering Sciences with a focus on Materials Science at Universidad Nacional de Colombia. He currently serves as a full professor at the Universidad Nacional de Colombia, Medellín Campus, and is a researcher at the Mineral Institute CIMEX. His research interests encompass the characterization of minerals, hydrometallurgy of precious metals, recovery of metals from waste materials, and rheology of mineral suspensions.
ORCID: 0000-0002-1644-471X.