



Revista UIS Ingenierías
ISSN: 1657-4583
ISSN: 2145-8456
revistaingenierias@uis.edu.co
Universidad Industrial de Santander
Colombia

Comparative study of the mechanical and vibratory properties of a composite reinforced with fique fibers versus a composite with E-glass fibers

Gómez, Sergio; Ramón, Bladimir; Guzman, Rolando

Comparative study of the mechanical and vibratory properties of a composite reinforced with fique fibers versus a composite with E-glass fibers

Revista UIS Ingenierías, vol. 17, no. 1, 2018

Universidad Industrial de Santander, Colombia

Available in: <http://www.redalyc.org/articulo.oa?id=553756967005>

Esta obra está bajo una Licencia Creative Commons Atribución-SinDerivar 4.0 Internacional.

Comparative study of the mechanical and vibratory properties of a composite reinforced with fique fibers versus a composite with E-glass fibers

Estudio comparativo de las propiedades mecánicas y vibratorias de un material compuesto reforzado con fibras de fique frente a un compuesto con fibras de vidrio-E

Sergio Gómez
Universidad Pontificia Bolivariana, Colombia
 sergio.gomez@upb.edu.co

Redalyc: <http://www.redalyc.org/articulo.oa?id=553756967005>

Bladimir Ramón
Universidad de Pamplona, Colombia
 hbladimir@unipamplona.edu.co

Rolando Guzman
Universidad Pontificia Bolivariana, Colombia
 rolando.guzman@upb.edu.co

Received: 12 February 2017

Accepted: 27 July 2017

ABSTRACT:

In the following research, the mechanical and dynamic vibratory properties between a fique fiber reinforced composite and a composite with E-glass fibers were compared. The materials were fabricated through a vacuum infusion manufacturing technique using a bioepoxy resin. The mechanical properties were obtained by tensile tests according to the ASTM standards for each configuration. The results demonstrated higher values in stiffness and strength for the composite with E-glass fiber. Experimental modal analysis was used for the dynamic vibrational study, obtaining very similar behaviors for each material. The interface between the materials was studied by scanning electron microscopy, in which a low adhesion between the natural fiber and the resin was evidenced; affecting the mechanical and dynamic properties of the fique composite compared to the E-glass composite.

KEYWORDS: Modal Analysis, composite, fique, E-glass, scanning electron microscopy, tensile test.

RESUMEN:

En la presente investigación se compararon las propiedades vibratorias mecánicas y dinámicas entre un compuesto reforzado con fibras y un compuesto con fibras de vidrio - E. Los materiales se fabricaron a través de una técnica de fabricación de infusión al vacío utilizando una resina bioepoxi. Las propiedades mecánicas se obtuvieron por ensayos de tracción según las normas ASTM para cada configuración. Los resultados demostraron valores más altos en rigidez y resistencia para el compuesto con fibra de vidrio - E. Se utilizó el análisis modal experimental para el estudio vibratorio dinámico, obteniendo conductas muy similares para cada material. La interfaz entre los materiales se estudió mediante microscopía electrónica de barrido, en la que se evidenció una baja adhesión entre la fibra natural y la resina; que afecta las propiedades mecánicas y dinámicas del compuesto fique en comparación con el compuesto de vidrio - E.

PALABRAS CLAVE: Análisis modal, compuesto, fique, vidrio - E, microscopía electrónica de barrido, ensayo de tracción.

1. INTRODUCTION

Synthetic fiber-reinforced composites, such as fiberglass, have played a major role in the manufacture of products over the last century. In some cases, synthetic fiber reinforced composites have replaced conventional materials due to their low density, high rigidity, easy installation, resistance to fatigue and environmental agents [1].

However, due to the oil prices variability and an increasing ecological awareness for the natural resources conservation, a new trend has been initiated using reinforced composite materials with natural fibers [2], [3].

Diverse natural fibers have been used for the composite manufacture, such as: jute [4], [5], sisal [6], [7], kenaf [8], [9] y el fique [10], [11].

Natural fibers biocomposite application has increased in industrial sectors such as automotive (manufacturing instrument panels, insulation elements, doors and backs), nautical, and construction [12].

The production of fique fiber in Colombia is of approximately 30,000 tons/year [13], and it is commonly used for the manufacture of ropes and coffee bags [14].

Recently, some researches regarding the properties of fique fiber composites have been carried out. Hidalgo et al [15] executed an analysis of the physicochemical, mechanical and thermal properties of fique fibers subjected to superficial modifications from chemical treatments, through FTIR, TGA, and tensile strength test. On the other hand, Mina et al [16] performed DMA, Pull-out, SEM, and stress tests to a composite with Cassava starch matrix.

In the literature, there are investigation evaluating the metallic and industrial composite material's vibratory dynamic behavior [17], [18] but few applied to natural fibers composites [19]. For this purpose, a comparative study was carried out between the mechanical and dynamic properties of two thermosetting matrix composite materials, reinforced with fique fiber and E- glass fibers. The interface of the materials was also evaluated by scanning electron microscopy.

2. METHODS

2.1. Materials

As a natural biocomposite reinforcement, fique fibers were used in random configuration, with a weight of 130 g / m² supplied by Coohilados del Fonce LTDA.

The fique employed had an average length of 1.76 ± 0.53 mm and a diameter of 0.0253 ± 0.0033 mm. The figure 1 show the fique configuration in SEM pictures.

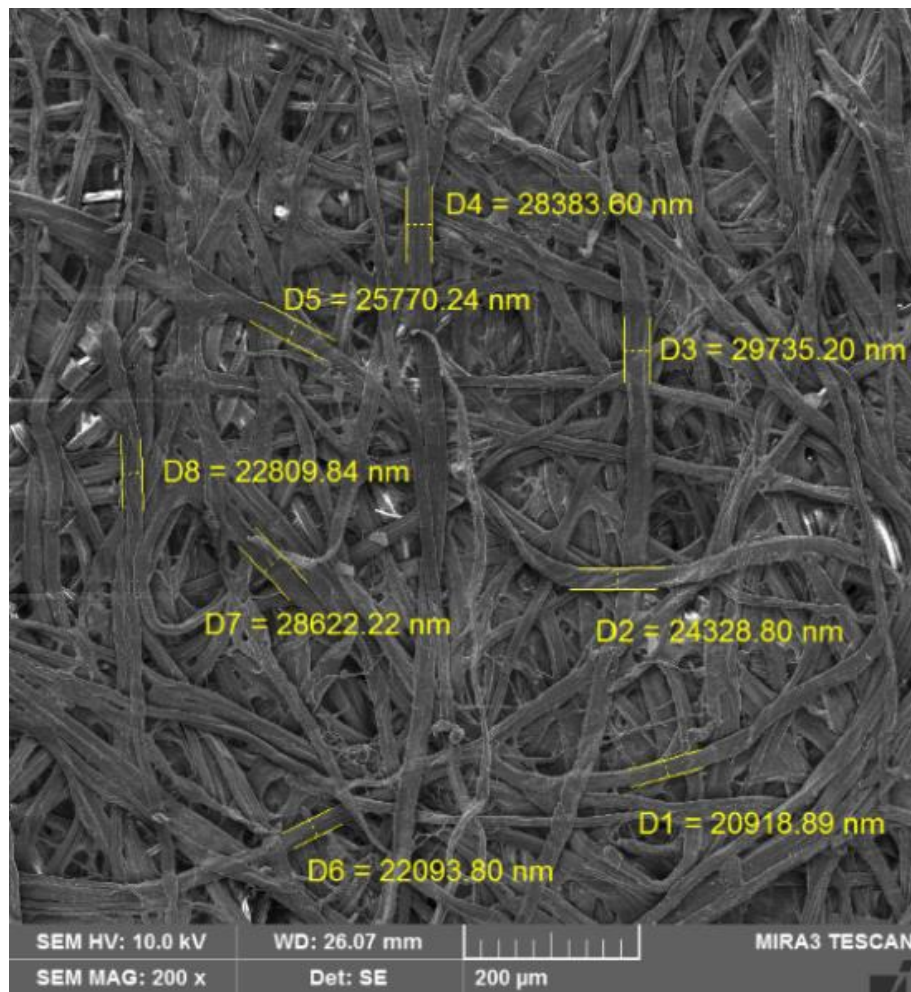


FIGURE 1
Random fibre configuration

Source. Own.

For the E-glass composite, random configuration fibers were used; and they were supplied by Ingequimicas LTDA. The fiber employed had an average length of 12.85 ± 2.15 mm and a diameter of 0.013 ± 0.0017 mm. The figure 2 show the E-glass configuration in SEM pictures.

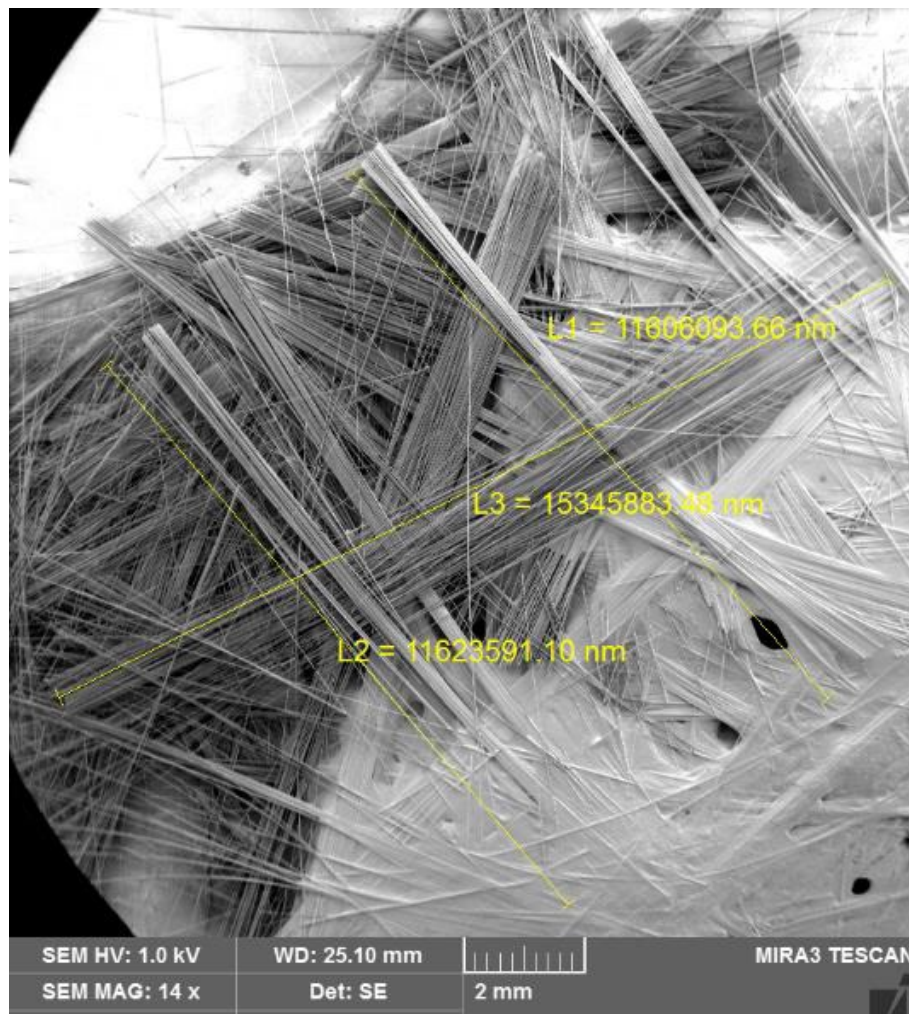


FIGURE 2
Random E-glass configuration
Source. Own.

The matrix used to manufacture both materials was the SuperSap®, epoxy resin from renewable materials. It was supplied by Entropy Resins. The percentage of resin catalyst (by weight) was 100: 33.

2.2. Composite manufacturing

Both composites (Natural and industrial) were manufactured using vacuum infusion technique, applying one bar of pressure, which guarantees the elimination of internal defects in the materials. The curing was performed at room temperature for 24 hours.

For the fique composite, four layers were applied, corresponding to 49% by weight and for the E-glass, four layers were applied, corresponding to 51% by weight.

The final geometry of the fique composite specimens was 25.3 ± 0.17 mm x 252 ± 2.2 mm x 2.52 ± 0.08 mm with a density of 929.7 ± 12.3 kg/m³. For the E-glass composite, the final geometry was 25.1 ± 0.21 mm x 254 ± 2.7 mm x 2.49 ± 0.09 mm with a density of 969.7 ± 15.7 kg/m³.

2.3. Tensile test

Both materials tensile test was performed according to ASTM D3039 / D3039M in a 10 KN, MTS universal machine model C43.104 at a speed of 2 mm / min with a temperature of 24.2 ° C. For each materials, five specimens were tested, taking into account the average of each of the properties. In figure 3, the jaw system used during the test is shown.

2.4. Dynamic vibratory test

The dynamic vibratory test was performed experimentally according to ISO 7626-2 “Mechanical vibration and shock Experimental determination of mechanical mobility Part 2: Measurements using single-point translation excitation with an attached vibration exciter”.

The Modal shop electromagnetic shaker (Excitation element) was placed in a fixed way, generating a sinusoidal sweep up to 300 Hz. The excitation being measured with a reference PCB force sensor 208C02, and the response with a PCB accelerometer reference 352C68, which was translated by five measurement points distributed evenly over the total specimens surface. Figure 4 shows the assembly.

The test specimens were assembled in a free way (without restrictions), using elastic elements.



FIGURE 3
Fique composite tensile test
Source. Own.



FIGURE 4
E-glass composite Dynamic vibratory test
Source. Own.

2.5. Scanning electron microscopy

Scanning electron microscopy was performed using a Tescan microscope model MIRA 3 FEG-SEM with secondary electron detector model A65c SED.

Initially, values were adjusted to 3 KV acceleration voltage. Also, the wild field scan mode was used, obtaining images at few increases in the samples. Subsequently, the scan mode was changed to resolution, varying the conditions to obtain images between 20 X to 5000 X (range from 2 mm to 20 microns), and electron acceleration voltage of up 10 kV.

A small gold layer covered the composite materials in order to improve the electrical conductivity.

3. RESULTS

3.1. Tensile test

Figure 5 shows the stress-strain curve of both composites.

According to the strain-deformation diagram, an elastic-linear behavior is evidenced for both materials because of the nature of their thermostable matrix.

In the case of the reinforced fique composite, a maximum tensile strength of $36.2 \text{ MPa} \pm 8.5 \text{ MPa}$ and a modulus of elasticity of $1272,98 \pm 41.2 \text{ MPa}$ were reached, while for the composite with glass fiber a tensile strength of $153.5 \pm 17.5 \text{ MPa}$, and a modulus of elasticity of $4290 \pm 131.2 \text{ MPa}$ were obtained.

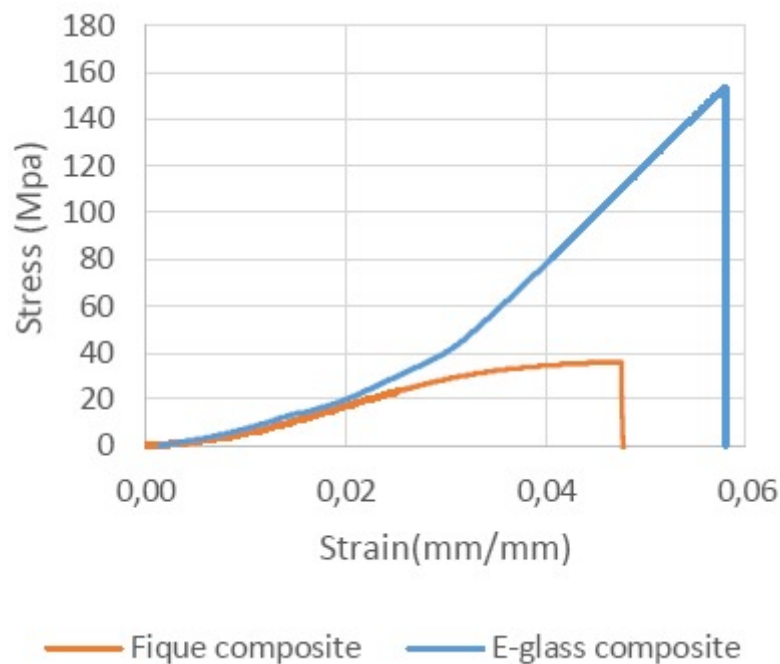


FIGURE 5
Fique and E-glass composites stress-strain curve
Source. Own.

This difference is due, in part, to the natural fiber inherent properties, because 2000 to 3000 MPa tensile stress values are reported for the E-glass fiber [20] while for fique, the reports are of the order of 50 to 500 MPa [15].

Additionally, the E-glass fiber composite has longer continuous fibers which allow a better transmission of stresses which is not interrupted due to the size of the fibers.

The mechanical properties of both materials were affected by the amount of fibers that were located in the direction of application of the load, which supporting the generated tensile.

3.2. Dynamic vibratory test

Figure 6 shows the amplitude of the frequency response measurement of both composites up to the 300 Hz.

Each peak on Figure 6 represents the tested material natural frequencies, because a higher response (Acceleration) is obtained at the same input (Force), indicating that the material at this frequency is in resonance. The values obtained for each material are shown in Table 1.

As it is shown in Table 1, the natural frequency values of both materials had similar behavior.

E-glass composite have natural frequency greater than the fique composite, this is because E-glass composite has greater body rigidity, which does not allow the material deflected avoiding the transmission of vibration although has more mass, which is opposed to the force that is applied.

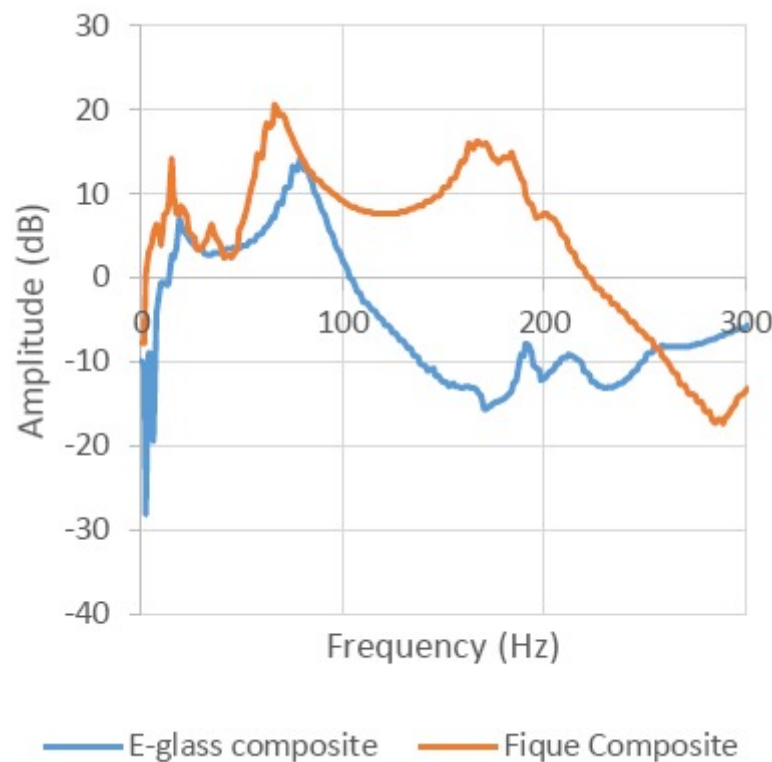


FIGURE 6
Figue and E-glass composites frequency response measurement
Source. Own.

TABLE 1
Composites natural frequencies

Modes	Natural Frequency (Hz)	
	Figue composite	E-glass composite
Mode 1	15 ± 2.1	18 ± 2.6
Mode 2	77 ± 3.4	78 ± 2.6
Mode 3	183.75 ± 8.1	191 ± 5.4

Source. Own.

However, fiber content, friction between the resin and the fibers, and the thickness of the interface also affect the dynamic behavior playing a key role the manufacturing process. [21]

3.3. Scanning electron microscopy

Figures 7 and 8 show the morphology images of the biocomposite bioepoxy/figue at different magnifications. The microstructure reveals spaces between the constituents of figue fibers and the matrix additionally show resin agglomerations, indicating that there was a low adhesion. This is due to the hydrophobic nature of the matrix, the hydrophilic fibers' characteristics and the manufacturing system indicating that the pressure,

prepreg and curing time not allowed good bonding between the components. This generate porosity in the fique composite surface wich was reduced increasing the pre impregnation time.

This low adhesion affected the fique composite's mechanical and dynamical properties, as it is observed in Figure 5 and figure 6. This behavior is due to the low charge transmission between the resin and the fiber, and the porosity stress concentrators.

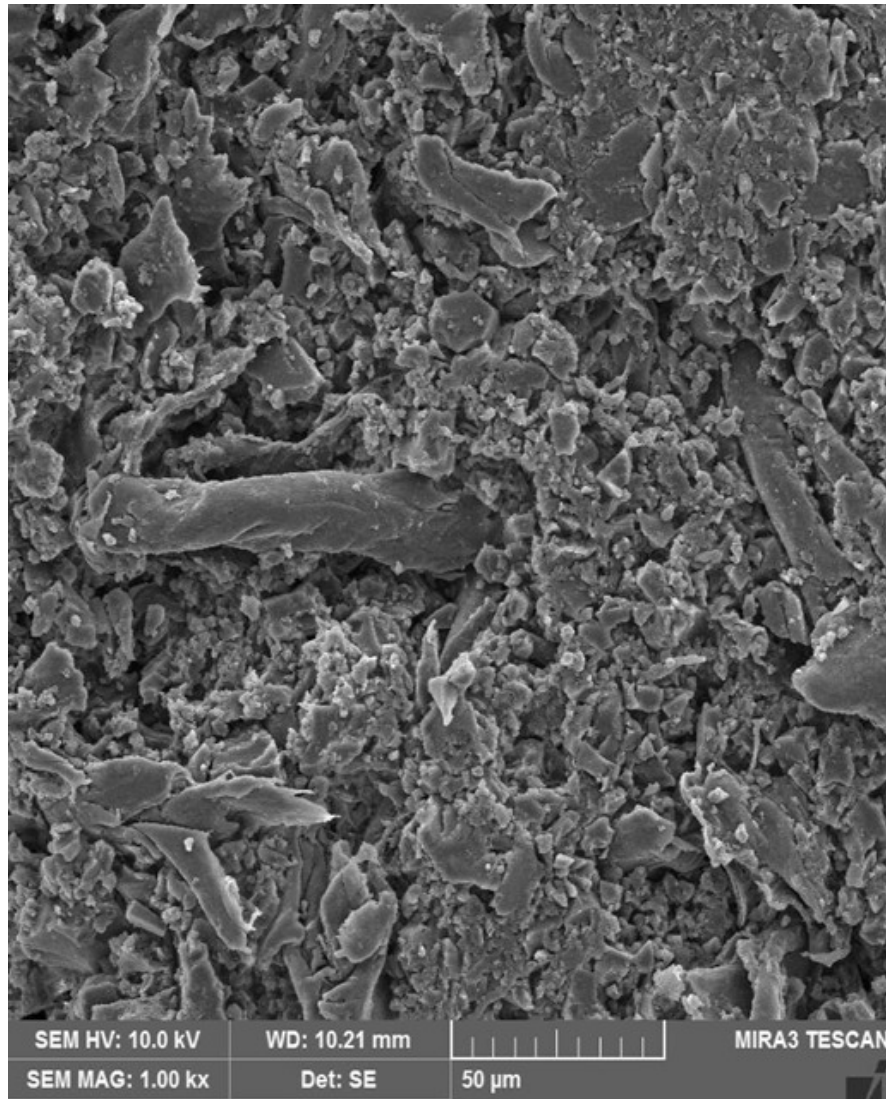


FIGURE 7
Scanning electron microscopy, Fique composite at 1000 X
Source. Own.



FIGURE 8
Scanning electron microscopy, Figue composite at 5000 X
Source. Own.

In contrast, as it is shown in Figures 9 and 10, in the E-glass fiber composite the fibers and matrix had a good adhesion with a better bond between the two components.

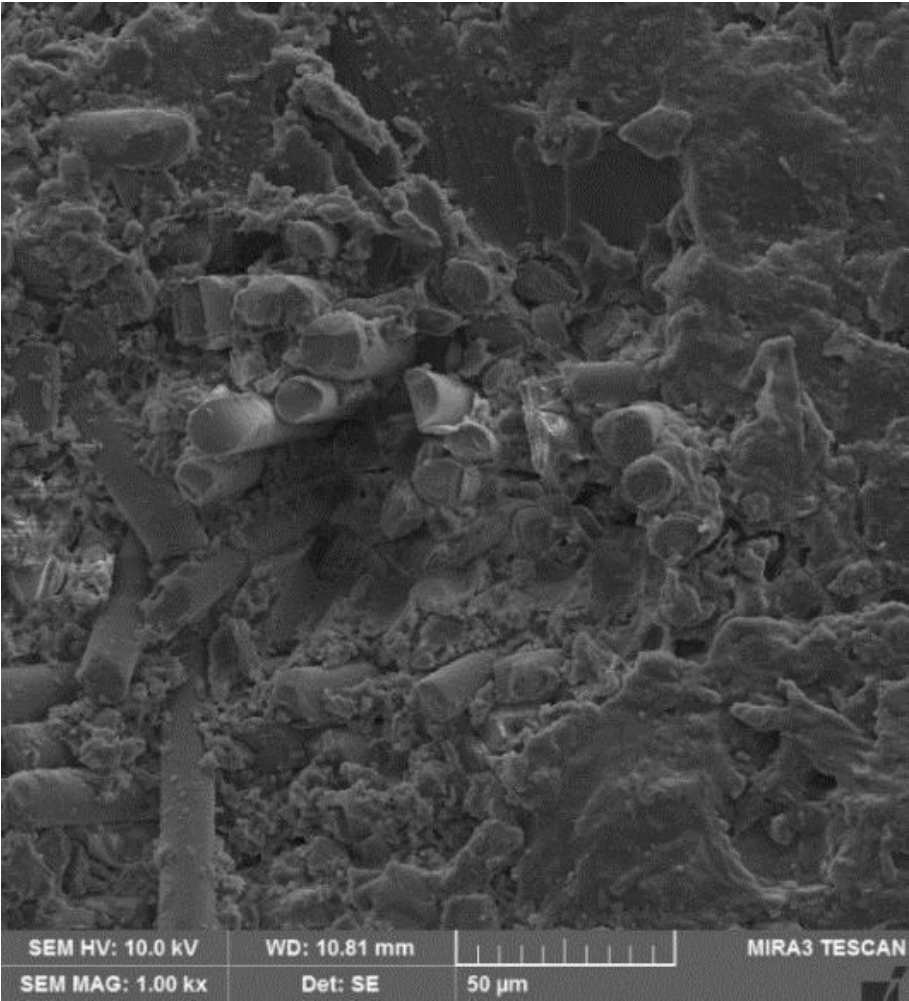


FIGURE 9
Scanning electron microscopy, E-glass composite at 1000 X
Source. Own

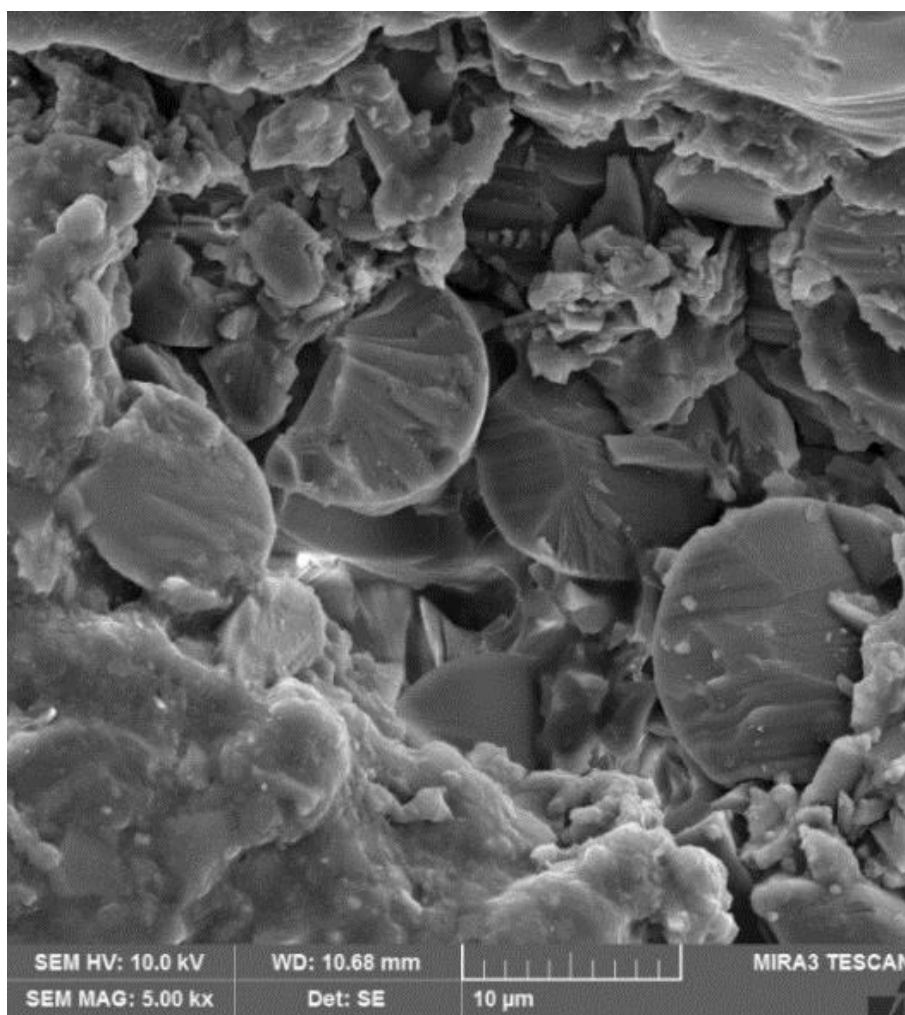


FIGURE 10
Scanning electron microscopy, E-glass composite at 5000 X
Source. Own.

4. CONCLUSIONS

The mechanical properties obtained from the E-glass fiber reinforced composites exceeded those of the composite reinforced with fique fibers. This is due to the natural fiber inherent properties, because for the E-glass, superior stresses tension values were reported. Additionally E-glass fiber composite has longer continuous fibers which allow a better transmission of stresses which is not interrupted due to the size of the fibers as shown Sumaila [22] in short banana fiber epoxy composite. The results obtained are comparable to the study carried out by Rodriguez et al [23], where a fiberglass composite exceeds in mechanical properties a Banana/plantain composite.

The dynamic characterization presented a similar response behavior for both materials. However, the E-glass fiber composite presented natural frequencies greater than fique composite, due to its higher body rigidity although has a little greater mass. Pitchaimani et al [24] obtained similar results in a woven banana/jute polyester composite, which had better dynamic behavior as relatively stronger fiber was oriented along the loading direction.

On the other hand, as it was observed in the SEM scanning electron microscopy, there is low adhesion for the fique composite due to its matrix hydrophobic nature and the fibers hydrophilic characteristics.

Those characteristics led to a low resin load transmission to the fiber affecting the mechanical and dynamic properties. Additionally surface porosities was detected in the fique composite because air bubbles were trapped when the catalyst resin mixture was made, this phenomenon was reduced increasing the pre impregnation time. This manufacturing system anomaly is reported in similar composite investigation [25], [26], [27], [28]. In order to reduce these imperfections for future works it is recommended to implement mitigation techniques as indicated by Lee Hamill et al [29].

Apply a chemical treatment such as alkanization to the fique fiber as indicated by Gañan [30] in order to improve the adhesion with the matrix is also recommending.

In the present work, only specimen bending modes are presented by their geometry in the dynamic analysis. So, in subsequent investigations, the torsional modes must be evaluated.

ACKNOWLEDGEMENTS

Special thanks to the Universidad Pontificia Bolivariana, Bucaramanga sectional who provided the equipment for the test execution, and also, to the Universidad de Pamplona materials laboratory who manufactured the composites samples.

REFERENCES

- [1] R. A. Khan et al., "Comparative Studies of Mechanical and Interfacial Properties Between Jute Fiber/PVC and E-Glass Fiber/PVC Composites," *Polym. Plast. Technol. Eng.*, vol. 50, no. 2, pp. 153–159, 2011.
- [2] F. M. AL-Oqla and M. S. Salit, "2 - Natural fiber composites," in *Materials Selection for Natural Fiber Composites*, F. M. AL-Oqla and M. S. Salit, Eds. Woodhead Publishing, 2017, pp. 23–48.
- [3] P. Haldar, N. Modak, and G. Sutradhar, "Comparative Evaluation of Mechanical Properties of Sisal-Epoxy Composites with and Without Addition of Aluminium Powder," *Mater. Today Proc.*, vol. 4, no. 2, pp. 3397–3406, 2017.
- [4] S. Das, "Mechanical properties of waste paper/jute fabric reinforced polyester resin matrix hybrid composites," *Carbohydr. Polym.*, vol. 172, pp. 60–67, 2017.
- [5] A. Deb, S. Das, A. Mache, and R. Laishram, "A Study on the Mechanical Behaviors of Jute-polyester Composites," *Procedia Eng.*, vol. 173, pp. 631–638, 2017.
- [6] S. S. Rana, M. K. Gupta, and R. K. Srivastava, "Effect of variation in frequencies on dynamic mechanical properties of short sisal fibre reinforced epoxy composite," *Mater. Today Proc.*, vol. 4, no. 2, pp. 3387–3396, 2017.
- [7] G. L. E. Prasad, B. S. K. Gowda, and R. Velmurugan, "Comparative Study of Impact Strength Characteristics of Treated and Untreated Sisal Polyester Composites," *Procedia Eng.*, vol. 173, pp. 771–777, 2017.
- [8] M. N. Akhtar et al., "Influence of alkaline treatment and fiber loading on the physical and mechanical properties of kenaf/polypropylene composites for variety of applications," *Prog. Nat. Sci. Mater. Int.*, vol. 26, no. 6, pp. 657–664, 2016.
- [9] R. Dunne, D. Desai, and R. Sadiku, "Material characterization of blended sisal-kenaf composites with an ABS matrix," *Appl. Acoust.*, vol. 125, pp. 184–193, 2017.
- [10] C. Gómez Hoyos and A. Vázquez, "Flexural properties loss of unidirectional epoxy/fique composites immersed in water and alkaline medium for construction application," *Compos. Part B Eng.*, vol. 43, no. 8, pp. 3120–3130, 2012.
- [11] M. A. Hidalgo-Salazar, M. F. Muñoz, and J. H. Mina, "Influence of Incorporation of Natural Fibers on the Physical, Mechanical, and Thermal Properties of Composites LDPE-Al Reinforced with Fique Fibers," *Int. J. Polym. Sci.*, vol. 2015, 2015.
- [12] B. Zuccarello and R. Scaffaro, "Experimental analysis and micromechanical models of high performance renewable agave reinforced biocomposites," *Compos. Part B Eng.*, vol. 119, pp. 141–152, 2017.

- [13] P. Gañán and I. Mondragon, "Thermal and degradation behavior of fique fiber reinforced thermoplastic matrix composites," *J. Therm. Anal. Calorim.*, vol. 73, no. 3, pp. 783–795, 2003.
- [14] P. Gañán and I. Mondragon, "Fique fiber-reinforced polyester composites: Effects of fiber surface treatments on mechanical behavior," *J. Mater. Sci.*, vol. 39, pp. 3121–3128, 2004.
- [15] M. F. Muñoz, M. A. Hidalgo, and J. H. Mina, "Fibras de fique una alternativa para el reforzamiento de plásticos. Influencia de la modificación superficial," vol. 12, no. 2, pp. 60–70, 2014.
- [16] J. H. Mina, "Caracterización Físico-Mecánica De Un Almidón Termoplastico De Yuca Y Análisis Interfacial Con Fibras De Fique," *Biotechnol. en el Sect. Agropecu. y Agroindustrial*, vol. 10, no. 2, pp. 99–110, 2012.
- [17] H. . Sánchez, J. Uscátegui, and S. Gómez, "Metodología para la detección de fallas en una estructura entramada metálica empleando las técnicas de análisis modal y PSO," *Rev. UIS Ing.*, vol. 16, no. 2, pp. 43–49, 2017.
- [18] O. A. Gonzalez Estrada, J. Leal Enciso, and J. D. Reyes Herrera, "Análisis de integridad estructural de tuberías de material compuesto para el transporte de hidrocarburos por elementos finitos," *Rev. UIS Ing.*, vol. 15, no. 2, pp. 105–116, 2016.
- [19] K. Senthil Kumar, I. Siva, P. Jeyaraj, J. T. Winowlin Jappes, S. C. Amico, and N. Rajini, "Synergy of fiber length and content on free vibration and damping behavior of natural fiber reinforced polyester composite beams," *Mater. Des.*, vol. 56, no. October, pp. 379–386, 2014.
- [20] K. L. Pickering, M. G. A. Efendy, and T. M. Le, "A review of recent developments in natural fibre composites and their mechanical performance," *Compos. Part A Appl. Sci. Manuf.*, vol. 83, pp. 98–112, 2015.
- [21] R. Chandra, S. P. Singh, and K. Gupta, "Damping studies in fiber-reinforced composites - a review," *Compos. Struct.*, vol. 46, no. 1, pp. 41–51, 1999.
- [22] M. Sumaila, I. Amber, and M. Bawa, "Effect of Fiber Length on the Physical and Mechanical Properties of Random Oreinted, Nonwoven Short Banana, Musa," *Cellulose*, vol. 2, no. 1, pp. 39–49, 2013.
- [23] L. J. Rodríguez, W. A. Sarache, and C. E. Orrego, "Compuestos de poliéster reforzados con fibra de plátano/ banano, Musa paradisiaca modificada químicamente. Comparación con fibra de vidrio y fique (*Furcraea andina*)," *Inf. Tecnol.*, vol. 25, no. 5, pp. 27–34, 2014.
- [24] M. Rajesh and J. Pitchaimani, "Dynamic mechanical analysis and free vibration behavior of intra-ply woven natural fiber hybrid polymer composite," *J. Reinf. Plast. Compos.*, vol. 35, no. 3, pp. 228–242, 2016.
- [25] D. C. Darrow, P. A. Propatic, and T. H. Brayden Jr, "Elimination of mold surface porosity on composite parts," *J. Adv. Mater.*, vol. 27, pp. 41–46, 1995.
- [26] L. Hamill, T. Centea, G. Nilakantan, and S. Nutt, "Surface Porosity in Out-of-Autoclave Prepreg Processing: Causes and Reduction Strategies," *International SAMPE Technical Conference*. 2014.
- [27] M. L. Herring, J. I. Mardel, and B. L. Fox, "The effect of material selection and manufacturing process on the surface finish of carbon fibre composites," *J. Mater. Process. Technol.*, vol. 210, no. 6–7, pp. 926–940, 2010.
- [28] M. L. Herring and B. L. Fox, "The effect of a rapid curing process on the surface finish of a carbon fibre epoxy composite," *Compos. Part B Eng.*, vol. 42, no. 5, pp. 1035–1043, 2011.
- [29] L. Hamill, T. Centea, and S. Nutt, "Surface porosity during vacuum bag-only prepreg processing: Causes and mitigation strategies," *Compos. Part A Appl. Sci. Manuf.*, vol. 75, pp. 1–10, 2015.
- [30] C. Gómez Hoyos, V. A. Alvarez, P. G. Rojo, and A. Vázquez, "Fique fibers: Enhancement of the tensile strength of alkali treated fibers during tensile load application," *Fibers Polym.*, vol. 13, no. 5, pp. 632–640, 2012.

CC BY-ND

ADDITIONAL INFORMATION

How to cite: S. Gómez, B. Ramón, R. Guzmán, "Comparative study of the mechanical and vibratory properties of a composite reinforced with fique fibers versus a composite with E-glass fibers," *Rev. UIS Ing.*, vol. 17, no. 1, pp. 43-50, 2018. Doi: <https://doi.org/10.18273/revuin.v17n1-2018004>