



Revista Técnica de la Facultad de Ingeniería, Universidad del Zulia

ISSN: 0254-0770

revistatecnica@gmail.com

Universidad del Zulia
Venezuela

Fernando Millán; José G. Prato; Luisa Carolina González; Andrés Márquez; Pablo Djabayan
Cu (II) Chemisorption on Calcined Substrates made with
an Oxidic Refractory Variable Charges Lithological Material

Revista Técnica de la Facultad de Ingeniería,
Universidad del Zulia, vol. 42, núm. 1, 2019, pp. 10-17
Universidad del Zulia
Maracaibo, Venezuela

Disponible en: <https://www.redalyc.org/articulo.oa?id=605766254003>

- Cómo citar el artículo
- Número completo
- Más información del artículo
- Página de la revista en redalyc.org

redalyc.org

Sistema de Información Científica Redalyc

Red de Revistas Científicas de América Latina y el Caribe, España y Portugal
Proyecto académico sin fines de lucro, desarrollado bajo la iniciativa de acceso
abierto



REVISTA TÉCNICA

DE LA FACULTAD DE INGENIERÍA

Una Revista Internacional Arbitrada
que está indizada en las publicaciones
de referencia y comentarios:

- SCOPUS
- Compendex
- Chemical Abstracts
- Metal Abstracts
- World Aluminium Abstracts
- Mathematical Reviews
- Petroleum Abstracts
- Current Mathematical Publications
- MathSci
- Revencyt
- Materials Information
- Periódica
- Actualidad Iberoamericana

UNIVERSIDAD DEL ZULIA



Quiébrase de la Facultad de Ingeniería de la Universidad del Zulia

Patrimonio del Estado Zulia e
interés Cultural desde 2001

Fecha de Construcción:
1954-1958

Diseño: Arquitecto Carlos Raúl
Villanueva, con elementos
novedosos de adaptación
climática.

Policromía de la obra: Artista
Zuliano Víctor Valera.

Cu (II) Chemisorption on Calcined Substrates made with an Oxidic Refractory Variable Charges Lithological Material

Fernando Millán^{1*} , José G. Prato^{2,3} , Luisa Carolina González⁴ , Andrés Márquez¹ 
Pablo Djabayan⁵ 

¹Polytechnic Institute "Santiago Mariño" IUPSM-Mérida, Venezuela, Chemical Engineering School,

²Universidad Nacional de Chimborazo (Unach), Facultad de Ingeniería, Riobamba, Ecuador.

³Los Andes University, (ULA), Chemical Engineering School, Mérida, Venezuela.

⁴Universidad Nacional de Chimborazo (Unach), Facultad de Ciencias de la Salud, Carrera Laboratorio Clínico e Histopatológico, Riobamba, Ecuador.

⁵Universidad Nacional de Chimborazo (Unach), Facultad de Ciencias de la Salud, Medicina, Riobamba, Ecuador

*Autor de Contacto: fcarlosmillan@gmail.com, pratoj@gmail.com

<https://doi.org/10.22209/rt.v42n1a02>

Recepción: 01/03/2018 | Aceptación: 20/10/2018 | Publicación: 31/12/2018

Abstract

This work presents a complementary study on the nature of copper ions adsorption reaction on calcined substrates with variable charge surfaces prepared with refractory lithological materials obtained from San Juan de Lagunillas, near the city of Mérida, Mérida State, Venezuela. The study was performed on activated and non-activated calcined substrate, prepared with granulometric fraction between 425 μm – 250 μm . The results of the PZC showed that thermal treatment favors the formation of amphoteric oxides with pH_0 6 – 7 similar to those reported in the literature. Although the isotherms obtained in previous experiments are *L* type which indicative of strong affinity of copper ions with the surfaces of the substrates, they do not represent an absolute proof about a chemisorption reaction. This kind of adsorption reaction should produce H_3O^+ ion that acidifies the solution. The adsorption experiment performed on 2 g of calcined substrates with solutions of 0.001, 0.01 and 0.1 M Cu^{+2} produced 0.11, 0.27 and 1.19 mmol of protons ions respectively. These data complement the information given by the isotherms about the chemisorption of copper ions with the surface of this calcined substrate, confirming the specific adsorption.

Keywords: Adsorption; lithological materials; variable charge surface; copper ion.

Quimioadsorción de Cu (II) sobre un Sustrato Calcinado preparado con un Material Litológico Refractario de Carga Variable


Resumen

Este trabajo presenta un estudio complementario sobre la naturaleza de la reacción de adsorción de iones cobre sobre la superficie de carga variable de sustratos calcinados preparados a partir de materiales litológicos refractarios obtenidos de San Juan de Lagunillas, Mérida, Venezuela. El estudio se realizó sobre sustrato calcinado activado y no activado, preparado a partir de la fracción granulométrica entre 425 y 250 μm . Los resultados del experimento de PCC mostraron que el tratamiento térmico favorece la formación de óxidos anfóteros con pH_0 entre 6 y 7 similares a los reportados en la literatura. Aunque las isotermas obtenidas en estudios previos son de tipo *L* indicativas de una fuerte afinidad de iones Cu^{+2} con las superficies de los sustratos, no representan una prueba absoluta sobre una reacción de quimioadsorción. Este tipo de reacción tiene asociada la producción de protones que acidifican la solución. Los experimentos de adsorción realizados sobre 2 g de sustrato calcinado con soluciones de 0,001, 0,01 y 0,1 M de iones cobre producen 0,11, 0,27 y 1,19 mmol de protones respectivamente. Estos datos complementan la información de las isotermas a favor de una quimioadsorción de los iones cobre con la superficie del sustrato calcinado, lo que confirma la adsorción específica.


Palabras clave: Adsorción; materiales litológicos; superficie de carga variable; iones cobre.

Introduction

Transitional metal adsorption in variable charge soils have been well studied by several authors [1, 2] but has not been treated for the case of calcined substrates prepared with oxidic refractory lithological materials. In both cases the Fe and Al, as well as Mn and Ti amphoteric oxides are the most important source of variable charge; these amphoteric surfaces can be either protonated or deprotonated by acid or alkaline treatment to create positive or negative charges on the oxides surfaces, leading to cation and anion adsorption reactions respectively, according to equation (1) [3].



The literature also suggest a mechanism for which the adsorption of transitional metals on these kind of surfaces, through the formation of a covalent bond between the metal ion and the oxidic surface, called chemisorption, according to equation (2) where M could be any transitional metal.



Such kind of reaction modifies the surface charge through more positive values, which allows anion adsorption, and produces acidification through the formation of H₃O⁺ ion. This process is defined as specific adsorption or chemisorption, which has the tendency to be irreversibility. In previous publications [4, 5] copper adsorptions on calcined substrates prepared with some of these refractory lithologic materials which have surface variable charges were described. This physicochemical characteristic is due to the presence of amphoteric oxides in the material, such as Fe, Al, Mn and Ti, previously described in the literature [6, 7]. As a consequence of these particular properties, these lithological materials are versatile for preparing calcined adsorbing substrates and their applications in water treatment. Furthermore, due to their capacity for anion/cation exchange, heavy metals, oxyanions and organic matter are removed by adsorption processes. In previous publications the application to water softening [8], cation adsorption reactions [4], anion adsorption reactions [9, 10] and water treatment [11] have been described. The objective of this paper is to complement the information presented by the previous articles with new findings which support the hypothesis of the chemisorption of copper ions on the oxidic surface of these calcined substrates, in order to continue working on this project. Moreover, according to the theoretic

model described above, H₃O⁺ ion must be one of the reaction products, producing acidification in the solution. Therefore, by following up the pH evolution during the adsorption reaction it should show this acidification process.

Experimental Section

Geografic localization and characterization of the lithologic material have been described in the literature [7]. Being an arid zone, the soils are classified as aridisols [12], presenting serious limitations for agronomical uses. However, some of these lithological materials are used by potters for making kitchen hardware and constructions materials like bricks and crockery using thermal treatment due to its refractory properties. Calcined substrates were prepared according to the procedure described in the literature [4 - 6], so by using the granulometric fraction between 425 - 250 mm for the determination of the zero charge point, the pH and the electrical conductivity measurements. The specific surface was measured by the BET technique using isothermal N₂ adsorption. The procedure for the deprotonation reaction of the calcined substrate (substrate activation) is also described in the same literature where the substrate is chemically treated

with a NaOH 0.1 M solution during 12 h and finally the excess of alkali is washed out with distillate water until it reaches pH 7, and later it dries in a furnace at 120°C. The determination of Point of Zero Charge (PZC) of raw the material, (RM), calcined non-activated (NAS) and activated substrates (AS) was performed according to the method described by the literature [13, 14]. The pH was measured at different ionic strength against pH in aqueous extract and p*H*₀ was recorded on a graphic of ΔpH against p*H*_{H₂O} which gives de p*H*₀ at the intersection of p*H*_{H₂O} axe. The adsorption study was performed by triplicate, in isothermal conditions at 20 ± 2 °C for 24 h, using batch equilibration procedure by treating 2 g of calcined substrate with 5, 10, 15, 20, 25, 30 and 40 mL of 0.001 M Cu⁺², in closed vessels. Then the Cu⁺² equilibrium concentration were determined by the complexometric titration at pH 10 with a 0.001 M EDTA standard solution and NET as metalochromic indicator. Thus, adsorption isotherms were obtained by plotting the amount of copper adsorbed (mmol g⁻¹ substrate) against the equilibrium concentration (mmol) and fitted to the linear form of the Langmuir equation [15-17]. The pH and the EC variations were measured using the same batch equilibration procedure, in triplicate samples, by treating 2 g of raw material, activated and non-activated calcined substrate, with increasing volume of 0.001 M, 0.01 M and 0.1 M of

Cu^{+2} solutions. Suspensions were periodically shaken at $20 \pm 2^\circ\text{C}$ for 24 h in 100 mL glass beakers. pH was measured with a Hanna 211 pHmeter, calibrated with commercial buffer solutions of pH 4 and 7. Electrical Conductivity was measured with a Trans Instrument HC3010 Conductimeter, calibrated with standard reference.

Results and Discussion

Determination of surface zero charge point

Amphoteric oxides have surface charges that are pH dependent; they react in alkaline or acid medium to create negative or positive charges which are responsible for the cation or anion adsorption reactions. So, the pH value at which surface positive charge equals to the surface negative charge is called the point of zero charge, PZC or pH_0 [18]. Figure 1 shows the results of the potentiometric titration on the raw material as well as on the non-activated activated substrates. The intersection of the curves with the $\text{pH}_{\text{H}_2\text{O}}$ axis shows the pH value when the surface diffuses electrical charge equals to zero, indicating the PZC. All the curves present a single intersection point; therefore the PZC is defined by a unique pH value. For the raw material PZC is around 6 however, the ΔpH values are positive indicating that the surface charges are basically negative. However, in the case of calcined substrates surface charges varies according to the solution pH, indicating that the thermal treatment favors the formation of amphoteric oxides.

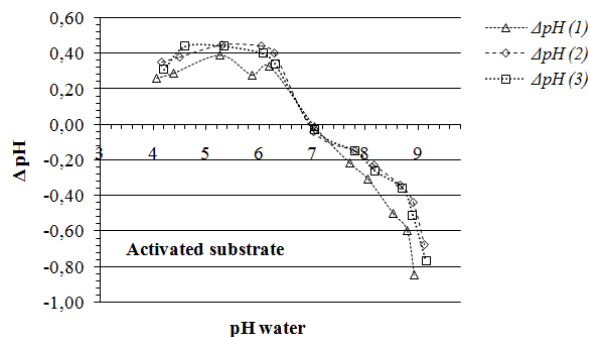
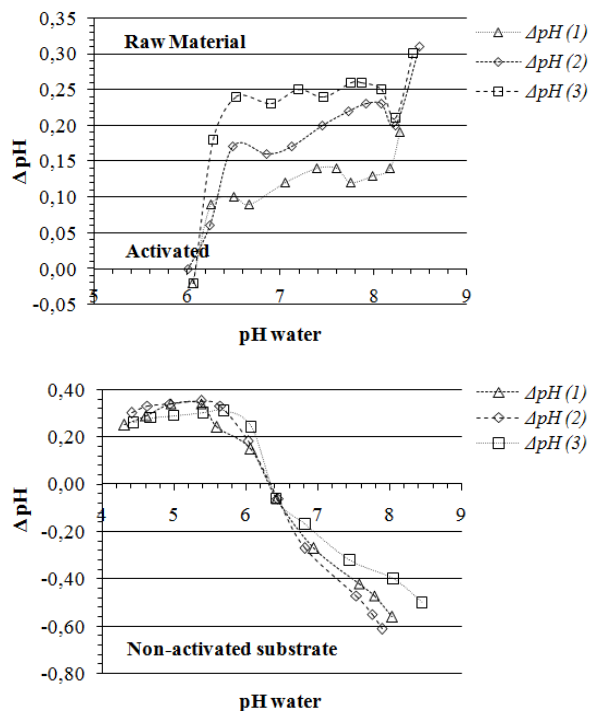


Figure 1. Potentiometric titrations for the determination of zero-point charge (ZPC) in raw material, non-activated and activated substrates.

The PZC values for the calcined substrates lies between 6 and 7.2 and the PZC in calcined substrates shifts from 6.4 to 7 because of the alkaline treatment which creates a greater negative charge density on the substrate surface due to the oxides deprotonation reaction. The range in which the PZC of the raw material and the calcined substrates lies is similar to the PZC values for pure $\alpha\text{-Fe}_2\text{O}_3$, goethite and gibbsite [19]. Moreover, the differences with these experimental values are probably due to a mixture of amorphous variable charge oxides in the material. In reality, minerals and clays are rarely found in soils as pure mineral because particles can be formed of stratified layers of different mineral phases; clays could also be deeply associated with oxides and the amorphous material, making particular identification of minerals very difficult. Although it has been reported that mixing clays and minerals are very common in many types of soils [12].

Adsorption isotherm

Adsorption of copper ions takes place on active sites where amphoteric oxides are deprotonated, creating negative charges not only on non-activated but also in activated surface. Figure 2 shows the adsorption isotherm of Cu^{+2} on adsorbent substrate activated with 0.10 N NaOH and non-activated. As it was pointed out in a previous paper [5], the L type isotherm indicates great affinity between copper ions and the substrate's surface with the formation of a saturated monolayer of copper ions on the surface bounded probably through an inner sphere complex, as is predicted by the Langmuir model. The activated substrate enhances the adsorption reaction due to the greater negative charge density created after oxides deprotonation through alkaline treatment. The Isotherm profiles obtained from copper ions adsorption are similar to those reported from the Cu^{+2} adsorption on goethite and $\gamma\text{-Al}_2\text{O}_3$, and TiO_2 surfaces, confirming specific adsorption or chemisorption between Cu^{+2} ions and oxide surface [20, 21]. The mechanism reported suggests the acidification of solution by the formation of H_3O^+ ions, which is showed by the pH measurement in different experimental conditions.

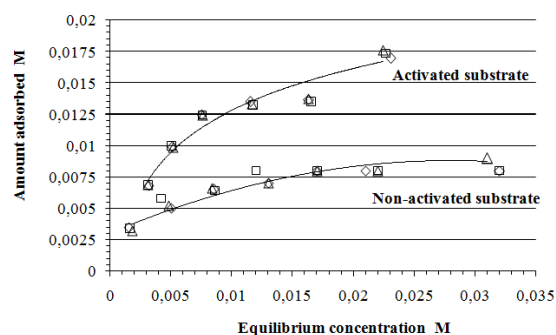


Figure 2. Adsorption isotherms obtained from copper ions adsorption reaction on calcined substrate prepared with the granulometric fraction between 425 – 250 μm .

The adjustments to the Langmuir model was presented in the literature cited above [5] showing a good linear correlation and little average difference between experimental and calculated values. Table 1 shows the fitted equations and K values obtained for the adsorption reaction on the activated and non-activated substrate prepared with the granulometric fraction between 425 – 250 μm . The constant K_2 which defines the straight line slope is greater for the case of adsorption reaction on the activated substrate which agrees with the information given by the isotherm in the Figure 1.

Table 1. Fitted equation, correlation coefficients and K_1 and K_2 values, corresponding to the adsorption isotherm obtained from copper ions adsorption on calcined substrate

Substrate	Fitted equation	r	K_1	K_2
NAS	$C_{eq}/x/m = 0.4850 + 230.31 C_{eq}$	0.9977	474.86	0.0043
AS	$C_{eq}/x/m = 0.5703 + 98.21 C_{eq}$	0.9868	172.20	0.0102

However, isotherm may show but does not confirm information about the interaction between Cu^{+2} ions and calcined substrate surface; neither does the FTIR spectra [5]. Nevertheless, L type isotherm is indicative of great affinity between copper ions and calcined substrate surfaces. Likewise, according to the literature, in a chemisorption reaction transitional metals should bond to the amphoteric surface through to the formation of a covalent bonding in an inner-sphere complex in which the metal becomes part of the oxide surface structure, according to the reaction 2 in which H_3O^+ ions are ones of the reaction products which acidifies the solution [3]. Unfortunately, the isotherm doesn't explain the production of H_3O^+ ion during the adsorption reaction and cannot explain by

itself the real interaction between copper ions and the substrate surface.

pH study

The information given by the isotherm graph and the fitting equations to the Langmuir model is insufficient to confirm the hypothesis of a chemisorption reaction between copper ions and substrate surface. The theoretical model for the specific adsorption or chemisorption type reaction between transitional metals and amphoteric oxides, described by equation (2), suggests the production of H_3O^+ ions during the adsorption reaction. Therefore, the pH measurement should provide the evidence of an acidifying process during the adsorption reaction. Figure 3 shows the pH variation, by triplicating the measurement, during the adsorption process as a function of mmol of Cu^{+2} ions, added from a solution 0.001 M, to the raw material, and calcined activated and non-activated substrate. In all cases, copper adsorption reaction produces acidification of the solution, because of H_3O^+ ion production. However, acidification in the solution is more accentuated in the non-activated and activated substrates. The smaller acidification in the raw material has to be related to the smaller density of negative charges in the surface material.

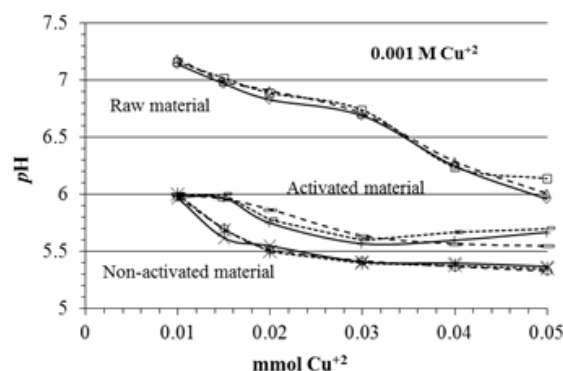


Figure 3. pH variation, of the triplicated measurement, as a function of mmol of Cu^{+2} ions added to the raw material, and calcined activated and non-activated substrate. Dotted, dashed and continued lines represent the three replicates measurements.

Figure 4 shows the pH variation, by triplicated measurements, as a function of mmol of Cu^{+2} added to the activated calcined substrate. The three graphics correspond to the adsorption reaction with the 0.001 M, 0.01 M, and 0.1 M Cu^{+2} solutions used for the experiment. All curves show an evident acidification of the solution, indicating once again the production of H_3O^+ ions during the adsorption reaction. Consequently, solutions become more acidic as the copper ion concentration increase. Table 2 shows the mmol of H^+ ions produced at the beginning and at the end of the adsorption experiment for the conditions described in Figures 3 and 4. In all cases the final concentration of H^+ ions is at least 10 times greater in relation to the initial concentration, but also the greater the copper concentration is, the more acidic the solution become. The net acidification for the three experimental condition described in the Figure 4 are equivalent to 0.11, 0.27 and 1.19 mmol of H^+ ions, respectively.

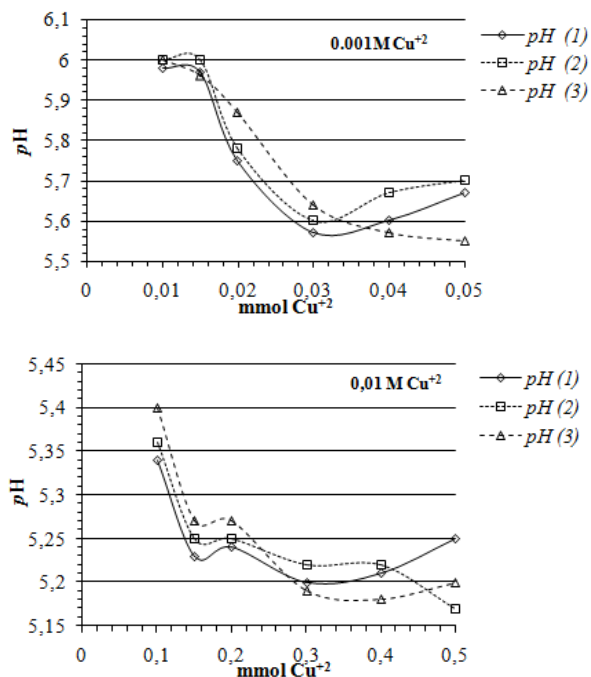


Table 2.- mmol of H_3O^+ ions produced during the adsorption reaction

Cu^{+2} M	mmol H^+ 10 mL soln.	mmol H^+ 50 mL soln.	Net mmol H^+	RED
0.001/RM	$6.71 \times 10^{-7} \pm 2.39 \times 10^{-8}$	$4.60 \times 10^{-5} \pm 9.50 \times 10^{-6}$	$4.59 \times 10^{-5} \pm 9.03 \times 10^{-6}$	19.7
0.001/NAS	$1.04 \times 10^{-5} \pm 3.60 \times 10^{-7}$	$2.23 \times 10^{-4} \pm 1.05 \times 10^{-5}$	$2.13 \times 10^{-4} \pm 1.05 \times 10^{-5}$	4.9
0.001/AS	$1.02 \times 10^{-5} \pm 2.84 \times 10^{-7}$	$1.16 \times 10^{-4} \pm 2.30 \times 10^{-5}$	$1.06 \times 10^{-4} \pm 2.20 \times 10^{-5}$	20
0.01/AS	$4.31 \times 10^{-5} \pm 3.00 \times 10^{-6}$	$3.11 \times 10^{-4} \pm 2.87 \times 10^{-5}$	$2.68 \times 10^{-4} \pm 2.84 \times 10^{-5}$	10
0.1/AS	$2.78 \times 10^{-4} \pm 2.89 \times 10^{-5}$	$1.47 \times 10^{-3} \pm 2.31 \times 10^{-5}$	$1.192 \times 10^{-3} \pm 3.70 \times 10^{-5}$	3

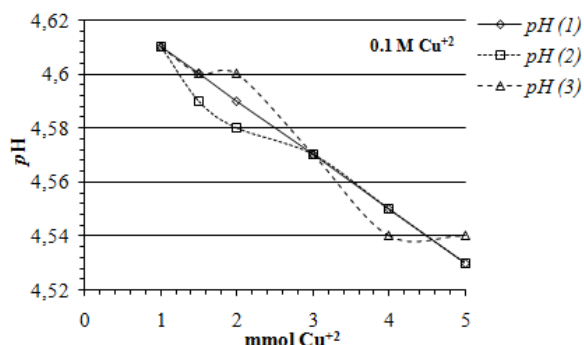



Figure 4. pH variation, of the triplicate measurement, as a function of mmol of Cu^{+2} ion added to the calcined substrate, activated in alkaline medium. Dotted, dashed and continued lines represent the three replicates measurements.

According to the information given by the isotherm graph and the pH study, it can be suggested that the interaction between copper ions and the amphoteric surface of the substrate can be explained by a chemisorption reaction according to the reaction (3):

In any case, the interaction between copper ions and the oxidic surface must be strong enough because attempts for desorption even with strong acid solutions were infructuous.

Electrical conductivity study

Figure 5 shows the Electric Conductivity (EC) variation as a function of mmol of Cu^{+2} ions added to the raw material, and calcined activated and non-activated substrate, using a 0.001 M Cu^{+2} solution. In all cases EC of the solution decrease due to the adsorption reaction. In the case of the raw material, there is a contribution to the EC from the dissolved fraction in the solution.

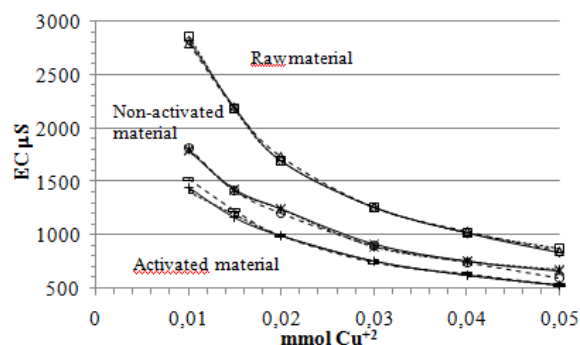


Figure 5. Electric conductivity variation, of the triplicated measurements, as a function of mmol of Cu^{+2} ions added, from a solution 0.001 M, to the raw material, and the calcined activated and non-activated substrates. Dotted, dashed and continued lines represent the three replicates measurements.

However, in the case of calcined substrates, the EC rely only on copper and sulphate ions, due to their greater concentration, other ionic species coming from the calcined substrate has minor contribution because calcined substrate is slightly soluble, so the dissolved fraction is negligible. On the other hand, the adsorption reaction on activate and non-activated substrates seems to take place by the same mechanism, but it is produced in a greater extend on activated material due to the creation of new activated sites through the deprotonation reaction. This aspect was also evidenced by the isotherms and Langmuir constants. The lowest EC values during adsorption reaction on activated substrate in relation to non-activated substrate shows that adsorption reaction actually takes place more extensively on this substrate.

Figure 6 shows the average quantities of copper ions adsorbed on 2 g of raw material and 2 g of the activated and non-activated calcined substrate. These quantities are similar to those reported in previous experiment [5] and confirm that the surface activation reaction creates a greater negative charge density on the surface where the adsorption reaction may occur. The greater adsorption on the raw material is due to the greater specific surface that reacts, and the lowest adsorption on calcined substrates shows that calcination process affects the net surface available for the adsorption reaction [11]. Table 3 present specific surface data for raw material and calcined substrate; according to these results, specific surface of calcined substrate decreases about 55% in relation with raw material. However, these values could be underestimated because the limitations of N_2 adsorption method, when applied to charged surfaces with specific surfaces of about $10 \text{ m}^2/\text{g}$, due to the non-polarity of N_2 molecule [11].

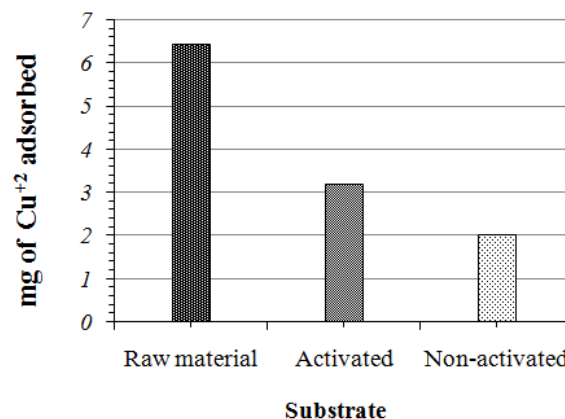
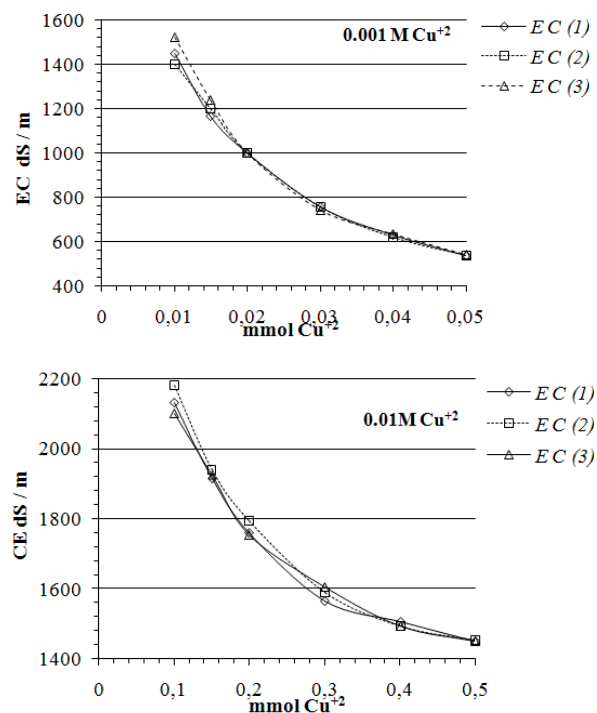


Figure 6. Amount of copper ions, in mg, adsorbed on 2 g of the raw material and the calcined substrate, with activated and non-activated surface.

Figure 7 shows Electrical Conductivity (EC) variation, of the triplicated measurements, as a function of mmol of Cu^{+2} solutions added to the calcined substrate, activated in alkaline medium. The three graphics correspond to the 0.001 M, 0.01 M, and the 0.1 M Cu^{+2} solutions used for the experiment. The EC decreases because of the adsorption reaction which is better defined at lower concentration where the EC decreases to 900 mS during the reaction, instead of 700 mS where the Cu^{+2} concentration is ten times greater and 150 mS when the concentration is 100 times greater.



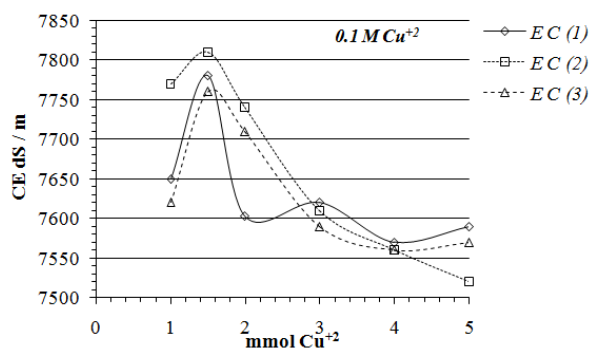


Figure 7. Electrical conductivity variation as a function of mmol of Cu^{+2} ions added to the calcined substrate. Dotted, dashed and continued lines represent the three replicates measurements.

Table 3. – Specific surface data for raw material and calcined substrate.

	Raw material	Calcined substrate
Pore superficial área (m^2/g)	56.35	20.51
Pore volumen (mL/g)	85.80	46.30
External Surface (m^2/g)	68.17	23.60
BET specific surface (m^2/g)	77.91	21.05

Conclusions

The objective of this study is to take advantage of the physicochemical characteristics of the lithologic material found in the town of San Juan de Lagunillas, Mérida, Venezuela and uses it for the preparation of a calcined substrate that can be applied as a granular media for heavy metal retention in water treatment. Although more studies are required, the results obtained from previous works have shown that the lithologic material is appropriate for the preparation of ionic adsorbent substrates and their application in copper retention from aqueous solutions. Some of these results have shown great affinity between metal ion and adsorbent calcined surface characterized by an *L* type isotherm, and associated to chemisorption reaction between adsorbate and adsorbent. The mechanism of copper adsorption on oxidic surface seems to be the same for activated and non-activated surfaces however, the differences is given by the greatest density of negative charges created by the alkaline treatment, which deprotonates amphoteric oxides, enhancing adsorption reaction. Nevertheless, this evidence had to be complemented with additional data by proving the associated production of H_3O^+ ion to such kind of reaction. The *pH* measurements during the adsorption reaction showed a significant acidification along the reaction, which validates the literature about transitional metals chemisorption on amphoteric surface with variable charges. This acidification process became more intense as the concentration of copper ions in the solution increases;

however, the adsorption reaction is better defined at low concentration. The hypothesis of the chemisorption reaction is also supported by the resistance of copper ions to desorption reaction. This fact could be interpreted in terms of a covalence formation between copper ions and the calcined substrate in specific adsorption reaction. It is expected that other transitional metals can suffer such kind of reaction on the surface of these kinds of substrates, and it is possible to separate it from the contaminated waters during a filtration process in a granular media. The variable charge properties of the oxidic surface is evidenced not only by the PZC experiment, but also by the activation reaction, which creates new negative charges that can participate in the adsorption phenomena, thus improving the efficiency of calcined adsorbent substrate for ionic retention. The amphoteric metallic oxides deprotonate in alkaline medium, increasing negative

charge density on calcined adsorbent surface. The thermal treatment favors the formation of the amphoteric oxides with PZC similar to the reported values for pure Fe and Al oxides. The deprotonation reaction of the reactive groups in the substrate surface have been also proved by the EC measurements, showing that adsorption phenomenon is enhanced on activated surfaces with alkaline treatment just because Copper ions adsorb irreversibly on the amphoteric surface being unable to participate as mobile ions in the solution.

References

- [1] Xu, R. K, Qafoku, N. P, Van Ranst, E., Li, J. Y. and Jiang, J.: "Adsorption properties of subtropical and tropical variable soils: Implication from climate change and biochar amendment". In: Donald Sparks, editors: *Advances in Agronomy*, Vol. 135, chapter one, p 1 – 58. Academic Press. 2016.
- [2] Qafoku N. P, van Ranst, E., Noble, A. and Baes, G.: "Variable charge soils: their mineralogy, chemistry and management". *Advances in Agronomy*; 84. (2004) 170 – 172.
- [3] McBride, M. B.: "Environmental chemistry of soils". Ed. Oxford Univ. Oxford. 1994.
- [4] Millán, F, Prato, J. G. García, M. Díaz, I. and Sánchez Molina, J. "Adsorción de iones Cu^{+2} y Zn^{+2} por materiales litológicos de carga variable, provenientes

- de suelos del estado Mérida, Venezuela". *Rev. Téc. Ing. Univ. Zulia*, Vol 36, N° 3 (2013) 195 – 201.
- [5] Millán F., Prato, J. G., Zerpa, D. and Levei, E-A.: "Copper adsorption on calcined substrates from three granulometric fractions coming from two refractory variable charges lithological Materials". *International Journal of Recent Development in Engineering and Technology*. Vol 6, N° 8, (2017) 7 – 17. (ISSN 2347-6435). http://www.ijrdet.com/files/Volume6Issue8/IJRDET_0817_02.pdf
- [6] Millán, F., Prato, J. G. and García, M.: "Characterization of oxidic lithologic materials for ionic adsorption studies". "in extensu" Publication in Proceedings of XIX Congress of Venezuelan Soil Science Society. National Institute for Agronomical Research, INIA, Calabozo, Venezuela. 2011.
- [7] Millán, F., Zerpa, D., Prato, J. G., Senila, M., Levei, E-A., Tanaselia, C. and Lomónaco, S.: "Caracterización química de tres fracciones granulométricas de materiales litológicos oxidicos". In extensu Publication in Proceedings of XXI Congreso de la Sociedad Venezolana de la Ciencia del Suelo, Instituto Nacional de Investigaciones Agronómicas, UNET, San Cristóbal. ISBN: 978-980-6300-94-1. http://www.unet.edu.ve/evento/suelos/files/Memorias_cvcs2015.pdf. 2015.
- [8] Millán, F., Prato, J. G., López, Ma. A. and López, L.: "Estudio de la retención de iones calcio por materiales térmicamente modificados provenientes de suelos de la región de San Juan de Lagunillas, estado Mérida, Venezuela". *Rev. Téc. Ing. Univ. Zulia*, Vol. 32, N° 1 (2009). 48 – 54.
- [9] Prato, J. G., Millán, F., Pariata, A. and Fuentes, M.: Caracterización de materiales litológicos térmicamente modificados para la adsorción de iones SO_4^{-2} en aguas". *Memorias X Congreso de la Sociedad Venezolana de Química, Universidad Simón Bolívar, Núcleo Vargas, Venezuela*. 2011.
- [10] Prato, J. G., Ortiz, L., Gómez, R., Millán, F., Palomares, A. E., Díaz, I. and Sánchez Molina, J.: "Evaluación de la adsorción de fosfatos de aguas naturales a partir de lechos preparados con suelo proveniente de Lomas Bajas, municipio Independencia, estado Táchira". *Memorias XX Congreso Venezolano de la Ciencia del Suelo, Universidad Experimental de Los Llanos Centrales "Rómulo Gallegos", San Juan de Los Morros, Venezuela*. 2013.
- [11] Millán, F., Prato, J. G., Montilla, T. and Tănăsalia, C.: "Using of variable charge adsorption beds for filtration of residual waters". *Rev. Téc. Ing. Univ. Zulia*, Vol 41, N° 1 (2018) 98 - 110. (on line: <http://www.produccioncientifica.luz.edu.ve/index.php/tecnica/>).
- [12] FitzPatrick, E. A.: *Suelos: Su formación, clasificación y distribución*. Editorial CECSA, México. 1985.
- [13] Sakurai, K., Ohdate, Y. y Kyma, K.: "Comparison of salt titration and potentiometric titration methods for the determination of zero point charge (ZPC)". *Soil Sci.Plant Nutr.* 34 (1988) 171 – 182.
- [14] Sposito G.: "The operacional definition of the zero point of charge in soils". *Soil Sci. Soc. Am. J.*, N° 45 (1981) 292-297.
- [15] Castellan, G.: "Fisicoquímica". Fondo Educativo Interamericano, México. 1976.
- [16] Castellan, G.: "Fisicoquímica: Problemas resueltos". Fondo Educativo Interamericano. 1982.
- [17] Bareš, J., Černý, Č., Fried, V. and Pick, J.: "Collection of problems in physical chemistry". Addison – Wesley Pub. Co. Massachusetts. 1962.
- [18] Tan, K. H.: "Principles of soil chemistry". 2nd ed. Marcel Dekker, Inc., New York. 1993.
- [19] Adams, M.: "Fundamentos de química de suelos". Ed. CDCH, UCV, Caracas. 1995.
- [20] Jiang, J., Xu, R. K., and Li, S-Z.: "Effect of ionic strength and mechanism of Cu(II) adsorption by Goethite and $\gamma\text{-Al}_2\text{O}_3$ ". *J. Chem. Eng. Data*, 55, (2010) 5547 – 5552.
- [21] Yang, J. K., Lee, S. M., and Davis, A. P.: "Effect of background electrolytes and pH on the adsorption of Cu (II) /EDTA onto TiO_2 ". *J. Colloid Interface Sci.* 295, (2006) 14 – 20.



UNIVERSIDAD
DEL ZULIA

REVISTA TECNICA

DE LA FACULTAD DE INGENIERIA
UNIVERSIDAD DEL ZULIA

Vol. 42. N°1, Enero - Abril 2019, pp. 02 - 45 _____

*Esta revista fue editada en formato digital y publicada
en Diciembre de 2018, por el **Fondo Editorial Serbiluz**,
Universidad del Zulia. Maracaibo-Venezuela*

www.luz.edu.ve
www.serbi.luz.edu.ve
produccioncientifica.luz.edu.ve