



Biotecnia

ISSN: 1665-1456

Universidad de Sonora, División de Ciencias Biológicas y de la Salud

García-Sifuentes, Celia Olivia; Zamorano-Apodaca, Julio Cesar; Martínez-Porchas, Marcel; Scheuren-Acevedo, Susana Maria; Mazorra-Manzano, Miguel Angel
Isolation and properties of collagen extracted from mixed by-products obtained from different fish species

Biotecnia, vol. 23, no. 3, 2021, pp. 109-116
Universidad de Sonora, División de Ciencias Biológicas y de la Salud

DOI: <https://doi.org/10.18633/biotecnia.v23i3.1463>

Available in: <https://www.redalyc.org/articulo.oa?id=672971079013>

- How to cite
- Complete issue
- More information about this article
- Journal's webpage in redalyc.org



Scientific Information System Redalyc

Network of Scientific Journals from Latin America and the Caribbean, Spain and Portugal

Project academic non-profit, developed under the open access initiative

Isolation and properties of collagen extracted from mixed by-products obtained from different fish species

Aislamiento y propiedades de colágeno extraído de una mezcla de subproductos de diferentes especies de pescado

Celia Olivia García-Sifuentes*, Julio Cesar Zamorano-Apodaca, Marcel Martínez-Porchas, Susana Maria Scheuren-Acevedo, and Miguel Angel Mazorra-Manzano.

Laboratorio de Bioquímica y Calidad de Productos Pesqueros. Centro de Investigación en Alimentación y Desarrollo A.C. (CIAD), Carretera Gustavo Astiazarán Rosas No. 46. Hermosillo, Sonora, México, Cp 83304. Ph/Fax: +52(662)280-0421, +52(662)289-2400 ext 606

ABSTRACT

Fish by-products consisting of skin, bones, or scales are collagen sources. Acid-soluble collagen (ASC) and pepsin-soluble collagen (PSC) mixed by-products derived from different fish species were extracted and evaluated. The properties evaluated for both collagens were chemical composition, amino acid- and SDS-PAGE- protein profiles, Fourier transform infrared spectroscopy (FTIR), denaturation temperature (T_{max}), enthalpy (ΔH), and solubility. The ASC and PSC registered a protein content of 48.56 and 38.80 %, respectively. From the total amino acids detected, hydroxyproline accounted for 7 % and 6 % for ASC and PSC, respectively. The electrophoretic profile showed the presence of the type I collagen bands ($\alpha 1$, $\alpha 2$, β , and γ), whereas FTIR spectrum showed the presence of diverse collagen functional groups (Amide A, B, I, II, and III) for both extracted types, and demonstrated that the extraction process did not affect the collagen's triple-helical structure. The T_{max} of ASC and PSC were 38.27 and 38.07° C, respectively, whereas ΔH were 0.64 and 0.33 J g⁻¹. The lowest solubility was registered at pH 5 for ASC and pH 9 for PSC. The characteristics of the collagen extracted, indicated that a mixture of by-products from different species could be an alternative for their reutilization by the local markets.

Keywords: fish by-products, collagen, isolation, properties, physico-chemical, industrial application.

RESUMEN

Los subproductos de pescado como pieles, huesos o escamas son fuentes de colágeno. Se extrajo y evaluó el colágeno soluble en ácido (ASC) y soluble en pepsina (PSC) derivados de diferentes especies. Las propiedades evaluadas para ambos colágenos fueron composición química, amino ácidos, perfil electroforético, FTIR, temperatura y entalpía de desnaturalización y, solubilidad. El ASC y PSC registraron 48.6 y 38.8 % de proteína, respectivamente. El ASC y PSC presentaron 7 % y 6 % de hidroxiprolina. El perfil electroforético mostró la presencia de bandas de colágeno tipo I ($\alpha 1$, $\alpha 2$, β , and γ), el espectro de FTIR mostró los grupos funcionales del colágeno (Amide A, B, I, II, and III) y demostró que el proceso de extracción no afectó la estructura de triple hélice. La T_{max} de ASC y PSC fueron 38.27 y 38.07° C, respectivamente, mientras

que el ΔH fue 0.64 and 0.33 J g⁻¹. La solubilidad más baja fue a pH 5 para ASC y a pH 9 para PSC. Ambos tipos de colágeno se extrajeron exitosamente y, basados en sus características estructurales, pueden ser una alternativa para la industria de alimentos, biomédica y farmacológica.

Palabras clave: subproductos de pescado, colágeno, aislamiento, propiedades.

INTRODUCTION

Filleting of fish species generates a considerable amount of waste; for example, more than 70 % of solid by-products are discarded, including skeletons, bones, viscera, heads, tails and skins. Together, these constitute an excellent source of high-quality protein. Particularly skin, bones, and scales, can be used to produce collagen and gelatin (Karayanakidis and Zotos, 2016; Välimäa *et al.*, 2019). Approximately 29 different types of collagen have been identified, each with a different amino acid sequence and biophysical properties. The type I collagen is the most common, made up of three polypeptide chains twisted into a triple-helix. Two of the polypeptides are designed as $\alpha 1$ when the chain $\alpha 1$ bonded to another chain $\alpha 1$, form a third chain ($\alpha 2$), which are linked by a hydrogen bond (Yang *et al.*, 2016; Leilei *et al.*, 2017a; Tan and Chang, 2018). The molecular weight of collagen is 300 kDa and approximately 100 kDa for each chain. Most of the collagen obtained from fish by-products is type I and II, having a strong relationship among the molecular weight and the thermal stability. Usually, greater thermal stability occurs at a higher molecular weight. Therefore, the collagen extraction yield and its properties are affected by the extraction method, raw material, pre-treatment, and enzymes used (Pal and Suresh, 2016).

Currently, collagen is extracted from skins and bones of porcine and bovine. However, epidemic events affecting livestock encouraged researchers to endeavor in finding a new collagen source from fish, or fish waste materials, by isolating acid-soluble collagen (ASC), pepsin soluble collagen (PSC), salt soluble collagen (SSC), and ultrasonic collagen (UAC) (Pal *et al.*, 2015; Hamdan and Sarbon, 2019). Several studies have addressed the characterization and extraction of collagen from different fish by-products, such as *Thunnus albacares*, *Carcharhinus albimarginatus*, *Ctenopharyngodon*

*Autor para correspondencia: Celia Olivia García Sifuentes
Correo electrónico: sifuentes@ciad.mx

Recibido: 7 de abril de 2021

Aceptado: 21 de julio de 2021

Idella, *Ictalurus punctatus*, *Ictalurus punctatus*, *Oreochromis niloticus*, *Gadus macrocephalus*, *Rana nigromaculata* and *Ctenopharyngodon idella* (Onouma *et al.*, 2014; Elango *et al.*, 2014; Liu *et al.*, 2015a; Yuqing *et al.*, 2017; Wang *et al.*, 2017; Leilei *et al.*, 2017b; Leilei *et al.*, 2017a; Zhang and Duan, 2017; Zhu *et al.*, 2019); however, these focused on specific fish species. Still, there are scarce studies considering a mix of by-products generated after the filleting of different fish species, as happens frequently in different markets. For instance, more than 3000 tons of by-products produced per year in México can be used to obtain collagen instead of discarding as leftovers (García-Sifuentes *et al.*, 2020). In this sense, finding an alternative for using these mixtures of fish by-products is imperative, generating a potential added value while indirectly contributing to the reduction of waste generation at the local markets or distribution centers, and thus avoiding environmental impacts. Therefore, the objective of this study was to isolate and evaluate ASC and PSC from a mixture of by-products derived from different fish species.

MATERIALS AND METHODS

Materials

As described in a previous study (Zamorano-Apodaca *et al.*, 2020), leftovers of mixed by-products (skins, heads, and skeletons) from various fish species (different sharks, mullet, guitarfish, weakfish, snapper, ray, squid, seabass, and pompano dolphinfish), discarded by the largest distribution market in Mexico, were used for the study. Three different samples were analyzed. All chemicals used in the present work were of analytical grade.

Sample preparation

Once in the laboratory, the mixture of by-products were homogenized at 4° C, 5 minutes, and maximum velocity by using a cutter. The three samples obtained were stored at -20° C for less than a week for further analysis, and some sample was also lyophilized.

The pre-treatment of the sample obtained from the mix of different fish species by-products, and the subsequent extraction of acid (ASC) and pepsin soluble collagen (PSC), were conducted using the method described previously (Zamorano-Apodaca *et al.*, 2020).

Obtention of acid (ASC) and pepsin (PSC) soluble collagen

The ASC and PSC extractions were performed at 25° C. The ASC was extracted with a 0.5 M acetic acid solution for 24 h, as described by Zamorano-Apodaca *et al.* (2020). The PSC extraction was carried out with 0.01 % pepsin solution w/v (dissolved in 0.5M of acetic acid) for 24 h and centrifuged at 10,000 ×g for 20 minutes, considering the supernatant obtained as the PSC.

The ASC and PSC solutions were ultrafiltrated as described by Zamorano-Apodaca *et al.* (2020). The concentrated collagen was finally freeze-dried.

Yield and proximate composition

The yield was obtained based on the raw material wet weight, whereas, the proximate composition of the by-product homogenates, ASC and PSC, were estimated by quantifying protein, lipids, moisture, and ash, according to the AOAC (2000) methods (960.52, 920.39, 950.46, 920.153, respectively). To calculate the crude protein content the 6.25 general Jones conversion factor was used.

Amino acid quantification

The quantification of amino acids was carried out by HPLC (Vázquez *et al.*, 1997), with modifications described by Zamorano-Apodaca *et al.* (2020). Six to eight milligrams of both lyophilized collagen types were used for the analysis. The identification of amino acids was carried out by considering the retention time, compared with a standard mixture of amino acids and the results were reported as mg/g of sample.

Electrophoretic pattern

The electrophoretic separation of ASC and PSC was performed according to the method of Laemmli (1970) using 7 % separation gel and 4 % stacking gel. A 1 g sample of collagen was dissolved in a 5 % SDS and 0.1 % β-mercaptoethanol solution. Samples were homogenized and heated at 80° C for 1 h. The cold sample was centrifuged at 3,000 ×g for 15 minutes at 25° C (Avanti J-26S XPI, Beckman Instruments INC. Palo Alto CA), and 40 µg of protein were loaded per path once the protein was quantified (Gornall *et al.*, 1948). To calculate the proteins molecular weight, the bands were stained with coomassie brilliant blue, and a wide-range standard (6.5-200 kDa) was used to analyze these bands.

Structural properties

PSC and ASC functional groups were determined by Fourier Transform Infrared Spectroscopy (FTIR), following the method described by Yousefi *et al.* (2017). The infrared spectra used ranged from 4000 to 400 cm⁻¹ using a Bruker model IFS 66/S infrared spectrophotometer (Bruker Optics Limited, Coventry, UK), equipped with attenuated total reflectance ATR (SPECAC, Orpington, UK). Freeze-dried ASC and PSC were placed into the ATR and the resulting spectra were analyzed using the OriginPro 8 software (OriginLab Corporation, Northampton, United States).

Temperature and enthalpy of thermal denaturation

The temperature and enthalpy of thermal denaturation were monitored by following the methodology proposed by Rashidy *et al.* (2015), and using a DSC7 calorimeter (Perkin Elmer de México, S.A. Monterrey, México). Three mg of ASC and PSC were re-hydrated with 27 µL of 0.5 M acetic acid, and the sample was scanned at 5 °C per minute from 10 to 90° C under high atmospheric nitrogen conditions (40 mL N₂/minute). The initial and maximum transition temperatures (T_{ons}, T_{max}) and the enthalpy (ΔH) were calculated from the thermogram using the Pirys software (Perkin Elmer de México, S.A.).

Solubility

The ASC and PSC solubility was determined following the method described by Matmaroh *et al.* (2011). Briefly, the ASC and PSC samples were dissolved in 0.5 M acetic acid to a concentration of 3 mg/mL, and the mixtures were stirred at 4° C for 3h. Then, the collagen solution (3 mg/mL, aliquots of 8 mL) was adjusted to pH 3, 5, 7, 9 with 6 N NaOH or 6 N HCl as required. The volume of the solution was adjusted to 10 mL, stirred at 4°C for one h and centrifuged. Finally, the protein content in the supernatant was determined (Lowry *et al.*, 1951). The relative solubility was calculated by comparing this parameter with that obtained at the pH giving the highest solubility.

Statistical analyses

Three different samples were taken (random sampling), the experimental design was a one way analysis of variance (ANOVA) performed by using the NCSS software (NCSS, 2011) and a level of significance of 5 %. All the experiments were conducted in triplicates (n=3) for the three samples.

RESULTS AND DISCUSSION

Yield

Pepsin soluble collagen (PSC) and acid soluble collagen (ASC) were successfully isolated from a mix of by-products obtained from different fish species. The wet-weight basis yield of ASC (4.4 %) was 2-fold higher than PSC (2.2 %), in concordance to Hamdan and Sarbon (2019) and Veeruraj *et al.* (2015), who reported higher yields for ASC compared to PSC. Both studies explained that the low concentration of acetic acid used (0.5 M) had a significant efficiency, ensuring a complete extraction while maintaining the collagen structure. Likewise, ASC and PSC were isolated from sailfish skin with yields of 5.76 and 2.11 % (wet weight basis), respectively (Tamilmozhi *et al.*, 2013); however, the authors reported the incomplete solubilization of the skin. The type of sample probably influenced the yield obtained in our study since high amounts of non-collagenous proteins may be contained in a mix of by-products from different species. On the other hand, the market where the sample was obtained does not regulate the ratio of each by-product; however, the composition of the mixed by-products is similar throughout the year as reported by García-Sifuentes *et al.* (2020), therefore, it is assumed that the yield of the collagen is not significantly affected by the sampling period.

Additionally, the extraction time of the collagen was 24 h instead of 48, or even 72 h, as reported by other authors (Liu *et al.*, 2015a; Zhu *et al.*, 2019).

Regarding the extraction temperature, Liu *et al.* (2015a) showed that a complete extraction of ASC was maintained regardless of the extraction temperature (4, 10, 15, 20° C) at 0.5 M of acetic acid concentration, indicating that the extraction temperature did not affect the extraction yield in our experiment. Liu *et al.* (2015) did not find structural modifications of ASC at 20° C, which is a temperature that could be convenient for practical and industrial applications. Similar

results will be shown later in the present study.

Papain was used to remove non-collagenous protein (NCP) and the exposition time was 1h, at pH 7.8-8.0, and 23° C. Under these conditions and using an electrophoresis approach, Hong *et al.* (2019) reported that papain fails to disrupt the collagen structure after one hour of incubation. Still, after 24 hours the collagen structure was disrupted. In this study, the presence of collagen in NCP (data not shown) was not observed through electrophoresis nor amino acid quantification. The effectiveness of the papain enzyme is associated with its activity in the linear structure of the protein, whereas the collagen peptide bonds are not fully accessible to the proteases since the molecule has secondary and tertiary structures, in addition to enzymatic and non-enzymatic cross-linking between fibrils; therefore, hydrolysis would depend directly on the experimental conditions (pH, temperature, time, ion strength, etcetera). Thus, papain is not as effective for hydrolyzing collagen cross-link bonds under these conditions. Collagen hydrolysis with papain can be performed, but temperatures above 65° C and pH from 5 to 7 are required.

Proximate composition

The proximate composition of the mixed by-products from different fish species, ASC, and PSC are shown in Table 1. The raw homogenate of mixed by-products from various fish species was high in moisture content, coinciding with the value reported by Kosseva *et al.* (2013). The second essential component showing high levels was protein, enhancing the relevance of collagen extraction. The lipid content turned out to be a minor component, which is explained based on the lean species sampled and therefore, the collagen yield was not affected by this component. The protein content of ASC was 10 % higher than PSC, while ash and moisture were similar for both collagen types, and no lipids were detected, probably because the raw homogenate had a meager quantity (1.76 %) that could be removed during the first wash, after the deproteinization process. Protein content reported by Solari and Cordova (2015) was less than 74 %, which can be attributed to the modifications in the extraction process (Zamorano-Apodaca *et al.*, 2020). However, collagen recovery

Table 1. The proximate composition (%) of the mix of by-products homogenate from different fish species, acid soluble collagen (ASC) and pepsin soluble collagen (PSC).

Tabla 1. Composición proximal (%) de la mezcla de subproductos de diferentes especies, colágeno soluble en ácido (ASC) y colágeno soluble en pepsina (PSC).

Sample	Protein	Ash	Moisture	Fat
H (%)	17.41 ± 0.07	5.38 ± 0.07	72.50 ± 0.21	1.76 ± 0.08
ASC (%)	48.56 ± 3.77 ^a	27.69 ± 4.01 ^a	5.59 ± 0.10 ^a	nd
PSC (%)	38.80 ± 6.31 ^b	27.98 ± 0.01 ^a	5.49 ± 0.17 ^a	nd

Different superscript letters between ASC and PSC show significant difference ($P < 0.05$). H: mix of by-products homogenate. nd: not detected.

ery was not structurally affected by the extraction process, as shown by FTIR and DSC analyses. Though the lyophilized ASC and PSC extract were not utterly pure because both contained high ash levels, the results showed hydroxyproline contents of 7 and 6 %, respectively and therefore, the conversion factor to collagen was 14.28 and 16.66. Finally, when the total nitrogen content of the ASC and PSC was multiplied by the factor, it revealed that the protein recovered in lyophilized ASC and PSC was 100 % collagen.

Amino acid quantification

The ASC and PSC amino acid composition is shown in Table 2. Differences ($P < 0.05$) among them were observed for all amino acids quantified, except glutamic acid, histidine, serine, histidine, threonine, methionine, and lysine. Then, the major amino acid quantities were detected in the following descending order: glycine, proline, glutamic acid, arginine, alanine, and hydroxyproline for ASC, whereas for PSC were glycine, glutamic acid, arginine, proline, threonine, alanine, aspartic acid, and hydroxyproline. Glycine, proline, and hydroxyproline are the essential amino acids of collagen and its contents showing proportions of 27 %, 15 %, and 7 %, respectively for ASC, and 26 %, 9 %, and 6 %, respectively for PSC. Hydroxyproline is the most critical amino acid because it is exclusively associated with stromal proteins such as collagen. Glycine was the most abundant amino acid detected, and its quantity is explained because of its detection in every third amino acid residue of the collagen structure. The results

Table 2. Amino acid composition of acid soluble collagen (ASC) and pepsin soluble collagen (PSC).

Tabla 2. Composición de aminoácidos de colágeno soluble en ácido (ASC) y colágeno soluble en pepsina (PSC).

Amino acid	PSC (mg/g)	ASC (mg/g)
Aspartic acid	38.7 ± 5.5 ^a	31.6 ± 3.1 ^b
Glutamic acid	61.4 ± 6.8 ^a	59.1 ± 4.5 ^a
Serine	15.1 ± 1.7 ^a	16.3 ± 1.8 ^a
Histidine	1.9 ± 1.1 ^a	1.3 ± 0.4 ^a
Arginine	51.8 ± 7.0 ^a	57.7 ± 6.0 ^b
Glycine	143.4 ± 20.9 ^a	170.4 ± 22.1 ^b
Threonine	40.3 ± 12.4 ^a	31.6 ± 6.3 ^a
Alanine	41.1 ± 4.9 ^a	50.3 ± 7.4 ^b
Tyrosine	8.9 ± 1.8 ^a	5.4 ± 1.8 ^b
Methionine	5.2 ± 1.0 ^a	5.3 ± 0.8 ^a
Valine	14.0 ± 2.1 ^a	10.5 ± 2.0 ^b
Phenylalanine	8.4 ± 2.9 ^a	4.6 ± 1.7 ^b
Isoleucine	9.7 ± 1.2 ^a	7.4 ± 1.6 ^b
Leucine	17.8 ± 1.5 ^a	15.6 ± 1.8 ^b
Lysine	23.2 ± 4.1 ^a	24.6 ± 2.9 ^a
Proline	48.4 ± 14.8 ^a	94.1 ± 16.4 ^b
Hydroxyproline	31.5 ± 7.1 ^a	43.9 ± 16.1 ^b

All values are mean ± SD, n=3. Different superscript letters between same row show significant difference ($P < 0.05$).

obtained from this study were similar to those reported for pigskin and marine fish scales from Japan and Vietnam (*Saurida* spp., *Trachurus japonicus*, *Mugil cephalis*, *Cypselurus melanurus*, *Dentex tumifrons*), registering proline proportions of 13.1 % and 10.1 % respectively, 9.8 % and 6.4 % of hydroxyproline, and 32.2 % and 33.8 % of glycine (Thuy *et al.*, 2014; Duconseille *et al.*, 2015).

Electrophoretic pattern

Although, the protein patterns for ASC was reported in a previous study (Zamorano-Apodaca *et al.*, 2020), the comparison among both ASC and the PSC are shown in Figure 1. A similar pattern was observed for both collagen types, with higher molecular weights for $\alpha 1$ bands (129-139 kDa) than $\alpha 2$ bands (119-126 kDa). The β and γ bands for both collagen types were >200 kDa. These bands are characteristic properties of collagen because of their α triple helix chains with molecular weights around 100 kDa. The $\alpha 1$ and $\alpha 2$ chains can be linked together, forming the β chain, however, when three α chains ($\alpha 1$, $\alpha 2$) are linked together by intermolecular or intramolecular bonds, these form a new arrangement

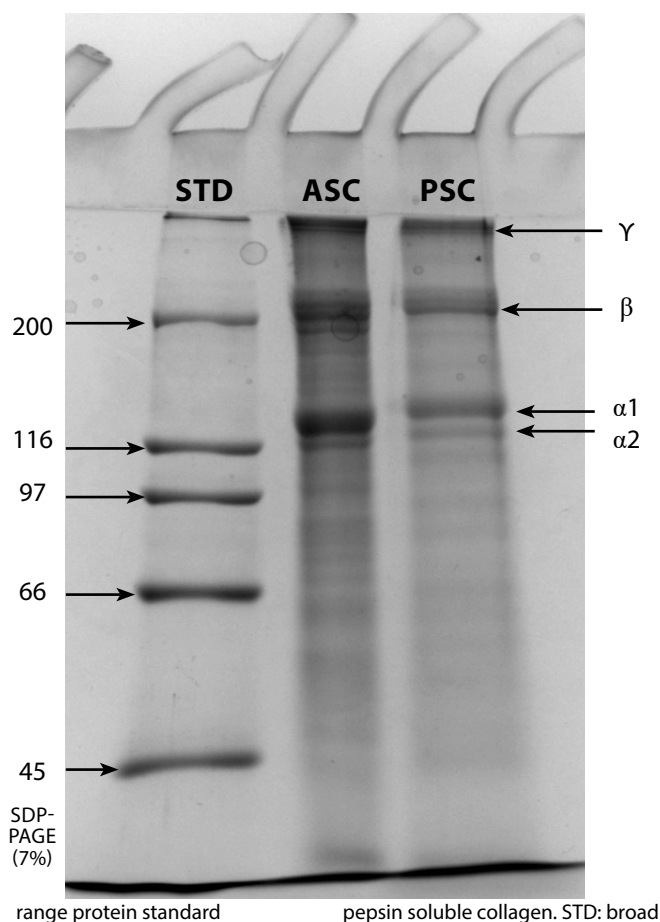


Figure 1. SDS-PAGE (7%) electrophoretic pattern of acid soluble collagen (ASC) and pepsin soluble collagen (PSC). STD: broad range protein standard.

Figura 1. Patrón electroforético por SDS-PAGE (7%) de colágeno soluble en ácido (ASC) y colágeno soluble en pepsina (PSC). STD: Estándar de amplio margen.

which is considered as the γ chain (Sun *et al.*, 2017; Yousefi *et al.*, 2017; Slimane and Sadok, 2018). The β and γ -chains observed in both ASC and PSC, indicate the presence of high MW cross-links, but the band intensity of β -chain and α -chain of ASC was more intense than that observed in PSC. This suggests that the acid was able to cleave the telopeptide region, thereby releasing more α - and β -chains in ASC. Contrary to our results, Ali *et al.* (2017) reported β -chain and α -chain more intense in PSC.

The most abundant and essential collagen is Type I, because it is a natural macromolecular hydrocolloid used by the food, pharmaceuticals, cosmetic, and biomedical industry. This kind of collagen could be obtained from bones, skin, ligaments, tendons, cornea, and scales of fisheries by-products (Jie *et al.*, 2018), as used in the present study.

Structural properties

Infrared spectroscopy with Fourier transform, attenuated total reflectance (FTIR-ATR)

As the peak of interest is produced at a specific wavelength and absorbance, the functional group (amide A, amide II, amide III) and its vibration mode could be identified.

Figure 2 shows the infrared spectrum of the ASC and PSC obtained from the tested by-products mixture. The spectrum show the presence of the specific functional groups of collagens (Amide A, B, I, II, and III).

The amide A functional group was located at 3293 and 3288 cm^{-1} for ASC and PSC, respectively, indicating the presence of amino groups (N-H) involved in the association of hydrogen bonds, and having a strong hydrogen bond into the ASC and PSC. The amide B functional group is associated with the asymmetric stretching vibrations of the $=\text{C-H}$ and $-\text{NH}^{+3}$ bonds. The ASC and PSC amide functional groups B were detected at 2932 cm^{-1} and 2933 cm^{-1} , respec-

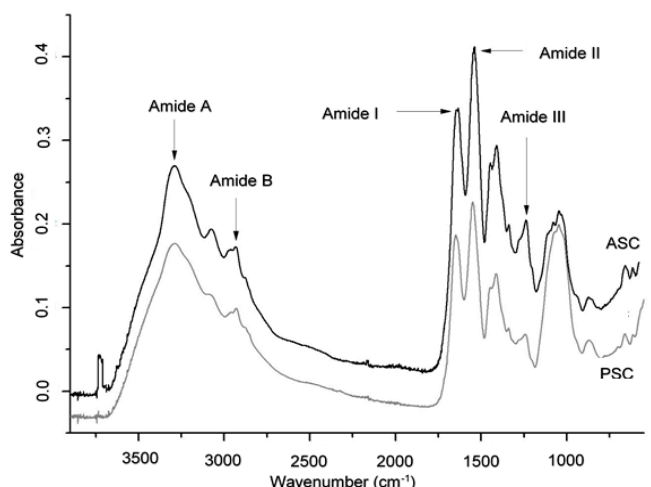


Figure 2. FTIR spectrum molecular identification of acid soluble collagen (ASC) and pepsin soluble collagen (PSC) from mixed by-products of different species.

Figura 2. Espectro de identificación molecular por FTIR de colágeno soluble en ácido (ASC) y colágeno soluble en pepsina (PSC).

tively. The amide I functional group is associated with the stretching vibrations of the carbonyl groups (C=O), either in the polypeptide or in the hydrogen bond coupled with a carboxyl group (COO^-) (Yousefi *et al.*, 2017; Ahmed *et al.*, 2018). In the ASC and PSC, this functional group was located at 1639 and 1648 cm^{-1} , indicating a good degree of molecular order, supporting the claim that “the lower the wave number of the functional group, the greater the molecular order of the collagen”. This observation confirmed that the formation of a hydrogen bond between N-H stretch (X position) and C=O (Gly) of the fourth residue is responsible for the formation of a triple helix.

The amide II functional group is associated with the flexion of the NH groups coupled with the stretching vibrations of the CN and NH groups. In the ASC and PSC samples, the functional group was located at 1541 cm^{-1} and 1550 cm^{-1} ; this indicates that the most of the hydrogen bonds are given by the amino groups (Barth and Zscherp, 2002; Yousefi *et al.*, 2017), and ASC presented more and/or stronger hydrogen bonds than PSC because the amide II peaks were detected at a lower wavelength. This suggests that acid disrupted the non-helical portion of telopeptide regions, resulting in a higher structure order of ASC.

The amide III functional group is associated with the flexion of the N-H group from the amide bonds and complex with intermolecular interactions in collagen as C-N stretching, N-H in plane bending from amide linkages as well as vibrations from CH_2 of glycine backbone and proline side-chains (Zhang *et al.*, 2014; Zhang and Duan, 2017). In the ASC and PSC samples, the amide III functional group was located at 1239 and 1240 cm^{-1} , indicating that hydrogen bonds were involved in ASC and PSC.

Additionally, the absorption peaks corresponding to pyrrolidine ring vibration of hydroxyproline and proline for ASC and PSC, were observed at 1450 y 1449 cm^{-1} , respectively. The ratio between amide III and pyrrolidine ring vibration of proline and hydroxyproline of ASC and PSC were 1.17 (~1) (Plepis *et al.*, 1996; Ahmed *et al.*, 2018), revealing that the ASC and PSC were not denatured during the extraction, and the triple-helical structure was still preserved. The triple helix structure is responsible for the rigidity and strength of the collagen fibers (Matmaroh *et al.*, 2011; Veeruraj *et al.*, 2013). Based on the position of amide A, I and, II bands of ASC that were shifted to lower wavenumber as compared to PSC, it could be inferred that ASC would result in a higher structure order of collagen.

Temperature and enthalpy of thermal denaturation

No significant differences were detected for the ASC and PSC initial thermal transition (T_{ons}) and maximum temperature of thermal denaturation (T_{max}), whereas for enthalpy (ΔH), differences were observed ($P < 0.05$). T_{ons} for ASC and PSC were $35.09 \pm 0.88^\circ \text{C}$ and $35.46 \pm 2.1^\circ \text{C}$, respectively, T_{max} of $38.27 \pm 0.87^\circ \text{C}$ and $38.07 \pm 2.09^\circ \text{C}$, and ΔH $0.64 \pm 0.21 \text{ J g}^{-1}$ and $0.33 \pm 0.19 \text{ J g}^{-1}$, respectively. Noteworthy, PSC had lower ΔH values compared to ASC, which might be due to

the permanence of the telopeptide region after treatment, resulting in a less compact PSC structure. Consequently, PSC requires less energy for destabilization than ASC. Benjakul *et al.* (2010) reported that the collagen thermal stability is associated with the pyrrolidine rings and hydrogen bonds of the hydroxyproline hydroxyl group, and in this sense, the amino acids content (20 and 14 % for ASC and PSC, respectively) also influenced the collagen stability.

T_{max} values were similar to the reported by Ali *et al.* (2017), for golden carp (*Probarbus jullieni*) scales, of ASC (37.67° C) and PSC (37.83° C), and higher than the reported for catfish, ASC (36.12° C) and PSC (35.57° C) by Tan and Chang (2018). Coinciding with our results, these authors also showed less ΔH for PSC.

Effect of pH on Solubility

ASC and PSC relative solubility results are shown in Figure 3. Overall, the PSC showed a higher solubility ($P < 0.05$) than ASC. The PSC relative solubility ranged from 62.8 to 100 %, while ASC from 62.2 to 99 %. As expected, both PSC and ASC showed the highest solubility at pH 3, whereas the lowest solubility was detected at pH 9. However, although a sharp decrease in solubility can be seen at pH 5 for PSC, probably due to the pepsin effect, its lowest solubility was at pH 9. Our results were similar to those reported for ASC and PSC obtained from spotted golden goatfish scales (Matmaroh *et al.*, 2011), carp (Catla) scales (Pal and Suresh, 2017), and channel catfish skin (Tan and Chang, 2018). These authors observed the highest solubility under acidic conditions (pH 2-5), with a sharp decrease at pH 5. However, the solubility increases at alkaline pH (11) as reported for the spotted golden goatfish scales PSC (Matmaroh *et al.*, 2011). The ASC and PSC highest solubility at acidic pH could be associated with the discrepancy between pH and the isoelectric point. The protein net charge was different to zero, then, the repulsion forces between the collagen chain molecules increased, resulting in better solubilization. In contrast, when the pH is

equal or close to the isoelectric point, the total net charge of the protein molecules approaches to zero, and the protein precipitation and aggregation occurs.

The results of our study revealed that the mixed by-products from different fish species represent a rich source of collagen with desirable physicochemical characteristics. At the same time, the extraction process is technically feasible, considering that no abrupt denaturation of the collagen structure happened.

CONCLUSION

Acid soluble collagen (ASC) and pepsin soluble collagen (PSC) obtained from mixed by-products from different fish species were successfully extracted. The yield, protein, and hydroxyproline contents of ASC were higher than PSC. However, both were identified as type I collagen, and the particular functional groups of collagens were observed. No denaturation of collagen was detected, demonstrating that the extraction process did not affect the collagen's structure. The PSC solubility was better than ASC, and the ΔH was lower. Therefore, PSC is probably more functional than ASC probably due to a less compact structure. One of the novel aspects of this work is the fact of employing a mixture of different species by-products, and in this sense, all these results could be used as a basis for crafting strategies to assist the reutilization of waste and by-products from the local markets or big distribution centers. Therefore, both extracted collagens could be an alternative for the food, pharmacological, and biomedical industries.

ACKNOWLEDGEMENT

The authors thank FONSEC-SEP-CONACyT for the project support.

REFERENCES

- Ahmed, R., Tilahun, A.G., Cho, J., Chun, B. 2018. Application of bacterial collagenolytic proteases for the extraction of type I collagen from the skin of bigeye tuna (*Thunnus obesus*). LWT- Food Science and Technology. 89: 44-51.
- Ali, M.A.M., Benjakul, S., Kishimura, H. 2017. Molecular characteristics of acid and pepsin soluble collagens from the scales of golden carp (*Probarbus jullieni*). Emirates Journal of Food and Agriculture. 29(6): 450-457.
- Barth, A., Zscherp, C. 2002. What vibrations tell about proteins. Quarterly Reviews of Biophysics. 35(4): 369-430.
- Benjakul, S., Thiansilakul, Y., Visessanguan, W., Roytrakul, S., Kishimura, H., Prodpran T., Meesane, J. 2010. Extraction and characterization of pepsin-solubilized collagens from the skin of bigeye snapper (*Priacanthus tayenus* and *Priacanthus macracanthus*). Journal of the Science of Food and Agriculture. 90(1): 132-138.
- Chi, C.F., Cao, Z.H., Wang, B., Hu, F.Y., Li, Z.R., Zhang, R. 2014. Antioxidant and Functional Properties of Collagen Hydrolysates from Spanish Mackerel Skin as Influenced by Average Molecular Weight. Molecules. 19(8): 11211-11230.
- Duconseille, A., Astruc, T., Quintana, N., Meersman, F. 2015. Gelatin structure and composition linked to hard capsule dissolution: A review. Food Hydrocolloids. 43: 360-372.

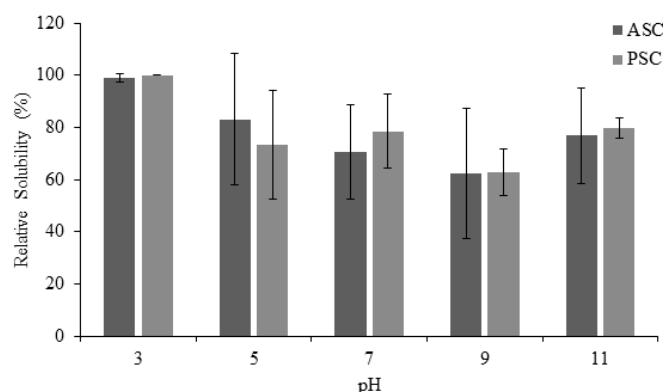


Figure 3. Relative solubility (%) of acid soluble collagen (ASC) and pepsin soluble collagen (PSP) from mixed by-products of different species at different pH. All the values are mean \pm standard deviation ($n=3$).

Figura 3. Solubilidad relativa (%) de colágeno soluble en ácido (ASC) y colágeno soluble en pepsina (PSC) derivados de una mezcla de subproductos de diferentes especies de pescado a diferentes pH. Los valores corresponden a la media \pm desviación estándar ($n=3$).

- Elango, J., Wua, W., Wang, N., He, L., Bin, B. 2014. Isolation, purification and characterization of pepsin soluble collagen isolated from silvertip shark (*Carcharhinus albimarginatus*) skeletal and head bone. *Process Biochemistry* 49: 1764-1777.
- García-Sifuentes, C.O., Scheuren-Acevedo, S.M., Zamorano-Apodaca, J.C. 2020. Exploring different by-products considered as residues by the fishery industry in México. *Biotechnia*. XXII(2): 61-69.
- Hamdan, F.S., Sarbon, N.M. 2019. Isolation and characterization of collagen from fringescale sardinella (*Sardinella fimbriata*) waste materials. *International Food Research Journal*. 26(1): 133-140.
- Hong, H., Fan, H., Chalamaiah, M., Wu, J. 2019. Preparation of low-molecular-weight, collagen hydrolysates (peptides): Current progress, challenges, and future perspectives. *Food chemistry*. 30(15): 125222.
- Jie, L., Wang, M., Qiao, Y., Tian, Y., Liu, J., Qin, S., Wu, W. 2018. Extraction and characterization of type I collagen from skin of tilapia (*Oreochromis niloticus*) and its potential application in biomedical scaffold material for tissue engineering. *Process Biochemistry*. 74: 153-163.
- Karayannakidis, D.P., Zotos, A. 2016. Fish Processing By-Products as a Potential Source of Gelatin: A Review. *Journal of Aquatic Food Product Technology*. 25(1): 65-92.
- Kosseva, M.R. 2013. Sources, Characterization, and Composition of Food Industry Wastes. In: *Food Industry Wastes*. R.M Kosseva y C. Webb (Ed.), pp 37-60. Elsevier Inc. USA.
- Leilei, S., Bafang, L., Wenkui, S., Leilei, S., Hu, H. 2017b. Characterization of Pacific cod (*Gadus macrocephalus*) skin collagen and fabrication of collagen sponge as a good biocompatible biomedical material. *Process Biochemistry*. 63: 229-235.
- Leilei, S., Hu, H., Bafang, L., Zhang, Y. 2017a. Characterization of acid- and pepsin-soluble collagen extracted from the skin of Nile tilapia (*Oreochromis niloticus*). *International Journal of Biological Macromolecules*. 99: 8-14.
- Liu, D., Wei, G., Li, T., Hu, J., Lu, N., Regenstein, J.M., Zhou, P. 2015a. Effects of alkaline pre-treatments and acid extraction conditions on the acid-soluble collagen from grass carp (*Ctenopharyngodon idella*) skin. *Food Chemistry*. 172: 836-843.
- Liu, D., Zhang, X., Li, T., Yang, H., Zhang, H., Regenstein, J.M., Zhou, P. 2015a. Extraction and characterization of acid-and pepsin-soluble collagens from the scales, skins and swim-bladders of grass carp (*Ctenopharyngodon idella*). *Food Bioscience*. 9: 68-74.
- Matmaroh, K., Benjakul, S., Prodpran, T., Encarnacion, A., Kishimura, H. 2011. Characteristics of acid soluble collagen and pepsin soluble collagen from scale of spotted golden goatfish (*Parupeneus heptacanthus*). *Food Chemistry*. 129(3): 1179-1186.
- Nagai, T., Suzuki, N. 2000. Isolation of collagen from fish waste material-skin, bone and fins. *Food Chemistry*. 68(3): 277-281.
- Onouma, K., Sootawat, B., Thammarat, K., Hideki, K. 2014. Characteristics of collagens from the swim bladders of yellowfin tuna (*Thunnus albacares*). *Food Chemistry*. 155: 264-270.
- Pal, G.K., Suresh, P.V. 2016. Sustainable valorization of seafood by-products: Recovery of collagen and development of collagen-based novel functional food ingredients. *Innovative Food Science and Emerging Technologies*. 37: 201-215.
- Pal, G.K., Suresh, P.V. 2017. Comparative assessment of physico-chemical characteristics and fibril formation capacity of thermostable carp scales collagen. *Materials Science and Engineering*. 70(1): 32-40.
- Pal, G.K., Nidheesh, T., Suresh, P.V. 2015. Comparative study on characteristics and in vitro fibril formation ability of acid and pepsin soluble collagen from the skin of catla (*Catla catla*) and rohu (*Labeo rohita*). *Food Research International*. 76(3): 804-812.
- Plepis, A.M.D.G., Goisis, G., Das-Gupta D.K. 1996. Dielectric and Pyroelectric Characterization of Anionic and Native Collagen. *Polymer Engineering & Science*. 36(24): 2932-2938.
- Rashidy, A.A., Ahmed, G., Abd, E.H.G., Abu, H., Shaymaa, I., Habib,., Badr, N.A., Badr, A. 2015. Chemical and biological evaluation of Egyptian Nile Tilapia (*Oreochromis niloticus*) fish scale collagen. *International Journal of Biological Macromolecules*. 79: 618-626.
- Serrano, G., Velásquez, L. 2011. Estandarización de un proceso de extracción de colágeno a partir de los residuos de fileteo de tilapia (*Oreochromis sp*) y cachama (*Piaractus brachypomus*). Tesis de Maestría. Universidad Nacional de Colombia.
- Slimane, E.B., Sadok, S. 2018. Collagen from cartilaginous fish by-products for a potential application in bioactive film composite. *Marine Drugs*. 16(6): 211.
- Solari, A., Cordova, J.S. 2015. Extracción de Colágeno proveniente de residuos del Procesamiento de (*Engraulis ringes*) "Anchoqueta". *Ciencia e Investigación*. 18(2): 65-68.
- Sun, L., Hou, H., Li, B., Zhang, Y. 2017. Characterization of acid- and pepsin-soluble collagen extracted from the skin of Nile tilapia (*Oreochromis niloticus*). *International Journal of Biological Macromolecules*. 99: 8-14.
- Tamilmozhi, S., Veeruraj, A., Arumugam, M. 2015. Isolation and characterization of acid and pepsin-solubilized collagen from the skin of sailfish (*Istiophorus platypterus*). *Food Research International*. 54(2): 1499-505.
- Tan, Y., Chang, S.K.C. 2018. Isolation and characterization of collagen extracted from channel catfish (*Ictalurus punctatus*) skin. *Food Chemistry*. 242(1): 147-155.
- Thuy, M.L.T., Okazaki E., Osako, K. 2014. Isolation and characterization of acid-soluble collagen from the scales of marine fishes from Japan and Vietnam. *Food Chemistry*. 149: 264-270.
- Välimaa, A.L., Mäkinen, S., Mattila, P., Marnila, P., Pihlanto, A., Mäki, M., Hiidenhovi, J. 2019. Fish and fish side streams are valuable sources of high-value components. *Food Quality and Safety*. 3(4):209-226.
- Vázquez, O., Caire, F.A., Higuera, C.G., Hernández, W.G. 1997. High performance liquid chromatographic determination of free amino acids in Shrimp. *Journal Liquid Chromatography*. 18(10): 2059-2068.
- Veeruraj, A., Arumugam, M., Balasubramanian, T. 2013. Isolation and characterization of thermostable collagen from the marine eel-fish (*Evenchelys macrura*). *Process Biochemistry*. 48: 1592-1602.
- Veeruraj, A., Arumugam, M., Ajithkumar, T., Balasubramanian, T. 2015. Isolation and characterization of collagen from the outer skin of squid (*Doryteuthis singhalensis*). *Food Hydrocolloids*. 43: 708-716.
- Wang, J., Pei, X., Liu, H., Zhou, D. 2017. Extraction and characterization of acid-soluble and pepsin-soluble collagen from skin of loach (*Misgurnus anguillicaudatus*). *International Journal of Biological Macromolecules*. 106: 544-550.

- Yang, Y., Li, C., Song, W., Wang, W., Qian, G. 2016. Purification, optimization and physicochemical properties of collagen from soft-shelled turtle calipash. *International Journal of Biological Macromolecules*. 89: 344-352.
- Yousefi, M., Ariffin, F., Huda, N. 2017. An alternative source of type I collagen based on by-product with higher thermal stability. *Food Hydrocolloids*. 63: 372-382.
- Yuqing, T., Sam, K. C., Chang. 2017. Isolation and characterization of collagen extracted from channel catfish (*Ictalurus punctatus*) skin. *Food Chemistry*. 242: 147-155.
- Zamonnano-Apodaca, J.C., Garcia-Sifuentes, C.O., Carvajal-Millán, E., Vallejo-Galland, B., Scheuren-Acevedo, S.M., Lugo-Sánchez, M.E. 2020. Biological and functional properties of peptide fractions obtained from collagen hydrolysate derived from mixed by-products of different fish species. *Food Chemistry*. 331: 127350.
- Zhang, J., Duan, R. 2017. Characterization of acid-soluble and pepsin-solubilized collagen from frog (*Rana nigromaculata*) skin. *International Journal of Biological Macromolecules*. 101: 638-642.
- Zhang, J., Duan, R., Huang, L., Song, Y., Regenstein, J.M. 2014. Characterization of acid-soluble and pepsin-solubilized collagen from jellyfish (*Cyanea nozakii Kishinouye*). *Food Chemistry*. 150: 22-26.
- Zhu, S., Yuan, Q., Yang, M., You, J., Yin, T., Gu, Z., Hu, Y., Xiong, S. 2019. A quantitative comparable study on multi-hierarchy conformation of acid and pepsin-solubilized collagens from the skin of grass carp (*Ctenopharyngodon idella*). *Materials science and engineering*. 96: 446-457.