



**Biotecnia**

ISSN: 1665-1456

Universidad de Sonora, División de Ciencias Biológicas y de la Salud

Gómez-Rodríguez, Gabriel Humberto; Lizardi-Mendoza, Jaime; Argüelles-Monal, Waldo; Álvarez-Bajo, Osiris; López-Franco, Yolanda Leticia  
Chemical modifications of galactomannans: synthesis and structure-function analysis  
Biotecnia, vol. 25, no. 2, 2023, May-August, pp. 126-135  
Universidad de Sonora, División de Ciencias Biológicas y de la Salud

DOI: <https://doi.org/10.18633/biotecnia.v25i2.1883>

Available in: <https://www.redalyc.org/articulo.oa?id=672975613004>

- ▶ How to cite
- ▶ Complete issue
- ▶ More information about this article
- ▶ Journal's webpage in redalyc.org

UNEM 

Scientific Information System Redalyc

Network of Scientific Journals from Latin America and the Caribbean, Spain and Portugal

Project academic non-profit, developed under the open access initiative

# Chemical modifications of galactomannans: synthesis and structure-function analysis

Modificaciones químicas de galactomananos: síntesis y análisis estructura-función

Gabriel Humberto Gómez-Rodríguez<sup>1</sup>, Jaime Lizardi-Mendoza<sup>1</sup>, Waldo Argüelles-Monal<sup>1</sup>, Osiris Álvarez-Bajo<sup>2</sup>, Yolanda Leticia López-Franco<sup>1\*</sup>

<sup>1</sup> Research Center for Food and Development, CIAD, A.C., Carretera Gustavo Enrique Astiazaran Rosas No. 46, Hermosillo 83304, Sonora, Mexico.

<sup>2</sup> Department of Physics Research, University of Sonora, Rosales and Encinas, Hermosillo 83000, Sonora, Mexico.

## ABSTRACT

Galactomannans (GM) are multifunctional polysaccharides made up of a  $\beta$  (1 $\rightarrow$ 4)-D-mannopyranose backbone with D-galactopyranose branches linked by  $\alpha$  (1 $\rightarrow$ 6) glycosidic bonds. They are obtained from plants endosperm of seeds by different extraction methods. The chemical modification of polysaccharides has been used as strategy to change structural characteristics and functional properties, as solubility, polarity, ionic charge, bioactivity, and others. Reported modifications of GM includes hydrolyzation, esterification, etherification, and addition of functional groups as sulphates or phosphates producing GM derivatives with biological and technological application potentials. Therefore, this review focuses on the synthetic routes and the analysis of the structures of chemically modified GM.

**Keywords:** galactomannans, chemical modifications, esterification, carboxymethyl etherification, addition of functional groups

## RESUMEN

Los galactomananos (GM) son polisacáridos multifuncionales formados por una cadena de  $\beta$  (1 $\rightarrow$ 4)-D-manopiranosas con ramificaciones de D-galactopiranosas unidas por enlaces glucosídicos  $\alpha$  (1 $\rightarrow$ 6). Se obtienen del endospermo de semillas de leguminosas por diferentes métodos de extracción. La modificación química de polisacáridos se ha utilizado como estrategia para cambiar características estructurales y propiedades funcionales, como solubilidad, polaridad, carga iónica, bioactividad, entre otras. Las modificaciones reportadas de GM incluyen hidrólisis, esterificación, eterificación y adición de grupos funcionales como sulfatos o fosfatos que originan derivados de GM con potencial de aplicación biológica y tecnológica. Por lo tanto, esta revisión se centra en las rutas sintéticas y el análisis de las estructuras de los GM modificados químicamente.

**Palabras clave:** galactomananos, modificaciones químicas, esterificación, carboximetilación, adición de grupos funcionales

## INTRODUCTION

The plant cell wall is composed of various polysaccharides, such as cellulose, hemicelluloses, and pectin. Among these, cellulose is the most abundant, constituting 30-50 % of the total cell wall dry mass, while hemicelluloses constitute 20 - 35 % (Pauly and Keegstra, 2008). Based on their main structure, hemicelluloses are grouped into xyloglucans, xylans, and mannans. Galactomannans (GM) are included in the latter group. These are multifunctional macromolecular carbohydrates formed by D-mannopyranose main chain linked by  $\beta$  (1 $\rightarrow$ 4) glycosidic bonds with D-galactopyranose branches linked to the mannan main chain by  $\alpha$  (1 $\rightarrow$ 6) bonds (Figure 1). The mannose/galactose ratio (M/G) varies according to the source and extraction procedures used (Sharma *et al.*, 2022).


GM are commonly obtained from arboreal legume seeds, for example carob or locust bean (*Ceratonia siliqua*), tara (*Caesalpinia spinosa*), guar (*Cyamopsis tetragonoloba* L.), fenugreek (*Trigonella spp*) or mesquite seeds (*Prosopis sp*) (Wielinga, 2009; López-Franco *et al.*, 2013). GM can be distinguished from each other by the M/G ratio which varies between 1.1 to 3.5 approximately. Carob gum has a M/G ratio of 3.5 (Fidan *et al.*, 2020), tara gum 3.0 (Wu *et al.*, 2015), guar and mesquite gum 1.5 (López-Franco *et al.*, 2013; Liyanage *et al.*, 2015), and fenugreek gum with 1.2 (Dhull *et al.*, 2020).

GM are the product of photosynthesis, followed by additional biosynthetic modifications in nature, and have great industrial relevance (Sharma *et al.*, 2022). The structural characteristics of these polysaccharides make them soluble in water at a wide range of temperatures, and chemically and biochemically reactive. Due to their large number of hydroxyl (-OH) groups and the absence of ionic charges in their structure, GM are susceptible to molecular changes (Geronço *et al.*, 2021).

GM derivatives, e.g. obtained by hydrolysis, sulfation, or phosphorylation, provide biological and technological functionalities that are of interest in food, biomedical and other industries (Table 1). This review aims to describe the synthesis and structural analysis of chemically modified GM to improve their physicochemical properties and expand their industrial application.

\*Author for correspondence: Yolanda L. López-Franco  
e-mail: lopezf@ciad.mx

Received: October 31, 2022  
Accepted: February 13, 2023

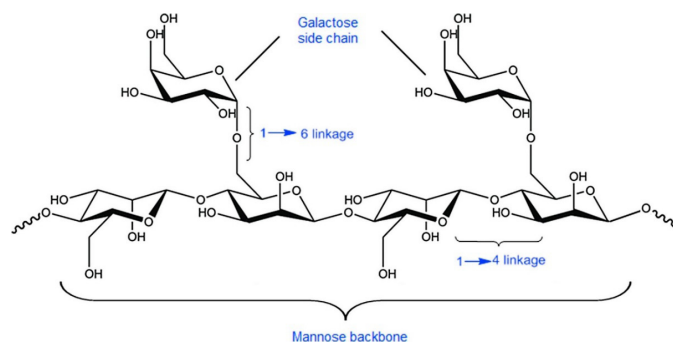

**Figura 1.** Representación esquemática de la estructura química de los galactomananos (George *et al.*, 2019).

**Figure 1.** Schematic representation of the chemical structure of galactomannans (George *et al.*, 2019).

**Tabla 1.** Estructura-función de derivados de galactomananos de diferentes fuentes.

**Table 1.** Structure-function of galactomannan derivatives from different sources.

Galactomannan source	Derivatized obtaining process	Functional properties	Reference
<i>Cyamopsis tetragonolobus</i> L.	Hydrolysis	Hepatoprotective	Wu <i>et al.</i> , 2019
<i>Cerantonía siliqua</i>	Hydrolysis	Immunomodulatory	Chen <i>et al.</i> , 2018
<i>Sesbania cannabina</i>	Hydrolysis	Antioxidant and immunomodulatory	Tao <i>et al.</i> , 2021
<i>Caesalpinia pulcherrima</i>	Hydrolysis	Dietary fiber	Buriti <i>et al.</i> , 2014
<i>Caesalpinia ferrea</i>	Sulfation	Antiviric	Lopes <i>et al.</i> , 2013
<i>Adenanthera pavonina</i> L., <i>Caesalpinia ferrea</i> Mart., and <i>Dimorphandra gardneriana</i> Tull	Sulfation	Antioxidant and antivirc	Mendes-Marques <i>et al.</i> , 2015
<i>Cyamopsis tetragonolobus</i> L.	Esterification	Emulsifier	Sarkar and Singhal, 2011
<i>Cyamopsis tetragonolobus</i> L.	Esterification	Emulsifier	Cerqueira <i>et al.</i> , 2019
<i>Sesbania cannabina</i>	Esterification	Film former	Liu <i>et al.</i> , 2021
<i>Cyamopsis tetragonolobus</i> L.	Carboxymethylation	Binder	Wang <i>et al.</i> , 2021
<i>Cyamopsis tetragonolobus</i> L.	Carboxymethylation	Thickener	Iqbal <i>et al.</i> , 2020
<i>Cassia obtusifolia</i>	Carboxymethylation	Gelling agent	Verma <i>et al.</i> , 2020
<i>Cyamopsis tetragonolobus</i> L.	Carboxymethylation	Gelling agent	Li <i>et al.</i> , 2021
<i>Cyamopsis tetragonolobus</i> L.	Etherification	Corrosion inhibitor	Biswas <i>et al.</i> , 2017
<i>Cyamopsis tetragonolobus</i> L.	Etherification	Corrosion inhibitor	Singh <i>et al.</i> , 2021
<i>Cyamopsis tetragonolobus</i> L.	Phosphorilation	Antioxidant	Wang <i>et al.</i> , 2014

## STRUCTURE, PHYSICOCHEMICAL CHARACTERISTICS AND APPLICATIONS OF GALACTOMANNANS

GM is a nonionic polysaccharide conformed by a linear chain of  $\beta$ -(1 $\rightarrow$ 4)-D-mannose with branches of  $\alpha$ -(1 $\rightarrow$ 6)-D-galactose, where the M/G ratio and molecular weight is closely related to its structure-function (Wielinga and Meyhall, 2009). Previously it was thought that these galactose units are linked at regular intervals, that is, alternate in each mannose of the main chain. However, subsequent enzymatic degradation analysis, NMR spectroscopy and computer simulation suggested the irregularity of side chains in such a way that the galactose units are arranged in the form of random doublets and triplets along the main chain (Mudgil *et al.*, 2014; Gupta and Variyar, 2018). Said random substitution of the galactose units leads to regions of high and low substitution in the mannan main chain (Figure 2). In galactose-

poor regions, non-covalent interactions between polymer chains could take place, while in galactose-rich regions, this high substitution prevents the formation of more organized structures due to steric hindrance of the side chains, which also results in a high solubility in aqueous solutions (Saurabh *et al.*, 2013).

The GM molecular weight one of the highest among natural polysaccharides, it could be up to  $2 \times 10^6$  Da, measured by size exclusion chromatography with multiangle laser light scattering (López-Franco *et al.*, 2017; Gupta and Variyar, 2018). Due to the native characteristics of GM, it exhibits non-Newtonian behavior in solution and, like most polysaccharides with these characteristics, it has a pseudoplastic, or shear-thinning nature. This shear-thinning behavior of aqueous solutions increases with GM concentration and molecular weight. The apparent viscosity of these solutions demonstrates a decrease with an increasing shear rate. By

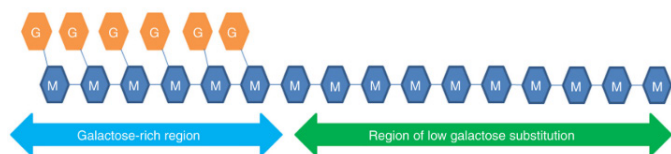


Figura 2. Representación esquemática de las regiones altamente sustituidas y poco sustituidas en galactosa (G) en la cadena principal de manosa (M) (Gupta y Variyar, 2018).

Figure 2. Schematic representation of galactose (G) highly substituted and low substituted regions in the mannose backbone (M) (Gupta y Variyar, 2018).

increasing the shear rate, disruption predominates over formation of new entanglements; molecules align in the direction of the flow and consequently a decrease in viscosity is observed (Hussain *et al.*, 2015). However, at very low and very high shear rates, GM solutions show Newtonian behavior (Whistler and Hymowitz, 1979).

Due to their hydrophilic character, GM have unique functional properties for various food uses. Among these are the water retention capacity, reduced evaporation rate, modification of the formation of ice crystals, regulation of rheological behavior and its emulsifying capacity (Gupta and Variyar, 2018). In this sense, the addition of GM in the preparation of white bread generally results in a greater absorption of water at the time of dough formation. Rodge *et al.* (2012) reported an 8 % increase in water absorption capacity with the addition of GM at 1 % in wheat flour; likewise, an increase in loaf volume of 30 % was observed compared to control. This behavior can be attributed mainly to the hydrophilic nature of the polysaccharide and its capacity to retain water during baking, in such a way that said moisture evaporates through an increase in vapor pressure, resulting in an improvement in bread volume.

On the other hand, the use of GM as an additive for ice cream has been a strategy to prevent the development of crystals and as a texturizing agent during freezing, however, the use of this polysaccharide is only suitable for short-duration ice cream at high temperature. This, mainly because it has a short hydration time, in addition, the GM is thermodynamically incompatible with milk proteins of the food system, given the phase separation between both biopolymers due to hydrophilicity differences of the protein and GM (Mudgil and Barak 2014). Therefore, to avoid phase separation in this type of product, GM is generally added together with other hydrocolloids, such as k-carrageenan (BahramParvar *et al.*, 2013; Javidi *et al.*, 2016). Also, GM have been used in the preparation of low-fat yogurt with a high content of dietary fiber. Lee and Chang (2016) reported a yogurt preparation with improved rheological characteristics by adding GM, which resulted in reduced syneresis and improved texture with acceptable sensory characteristics comparable to control products.

Additionally, GM are part of the most popular and widely used hydrocolloids in the formulation of ketchup-type sauces, to prevent syneresis during freezing and provide stability in heating by cooking. Torbica *et al.* (2016) have

previously reported the preparation of a ketchup-type sauce derived from tomato pomace, with acceptable sensory and textural qualities using GM and xanthan gum as thickeners, managing to reduce whey loss. Likewise, this hydrocolloid has been added in the formulation of mayonnaise and dressings, to reduce the dispersed phase (oil) and increase the water content in the emulsion to create low-fat products. However, due to its hydrophilic characteristics, the use of native GM is restricted the formulation of systems that contain water as a dispersant phase. The uses and potential applications of GM could expand with the knowledge of different synthetic routes of chemical modification applied to obtain changes on the structure-function relationship of polysaccharide.

## CHEMICAL MODIFICATION OF GALACTOMANNANS

### Hydrolyzed galactomannans

Hydrolysis, either by chemical methods or enzymatic reactions, is one of the most important and practical strategies for the modification of polysaccharides such as GM (Geronço *et al.*, 2021). In the enzymatic method, the galactose side chains or the mannose main chain, can be hydrolyzed by  $\alpha$ -galactosidase and  $\beta$ -mannanase, respectively, it is simple to control, and the reaction conditions are mild compared to chemical hydrolysis which is non-specific and highly aggressive (Ba *et al.*, 2012). The GM functional properties are greatly influenced by their molecular weight, and based on this, the hydrolysis of the mannose main chain and galactose side chain results in a strategy for the modification of its viscoelastic properties (Zhou *et al.*, 2016).

For this purpose, hydrochloric, sulfuric, and trifluoroacetic acids are used, in addition to the application of heat to accelerate the hydrolysis reaction of the side chains by mild conditions (Biermann, 1989). However, this type of hydrolysis results in a difficult elimination of acidic remnants with the probable exception of trifluoroacetic acid, which can be removed by rotary evaporation due to its volatility at not very high temperatures (Liu *et al.*, 2020). Hence, research on obtainment and fractionation of GM hydrolysates has focused mainly on the use of enzymatic catalysis as a less complicated way to obtain manno oligosaccharides.

Wu *et al.* (2019) evaluated the hepatoprotective effect of GM partially hydrolyzed with  $\beta$ -mannanase from *Rhizomucor miehei*. The composition of these hydrolysates was 24.9 % (w/w) of manno oligosaccharides with a degree of polymerization of < 7. The average molecular weight of the hydrolyzed GM was  $2.5 \times 10^4$  Da identified by gel permeation chromatography, the decrease of which was effective by enzymatic treatment. These hydrolyzed GM had a hepatoprotective effect in Kunming mice, by increasing the activity of the superoxide dismutase and glutathione peroxidase antioxidant enzymes. This event, in turn, decreased alcohol-induced lipid peroxidation, and thus the integrity and fluidity of cell membranes.

Similarly, Chen *et al.* (2018) hydrolyzed GM with 8 U/mL of a *Pichia pastoris* thermostable  $\beta$ -mannanase at different times of action on the substrate at 50 °C. Native GM had a

higher molecular weight than the hydrolyzed ones with a significant decrease from  $5.58 \times 10^6$  to  $3.18 \times 10^3$  Da, demonstrating the presence of manooligosaccharides after 24 h. These hydrolysates exhibited immunomodulatory activity by stimulating the production of TNF- $\alpha$  in RAW 264.7 cells, an important cytokine that intervenes in the inflammation and apoptosis processes.

Recently, hemicellulosic polysaccharides such as GM and their degradation products are gaining more attention due to their excellent *in vitro* and *in vivo* antioxidant enhancement and immunomodulatory activities. Tao *et al.* (2021) hydrolyzed GM from  $\beta$ -endo-mannanase of *Trichoderma reesei* and evaluated its antioxidant and immunomodulatory effect. GM hydrolysates showed a strong protective effect against induced oxidative stress, using a model of RAW 264.7 cells injured with hydrogen peroxide, as indicated by superoxide dismutase activity and malondialdehyde content.

Structurally, manooligosaccharides continue to be only the repeating unit of GM in its native form, as its general composition and most of its physicochemical properties are not affected. For example, the FTIR spectrum is very similar to GM and their hydrolysates that show characteristic absorption bands of this polysaccharide as reported in the literature (Cerqueira *et al.*, 2011; Mudgil *et al.*, 2012). Furthermore, the partial hydrolysis of GM leads to a decrease in the polydispersity index by up to one-third, this is due to the general reduction of all molecular weight populations (Buriti *et al.*, 2014). Partially hydrolyzed GM, as it does not suffer significant alterations, seems to be a potential alternative, increasing the availability of new food ingredients, as a source of dietary fiber.

### Sulfated galactomannans

A promising derivatized structure of GM is the synthesis of their compounds that contain a sulfonic group ( $-\text{SO}_3\text{H}$ ) or their salt ( $-\text{SO}_3\text{Na}$ ). The addition of this functional group in a biopolymer macromolecule changes its physicochemical characteristics, increasing its solubility in water and its biodegradability (Kazachenko *et al.*, 2020). The presence of the  $-\text{SO}_3\text{H}$  group in the polysaccharide structure (Figure 3) provides important properties, since the sulfate group has a negative charge in a determined pH range to electrostatically bind to positively charged molecules. However, the synthesis of sulfated polysaccharides is a challenge due to the many stereocenters in their structure, the presence of similar functional groups, and the need to preserve the orientation of the glycosidic bonds. Therefore, from a chemical perspective, sulfated polymeric structures are synthesized by sulfating natural polysaccharides or polymeric analogs (Caputo *et al.*, 2019).

There are many challenges associated with polysaccharide sulfation, such as low -OH group reactivity, poor solubility in organic solvents, regioselectivity, degree of sulfation, and isolation of the derivatized polysaccharide. There are scarce solvents in which both the polysaccharide and the sulfated derivatized are soluble, and the reactions are not complete

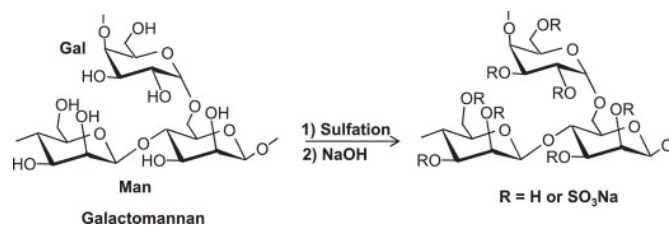


Figura 3. Esquema del proceso de sulfatación de galactomannanos (Muschin *et al.*, 2016)

Figure 3. Scheme of sulfation process of galactomannans (Muschin *et al.*, 2016).

(Richter and Klemm, 2003). On the other hand, identifying and targeting a specific sulfation site is complicated due to the many -OH groups in the polysaccharide. Thus, protecting groups are required which increases the complexity, and decreases yield. Furthermore, sulfating multiple -OH on a single monosaccharide unit is complicated due to electrostatic repulsion between neighboring  $-\text{SO}_3\text{H}$  adding a grade of complexity to the derivatization (Al-Horani and Desai, 2010).

Given the structure-function relationship of polysaccharides, the degree of sulfation becomes an important parameter to control, when synthesizing sulfated GM (Caputo *et al.*, 2019). The chlorosulfonic acid and sulfuric acid are currently used in the sulfation process of GM as a sulfating reagent in presence of a strong base (pyridine or piperidine), and its subsequent isolation by converting it into sodium salt. In this sense, the use of chlorosulfonic acid is the most used route to obtain sulfated GM with different sulfation degrees. In contrast to these reagents, sulfamic acid is a stable non-hygroscopic crystalline substance with the reactivity like that of the  $-\text{SO}_3$  tertiary amine complex that in the presence of urea, which plays a role of the main catalyst, its sulfation occurs (Kuznetsov *et al.*, 2018).

In this sense, Kazachenko *et al.* (2021) synthesized sulfated GM from sulfamic acid-urea complexes at different reaction times and temperatures. In this study they determined that at 80 °C and for 60 min, the highest possible degree of sulfation (1.67) is obtained by this synthetic route. Thus, from these milder conditions it is possible to have a more effective sulfation process from eco-friendly reagents than from the conventional chlorosulfonic acid route. Qin *et al.*, (2020) evaluated a response surface methodology (RSM) study for the optimization of the sulfation process by varying the chlorosulfonic acid / pyridine ratio, temperature, and reaction time. This study provided optimal sulfation conditions for GM with a 66 % degree of sulfation, which were an acid chlorosulfonic / pyridine ratio of 3:1, reaction time of 4 h and reaction temperature of 40 °C. Two characteristic absorption peaks appeared in FTIR spectra at 1250  $\text{cm}^{-1}$  and 806  $\text{cm}^{-1}$ , indicating sulfation of GM. The  $^{13}\text{C}$ -CP/MAS NMR spectra confirmed that the substitution position was mainly at C6 in sulfated GM.

Previously, Wang *et al.* (2014) optimized the sulfation process by varying the same parameters by RSM. In this study, a mathematical model was constructed where the optimal reaction conditions of GM were a chlorosulfonic

acid / pyridine ratio of 1.27, reaction time of 120 min, and reaction temperature of 50.8 °C. Among the three reaction parameters studied, reaction time was the most significant factor to have an effect on the sulfation process, based on the slope gradient in the 3D response surface plots (Wang *et al.*, 2014; Qin *et al.*, 2020).

Lopes *et al.* (2013) sulfated GM with chlorosulfonic acid in pyridine/formamide to study the inhibition of herpes simplex virus (HSV-1) and poliovirus (PV-1). These authors reported an 8.7 % degree of sulfation obtained from three consecutive sulfation procedures. FTIR analysis demonstrated the presence of sulfated polysaccharides with a band at 1255 cm<sup>-1</sup> which refers to the vibration of asymmetric stretching of the ester sulfate bond (S=O). These sulfated products inhibited HSV-1 and PV-1 with an IC<sub>50</sub> of 405 µg/mL and 1.73 µg/mL, respectively, interfering various stages of viral replication, adsorption, and penetration in both cases.

Similarly, Mendes-Marques *et al.* (2015) sulfated GM with the same method for the inhibition of dengue virus, in this case they reported a 33 - 39 % degree of sulfation and mentioned the importance of this parameter in its activity. Confirmation of the sulfation process was performed by FTIR spectroscopic analysis with the presence of a band at 1259 cm<sup>-1</sup> corresponding to the stretching vibrations of the S=O group mentioned above. Likewise, these derivatized polysaccharides presented a positive correlation between the degree of sulfation and the antiviral activity against the dengue virus DENV-2 and its antioxidant capacity.

### Galactomannan fatty acid esters

Chemical modification has conventionally been used as a strategy to change the hydrophilicity of polysaccharides, through the formation of esters. The esterification of GM is carried out regioselectively, this is that the primary alcohol will always be more nucleophilic than the secondary alcohol in the polysaccharide structure (Kanelli and Topakas, 2017). Their respective rate constants for the primary and secondary alcohols do not change during the esterification process, where primary alcohol reacts faster than secondary alcohol, decreasing its concentration as the reaction progresses. Therefore, eventually, the reaction rates will become similar and the regioselectivity will decrease (Fox *et al.*, 2011; Koschella *et al.*, 2006).

Esterification generally involves the reaction of an alcohol with an acylating agent, such as vinyl carboxylates, acyl chlorides, acid anhydrides, as well as the carboxylic acids themselves. On this basis, carboxylic acids have been obtained by Fischer esterification conventionally by strong acid catalysis (concentrated H<sub>2</sub>SO<sub>4</sub>), or by in situ activation of the carboxylic group under mild conditions for the acylation of polysaccharides (Cumpstey, 2011). Previously, different synthetic routes have been reported to obtain GM esters, through both chemical and enzymatic routes, either using strong acids or strong bases to react with the acyl donor or using enzymes such as lipase or transferases to catalyze the reaction.

Fujioka *et al.* (2009) synthesized GM esters through the esterification of the succinate group in the polymer chains. They reacted native GM with succinic anhydride, using DMSO as a solvent and 4-dimethylaminopyridine as a catalyst. FTIR spectroscopy was used to demonstrate the presence of the ester group, showing absent absorption bands at 1735 cm<sup>-1</sup> and 1550 cm<sup>-1</sup> in the spectrum of the native GM indicating the esterification of the polysaccharide with a degree of substitution of 0.6. In another study, Shenoy and Melo (2010) esterified hydroxypropyl GM using acetic anhydride as donor acyl and pyridine as a catalyst, to be used as filler in unsaturated polyester compounds. The esterification of this polysaccharide leads to an increase in the hydrophobic character of the resulting polymer where the variation of the reaction time results in the formation of esterified GM with degrees of substitution of 0.58, 1.1, 1.8, and 3.0. The FTIR of the products showed an increase in the intensity of the carbonyl band obtained in the region of 1735 - 1750 cm<sup>-1</sup> derived from the increase in the degree of substitution of the polymer.

On the other hand, Iqbal *et al.* (2020a) reported GM esters of aliphatic carboxylic acids of medium and long chain (C5-C18) from acyl chlorides, examining their physical properties concerning the length of the fatty acid chain and degree of substitution. The FTIR spectrum showed typical bands of a structurally native GM for all samples, added to the bands at 1754 cm<sup>-1</sup> and 723 cm<sup>-1</sup> corresponding to the C=O bond of the ester group and the oscillating vibrations of the -CH<sub>2</sub> groups of the aliphatic chain, respectively. However, this type of reaction leads to polymer degradation and not very high degrees of substitution due to the use of aggressive catalysts with respect to pH.

An alternative to this process has been biocatalysts through the use of enzymes to modify the structure of polysaccharides, with the advantage that it is often chemo specific, which allows the synthesis of products with well-defined or stereo-specific structures (Cumpstey, 2011; Cheng and Gu, 2012). Some enzymes have a wide tolerance to the substrate and catalyze reactions in generic structures, hence, esterases, proteases, and lipase have been used to catalyze the formation of esters in polysaccharides, even being an unnatural function of the enzyme. This is because they do not differentiate the -OH groups, but the enzyme will tend to act on the -OH group (esterification) or ester (hydrolysis) that is more sterically accessible, that is, located in primary positions (Cumpstey, 2011). Enzymes normally require at least an amount of water to carry out their action correctly, being structurally unstable in non-aqueous media. However, water is not a good medium for ester synthesis, in these conditions is reversible. When the water is in excess, the chemical equilibrium of the reaction tends towards hydrolysis, so the degree of substitution of the products would be very low (Alissandratos *et al.*, 2010).

On the other hand, polar solvents such as DMSO and DMF can remove essential catalytic water from the surface of enzymes, inactivating them and thus have lower hydrogen bonding capacity leading to higher enzymatic activity (Gu

and Cheng, 2005). However, there are no well-established protocols for GM enzymatic esterification, unlike starch and cellulose, which are the most widely used for this chemical modification (Yang and Wang, 2003; Rajan *et al.*, 2008). Most studies are mainly focused on their interaction with hydrophobic compounds and not on the application of GM esters.

In that context, Sarkar and Singhal (2011) elaborated GM succinate and oleate as microencapsulation material in O/W emulsions. The addition of these aliphatic chains leads to an improvement in its emulsifying capacity with low droplet size and viscosity, which makes it an important material for the protection of different food components. In another study, Cerqueira *et al.* (2019) elaborated GM acetate nanomicelles as carrier material for hydrophobic compounds such as curcumin. These modifications to the GM led to an encapsulation efficiency greater than 99 % and a  $\zeta$  potential of -18.1 mV, indicating an effective charge of curcumin and repulsion between the nanomicelles to prevent them from agglomerating.

In contrast, in the esterification of GM for the addition of aliphatic chains, hydrophobic films of GM acetate have also been developed as a barrier system and protection against water in food packaging (Liu *et al.*, 2021). In this work, the chemical modification provides a good hydrophobicity to the film with a contact angle of 107 ° and a decrease in its water vapor permeability properties. Thus, the synthesis of these amphiphilic compounds contributes to the development of new compounds for hydrophobic systems. In addition, it will be of vital importance when establishing the synthetic routes to produce GM esters and choose the appropriate compounds for the correct esterification of the polysaccharide.

## OTHER DERIVATIZED GALACTOMANNANS

### Carboxymethyl galactomannan

Carboxymethyl galactomannan (CMG) is an anionic GM derivative with a high dissolving rate of viscosity and good stability. Various synthetic routes have been developed to obtain CMG (Figure 4). This is produced by reacting monochloroacetic acid or its sodium salt with deprotonated GM. A strong base, such as sodium hydroxide, is needed to activate the -OH group of GM for nucleophilic substitution (Cumpstey, 2011). Previous studies related to CMG preparation used organic solvents such as acetone, ethanol, isopropanol, and butanol as the medium (Gao and Grady, 2018). GM has been previously dissolved in water, however, the use of excess water in a ratio of approximately 50:1 generally has poor compatibility, because water can hydrolyze the alkylating agent (Dodi *et al.*, 2011).

The synthesis of CMG is widely studied; Wang *et al.* (2021) obtained CMG as robust water-soluble binder for silicon anodes in lithium-ion batteries, and the  $^1\text{H}$  NMR spectrum shows that carboxymethyl was attached to position C-6. Additionally, in the FTIR spectrum, two new bands appear at 1602  $\text{cm}^{-1}$  and 1411  $\text{cm}^{-1}$  corresponding to the asymmetric and symmetric stretching vibrations of the  $\text{COO}^-$  group

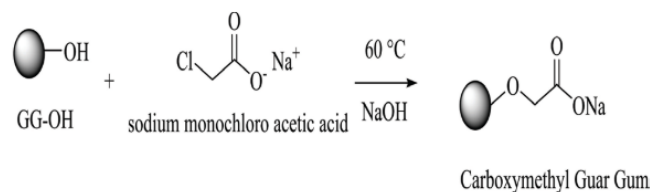


Figura 4. Síntesis de carboximetil galactomanano (CMG) de goma guar (Iqbal *et al.*, 2020)

Figure 4. Synthesis of carboxymethyl galactomannan (CMG) of guar gum (Iqbal *et al.*, 2020).

respectively, which further confirms the carboxymethylation of GM. In another study, Iqbal *et al.* (2020b) synthesized carboxymethylated GM derivatives and their structural characteristics as a synthetic thickener for textile prints. These had a degree of substitution of 0.35, and the FTIR spectrum demonstrates the substitution of carboxymethyl in GM with the bands corresponding to the  $\text{COO}^-$  vibrations that are symmetric or asymmetric at points 1429  $\text{cm}^{-1}$  and 1615  $\text{cm}^{-1}$ , respectively.

The potential applications for CMG can be diverse, for example, Verma *et al.* (2020) evaluated the CMG pharmaceutical applications by making ionotropically gelled beads using sodium diclofenac as a model drug, optimizing its design by RSM. The formulation used was 2.85 % (w/v) CMG and 15 % (w/v)  $\text{CaCl}_2$  where the beads showed a loading efficiency of 95.41 % and a release of 93.32 % of diclofenac during 24 h. In another study, Li *et al.* (2021) fabricated polyelectrolytic gels of CMG and quaternary ammonium GM for the removal of dyes in water contaminated with Congo red and methylene blue as study models. These gels were pH and ion sensitive, with maximum adsorption capacities of 1441 and 94.52 mg/g of Congo red and methylene blue, respectively, mediated by electrostatic interactions.

### Galactomannan alkyl ethers

Etherification of polysaccharides involves the reaction of the saccharide alcohol groups with an alkylating agent, these include alkyl halides (e.g. bromides, chlorides, and iodides), or less commonly, alkyl sulfonates. Typically, a strong base is used to deprotonate a saccharide alcohol to form an alkoxide ion that attacks the alkyl halide, through an  $\text{S}_{\text{N}}2$  mechanism to form a polysaccharide alkyl ether. Usually, the alcohol from which the alkoxide is derived can be used as solvent, but it improves the reaction performance if we use aprotic solvents such as DMF or DMSO (Cumpstey, 2011). Currently, derivatized GM alkyl ethers have been reported, such as: methyl, butyl, benzyl, ethyl acrylate and 2-hydroxypropyl trimethylammonium chloride (HPTAC) GM ethers (Kazachenko *et al.*, 2022a).

The synthesis of methyl and benzyl GM ether has been widely studied, for instance, Mohammed and Ragab (2021) synthesized these GM ethers in a DMSO/paraformaldehyde system using dimethyl sulfate and benzyl chloride as alkylating agents in presence of sodium hydroxide as a catalyst. The correct etherification of the polysaccharide was determi-

ned from FTIR shown new peaks at  $1114\text{ cm}^{-1}$  and  $1056\text{ cm}^{-1}$  indicating C-O stretching vibration of functional group of ether for methyl GM and benzyl GM respectively. In another study, Kazachenko *et al.* (2022b) synthesized GM butyl ether using bromobutane as an alkylating agent in the presence of sodium hydroxide as a catalyst. Etherification was confirmed by FTIR showing absorption bands at  $1077$ ,  $879$ ,  $815$  and  $796\text{ cm}^{-1}$ , corresponding to the vibrations of the ether bond of the -C-O-C- groups.

The potential applications of GM alkyl ethers have not yet been as extensively studied. The etherification of HPTAC has been used as a strategy for obtaining cationic GM as a corrosion inhibitor (Biswas *et al.*, 2017). Similarly, Singh *et al.* (2021) synthesized galactomannan ethyl acrylate ether as a corrosion inhibitor on steel under acidic conditions. However, it is necessary to address the possible applications of all types of GM alkyl ethers including those synthesized from uncharged alkyl groups to obtain a more diverse picture in the use of this type of derivatized GM.

### Phosphorylated galactomannan

The production of phosphorylated GM is carried out by different synthetic routes: phosphoric acid, phosphoric anhydride, phosphorous trichloride (Figure 5), or dimethyl phosphate (Suflet *et al.*, 2006). Furthermore,  $\text{H}_3\text{PO}_4$  and  $\text{H}_3\text{PO}_3$  have been usually used as phosphorylating reagents at higher temperatures, generally leading to a low degree of substitution (0.26, phosphate content 4.05 %) and polysaccharide degradation (Wang *et al.*, 2013). The applications for phosphorylated GM have not been so widely studied, being its antioxidant capacity and its relationship with DS one of the few reports found. In this sense, Wang *et al.* (2014) synthesized phosphorylated GM with  $\text{POCl}_3$  to evaluate the effect of the degree of substitution with respect to its conformation in solution. The degree of substitution varied from 0.35 to 0.52, and the FTIR spectrum showed new peaks around  $1250\text{ cm}^{-1}$  that describe an asymmetric P=O stretching vibration, a shoulder at  $1050\text{ cm}^{-1}$  corresponding to the P-OH bond, which is attributed to the presence of phosphorylated GM. Finally, the antioxidant capacity was increased to a higher DS of 0.52, which indicates that this derivatized polysaccharide could be effective in scavenging radicals *in vitro*.

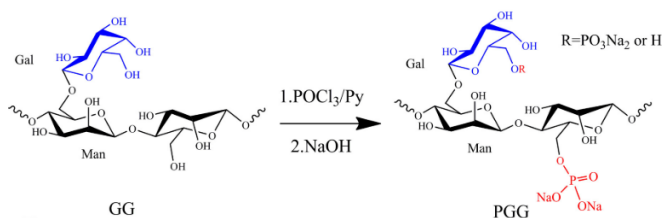


Figura 5. Ruta esquemática para obtener galactomananos fosforilados mediante  $\text{POCl}_3$  (Wang *et al.*, 2014).

Figure 5. Schematic route for obtaining phosphorylated GM by  $\text{POCl}_3$  (Wang *et al.*, 2014).

### CONCLUSIONS

This review highlighted the different chemical modifications and structural characteristics of different derivatized products of GM. Naturally, polysaccharides like these already possess characteristic physicochemical properties such as solubility, swelling, and viscosity inherent in their origin, which are not always desirable for other types of unconventional applications. The chemical modification of GM, on the other hand, leads to structures with new characteristics that can compete with different synthetic excipients already available on the market. This in turn provides excipients that can be less toxic than various synthetic polymers. The future of formulations design using natural polymers and their different chemical modifications is in a strong position. Therefore, natural and derivatized polymers can compete if scientists continue to explore materials and modify them for various formulation designs.

### REFERENCES

- Al-Horani, R. A. and Desai, U. R. 2010. Chemical sulfation of small molecules-advances and challenges, *Tetrahedron*, 66(16), pp. 2907-2918. doi: 10.1016/j.tet.2010.02.015.
- Alissandratos, A., Baudendistel, N., Flitsch, S. L., Hauer, B. and Halling, P. J. 2010. Lipase-catalysed acylation of starch and determination of the degree of substitution by methanolysis and GC, *BMC Biotechnology*, 10, pp. 0-7. doi: 10.1186/1472-6750-10-82.
- Ba, J., Gao, Y., Xu, Q. H. and Qin, M. H. 2012. Research development of modification of galactomannan gums from plant resources, *Advanced Materials Research*, 1628-1631. doi: 10.4028/www.scientific.net/AMR.482-484.1628.
- BahramParvar, M., Tehrani, M. M. and Razavi, S. M. A. 2013. Effects of a novel stabilizer blend and presence of  $\kappa$ -carrageenan on some properties of vanilla ice cream during storage, *Food Bioscience*, 3, pp. 10-18. doi: 10.1016/j.fbio.2013.05.001.
- Biermann, C. J. 1989. Hydrolysis and other cleavage of glycosidic linkages. In: *Analysis of Carbohydrates by GLC and MS*. C.J Biermann and G.D McGinnis (ed.) pp. 27-42. CRC Press, Boca Raton.
- Biswas, A., Pal, S. and Udayabhanu, G. 2017. Effect of chemical modification of a natural polysaccharide on its inhibitory action on mild steel in 15% HCl solution, *Journal of Adhesion Science and Technology*, 31(22), pp. 2468-2489. Doi: 10.1080/01694243.2017.1306912.
- Buriti, F. C., dos Santos, K. M., Sombra, V. G., Maciel, J. S., Teixeira Sá, D. M., Salles, H. O., Oliveira, G., de Paula, R. C., Feitosa, J. P., Monteiro Moreira, A. C., Moreira, R. A. and Egito, A. S. 2014. Characterisation of partially hydrolysed galactomannan from *Caesalpinia pulcherrima* seeds as a potential dietary fibre, *Food Hydrocolloids*, 35, pp. 512-521. doi: 10.1016/j.foodhyd.2013.07.015.
- Caputo, H. E., Straub, J. E. and Grinstaff, M. W. 2019. Design, synthesis, and biomedical applications of synthetic sulphated polysaccharides, *Chemical Society Reviews*, 48(8), pp. 2338-2365. doi: 10.1039/c7cs00593h.
- Carter-Fox S., Li B., Xu D., and Edgar K. J. 2011. Regioselective esterification and etherification of cellulose: A review, *Biomacromolecules*, 12(6), pp. 1956-1972. doi: 10.1021/bm200260d.



- Cerqueira, M. A., Souza, B. W., Simões, J., Teixeira, J. A., Domingues, M. R. M., Coimbra, M. A. and Vicente, A. A. 2011. Structural and thermal characterization of galactomannans from non-conventional sources, *Carbohydrate Polymers*, 83(1), pp. 179-185. doi: 10.1016/j.carbpol.2010.07.036.
- Cerqueira, M. A., Pinheiro, A. C., Pastrana, L. M. and Vicente, A. A. 2019. Amphiphilic modified galactomannan as a novel potential carrier for hydrophobic compounds, *Frontiers in Sustainable Food Systems*, 3, pp. 1-8. doi: 10.3389/fsufs.2019.00017.
- Chen, W., Chen, H., Guo, G., Huang, Y., Chen, C., Tsai, Y., Huang, K. and Yang, C. 2018. Locust bean gum galactomannan hydrolyzed by thermostable  $\beta$ -D-mannanase may reduce the secretion of pro-inflammatory factors and the release of granule constituents, *International Journal of Biological Macromolecules*, 114, pp. 181-186. doi: 10.1016/j.ijbiomac.2018.03.097.
- Cheng, H. N. and Gu, Q. M. 2012. Enzyme-catalyzed modifications of polysaccharides and poly(ethylene glycol), *Polymers*, 4(2), pp. 1311-1330. doi: 10.3390/polym4021311.
- Cumpstey, I. 2011. *Chemical Modification of Polysaccharides*, ISRN Organic Chemistry, 2013, pp. 383-406.
- Dhull, S. B., Sandhu, K. S., Punia, S., Kaur, M., Chawla, P. and Malik, A. 2020. Functional, thermal and rheological behavior of fenugreek (*Trigonella foenum-graecum* L.) gums from different cultivars: A comparative study, *International Journal of Biological Macromolecules*, 159, pp. 406-414. doi: 10.1016/j.ijbiomac.2020.05.094.
- Dodi C. and Popa, M. I. 2011. Carboxymethylation of guar gum: Synthesis and characterization, *Cellulose Chemistry and Technology*, 45(3-4), pp. 171-176.
- Fidan, H., Stankov, S., Petkova, N., Petkova, Z., Iliev, A., Stoyanova, M., Ivanova, T., Zhelyazkov, N., Ibrahim, S., Stoyanova, A. and Ercisli, S. 2020. Evaluation of chemical composition, antioxidant potential and functional properties of carob (*Ceratonia siliqua* L.) seeds, *Journal of Food Science and Technology*, 57(7), pp. 2404-2413. doi: 10.1007/s13197-020-04274-z.
- Gao, J. and Grady, B. P. 2018. Reaction kinetics and subsequent rheology of carboxymethyl guar gum produced from guar splits, *Industrial and Engineering Chemistry Research*, 57(22), pp. 7345-7354. doi: 10.1021/acs.iecr.8b00782.
- George, A., Shah, P. A. and Shrivastav, P. S. 2019. Guar gum: Versatile natural polymer for drug delivery applications, *European Polymer Journal*, 112, pp. 722-735. doi: 10.1016/j.eurpolymj.2018.10.042.
- Geronço, M. S., da Silveira Ramos, I. F., da Silva Filho, E. C., dos Santos Rizzo, M., Ribeiro, A. B. and da Costa, M. P. 2021. Are Structurally Modified Galactomannan Derivatives Biologically Active?, *Polysaccharides*, 2(1), pp. 1-15. doi: 10.3390/polysaccharides2010001.
- Gu, Q. M. and Cheng, H. N. 2005. Enzyme-Catalyzed Condensation Reactions for Polymer Modifications, (1), pp. 427-436. doi: 10.1021/bk-2005-0900.ch030.
- Gupta, S. and Variyar, P. S. 2018. *Guar Gum: A Versatile Polymer for the Food Industry*, *Biopolymers for Food Design*. Elsevier Inc. doi: 10.1016/B978-0-12-811449-0.00012-8.
- Hussain, M., Bakalis, S., Gouseti, O., Zahoor, T., Anjum, F. M. and Shahid, M. 2015. Dynamic and shear stress rheological properties of guar galactomannans and its hydrolyzed derivatives, *International Journal of Biological Macromolecules*, 72, pp. 687-691. doi: 10.1016/j.ijbiomac.2014.09.019.
- Iqbal, D. N., Hussain, E. A., Ghani, A., Hassan, F., Bukhari, A., Iftikhar, S., Nazir, A., Ahmad, A. and Iqbal, M. 2020a. Green and environmentally friendly techniques for enhanced physicochemical characteristics attributed to polysaccharides for industrial applications, *Polish Journal of Environmental Studies*, 29(5), pp. 3457-3466. doi: 10.15244/pjoes/111511.
- Iqbal, D. N., Nazir, A., Iqbal, M., and Yameen, M. 2020b. Green synthesis and characterization of carboxymethyl guar gum: Application in Textile Printing Technology, *Green Processing and Synthesis*, 9(1), pp. 212-218. doi: 10.1515/gps-2020-0022.
- Javidi, F., Razavi, S. M., Behrouzian, F. and Alghooneh, A. 2016. The influence of basil seed gum, guar gum and their blend on the rheological, physical and sensory properties of low-fat ice cream, *Food Hydrocolloids*, 52, pp. 625-633. doi: 10.1016/j.foodhyd.2015.08.006.
- Kanelli, M. and Topakas, E. 2017. Acylation of soluble polysaccharides in a biphasic system catalyzed by a CE2 acetyl esterase, *Carbohydrate Polymers*, 163, pp. 208-215. doi: 10.1016/j.carbpol.2017.01.057.
- Kazachenko A. S., Malyar, Y. U. N., Vasilyeva, N. Y. U., Bondarenko, G. N., Korolkova, I. V., Antonov, A. V., Karacharov, A. A., Fetisova, O. Y. U., and Skvortsova, G. P., 2020. Green synthesis and characterization of galactomannan sulfates obtained using sulfamic acid. *Biomass Conversion and Biorefinery*, pp 1-10, doi: 10.1007/s13399-020-00855-2.
- Kazachenko, A. S., Malyar, Y. N., Vasilyeva, N. Y., Borovkova, V. S., and Issaoui, N. 2021. Optimization of guar gum galactomannan sulfation process with sulfamic acid, *Biomass Conversion and Biorefinery*. doi: 10.1007/s13399-021-01895-y.
- Kazachenko, A. S., Malyar, Y. N., Ghatfaoui, S., Issaoui, N., Al-Dossary, O., Wojcik, M. J., and Berezhnaya, Y. D. 2022a. A density functional theory calculations of infrared spectra of galactomannan butyl ether, *Journal of Molecular Structure*, 1251, p. 131998. doi: 10.1016/j.molstruc.2021.131998.
- Kazachenko, A. S., Fetisova, O. Y., Antonov, A. V., Bondarenko, G. N., and Sychev, V. V. 2022b. Production and description the characterization of guar gum galactomannan butyl ether, *Iraqi Journal of Agricultural Sciences*, 53(1), pp. 198-206. doi: 10.36103/ijas.v53i1.1525.
- Koschella, A., Fenn D., Illy N., and Heinze T. 2006. Regioselectively functionalized cellulose derivatives: A mini review, *Macromolecular Symposia*, 244, pp. 59-73. doi: 10.1002/masy.200651205.
- Kuznetsov, B. N., Levdansky, V. A., Kuznetsova, S. A., Garyntseva, N. V., Sudakova, I. G., and Levdansky, A. V., 2018. Integration of peroxide delignification and sulfamic acid sulfation methods for obtaining cellulose sulfates from aspen wood. *European Journal of Wood and Wood Products* 76(3): 999-1007. doi: 10.1007/s00107-017-1262-z.
- Li, P., Wang, T., He, J., Jiang, J. and Lei, F. 2021. Synthesis, characterization, and selective dye adsorption by pH- and ion-sensitive polyelectrolyte galactomannan-based hydrogels, *Carbohydrate Polymers*, 264, p. 118009. doi: 10.1016/j.carbpol.2021.118009.
- Liu, W., Gu, J., Huang, C., Lai, C., Ling, Z. and Yong, Q. 2021. Fabrication of hydrophobic and high-strength packaging films based on the esterification modification

- of galactomannan, *International Journal of Biological Macromolecules*, 167, pp. 1221-1229. doi: 10.1016/j.ijbiomac.2020.11.076.
- Liu, Y., Lei, F., He, L., Xu, W. and Jiang, J. 2020. Comparative study on the monosaccharides of three typical galactomannans hydrolyzed by different methods, *Industrial Crops and Products*, 157, p. 112895. doi: 10.1016/j.indcrop.2020.112895.
- Lopes, N., Faccin-Galhardi, L. C., Espada, S. F., Pacheco, A. C., Ricardo, N. M. P. S., Linhares, R. E. C. and Nozawa, C. 2013. Sulfated polysaccharide of *Caesalpinia ferrea* inhibits herpes simplex virus and poliovirus, *International Journal of Biological Macromolecules*, 60, pp. 93-99. doi: 10.1016/j.ijbiomac.2013.05.015.
- López-Franco, Y., Cervantes-Montaño, C., Martínez-Robinson, K., Lizardi-Mendoza, J. and Robles-Ozuna, L. 2013. Physicochemical characterization and functional properties of galactomannans from mesquite seeds (*Prosopis* spp.), *Food hydrocolloids*, 30(2), pp. 656-660. doi: 10.1016/j.foodhyd.2012.08.012.
- López-Franco, Y. L., Toledo-Guillén, A. R., and Lizardi-Mendoza, J. 2017. Biopolymers from mesquite tree (*Prosopis* spp). In: *Advances in Physicochemical Properties of Biopolymers (Part 1)*. M. Masuelli and D. Renard (eds.), pp 273-294. <https://doi.org/10.2174/9781681084534117010012>.
- Mendes-Marques, M. M., Maia-de Morais, S., Araújo-da Silva, A. R., Dutra-Boroso, N., Pontes-Filho, T. R., de Carvalho-Araújo, F. M., Pinto-Vieira, I. G., Malta-Lima, D., and Florindo-Guedes, M. 2015. Antiviral and Antioxidant Activities of Sulfated Galactomannans from Plants of Caatinga Biome, *Evidence-based Complementary and Alternative Medicine*, pp 1-8. doi: 10.1155/2015/591214.
- Mohammed, S. E. and Ragab, Y. A. 2021. Preparation of Methyl and Benzyl Guar using Dimethyl Sulfoxide/Paraformaldehyde Solvent System, *Al-Butana Journal of Applied Science*, (12), pp. 12-28.
- Mudgil, D., Barak, S. and Khatkar, B. S. 2012. X-ray diffraction, IR spectroscopy and thermal characterization of partially hydrolyzed guar gum, *International Journal of Biological Macromolecules*, 50(4), pp. 1035-1039. doi: 10.1016/j.ijbiomac.2012.02.031.
- Mudgil, D., Barak, S. and Khatkar, B. S. 2014. Guar gum: Processing, properties and food applications - A Review, *Journal of Food Science and Technology*, 51(3), pp. 409-418. doi: 10.1007/s13197-011-0522-x.
- Muschin, T., Budragchaa, D., Kanamoto, T., Nakashima, H., Ichiyama, K., Yamamoto, N., Shuqin, H. and Yoshida, T. 2016. Chemically sulfated natural galactomannans with specific antiviral and anticoagulant activities, *International Journal of Biological Macromolecules*, 89, pp. 415-420. doi: 10.1016/j.ijbiomac.2016.05.005.
- Pauly, M. and Keegstra, K. 2008. Cell-wall carbohydrates and their modification as a resource for biofuels, *Plant Journal*, 54(4), pp. 559-568. doi: 10.1111/j.1365-313X.2008.03463.x.
- Qin, X., Li, R., Zhu, S., Hu, J., Zeng, X., Zhang, X., Xu, H., Kong, W., Liang, J., Zhang, H., Zhang, J. and Wang, J. 2020. A comparative study of sulfated tara gum: RSM optimization and structural characterization, *International Journal of Biological Macromolecules*, 150, pp. 189-199. doi: 10.1016/j.ijbiomac.2020.02.031.
- Rajan, A., Sudha, J. D. and Abraham, T. E. 2008. Enzymatic modification of cassava starch by fungal lipase, *Industrial Crops and Products*, 27(1), pp. 50-59. doi: 10.1016/j.indcrop.2007.07.003.
- Richter, A. and Klemm, D. 2003. Regioselective sulfation of trimethylsilyl cellulose using different SO<sub>3</sub>-complexes, *Cellulose*, 10(2), pp. 133-138. doi: 10.1023/A:1024025127408.
- Rodge, A. B., Sonkamble, S. M., Salve, R. V. and Hashmi, S. I. 2012. Effect of hydrocolloid (guar gum) incorporation on the quality characteristics of bread, *Journal of Food Processing and Technology*, 3(2), pp. 136. doi: 10.4172/2157-7110.1000136
- Sarkar, S. and Singhal, R. S. 2011. Esterification of guar gum hydrolysate and gum Arabic with n-octenyl succinic anhydride and oleic acid and its evaluation as wall material in microencapsulation, *Carbohydrate Polymers*, 86(4), pp. 1723-1731. doi: 10.1016/j.carbpol.2011.07.003.
- Saurabh, C. K., Gupta, S., Bahadur, J., Mazumder, S., Variyar, P. S. and Sharma, A. 2013. Radiation dose dependent change in physicochemical, mechanical and barrier properties of guar gum based films, *Carbohydrate Polymers*, 98(2), pp. 1610-1617. doi: 10.1016/j.carbpol.2013.07.041.
- Sharma, P., Sharma, S., Ramakrishna, G., Srivastava, H., and Gaikwad, K. 2022. A comprehensive review on leguminous galactomannans: structural analysis, functional properties, biosynthesis process and industrial applications, *Critical Reviews in Food Science and Nutrition*, 62(2), pp. 443-465. doi: 10.1080/10408398.2020.1819196.
- Shenoy, M. A. and D'Melo, D. J. 2010. Evaluation of properties of unsaturated polyester/acetylated hydroxypropyl guar gum composites, *Journal of Applied Polymer Science*, 17, 3204-3210. doi: 10.1002/app.32192.
- Singh, A., Ansari, K. R., Quraishi, M. A., Kaya, S., and Erkan, S. 2021. Chemically modified guar gum and ethyl acrylate composite as a new corrosion inhibitor for reduction in hydrogen evolution and tubular steel corrosion protection in acidic environment, *International Journal of Hydrogen Energy*, 46(14), pp. 9452-9465. doi: 10.1016/j.ijhydene.2020.12.103.
- Suflet, D. M., Chitanu, G. C. and Popa, V. I. 2006. Phosphorylation of polysaccharides: New results on synthesis and characterisation of phosphorylated cellulose, *Reactive and Functional Polymers*, 66(11), pp. 1240-1249. doi: 10.1016/j.reactfunctpolym.2006.03.006.
- Tao, Y., Wang, T., Lai, C., Ling, Z., Zhou, Y. and Yong, Q. 2021. The in vitro and in vivo Antioxidant and immunomodulatory activity of incomplete degradation products of hemicellulosic polysaccharide (Galactomannan) from *Sesbania cannabina*, *Frontiers in Bioengineering and Biotechnology*, 9:679558. doi: 10.3389/fbioe.2021.679558.
- Torbica, A., Belović, M., Mastilović, J., Kevrešan, Ž., Pestorić, M., Škrobot, D. and Dapčević Hadnađev, T. 2016. Nutritional, rheological, and sensory evaluation of tomato ketchup with increased content of natural fibres made from fresh tomato pomace, *Food and Bioproducts Processing*, 98, pp. 299-309. doi: 10.1016/j.fbp.2016.02.007.
- Verma, S., Rimpay and Ahuja, M. 2020. Carboxymethyl modification of *Cassia obtusifolia* galactomannan and its evaluation as sustained release carrier, *International Journal of Biological Macromolecules*, 164, pp. 3823-3834. doi: 10.1016/j.ijbiomac.2020.08.231.
- Wang, J., Yang, T., Tian, J., Liu, W., Jing, F., Yao, J., Zhang, J. and Lei, Z. 2014. Optimization of reaction conditions by RSM

- and structure characterization of sulfated locust bean gum, *Carbohydrate Polymers*, 114, pp. 375-383. doi: 10.1016/j.carbpol.2014.08.035.
- Wang, J., Yang, T., Tian, J., Zeng, T., Wang, X., Yao, J., Zhang, J. and Lei, Z. 2014. Synthesis and characterization of phosphorylated galactomannan: The effect of DS on solution conformation and antioxidant activities, *Carbohydrate Polymers*, 113, pp. 325-335. doi: 10.1016/j.carbpol.2014.07.028.
- Wang, X., Zhang, Z., Yao, Q., Zhao, M. and Qi, H. 2013. Phosphorylation of low-molecular-weight polysaccharide from *Enteromorpha linza* with antioxidant activity, *Carbohydrate Polymers*, 96(2), pp. 371-375. doi: 10.1016/j.carbpol.2013.04.029.
- Wang, Z., Huang, T. and Yu, A. 2021. A carboxymethyl vegetable gum as a robust water -soluble binder for silicon anodes in lithium-ion batteries, *Journal of Power Sources*, 489, p. 229530. doi: 10.1016/j.jpowsour.2021.229530.
- Whistler, R.L., Hymowitz, T., 1979. *Guar: Agronomy, Production, Industrial Use, and Nutrition*. Purdue University Press, West Lafayette. pp.ix + 124 pp. eBook ISBN: 9780911198515.
- Wielinga, W. C. and Meyhall, A. G. 2009. Galactomannans. In: *Handbook of Hydrocolloids: Second Edition*, G. Phillips and P. Williams (eds.). pp. 228-251. eBook ISBN: 9781845695873; Hardcover ISBN: 9781845694142.
- Wu, C., Liu, J., Tang, Y., Li, Y., Yan, Q. and Jiang, Z. 2019. Hepatoprotective potential of partially hydrolyzed guar gum against acute alcohol-induced liver injury in vitro and vivo, *Nutrients*, 11(5), pp. 1-17. doi: 10.3390/nu11050963.
- Wu, Y., Ding, W., Jia, L. and He, Q. 2015. The rheological properties of tara gum (*Caesalpinia spinosa*), *Food Chemistry*, 168, pp. 366-371. doi: 10.1016/j.foodchem.2014.07.083.
- Yang, K. and Wang, Y. J. 2003. Lipase-Catalyzed Cellulose Acetylation in Aqueous and Organic Media, *Biotechnology Progress*, 19(6), pp. 1664-1671. doi: 10.1021/bp0341388.
- Yang, Z., Peng, H., Wang, W., and Liu, T. 2010. Crystallization behavior of poly( $\epsilon$ -caprolactone)/layered double hydroxide nanocomposites, *Journal of Applied Polymer Science*, 116(5), pp. 2658-2667. doi: 10.1002/app.
- Zhou, Z., Zhang, W., Duan, J., Zhang, W., Sun, D. and Jiang, J. 2016. Enhancement of *Gleditsia sinensis* gum rheological properties with pressure cell treatment in semi-solid state, *International Journal of Biological Macromolecules*, 84, pp. 254-260. doi: 10.1016/j.ijbiomac.2015.12.061.