



Revista Ambiente & Água

ISSN: 1980-993X

Instituto de Pesquisas Ambientais em Bacias Hidrográficas

Santos, Bruna Assis Paim dos; Cossolin, Aline Silva; Reis, Hélien Cristina Oliveira dos; Castro, Ketinny Camargo de; Silva, Evanleide Rodrigues da; Pereira, Gabriele de Menezes; Sousa, Paulo Teixeira de; Dall'Oglio, Evandro Luiz; Vasconcelos, Leonardo Gomes de; Morais, Eduardo Beraldo de
Baker's yeast-MnO₂ composites as biosorbent for Malachite green:
An ecofriendly approach for dye removal from aqueous solution
Revista Ambiente & Água, vol. 14, no. 1, 2019
Instituto de Pesquisas Ambientais em Bacias Hidrográficas

DOI: 10.4136/ambi-agua.2254

Available in: <http://www.redalyc.org/articulo.oa?id=92860467007>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

UAEM redalyc.org

Scientific Information System Redalyc

Network of Scientific Journals from Latin America and the Caribbean, Spain and Portugal


Project academic non-profit, developed under the open access initiative



Baker's yeast-MnO₂ composites as biosorbent for Malachite green: An ecofriendly approach for dye removal from aqueous solution

ARTICLES doi:10.4136/ambi-agua.2254

Received: 13 Mar. 2018; Accepted: 01 Nov. 2018

**Bruna Assis Paim dos Santos¹ ; Aline Silva Cossolin¹ ;
Hélen Cristina Oliveira dos Reis¹ ; Ketinny Camargo de Castro¹ ;
Evanleide Rodrigues da Silva² ; Gabriele de Menezes Pereira³ ;
Paulo Teixeira de Sousa Junior³ ; Evandro Luiz Dall'Oglio³ ;
Leonardo Gomes de Vasconcelos³ ; Eduardo Beraldo de Morais^{1*} **

¹Universidade Federal de Mato Grosso (UFMT), Cuiabá, MT, Brasil

Departamento de Engenharia Sanitária e Ambiental (DESA). E-mail: bruna.santos_assis@hotmail.com, aline.cossolin@gmail.com, helenreis08@gmail.com, ketinnycamargo@gmail.com, beraldo_morais@yahoo.com.br

²Universidade Federal de Mato Grosso (UFMT), Cuiabá, MT, Brasil

Programa de Pós-Graduação em Recursos Hídricos (PPGRH). E-mail: evy_tha@hotmail.com

³Universidade Federal de Mato Grosso (UFMT), Cuiabá, MT, Brasil

Departamento de Química. E-mail: gabriele_menezes@hotmail.com, pauloteixeiradesousa@gmail.com, dalloglio.evandro@gmail.com, vasconceloslg@gmail.com

*Corresponding author

ABSTRACT

In this study, baker's yeast-MnO₂ composites, produced by direct oxidation of yeast with KMnO₄ under acidic conditions, were used as biosorbent to remove the triphenylmethane dye Malachite green (MG) from an aqueous solution. Parameters that influence the adsorption process, such as pH, contact time, temperature, initial dye concentration and biosorbent dosage, were evaluated in batch experiments. The optimum removal of MG was found to be 86.7 mg g⁻¹ at pH 10, 1.0 g L⁻¹ of biomass dosage and 45°C. The kinetic data of dye removal was better described by the pseudo-second-order model. The adsorption process followed the Langmuir isotherm model and the maximum biosorption capacity was estimated to be 243.9 mg g⁻¹ (at 25°C). The negative values of ΔG° and the positive value of ΔH° indicated that the MG biosorption onto yeast-MnO₂ composites is spontaneous and endothermic. Fourier transform infrared spectroscopy (FTIR) indicated that the nano-MnO₂ particles deposited on yeast-MnO₂ composites surface facilitated the MG adsorption. It was concluded that baker's yeast-MnO₂ composites have potential for application as adsorbent for removal of MG from aqueous solution.

Keywords: biosorption, isotherm and kinetic models, thermodynamic model.



Compósitos de MnO_2 -levedura de pão como bioissorvente de verde Malaquita: uma abordagem ambientalmente amigável para a remoção de corante de solução aquosa

RESUMO

Neste estudo, compósitos de MnO_2 -levedura de pão, produzidos pela oxidação direta da levedura com KMnO_4 sob condições ácidas, foram usados como bioissorvente para remover o corante trifenilmetano verde Malaquita (VM) de solução aquosa. Os parâmetros que influenciam o processo de adsorção tais como pH, tempo de contato, temperatura, concentração inicial do corante e concentração do bioissorvente foram avaliados em experimentos de bancada. As condições ótimas de descoloração foram observadas em pH 10 e concentração de biomassa igual a $1,0 \text{ g L}^{-1}$. Os resultados de remoção do corante foram ajustados ao modelo cinético de pseudo segunda ordem. O processo de adsorção foi descrito pelo modelo isotérmico de Langmuir e a capacidade máxima de bioissorção foi estimada em $243,9 \text{ mg g}^{-1}$ (na temperatura de 25°C). Os valores negativos de ΔG° e valores positivos de ΔH° indicaram que a bioissorção do VM pelo compósito MnO_2 -levedura é espontâneo e endotérmico. A técnica de espectroscopia no infravermelho com transformada de Fourier indicou que nanopartículas de MnO_2 depositadas na superfície do compósito MnO_2 -levedura facilitaram a adsorção do VM. Concluiu-se que o compósito MnO_2 -levedura de pão possui potencial para ser usado como adsorvente na remoção de VM de solução aquosa.

Palavras-chave: bioissorção, modelos isotérmicos e cinéticos, modelo termodinâmico.

1. INTRODUCTION

Most dyes are synthetic chemicals widely used in textile, rubber, tanneries, paper, plastic, and paint industries for coloring purposes. It is estimated that there are more than 100,000 commercial dyes with a production of 7×10^5 – $1 \times 10^6 \text{ t}$ per year and approximately 280,000 t dyes are discharged together with industrial effluent annually worldwide (Fan et al., 2012). The presence of dyes in aquatic ecosystems is the cause of serious environmental and health concerns. The colored wastewaters do not only affect the transparency and aesthetics of natural water bodies, but also reduce photosynthesis by decreasing light penetration (Zhang et al., 2011). In addition, many dyes and their degradation products are potentially toxic, mutagenic and carcinogenic to living systems (Akar et al., 2015).

Some traditional chemical, physical and biological methods, such as coagulation, precipitation, ultrafiltration, electrolysis, color irradiation, ozonation and activated sludge have been employed for the treatment of dye-containing wastewater (Wu et al., 2011). However, there are disadvantages in all these methods, such as high cost, intensive energy requirements and formation of toxic by-products (secondary pollution) (Akar et al., 2009). On the other hand, biosorption technology utilizing different types of biomasses is an efficient and economic process to remove pollutants from wastewater. This is attributed to easy availability of some biosorbents, simplicity of design and operation and ability to treat wastewater with high concentration of pollutants (Castro et al., 2017). In the past decade, biosorbents including agro-industrial by-products (Akar et al., 2009), and biomass of algae (Khataee et al., 2013), filamentous fungi (Yang et al., 2011) and yeast (Castro et al., 2017) have been successfully applied to decolorize aqueous solutions and textile wastewater.

Baker's yeast (*Saccharomyces cerevisiae*) is an inexpensive and readily available source of biomass used to remove pollutants from wastewater. It has been used efficiently to remove radionuclides (Kedari et al., 2001), heavy metals (Xia et al., 2015) and textile dyes (Yu et al., 2009; Castro et al., 2017) with minimal or no impact to the environment. Biomass of *S.*

cerevisiae can be produced cheaply using simple fermentation techniques or obtained as a waste from various industrial fermentation processes. Its dye-adsorptive ability is due to the chemical characteristics of its cell wall, which contains a high amount of polysaccharides, some proteins and other components. These biomacromolecules are sources of different functional groups such as amino, carboxyl, thiol, sulfhydryl and phosphate groups, which are responsible for dye adsorption (Fan et al., 2012). However, the amount of these functional groups on the biomass could be limited, and most biosorbents do not show a high sorption capacity for cationic dyes (Yu et al., 2009).

Since the adsorption of dyes takes place mainly on the biomass surface, current researches have focused on applying different chemical agents to modify the surface of biosorbents and to improve adsorption capacity. Yang et al. (2011) reported that modified biomass of *Penicillium* YW01 with cetylpyridinium chloride significantly improved the adsorption of Acid Blue 25 dye from aqueous solution and phosphoric-phosphate buffer. Akar et al. (2015) showed that pretreatment of sugar-beet pulp with quaternary ammonium-salt is able to improve adsorption efficiency for Acid Red 1.

In this work, Malachite green (MG) dye was used as a model compound. MG is a cationic triphenylmethane dye also called Basic Green 4. It is extensively used in the pigment industry, having numerous applications in paper printing, textile industry, and in leather and cosmetics manufacturing. Furthermore, MG is also used as a topical antiparasitic and antiprotozoal agent in aquaculture (Chowdhury and Saha, 2010). However, it has been found that MG is environmentally persistent and causes carcinogenesis, mutagenesis, chromosomal fractures, teratogenicity and respiratory toxicity (Baek et al., 2010). Despite this, due to its availability and low cost, it is still widely used.

This study evaluated the capability of baker's yeast-MnO₂ composites (yeast-MnO₂ composites) to remove MG from an aqueous solution under different experimental conditions, such as initial pH, contact time, temperature, dye concentration and biosorbent dosage. In order to obtain a better understanding of the biosorption mechanisms for future applications in real scale, the kinetics, isotherm and thermodynamics of dye removal were also studied. The preparation of yeast-MnO₂ composites was first described by Xia et al. (2015) and involved the direct oxidation of baker's yeast biomass with KMnO₄ under acidic conditions. This modification was first tested for Cd²⁺ removal and to the best of our knowledge, it has not been used yet for cationic dye removal from aqueous solutions.

2. MATERIAL AND METHODS

2.1. Baker's yeast, reagents and preparation of yeast-MnO₂ composites

Baker's yeast was purchased from a commercial market. It was washed several times with ultra-pure water to remove dirt and soluble impurities, and then dried at 80°C for 48 h. The powdered biomass was crushed and sieved to select particle fractions of less than 300 µm using an ASTM Standard sieve and then stored in desiccators for further use.

Stock solution of MG (1000 mg/L) was prepared using ultra-pure water and was used to prepare the aqueous solutions used in biosorption experiments. MG was purchased from VETEC – Sigma-Aldrich, Brazil. All other chemicals used were of analytical grade.

To prepare the yeast-MnO₂ composites, 20 g of baker's yeast was added to a 200 mL KMnO₄ (0.05 M) solution and the solution pH was adjusted to 2.0, using HCl (0.1 M) (Xia et al., 2015). The mixture was then agitated on a rotary shaker at 300 rpm for 30 min. The suspension was centrifuged (3600 rpm, 15 min) and biomass was washed repeatedly using ultra-pure water several times to remove the residual KMnO₄. Lastly, the biomass was dried at 80°C for 48 h, sieved to select particle fractions of less than 300 µm using an ASTM Standard sieve, and stored in desiccators for further use in biosorption tests.

2.2. Batch biosorption experiments

Experiments were conducted with 150 mL Erlenmeyer flasks containing a 50 mL aqueous solution of MG. Flasks were agitated on a rotary shaker at 120 rpm and 25°C. Because adsorption is directly influenced by physicochemical variables, variables such as different pH (2, 4, 6, 8 and 10, adjusted by the addition of 0.1 M HCl or 0.1 M NaOH solutions), initial dye concentration (100, 150, 200, 250, 300 and 350 mg L⁻¹), biosorbent dosage (1.0, 1.5, 2.0 and 3.0 g biomass L⁻¹) and temperature (25, 35 and 45°C) were evaluated. At the end of each equilibrium experiment, the biosorbent was removed from the suspension by centrifugation (3600 rpm, 15 min) and the residual dye in the solution was measured quantitatively by a UV–Vis spectrophotometer (Hach DR6000) at $\lambda_{\max} = 617$ nm. All biosorption experiments were performed in triplicate and the dye removal efficiency, R (%), and dye biosorption capacity (q_e , mg g⁻¹) of biomass at the equilibrium were calculated according to Equations 1 and 2, respectively:

$$R(\%) = \frac{C_i - C_e}{C_i} \times 100 \quad (1)$$

$$q_e = \frac{(C_i - C_e)}{B} \quad (2)$$

Where C_i and C_e are the initial and the equilibrium dye concentrations (mg L⁻¹) and B is the biosorbent concentration in solution (g L⁻¹).

2.3. FTIR analysis

Fourier transform infrared spectroscopy (FTIR) analyses were performed on a Shimadzu Irtaffinity-1 spectrophotometer (Model: IrtAffinity-1; Catalogue Number: 206-73500-38; Serial Number: A21374902249S1; Brand: Shimadzu Corporation). FTIR was used to determine the functional groups on the yeast-MnO₂ composites and their responsibility for MG adsorption. After adsorption of MG until equilibrium, the residual dye solution was centrifuged (3600 rpm, 15 min), the supernatant was discarded and the residual biosorbent dried at 80°C for 48 h after being washed with ultra-pure water three times. The samples (1 mg biosorbent) were mixed with spectroscopically pure KBr (100 mg), and pellets were fixed in a sample holder. The qualitative analyses were carried out using the following parameters: Measured Mode (% Transmittance), Apodization (Happ_Genzel), Number of Scans (200), Resolution (16), Range (400 a 4700 cm⁻¹), Gain (1). The acquisitions of spectra were made using IRTsolution software (Version 1.50). The background obtained from KBr disks was automatically subtracted from the sample disks spectra.

3. RESULTS AND DISCUSSION

3.1. Effect of initial pH

The pH is an important factor affecting the biosorption process since it influences the dye solubility and the ionizing functional groups of the biosorbent cell wall (Khataee et al., 2013). The pH also affects the structural stability of MG, and therefore its color intensity. Chen et al. (2014) observed color reduction when solution pH was more than 10 and lower than 2. Consequently, in our study the initial pH ranges from 2 to 10. Figure 1 illustrates the effect of different initial pH on the removal of MG by untreated baker's yeast and yeast-MnO₂ composites at a dye concentration of 100 mg L⁻¹ for 60 min, 25°C and 1.0 g biosorbent L⁻¹. As the pH of the aqueous solution increased, the removal of MG by two biosorbents also increased. This effect is related to the deprotonation of different functional groups on the surface of the biomass with increasing pH, which increases the net electronegativity of the biosorbent (Wu et al. 2011). Therefore, the electrostatic interactions between the negatively charged biosorbent

and the positively charged MG dye cations lead to dye removal from the solution. Figure 1 also shows that MG removal efficiency of yeast-MnO₂ composites was higher than the removal efficiency of untreated baker's yeast. This is explained by the destruction of yeast cell walls and the exposure of more functional groups during oxidation with KMnO₄ and the nano-MnO₂ particles that are deposited on yeast surface, which can facilitate the biosorption of dye (Xia et al., 2015). Since the greatest removal efficiency was observed at pH 10, this pH was used in subsequent experiments.

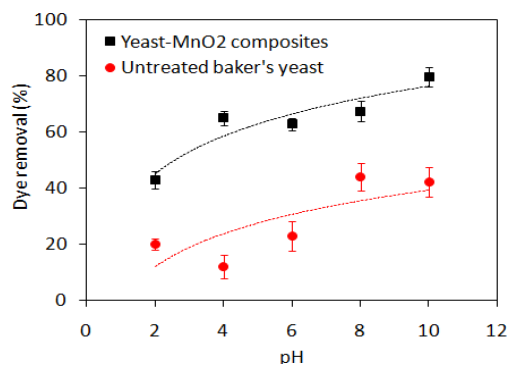


Figure 1. Effect of pH on the biosorption of MG by untreated baker's yeast and yeast-MnO₂ composites (biosorbent dosage = 1.0 g L⁻¹, dye concentration = 100 mg L⁻¹, contact time = 60 min, temperature = 25°C).

3.2. Effect of contact time

Considering the practical application, the ideal biosorption materials should be capable of rapidly adsorbing high concentrations of dyes from the wastewater and establishing equilibrium (Khataee et al., 2013). Therefore, the influence of the contact time on the MG biosorption capacity by yeast-MnO₂ composites was tested at 25, 35 and 45°C by varying the contact time between 10 and 120 min. Figure 2 shows that for the given temperatures, a rapid biosorption of MG occurred at 10 min and was gradually slowed down until equilibrium, which was achieved at 50-60 min. Also, it can be seen that the equilibrium biosorption capacity of yeast-MnO₂ composites increased from 86.5 to 95.7 mg g⁻¹ when the temperature was increased from 25 to 45°C. An increase in MG biosorption capacity of the biosorbent with temperature indicates that the biosorption of MG on yeast-MnO₂ composites is kinetically controlled by an endothermic process.

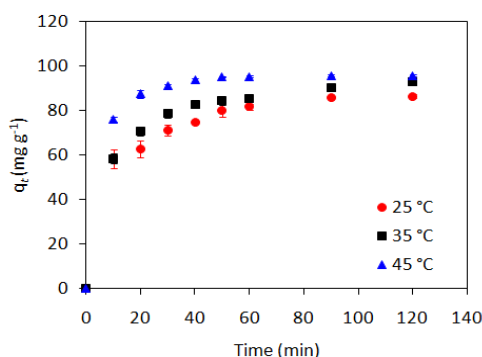


Figure 2. Effect of contact time on the biosorption of MG by yeast-MnO₂ composites at different temperatures (pH = 10, biosorbent dosage = 1.0 g L⁻¹, dye concentration = 100 mg L⁻¹).

3.3. Effect of biosorbent dosage

Figure 3 illustrates the effect of biosorbent dosage on the biosorption of MG. As can be seen, the percentage of removal increased when the biomass dosage rose from 1.0 to 1.5 g L⁻¹. A further increase in the biomass amount (2.0 and 3.0 g L⁻¹), however, caused no significant change in dye removal. On the other hand, the biosorption capacity decreased from 86.5 to 34.1 mg g⁻¹ when the biomass dosage increased from 1.0 to 3.0 g L⁻¹. The decrease in the biosorption capacity at higher yeast-MnO₂ composite dosages can be attributed to the adsorption sites that remained unsaturated during the adsorption reaction, whereas the number of sites available for adsorption is increased by increasing the biosorbent dosage (Castro et al., 2017).

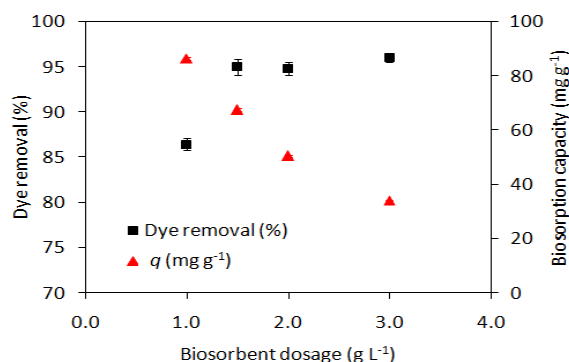


Figure 3. Effect of biosorbent dosage on the biosorption of MG by yeast-MnO₂ composites (dye concentration = 100 mg L⁻¹, contact time = 120 min, pH = 10, temperature = 25°C).

3.4. Effect of initial concentration of dye

The initial concentration of dye provides an important driving force to overcome all mass transfer resistances of the dye between the aqueous and the solid phases (Khataee et al., 2013). In this study, MG biosorption capacity of the yeast-MnO₂ composites was investigated using solutions of dye that ranged from 100 to 350 mg L⁻¹ and temperature of 25°C. The results in Figure 4 indicated that dye removal efficiency decreased with the increase in the initial dye concentration. On the other hand, biosorption capacity was increased and reached a maximum value of 214.1 mg g⁻¹ at an MG initial concentration of 300 mg L⁻¹. MG removal efficiency was higher at lower initial dye concentrations because all dye molecules may interact with the binding sites on the cell surface, while at higher dye concentrations, the binding sites on the biosorbent surface are saturated and no further biosorption occurs. A decrease in the biosorption capacity observed at a concentration of 350 mg L⁻¹ when compared to concentration of 300 mg L⁻¹ can be related to the repulsive forces between the dye molecules at the adjacent sites on the cell surface, which lead to a removal of some dye molecules from the surface (Castro et al., 2017).

3.5. Biosorption kinetics

Since sorption is a time-dependent process, the kinetic rate must be known for the design and evaluation of sorbents. In this study, kinetic studies of MG removal were conducted with a constant initial dye concentration (100 mg L⁻¹), 1.0 g biosorbent L⁻¹, at temperatures of 25, 35 and 45°C. The most-used kinetic models, including pseudo-first order, pseudo-second order and intraparticle diffusion, were applied to the experimental data from the MG biosorption experiments (Chowdhury and Saha, 2010).

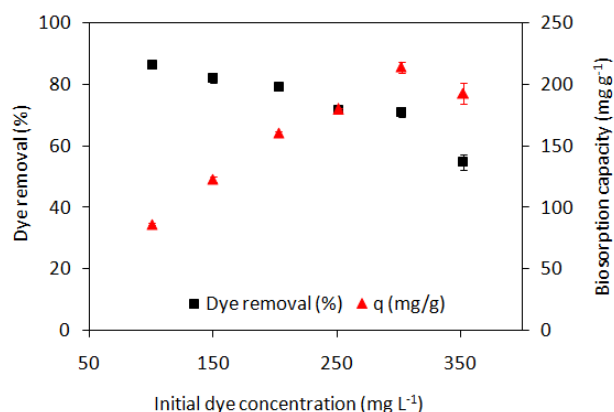


Figure 4. Effect of initial dye concentration on the biosorption of MG by yeast-MnO₂ composites (biosorbent dosage = 1.0 g biomass L⁻¹, dye concentration = 100 mg L⁻¹, contact time = 120 min, temperature = 25°C).

The linear form of the pseudo-first order model is represented by Equation 3:

$$\log(q_e - q_t) = \log q_e - \frac{K_1}{2.303} t \quad (3)$$

Where q_e and q_t are the amounts of dye adsorbed by biosorbent (mg g⁻¹) at equilibrium and at time t (min), respectively, and K_1 is the pseudo-first order rate constant (min⁻¹). The values of K_1 and the predicted q_e were determined from the plot of $\log(q_e - q_t)$ against t .

The linear form of the pseudo-second order model can be expressed as in Equation 4:

$$\frac{t}{q_t} = \frac{1}{K_2 q_e^2} + \frac{1}{q_e} t \quad (4)$$

Where q_e and q_t are the amounts of dye adsorbed by biosorbent (mg g⁻¹) at the equilibrium and at time t (min), respectively, and K_2 is the pseudo-second order rate constant (g mg⁻¹ min⁻¹). From the plot of t/q_t against t , the model's parameters K_2 and q_e could be determined.

The intraparticle diffusion model allows for the identification of the diffusion mechanisms and can be represented by Equation 5:

$$q_t = K_{id} t^{0.5} + C \quad (5)$$

Where C is the intercept (mg g⁻¹) and K_{id} is the intraparticle diffusion rate constant (mg g⁻¹ min^{-0.5}). By plotting q_t versus $t^{0.5}$, the values of K_{id} and C could be obtained. If the plot crosses the origin ($C = 0$), the adsorption process is controlled only by intraparticle diffusion.

The kinetic parameters for the MG biosorption for different temperatures are given in Table 1. Although the pseudo-first order model resulted in good fits ($R^2 > 0.964$, Figure 5a and Table 1), the experimental q_e values (86.5, 92.5 and 95.7 mg g⁻¹ at 25, 35 and 45°C) did not agree with the calculated ones (62.66, 41.02 and 30.39 mg g⁻¹ at 25, 35 and 45°C). The pseudo-second order model, on the other hand, resulted in the best fits ($R^2 = 0.999$ for all temperatures studied, Figure 5b) and the biosorption capacities (q_2) estimated were much closer to experimental q_e values (Table 1). When increasing the temperature, the pseudo-second order

rate constant values changed from 1.32×10^{-3} to 4.75×10^{-3} ($\text{g mg}^{-1} \text{min}^{-1}$). Similar results have been reported in the literature (Khataee et al., 2013; Wu et al., 2011). In the case of the intraparticle diffusion model, the biosorption results showed similar overall features of multilinear plots with two steps (Figure 5c). The first step is attributed to the external surface adsorption or instantaneous diffusion stage, during which a large amount of MG is rapidly adsorbed by the outer surface of the biosorbent. This is considered the fast step, demonstrated by the highest K_{id} constant values. The second step is the gradual biosorption stage controlled by intraparticle diffusion. As the plots did not cross the origin ($C \neq 0$), they suggest that intraparticle diffusion is not the only operative mechanism and that the biosorption kinetics of MG on yeast-MnO₂ composites was controlled by both surface and intraparticle diffusion processes.

Table 1. Kinetic parameters estimated by the pseudo first-order, pseudo second-order and intraparticle diffusion models for the MG biosorption on the yeast-MnO₂ composites.

Parameters	Temperature (°C)		
	25	35	45
$q_{\text{experimental}}$ (mg g^{-1})	86.5	92.5	95.7
<i>Pseudo-first order model</i>			
K_1 (min^{-1})	4.79×10^{-2}	3.15×10^{-2}	6.79×10^{-2}
q_1 (mg g^{-1})	62.66	41.02	30.39
R^2	0.964	0.981	0.969
<i>Pseudo-second order model</i>			
K_2 ($\text{g mg}^{-1} \text{min}^{-1}$)	1.32×10^{-3}	1.34×10^{-3}	4.75×10^{-3}
q_2 (mg g^{-1})	92.61	98.04	98.04
R^2	0.999	0.999	0.999
<i>Intraparticle diffusion model</i>			
<i>Step 1</i>			
K_{id} ($\text{mg g}^{-1} \text{min}^{-0.5}$)	5.517	7.858	5.589
C (mg g^{-1})	39.94	34.44	59.94
R^2	0.973	0.986	0.941
<i>Step 2</i>			
K_{id} ($\text{mg g}^{-1} \text{min}^{-0.5}$)	1.702	2.256	0.150
C (mg g^{-1})	68.53	68.33	94.13
R^2	0.928	0.990	0.960

3.6. Equilibrium isotherm

The equilibrium biosorption isotherm is a prerequisite to understand how adsorbates interact with adsorbents and how they could be used in the design of sorption systems. In this study, the equilibrium experiments were carried out with different initial dye concentrations ($100\text{--}350 \text{ mg L}^{-1}$), using $1.0 \text{ g biosorbent L}^{-1}$ at 25°C . The most widely used isotherm equations, including the Langmuir, Freundlich, and Dubinin and Radushkevich (D-R) models, were utilized (Chowdhury and Saha, 2010).

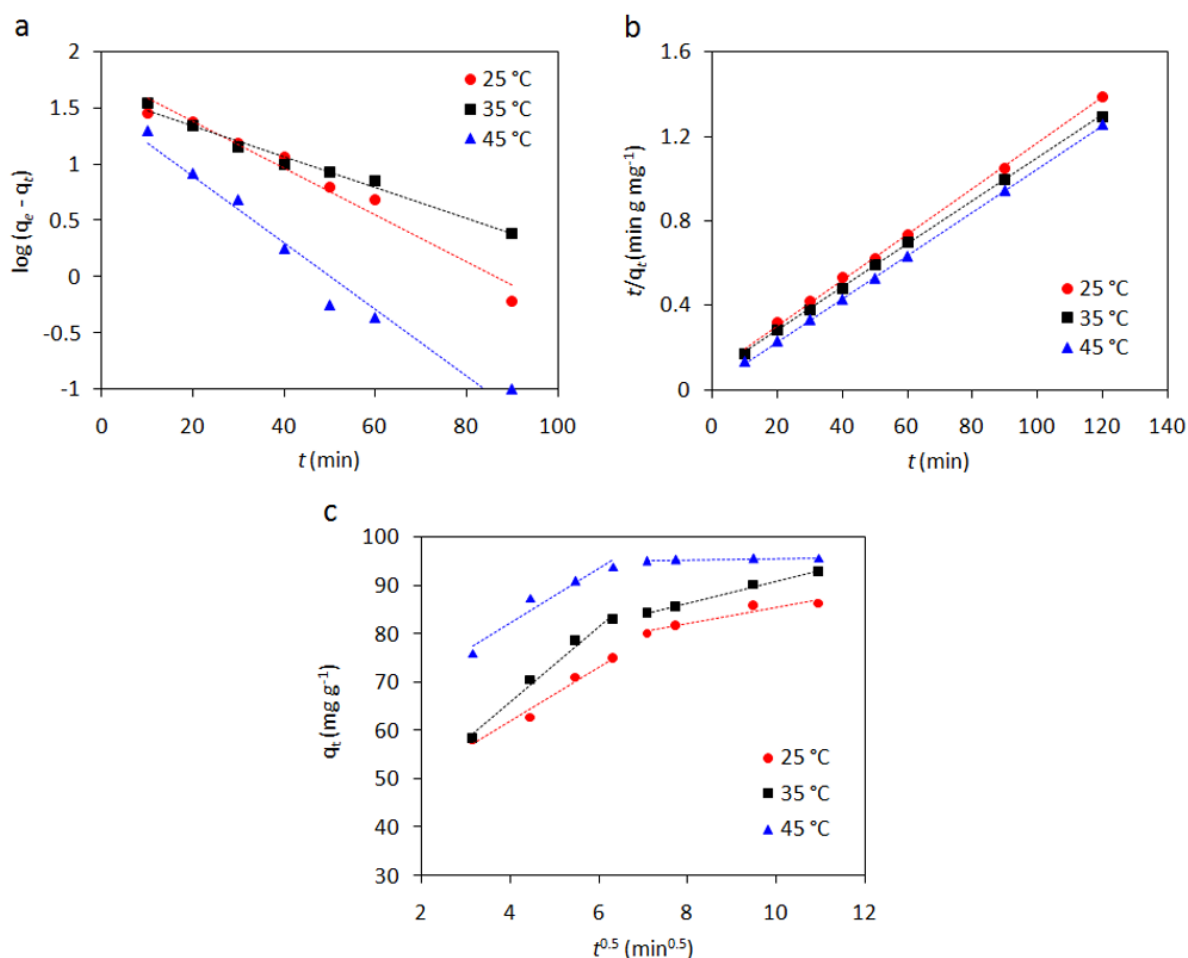


Figure 5. Plots for pseudo-first order (a), pseudo-second order (b) and intraparticle diffusion (c) models for the biosorption of MG onto yeast-MnO₂ composites, at different temperatures.

The Langmuir isotherm model assumes monolayer coverage of adsorbate over a homogeneous adsorbent surface. Also, all the binding sites of the surface have equal energy of sorption. The linear form of the Langmuir equation can be given as in Equation 6:

$$\frac{1}{q_e} = \frac{1}{q_{max}} + \left(\frac{1}{q_{max}K_L} \right) \frac{1}{C_e} \quad (6)$$

where q_e (mg g⁻¹) is the amount of dye adsorbed by the biosorbent at the equilibrium, C_e (mg L⁻¹) is the dye concentration in the solution at equilibrium, q_{max} (mg g⁻¹) is the maximum adsorption capacity, and K_L (L mg⁻¹) is the Langmuir constant related to free energy of adsorption. The plot of $1/q_e$ versus $1/C_e$ was employed to generate the values of q_{max} and K_L (Figure 6a).

The Freundlich isotherm, on the other hand, is an empirical equation employed to describe heterogeneous adsorption surface and is given by Equation 7:

$$\ln q_e = \ln K_f + \frac{1}{n} \ln C_e \quad (7)$$

Where K_f ((mg g⁻¹)(mg L⁻¹)^{-1/n}) is the Freundlich constant related to the adsorption capacity of adsorbent and n (dimensionless) is intensity of adsorption. K_f and n were calculated by plotting $\ln q_e$ and $\ln C_e$ (Figure 6b).

The D-R model was used to estimate the mean free energy of biosorption. The linearized form of the D-R model is expressed by Equation 8:

$$\ln q_e = \ln q_m - \beta \varepsilon^2 \quad (8)$$

Where q_e (mol g⁻¹) is the amount of dye adsorbed on the biosorbent, q_m (mol g⁻¹) is the maximum biosorption capacity, β (mol² kJ⁻²) is the constant related to the mean free energy of biosorption and ε is the Polanyi potential. The values of q_m and β were determined from the linear plot of $\ln q_e$ versus ε^2 (Figure 6c). The ε value was calculated with Equation 9:

$$\varepsilon = RT \ln \left(1 + \frac{1}{C_e} \right) \quad (9)$$

Where R (8.314 J mol⁻¹ K⁻¹) is the ideal gas constant and T (K) is the absolute temperature.

Using the activity coefficient β , it is possible to estimate the mean free energy of biosorption (E , kJ mol⁻¹), according to Equation 10:

$$E = \frac{1}{\sqrt{2\beta}} \quad (10)$$

The E value gives information about the mechanism involved in the biosorption. When E value falls in the range from 8 to 16 kJ mol⁻¹, the biosorption process is controlled by a chemical mechanism, while for $E < 8$ kJ mol, the biosorption process proceeds through a physical mechanism.

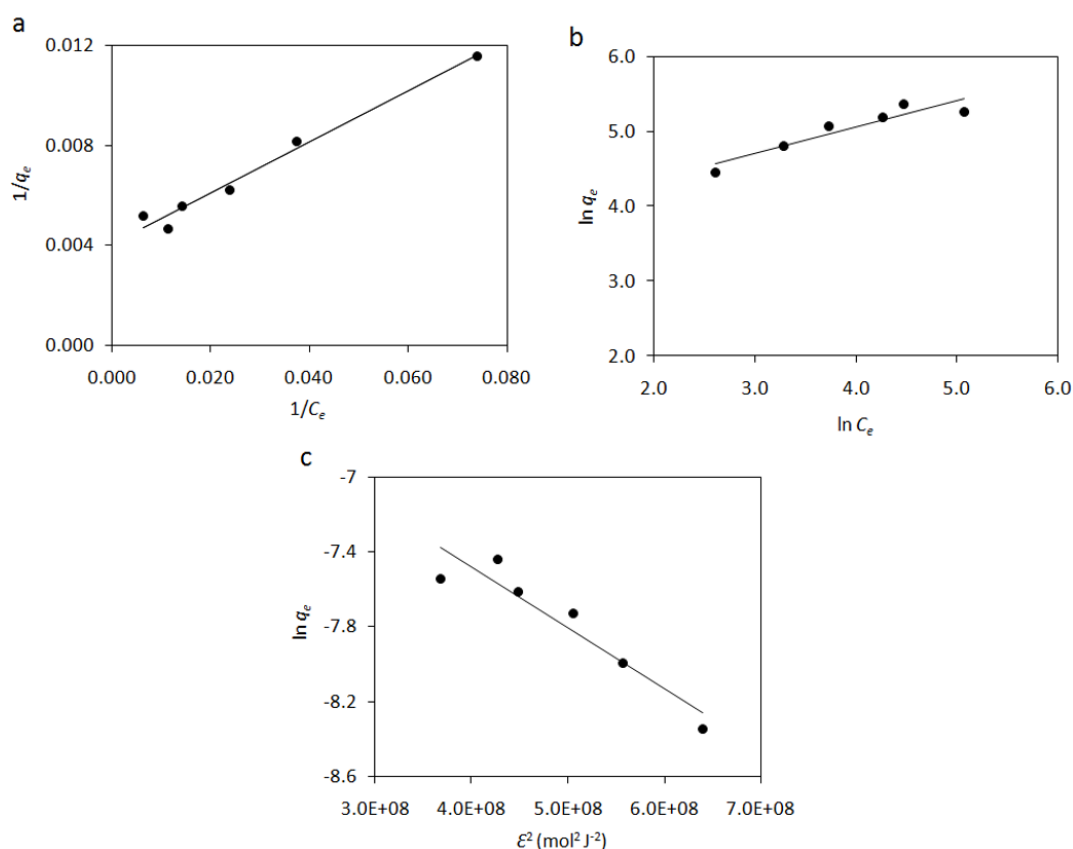


Figure 6. Plots for Langmuir (a), Freundlich (b) and D-R isotherms (c) for the biosorption of MG onto yeast-MnO₂ composites.

The parameters obtained from the isotherm models applied to the experimental data for MG biosorption onto yeast-MnO₂ composites are listed in Table 2. The linear correlation coefficients (R^2) show that the equilibrium data could be better interpreted by the Langmuir isotherm ($R^2 = 0.979$) than by the Freundlich isotherm ($R^2 = 0.866$). This suggests that the biosorption process of MG onto yeast-MnO₂ composites assumes a monolayer adsorption, and the maximum biosorption capacity was 243.90 mg g⁻¹. The maximum adsorption capacities of MG onto various adsorbents reported in the literature are listed in Table 3. The adsorption capacity of yeast-MnO₂ composites obtained for MG in this investigation is higher than those of many corresponding adsorbent materials.

The free energy of MG biosorption was considered via D-R model. A relatively high correlation coefficient ($R^2 = 0.890$) was found. As can be seen from Table 2, the mean biosorption energy (E) calculated was 12.91 kJ mol⁻¹, which indicates that the biosorption process of MG onto yeast-MnO₂ composites was considered to be a chemical adsorption.

Table 2. Biosorption isotherm constants for the biosorption of MG onto yeast-MnO₂ composites.

<i>Langmuir</i>		<i>Freundlich</i>		<i>D-R</i>	
q_{\max} (mg g ⁻¹)	243.90	K_F (mg g ⁻¹) (mg L ⁻¹) ^{-1/n}	38.18	q_m (mol g ⁻¹)	2.07×10^{-3}
K_L (L mg ⁻¹)	4.02×10^{-2}	n	2.819	β (mol ² J ⁻²)	3.00×10^{-9}
R^2	0.979	R^2	0.865	E (kJ mol ⁻¹)	12.91
				R^2	0.890

Table 3. Comparison of MG adsorption capacity of different adsorbents.

Adsorbent	T (°C)	pH	q_{\max} (mg g ⁻¹)	Reference
Brown-rotted pine wood	30	4.0	29.85	Zhang et al. (2011)
Leaf of pineapple (<i>Ananas comosus</i>)	25	9.0	54.64	Chowdhury et al. (2011)
Potato peel	25	4.0	32.39	Guechi and Hamdaoui (2016)
Sea shell powder	30	8.0	42.33	Chowdhury and Saha (2010)
Rice straw modified with citric acid	20	6.0	256.41	Gong et al. (2006)
Degreased coffee bean	25	4.0	55.30	Baek et al. (2010)
Baker's yeast-MnO ₂ composites	25	10	243.90	Present study

3.7. Thermodynamic study

To investigate the thermodynamics of MG biosorption onto yeast-MnO₂ composites, the main thermodynamic parameters, such as standard changes of free energy (ΔG°), enthalpy (ΔH°) and entropy (ΔS°) were calculated by the following Equations 11, 12 and 13:

$$\Delta G^\circ = -RT \ln K_D \quad (11)$$

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (12)$$

The combination of Equations 11 and 12 gives:

$$\ln K_D = \frac{\Delta S^\circ}{R} - \frac{\Delta H^\circ}{R} \times \frac{1}{T} \quad (13)$$

Where K_D (q_e/C_e) is the distribution coefficient, T (K) is the absolute temperature and R is the universal gas constant (8.314 J K⁻¹ mol⁻¹). The values of ΔH° and ΔS° were determined from the plot of $\ln K_D$ against $1/T$ (Figure 7).

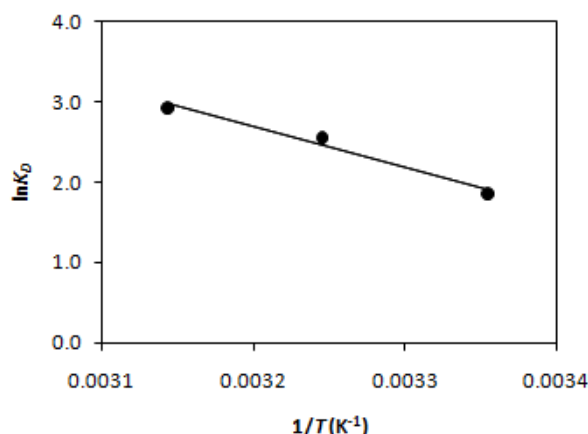


Figure 7. Plot of $\ln K_D$ versus $1/T$ for estimation of thermodynamic parameters.

The calculated thermodynamic parameters are listed in Table 4. The negative values of ΔG° indicate that the MG biosorption onto yeast-MnO₂ composites is spontaneous and feasible at all the studied temperatures (25, 35 and 45°C). The change in the standard enthalpy (ΔH°) was 42.1 kJ mol⁻¹. The positive value of ΔH° suggests that the biosorption is endothermic in nature and reflects the affinity of yeast-MnO₂ composites for MG. This trend may be explained by the availability of more active sites of biosorbent at higher temperatures due to increased surface activity and increased kinetic energy of the MG molecules (Akar et al., 2009). The ΔS° parameter was also found to be positive, thus suggesting that the randomness at the biosorbent/solution interface increases during the biosorption of dye.

Table 4. Thermodynamic parameters estimated for MG biosorption onto yeast-MnO₂ composites.

T (°C)	K_D	ΔG° (kJ mol ⁻¹)	ΔH° (kJ mol ⁻¹)	ΔS° (J mol ⁻¹ K ⁻¹)
25	6.39	-4.70	42.10	157.0
35	12.76	-6.27		
45	18.53	-7.84		

3.8. FTIR analysis

FTIR spectroscopy is an important technique to identify the functional groups in the surface of adsorbents and the possible interactions between them and the adsorbate. As seen in the spectrum of yeast-MnO₂ composites before MG adsorption (Figure 8a), a broad and strong band at around 3425.58 cm⁻¹ is indicative of the overlapping of O–H and N–H stretching vibrations (Yang et al., 2011). The peaks at 2924.09 and 2854.65 cm⁻¹ are attributed to the C–H stretching vibrations of aliphatic groups (Yang et al. 2011). Protein-related bonds of amide I, II and III are observed at peaks 1651.07, 1543.05 and 1242.16 cm⁻¹, respectively, while the band at 1404.18 cm⁻¹ is attributed to C–OH bend from carboxylic groups (Xia et al., 2015). The band at 1041.56 cm⁻¹ can be due to stretching of glycitols (C–OH), the P–O–C (Zhang et al., 2011) and C–OH dimer carboxylic acid. The peak observed at the low-frequency region around 470.63 cm⁻¹ is ascribed to Mn–O vibrations (Parikh and Chorover, 2005), indicating the presence of nano-MnO₂ particles on the yeast surface (Xia et al., 2015). After MG adsorption (Figure 8b), the peak at 470.63 cm⁻¹ disappeared and the presence of a new peak at 578.64 cm⁻¹ indicated that the nano-MnO₂ particles on yeast-MnO₂ composite surface were responsible for MG biosorption. Additionally, the peak at 3425.58 cm⁻¹ shifted to 3410.15, indicating that those functional groups might contribute to MG biosorption.

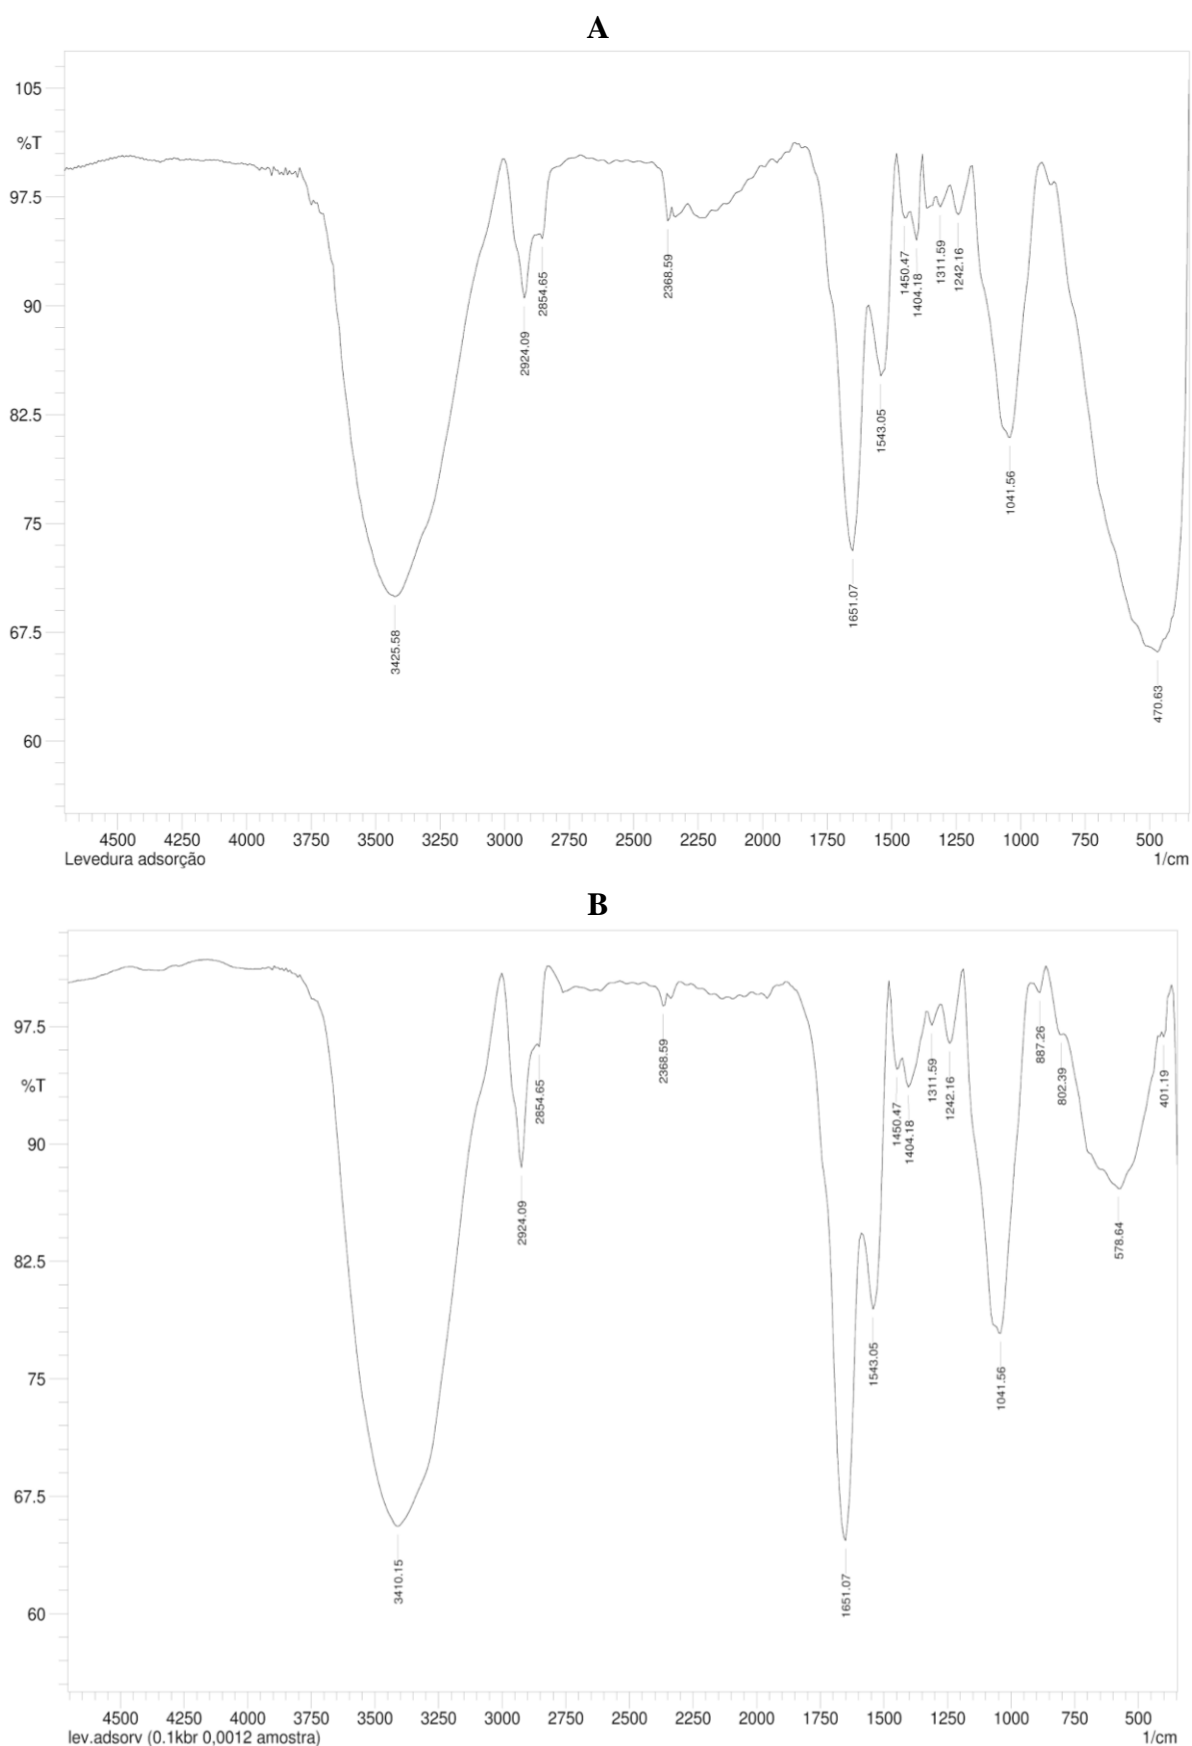


Figure 8. FTIR spectra of yeast-MnO₂ composites before MG adsorption (a) and after MG adsorption (b).

4. CONCLUSION

Modification of baker's yeast with KMnO_4 under acidic conditions significantly increased the biosorption capacity of MG compared to unmodified yeast. The biosorption process proved to be dependent on the pH of the solution, temperature, contact time, biosorbent dosage and initial concentration of dyes. The optimum removal of MG was found to be 86.7 mg g^{-1} at pH 10, 1.0 g L^{-1} of biomass dosage and 45°C . The experimental data fit well with pseudo-second-order model and Langmuir models, and the maximum biosorption capacity was estimated to be 243.9 mg g^{-1} (at 25°C). Thermodynamic parameters, ΔG° and ΔH° , indicated that the MG biosorption onto yeast- MnO_2 composites is spontaneous and endothermic. In conclusion, yeast- MnO_2 composites may be an economic, effective and eco-friendly option for the removal of the cationic dye MG from aqueous media.

5. ACKNOWLEDGMENTS

This work was supported by CNPq under Grant 486168/2013-1.

6. REFERENCES

- AKAR, S. T.; YILMAZER, D.; CELIK, S.; BALK, Y. Y.; AKAR, T. Effective bio decolorization potential of surface modified lignocellulosic industrial waste biomass. **Chemical Engineering Journal**, v. 259, p. 286–292, 2015. <http://dx.doi.org/10.1016/j.cej.2014.07.112>
- AKAR, T.; TOSUN, I.; KAYNAK, Z.; OZKARA, E.; YENI, O.; SAHIN, E. N.; TUNALI, S. An attractive agro-industrial by-product in environmental cleanup: Dye biosorption potential of untreated olive pomace. **Journal of Hazardous Materials**, v. 166, p. 1217–1225, 2009. <https://doi.org/10.1016/j.jhazmat.2008.12.029>
- BAEK, M. H.; IJAGBEMI, C. O.; O, S. J.; KIM, D. S. Removal of Malachite Green from aqueous solution using degreased coffee bean. **Journal of Hazardous Materials**, v. 176, n. 1–3, p. 820–828, 2010. <https://doi.org/10.1016/j.jhazmat.2009.11.110>
- CASTRO, K. C.; COSSOLIN, A. S.; REIS, H. C. O.; MORAIS, E. B. Biosorption of anionic textile dyes from aqueous solution by yeast slurry from brewery. **Brazilian Archives of Biology and Technology**, v. 60, p. 1–13, 2017. <https://doi.org/10.1590/1678-4324-2017160101>
- CHEN, Z.; DENG, H.; CHEN, C.; YANG, Y.; XU, H. Biosorption of malachite green from aqueous solutions by *Pleurotus ostreatus* using Taguchi method. **Journal of Environmental Health Science and Engineering**, v. 12, n. 1, p. 63, 2014. <http://dx.doi.org/jehse.biomedcentral.com/articles/10.1186/2052-336X-12-63>
- CHOWDHURY, S.; CHAKRABORTY, S.; SAHA, P. Biosorption of Basic Green 4 from aqueous solution by *Ananas comosus* (pineapple) leaf powder. **Colloids and Surfaces B: Biointerfaces**, v. 84, n. 2, p. 520–527, 2011. <http://dx.doi.org/10.1016/j.colsurfb.2011.02.009>
- CHOWDHURY, S.; SAHA, P. Sea shell powder as a new adsorbent to remove Basic Green 4 (Malachite Green) from aqueous solutions: Equilibrium, kinetic and thermodynamic studies. **Chemical Engineering Journal**, v. 164, n. 1, p. 168–177, 2010. <http://dx.doi.org/10.1016/j.cej.2010.08.050>

- FAN, H.; YANG, J.; GAO, T.; YUAN, H. Removal of a low-molecular basic dye (Azure Blue) from aqueous solutions by a native biomass of a newly isolated *Cladosporium* sp.: Kinetics, equilibrium and biosorption simulation. **Journal of the Taiwan Institute of Chemical Engineers**, v. 43, n. 3, p. 386–392, 2012. <http://dx.doi.org/10.1016/j.jtice.2011.11.001>
- GONG, R.; JIN, Y.; CHEN, F.; CHEN, J.; LIU, Z. Enhanced malachite green removal from aqueous solution by citric acid modified rice straw. **Journal of Hazardous Materials**, v. 137, n. 2, p. 865–870, 2006. <https://doi.org/10.1016/j.jhazmat.2006.03.010>
- GUECHI, E. K.; HAMDAOUI, O. Sorption of malachite green from aqueous solution by potato peel: Kinetics and equilibrium modeling using non-linear analysis method. **Arabian Journal of Chemistry**, v. 9, p. S416–S424, 2016. <https://doi.org/10.1016/j.arabjc.2011.05.011>
- KEDARI, C. S.; DAS, S. K.; GHOSH, S. Biosorption of long lived radionuclides using immobilized cells of *Saccharomyces cerevisiae*. **World Journal of Microbiology and Biotechnology**, v. 17, p. 789–793, 2001. <https://dx.doi.org/10.1023/A:1013547307770>
- KHATAEE, A. R.; VAFAEI, F.; JANNATKHAH, M. Biosorption of three textile dyes from contaminated water by filamentous green algal *Spirogyra* sp.: Kinetic, isotherm and thermodynamic studies. **International Biodeterioration and Biodegradation**, v. 83, p. 33–40, 2013. <http://dx.doi.org/10.1016/j.ibiod.2013.04.004>
- PARIKH, S. J.; CHOROVER, J. FTIR spectroscopic study of biogenic Mn-Oxide formation by *Pseudomonas putida* GB-1. **Geomicrobiology Journal**, v. 22, p. 207–218, 2005. <https://doi.org/10.1080/01490450590947724>
- WU, Y.; HU, Y.; XIE, Z.; FENG, S.; LI, B.; MI, X. Characterization of biosorption process of acid orange 7 on waste brewery's yeast. **Applied Biochemistry and Biotechnology**, v. 163, n. 7, p. 882–894, 2011. <https://doi.org/10.1007/s12010-010-9092-z>
- XIA, Y.; MENG, L.; JIANG, Y.; ZHANG, Y.; DAI, X.; ZHAO, M. Facile preparation of MnO₂ functionalized baker's yeast composites and their adsorption mechanism for Cadmium. **Chemical Engineering Journal**, v. 259, p. 927–935, 2015. <http://dx.doi.org/10.1016/j.cej.2014.08.071>
- YANG, Y.; JIN, D.; WANG, G.; LIU, D.; JIA, X.; ZHAO, Y. Biosorption of Acid Blue 25 by unmodified and CPC-modified biomass of *Penicillium* YW01: Kinetic study, equilibrium isotherm and FTIR analysis. **Colloids and Surfaces B: Biointerfaces**, v. 88, n. 1, p. 521–526, 2011. <http://dx.doi.org/10.1016/j.colsurfb.2011.07.047>
- YU, J. X.; LI, B. H.; SUN, X. M.; YUAN, J.; CHI, R. Polymer modified biomass of baker's yeast for enhancement adsorption of methylene blue, rhodamine B and basic magenta. **Journal of Hazardous Materials**, v. 168, n. 2–3, p. 1147–1154, 2009. <https://doi.org/10.1016/j.jhazmat.2009.02.144>
- ZHANG, H.; TANG, Y.; LIU, X.; KE, Z.; SU, X.; CAI, D. et al. Improved adsorptive capacity of pine wood decayed by fungi *Poria cocos* for removal of Malachite green from aqueous solutions. **Desalination**, v. 274, n. 1–3, p. 97–104, 2011. <https://doi.org/10.1016/j.desal.2011.01.077>