



CT&F Ciencia, Tecnología y Futuro

ISSN: 0122-5383

ctyf@ecopetrol.com.co

ECOPETROL S.A.

Colombia

Celis-Cornejo, Carlos-Mauricio; Granados-Zarta, Gustavo-Alberto; Bravo-Villarreal, Carlos-Eduardo;
Pérez-Martínez, David de Jesús; Giraldo-Duarte, Sonia-A.

KINETIC PARAMETERS DETERMINATION OF FCC GASOLINE HYDROTREATING USING
GENETIC ALGORITHMS

CT&F Ciencia, Tecnología y Futuro, vol. 5, núm. 3, diciembre-, 2013, pp. 79-93

ECOPETROL S.A.

Bucaramanga, Colombia

Available in: <http://www.redalyc.org/articulo.oa?id=46530513005>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

redalyc.org

Scientific Information System

Network of Scientific Journals from Latin America, the Caribbean, Spain and Portugal

Non-profit academic project, developed under the open access initiative

KINETIC PARAMETERS DETERMINATION OF FCC GASOLINE HYDROTREATING USING GENETIC ALGORITHMS

DETERMINACIÓN DE PARÁMETROS CINÉTICOS DEL HIDROTRATAMIENTO DE UNA NAFTA DE FCC USANDO ALGORITMOS GENÉTICOS

Carlos-Mauricio Celis-Cornejo¹, Gustavo-Alberto Granados-Zarta¹, Carlos-Eduardo Bravo-Villarreal¹,
David de Jesús Pérez-Martínez² and Sonia-A. Giraldo-Duarte^{1*}

¹Centro de Investigaciones en Catálisis (CICAT), Escuela de Ingeniería Química,
Universidad Industrial de Santander, Bucaramanga, Colombia

²ECOPETROL S.A. - Instituto Colombiano del Petróleo (ICP), A.A. 4185 Piedecuesta, Colombia

e-mail: sgiraldo@uis.edu.co

(Received: Jul. 22, 2013; Accepted: Dec. 05, 2013)

ABSTRACT

The kinetics parameters for the simultaneous reactions of hydrodesulfurization and hydrogenation of synthetic Fluid Catalytic Cracking (FCC) naphtha over CoMo/ γ -Al₂O₃ catalyst were determined. The proposed kinetic model considered a Langmuir-Hinshelwood adsorption mechanism (with 16 steps) with just one kind of active site. The amount of experimental data obtained was relatively limited, thus a genetic algorithm accompanied by an optimization through the Nelder-Mead Simplex method were used for the parameter estimations. Trimethylpentenes and 2-methylthiophene were used as representative molecules of unsaturated and sulfur compounds in FCC naphtha respectively. It was possible to calculate kinetic and thermochemical parameters, such as activation energies, adsorption heats and frequency factors with a good enough approach. This methodology results very useful since it allows the parameters determination with accuracy, reducing the amount of experimentation in comparison with traditional methodologies.

Keywords: Hydrodesulfurization, Olefins hydrogenation, CoMo/ γ -Al₂O₃ catalyst, Stochastic optimization.

How to cite: Celis-Cornejo, C. M., Granados-Zarta, G. A., Bravo-Villarreal, C. E., Pérez-Martínez, D. & Giraldo-Duarte, S. A. (2013). Kinetic parameters determination of FCC gasoline hydrotreating using genetic algorithms. *CT&F - Ciencia, Tecnología y Futuro*, 5(3), 79-94.

*To whom correspondence should be addressed

RESUMEN

Se determinaron los parámetros cinéticos para las reacciones simultáneas de hidrodesulfuración e hidrogenación de una carga representativa de una nafta de Craqueo Catalítico Fluidizado (FCC, de sus siglas en inglés) sobre un catalizador $\text{CoMo}/\gamma\text{-Al}_2\text{O}_3$. El modelo cinético propuesto consideró un mecanismo de adsorción de Langmuir-Hinshelwood (con 16 pasos) con un único tipo de sitio activo. La cantidad de datos experimentales fue relativamente baja, por lo tanto para la estimación de parámetros se utilizaron algoritmos genéticos en conjunto con el método de minimización de Nelder-Mead Simplex. Trimetilpentenos y 2-metiltiofeno fueron usados como moléculas representativas de compuestos insaturados y sulfurados de una nafta de FCC, respectivamente. Fue posible calcular con una buena aproximación parámetros termoquímicos y cinéticos, tales como, energías de activación, calores de adsorción y factores de frecuencia. Esta metodología resulta muy útil ya que permite la determinación de parámetros con buena aproximación reduciendo la cantidad de experimentación, en comparación con las metodologías tradicionales.

Palabras clave: Hidrodesulfuración, Hidrogenación de olefinas, Catalizador $\text{CoMo}/\gamma\text{-Al}_2\text{O}_3$, Optimización estocástica.

RESUMO

Foram determinados os parâmetros cinéticos para as reações simultâneas de hidrodessulfuração e hidrogenação de uma carga representativa de uma nafta de Craqueamento Catalítico Fluidizado (FCC, por sua sigla em inglês) sobre um catalisador $\text{CoMo}/\gamma\text{-Al}_2\text{O}_3$. O modelo cinético proposto considerou um mecanismo de adsorção de Langmuir-Hinshelwood (com 16 passos) com um único tipo de lugar ativo. A quantidade de dados experimentais foi relativamente baixa, portanto, para a estimativa de parâmetros foram utilizados algoritmos genéticos em conjunto com o método de minimização de Nelder-Mead Simplex. Trimetil-pentenos e 2-metil-tiofeno foram usados como moléculas representativas de compostos insaturados e sulfurados de uma nafta de FCC, respectivamente. Foi possível calcular com uma boa aproximação parâmetros termoquímicos e cinéticos, tais como, energias de ativação, calores de adsorção e fatores de frequência. Esta metodologia resulta muito útil já que permite a determinação de parâmetros com boa aproximação reduzindo a quantidade de experimentação, em comparação com as metodologias tradicionais.

Palavras-chave: Hidrodessulfuração, Hidrogenação de olefinas, Catalisador $\text{CoMo}/\gamma\text{-Al}_2\text{O}_3$, Otimização estocástica.

1. INTRODUCTION

The reduction of pollutants in fuels is nowadays a major challenge in the refining industry due to the increasingly demanding environmental regulations, especially regarding sulfur levels (United States Environmental Protection Agency, 2011). Hydrotreating (HDT) is widely used to remove heteroatoms (*S*, *N* and *O*) and aromatics contained in petroleum fractions processed in refineries. The development of appropriate catalysts is the keystone to selectively remove those pollutants (Brunet *et al.*, 2005; Ratnasamy & Sivasanker, 1980; Morterra & Magnacca, 1996; Pérez-Martínez *et al.*, 2010). Special attention should be placed on the hydrodesulfurization (HDS) of naphtha coming from the Fluid Catalytic Cracking (FCC) unit, which constitutes about 30% of the gasoline and accounts for 80 to 90% of the total sulphur content (Song, 2003; Kaufmann *et al.*, 2000).

A considerable amount of olefins are contained in FCC naphtha, and these are largely responsible for its high Research Octane Number (RON). Olefins usually are hydrogenated during the HDS process, thereby, reducing the RON in gasoline. Accordingly, HDS catalysts for FCC gasoline must be selective enough to make deep desulfurization without a significant reduction in the RON (Brunet *et al.*, 2005; Ratnasamy & Sivasanker, 1980; Morterra & Magnacca, 1996; Miller *et al.*, 2000). Particularly, HDT catalysts for FCC gasoline must promote the desulfurization reaction instead olefins hydrogenation (HYD), which means to be highly selective for HDS pathway (HDS/HYD). *CoMo*/ γ - Al_2O_3 and its modifications are preferred instead of *NiMo* ones, because of its better HDS/HYD selectivity (Brunet *et al.*, 2005; Ratnasamy & Sivasanker, 1980; Morterra & Magnacca, 1996).

A kinetic study of these reactions could be an important contribution since it is necessary to establish reaction mechanisms and notions for reactors design. Furthermore, an adequate and consistent kinetic model allows the determination of kinetic and thermodynamic parameters, which would not be easily measured. Classical nonlinear minimizations methods based on a steepest descent algorithm are commonly used for estimation of thermodynamics and kinetic parameters. Parijjs and Froment (1986) studied the kinetics of the thiophene

hydrogenolysis using an integral method and Marquardt optimization method as a mathematical tool. Vanrysselberghe and Froment (1996) developed a kinetic model applying a differential method for HDS of dibenzothiophene and a Marquardt routine for the estimation of parameters. Least squares Levenberg-Marquardt method was used in conjunction with the software Origin Lab by Slomkiewicz (2004) in the determination of the kinetic equation for the synthesis of ethers. Vrinat, Laurenti and Geantet (2012) determined kinetic parameters for deep HDS of refractory compounds such as 4,6-dimethyldibenzothiophene (4,6-DMDBT), to understand the inhibition effect of H_2S over the metal sulfide species, and the carrier effect on ReS_2 catalysts. Jarullah, Mujtaba and Wood (2011) developed kinetics for the HDS of oil using *CoMo*/ γ - Al_2O_3 catalysts. They established a system of algebraic differential equations, and solved these employing linear and non-linear approximations for the parameters estimation. Also they propose an optimization method based on the Sum of Squared Error (SSE) minimization, between the experimental and the predicted concentration.

Currently the Transition State Theory (TST) coupled with quantum dynamics calculations has been established as an important methodology for thermodynamics and kinetic parameters estimation, because it is now possible to perform quantum mechanical *ab initio* calculations without consuming too much computational time and resources (Truhlar, Garrett & Klippenstein, 1996). However, the implementation of this methodology is still very limited. Daudin *et al.* (2007), proposed kinetic models for HYD of 2,3-dimethyl-2-butene under the same operational conditions of HDS reactions, by means of the Brønsted-Evans-Polanyi relation. They found a kinetic model that allowed them to raise a rational interpretation of the observed phenomenon. In a later work Daudin *et al.* (2008) studied the competition between HDS and HYD with model molecules under realistic HDS conditions, over bulk monometallic and bimetallic catalysts. It was considered two simultaneous reactions assuming a unique type of active site in which HDS and HYD compete. The parameters estimation of the kinetics model developed was carried out using again the Brønsted-Evans-Polanyi relation and minimizing the deviation of theoretical HDS and the HYD rates from experimental data, by assuming a Langmuir-Hinshelwood mechanism rate, determining steps and the steady state approximation.

Some rigorous optimization problems do not converge easily with the gradient-based optimization methods because of their high dimensionality and non-linearity. The implementation of stochastic methods such as Monte Carlo, simulated annealing and Genetic Algorithms (GAs) are fair options in these cases. The advantage of using GAs instead of gradient-based methods, when mathematical robustness is required, is that GAs have a remarkable balance between exploration and exploitation of the search space, avoiding getting trapped in local minima (Elliott *et al.*, 2004). Abassi and Fetamy (2009) used GAs coupled with a very rigorous mathematical model to search for the optimal conditions in the HDS process of gas oil. The results show that the GAs were used successfully in the process optimization. Farooji, Vatani and Mokhtari (2010) have studied the reaction kinetics of oxidative coupling of methane catalyzed by perovskite, calculating optimized kinetic parameters through the application of genetic algorithms. By comparing the proposed kinetic with the experimental data they obtained an average error of 20%.

In this work, the HDS and the HYD reactions of simulated FCC naphtha feed over a $CoMo/\gamma-Al_2O_3$ catalyst were studied. The kinetics model proposed by Daudin *et al.* (2008) was used, applying the Langmuir-Hinshelwood adsorption mechanisms (Vrinat, 1983). Model parameters were calculated using genetic algorithms. Furthermore, these parameters were enhanced by applying the Nelder-Mead Simplex method (Forrest, 1993; Edgar, Himmelblau & Lasdon, 2001; Martínez-González, 2001; Navidi, 2006; Montgomery & Runger, 1996). Thermodynamic properties and frequency factors obtained were compared with those reported by Vanrysselberghe and Froment (1996) and Vanrysselberghe, Le Gall and Froment (1998). The latter were statistically validated by calculating confidence intervals, using covariance matrices.

2. EXPERIMENTAL

Catalyst Preparation

$CoMo$ catalyst containing 10.2% wt of MoO_3 and 2.1% wt of Co , supported on commercial $\gamma-Al_2O_3$ pro-

catalyse, was used. $\gamma-Al_2O_3$ (BET surface area: 208 m²/g, pore volume: 0.6 cm³/g and pore diameter: 116 Å) was modified with Mo and Co by incipient wetness impregnation with an aqueous solution of $(NH_4)_6Mo_7O_{24} \cdot 4H_2O$ (Merck, 99%), and subsequently with an aqueous solution of $Co(NO_3)_2 \cdot 6H_2O$ (Sigma-Aldrich, 99.5%). After each impregnation the solid was dried with N_2 flow (100 mL · min⁻¹) at 120°C for 12 h, and then was calcined under air flow (100 mL · min⁻¹) at 500°C for 4 h.

Experimental Procedure

Catalytic tests were made in a continuous-flow stainless-steel fixed-bed reactor. The catalyst was dried in situ with N_2 flow (100 mL · min⁻¹) at 120°C for 1h, followed by the activation at 400°C with a 15% v/v of H_2S/H_2 (100 mL · min⁻¹) for 3 h. The model feed was conformed of 2-methylthiophene (2MT, Sigma-Aldrich 98%), as a representative molecule of sulphur compounds, and a mixture of olefins consisting of 2,4,4-trimethylpentene (TMP, Sigma-Aldrich 99%) diluted in n-heptane (J. T. Baker, 99.4%) and dodecane (2wt.%, Sigma-Aldrich 99%) as internal standard for chromatographic analysis. The compositions of the model feed are shown in Table 1.

Table 1. Model feed concentration for each of the HDS reactions. Each experiment was performed at three temperature levels: 250, 260 and 270 °C.

Experiment	Concentration of reactant in the charge	
	2MT [wt.%]	TMP [wt.%]
1	1.0	10
2		15
3		20
4	1.5	10
5		15
6		20
7	2.0	10
8		15
9		20

2MT: 2-methylthiophene; TMP: 2, 4, 4-trimethylpentene.

The reactor was pressurized with H_2 until it reached 1.7 MPa then the liquid load was fed allowing the reac-

tion to start, at a liquid-flow rate of 20 ml·h⁻¹ and H₂ to liquid feed ratio of 500. In previous experiments Pérez-Martínez *et al.* (2010) the absence of any diffusion limitations has been demonstrated, under the mentioned conditions and applying the experiments suggested by Le Page (1987). Liquid samples were taken every hour for about 7 h of reaction, and these were analysed on a HP 6890 gas chromatograph with a FID detector and a column HP-1 (100 m × 0.25 mm × 0.5 µm). Steady state was reached after 3h of reaction; this was verified by the stabilization of the total conversion.

Table 1 shows the experimental 3^K (K=3) design used. The concentration of 2MT and TMP were varied at three levels. Each experiment was carried out at three different temperatures (250, 260 and 270°C).

The catalytic activity was expressed as the total conversion of the reactants (2MT and TMP) after the steady state was reached.

Mathematical Modeling

According to the HDS pathway of 2MT proposed by Pérez-Martínez *et al.* (2010), the 1-pentene, 2-pentene and n-pentene (C₅s) were considered desulfurized products. Although in the HDT of TMP, isomerization and cracking reactions occur at certain extent in order to simplify the kinetic model they were neglected and the direct HYD of TMP reaction producing isooctane was the only one considered as an assumption for the kinetic model.

Table 2 shows the equations that describe the considered mechanisms, corresponding to the reactions of TMP and 2MT respectively (Daudin *et al.*, 2008). For the TMP reactions, the rate determining step is (*Equation 5*), which is the first hydrogen transferred from the SH group to the adsorbed TMP. For the 2MT reaction, the controlling step is *Equation 10*, which is the first hydrogen transferred to the adsorbed 2MT. Only one type of active site is considered and both reactants are adsorbed competitively. This assumption ought to reduce the degrees of freedom, the mathematical complexity of the model and the number of experiments, without losing reliability in results (Daudin *et*

al., 2008). Thereby, *Equations 1 - 5* and *Equation 9* are in equilibrium. *Equations 6 - 8* and *Equations 11 - 15* corresponding to desorption and equilibrium for the global system of the reactions, are not taken into account due to these steps and do not contribute to the kinetics model approach. This is because adsorptions in a single active site and the controlling steps have been defined as the relevant criteria for the model (Daudin *et al.*, 2008).

Table 2. Reaction mechanisms for the HYD of TMP and reactions mechanisms for the HDS of 2MT.

$M^* + H_2S \xrightleftharpoons{K_S} MS + H_2$	(1)
$MS + M^* + H_2 \xrightleftharpoons{K_{H_2}} MSH + MH$	(2)
$MS + M^* + H_2S \xrightleftharpoons{K_{H_2S}} 2MSH$	(3)
$M^* + R \xrightleftharpoons{K_S} MR$	(4)
$MR + MSH \xrightleftharpoons{K_{SH}} MRH + MS$	(5)
$MRH + MH \rightarrow MRH_2 + M^*$	(6)
$MRH_2 \rightarrow RH_2 + M^*$	(7)
$2MRH_2 + H_2 \rightarrow 2M^* + 2H_2S$	(8)
$M^* + RS \xrightleftharpoons{K_{RS}} MRS$	(9)
$MRS + MSH \xrightleftharpoons{K_{SH}} MRHS + MS$	(10)
$MRHS + MH \rightarrow MRH_2S + M^*$	(11)
$MRH_2S + MH \rightarrow MRH_3S + M^*$	(12)
$MRH_3S + MSH \rightarrow MRH_4S + MS$	(13)
$MRH_4S + H_2 \rightarrow MRH_4 + H_2S$	(14)
$MRH_4 \rightarrow RH_4 + M^*$	(15)

M* corresponds to one adsorption site, S is a Sulphur; the TMP and the 2MT are denoted by R and RS respectively.

The reaction rate equations for HYD and HDS can be expressed as follows (Daudin *et al.*, 2008):

$$r_{HYD} = k_{HYD} C_{MR} C_{MSH} \quad (16)$$

$$r_{HDS} = k_{HDS} C_{MRS} C_{MSH} \quad (17)$$

And the sites conservation balance is represented in *Equation 18*.

$$C_{M^*} + C_{MR} + C_{MRS} + C_{MS} + C_{MSH} + C_{MH} = 1 \quad (18)$$

Consider *Equation 4* in which the first adsorption of TMP occurs. Since this step is in equilibrium, it is valid applying the steady state approximation, so the reaction rate can be written as represented in *Equation 19*.

$$\frac{dC_{MR}}{dt} = k_R C_{M^*} C_R - k_{-R} C_{MR} = 0 \quad (19)$$

Rearranging *Equation 19*, it is possible to find an expression for the concentration of sites occupied by TMP (CMR) as *Equation 20* shows, and this procedure is implemented in all the steps considered in equilibrium. This combined with the *Equation 18* leads to an expression for the concentration of metallic sites (M*). And, finally, because the reactions are occurring in vapor phase, concentrations can be replaced for partial pressures.

$$k_R C_{M^*} C_R = k_{-R} C_{MR} \text{ with } k_R = \frac{k_R}{k_{-R}} \quad (20)$$

$$C_{MR} = k_R C_{M^*} C_R$$

Based on these considerations, reaction rate equations for HYD and HDS were obtained (Daudin *et al.*, 2008) and are shown in *Equation 21* and *Equation 22* respectively.

$$r_{HYD} = k_{HYD} \frac{(K_R P_R)(K_{H_2S} P_{H_2S})^{1/2} \left(\frac{P_{H_2S}}{K'_S P_{H_2}} \right)^{1/2}}{\left[1 + (K_R P_R) + (K_{RS} P_{RS}) + \left(\frac{P_{H_2S}}{K_S P_{H_2}} \right) + (K_{H_2S} P_{H_2S})^{1/2} \left(\frac{P_{H_2S}}{K_S P_{H_2}} \right)^{1/2} + (K_{H_2} P_{H_2})(K_{H_2S} P_{H_2S})^{-1/2} \left(\frac{P_{H_2S}}{K_S P_{H_2}} \right)^{1/2} \right]^2} \quad (21)$$

$$r_{HDS} = k_{HDS} \frac{(K_{RS} P_{RS})(K_{H_2S} P_{H_2S})^{1/2} \left(\frac{P_{H_2S}}{K'_S P_{H_2}} \right)^{1/2}}{\left[1 + (K_R P_R) + (K_{RS} P_{RS}) + \left(\frac{P_{H_2S}}{K_S P_{H_2}} \right) + (K_{H_2S} P_{H_2S})^{1/2} \left(\frac{P_{H_2S}}{K_S P_{H_2}} \right)^{1/2} + (K_{H_2} P_{H_2})(K_{H_2S} P_{H_2S})^{-1/2} \left(\frac{P_{H_2S}}{K_S P_{H_2}} \right)^{1/2} \right]^2} \quad (22)$$

The terms k_{HYD} and k_{HDS} are rate constants for the HYD and HDS respectively, depending on the partial pressure and conversions. The latter obeys the Arrhenius law regarding temperature (Vanrysselberghe & Froment, 1996). K_R and K_{RS} are adsorption constants for TMP and 2MT; K_{H_2} and K_{H_2S} are equilibrium constants for hydrogen and hydrogen sulphide over the catalytic surface; K_S represents the equilibrium constant for the sulphur species. According to Van't Hoff's equation, it is possible to relate adsorption heats with temperature using thermodynamics relations as shown in *Equation 23*.

$$K_i = A_i \exp\left(-\frac{\Delta H^0}{RT}\right) \quad (23)$$

The design equation for the fixed-bed reactor (see *Equation 24*) was used to correlate the experimental results with the model proposed and then obtain model parameters.

$$\frac{W}{F_{A0}} = \int_{x_1}^{x_2} \frac{dx_A}{r_A} \quad (24)$$

Model parameters were obtained through an optimization strategy shown in Figure 1. As a first step, kinetic parameters reported in literature (Vanrysselberghe & Froment, 1996) from thiophenic and olefin compounds were taken as initial values to start the calculation. Parameters that fit better and had a lower overall error were used as initial population. Once the initial population and intervals are established, the kinetic parameters were estimated using GAs as implemented in Matlab *optimtool* GUI. Some characteristic information of the performed GAs is summarized in Table 3.

Mutation function was chosen as constrain dependent and scattered crossover was used. Some other options as time limit, fitness limit and functions tolerance were set as default. To find the optimal parameters values, a mean square error percentage expressed in Equation 25 was used as the objective function to minimize. This measures the gap between the experimental W/F_{A0} and the calculated $\langle W/F_{A0} \rangle$ values. $\langle W/F_{A0} \rangle$ was calculated through the combination of Equation 24 with Equation 21 and Equation 22. Equation 24 was solved by using Simpson's 1/3 integration method.

$$\sum \sum \frac{e_{2MT}^2}{N} * \frac{e_{TMP}^2}{N} * 100 \quad (25)$$

Where,

$$e_{2MT}^2 = \frac{(W/F_{A0} - \langle W/F_{A0} \rangle)^2}{W/F_{A0}}$$

$$e_{TMP}^2 = \frac{(W/F_{A0} - \langle W/F_{A0} \rangle)^2}{W/F_{A0}}$$

The parameters calculated through GAs were improved using the Nelder-Mead simplex direct search method (fminsearch-Unconstrained nonlinear minimization) minimizing Equation 25, leading to a reduction of the solution range. Both methods were performed sequentially to obtain the objective function global minimum. This strategy was repeated as many times as needed to reduce the solution range for each parameter, and thus minimizing the global error.

Table 3. Characteristic information of used genetic algorithms.

Parameter	Value
Population size	200
Number of generations	100
Time limit	Infinite (default)
Elite count	2 (default)
Crossover fraction	0.8 (default)

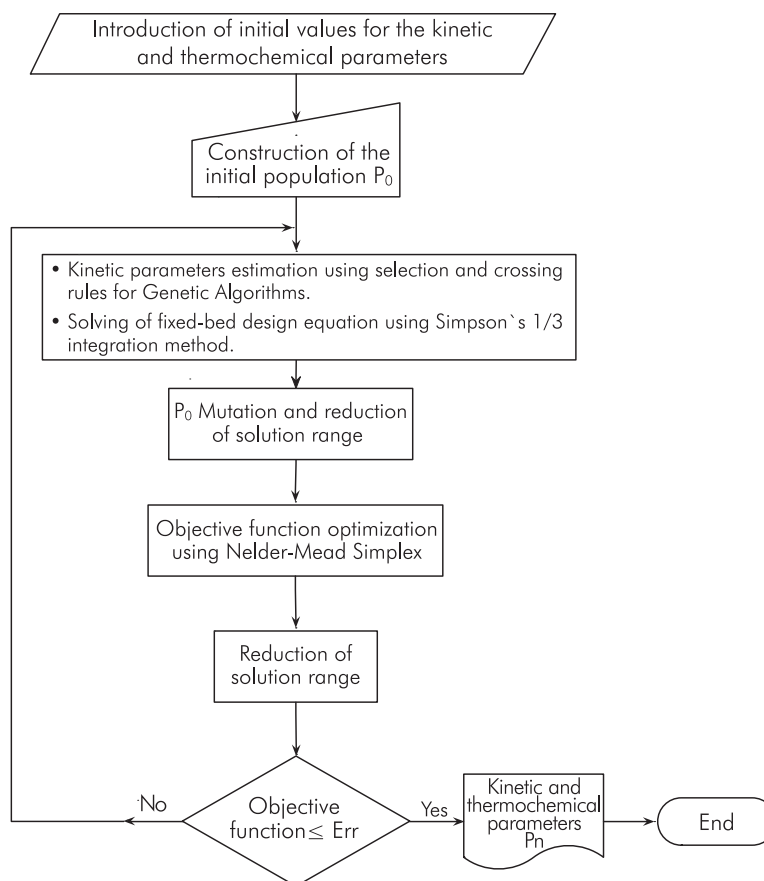


Figure 1. Optimization strategy for the thermochemical parameters estimation, using GAs as implemented in Matlab optimtool.

3. RESULTS AND DISCUSSION

Catalytic Evaluation

Experimental results are shown in Table 4, corresponding to the experimental design reactions presented in Table 1. It can be observed that, as expected, HDS and HYD conversion levels depend on both reactant concentration and on temperature level. Some trends could be easily observed in Table 4. For better illustration, some of these trends were plotted in Figure 2a and 2b. In Figure 2a for example, it could be observed that the HYD conversion is inhibited with the increase in 2MT concentration. In contrast, in Table 4, HDS conversion variations with increasing olefins concentration were less important. This could be an indicative that sulfur molecules are competitively absorbed with olefins on the HYD sites. In some way this observation could support the use of only one site for HYD and HDS in our kinetic model. Regarding selectivity, in Table 4 it could be observed that at the lowest 2MT concentration (1 wt.%) HDS conversion was higher than the HYD one, however at the medium and higher concentration levels (1.5 and 2 wt.%) the inverse trend was observed. Thus, with increasing 2MT concentration, the HDS/HYD ratio was reduced. In contrast, by increasing the olefin content, the HDS/HYD ratio was increased. Thus, selectivity depends strongly on the reactant concentrations. This observation could explain some contradictory results in the literature; for example, Vrinat (1983) observed

that the HYD conversion was higher than the HDS, meanwhile other authors (Mey *et al.*, 2004) observed the inverse trend.

The temperature influence is shown in Figure 2b as expected there is an exponential dependence of both HYD and HDS conversion with temperature. This could be ascribed to the Arrhenius law, which says that the rate constant vary exponentially with temperature. This behavior was also observed by Li *et al.* (2009). They found the rate constant after a linearization of the Arrhenius equation through a variable conversion. At lower temperatures, HYD conversion is clearly higher than HDS, however this difference is attenuated with the increasing in temperature. It is known that HYD reactions are thermodynamically limited at high temperatures because of their exothermicity (Jongpatiwut *et al.*, 2004).


Kinetics Model

Figures 3 and 4 show the predicted conversion by the model with respect to the experimental, for the HDS and HYD reactions respectively. Both figures give an idea of how close are the predicted values using the model with respect to the experimental data. It can be observed in both cases, that dispersion is considerably small, indicating a good prediction of the model. There is a better fit for HDS, for which the calculation of the overall error at the three different temperatures was


Table 4. Experimental conversions (C_i) of HDS of 2MT and HYD of TMP.

TMP(wt.%) → 2MT(wt.%) ↓	10		15		20		Temperature (°C)
	%C _{2MT}	%C _{TMP}	%C _{2MT}	%C _{TMP}	%C _{2MT}	%C _{TMP}	
1.0	58.8	59.3	60.8	52.3	60.2	47.1	250
1.5	38.3	51.9	39.8	37.7	33.6	28.3	
2.0	25.3	47.8	29.6	37.9	22.2	28.5	
1.0	80.1	72.5	74.5	65.1	78.5	61.7	260
1.5	54.2	65.5	53.3	47.2	52.3	40.1	
2.0	40.3	61.9	45.3	50.3	34.7	38.5	
1.0	89.5	84.1	88.2	78.2	90.4	74.6	260
1.5	76.5	80.1	74.2	63.8	71.2	53.8	
2.0	60.5	76.1	64.2	67.5	58.3	60.2	

2MT: 2-methylthiophene concentration; TMP: 2,4,4-trimethylpentene concentration.

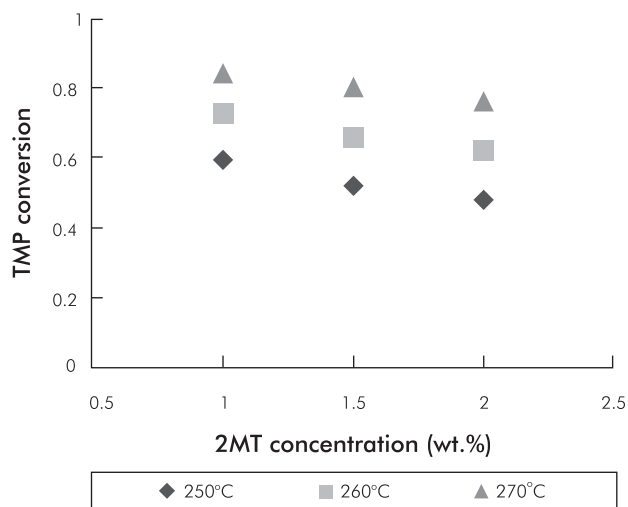

(a)

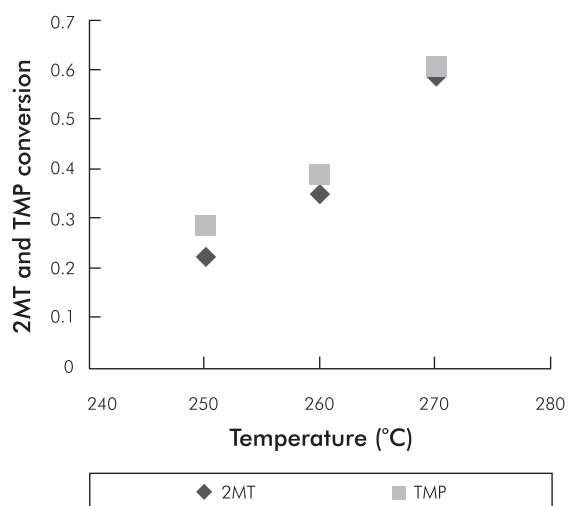

(b)

Figure 2. (a) TMP conversion as a function of 2MT concentration at (♦) 250°C, (■) 260°C, and (▲) 270°C. (b) conversions of (♦) 2MT and (■) TMP depending on the temperature, for the reactions with a 2 wt.% of 2MT and 20 wt.% of TMP.

only 6%. On the other hand, the HYD presents a larger deviation regarding the model and leads to an overall error of 10%. This could be explained, because certain reactions of isomerization and cracking were neglected in the modeling, as mentioned above. However, in spite of the certain level of dispersion in the predicted data, the trends of HDS and HYD with reactants concentration and temperature described above for the experimental data, are still observed in the predicted data.

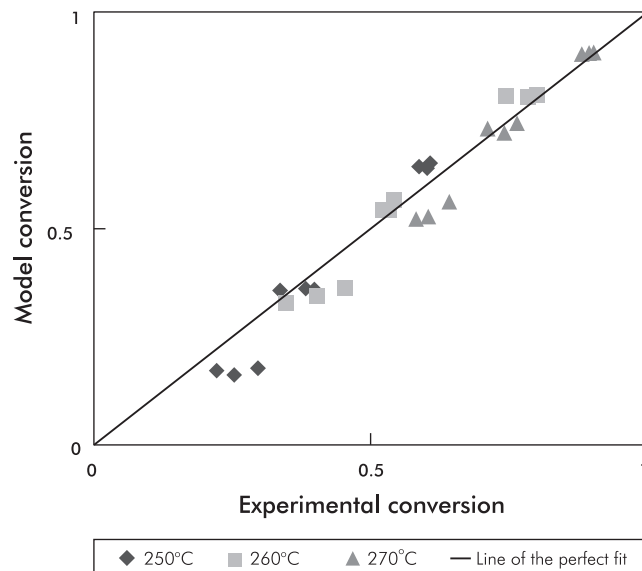


Figure 3. Dispersion of the experimental data. HDS conversion calculated by the GA simulations versus the HDS experimental conversion.

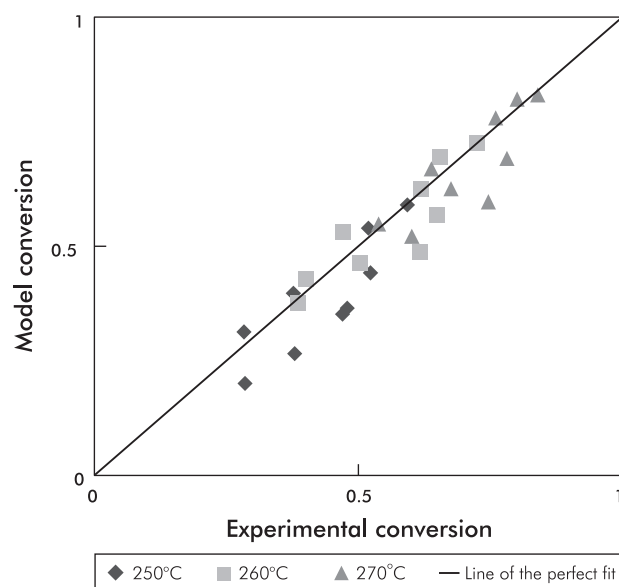


Figure 4. Dispersion of the experimental data; HYD conversion calculated by the GA simulations versus the HYD experimental conversion.

Figure 5a shows the objective function minimization evolution using GAs. The error percentage decreases as long as this becomes smaller. As Figure 5a shows, GAs were initially performed for finding global minimum. Thereafter (as shown in Figure 5b), it must be noted that values obtained through GAs were substantially refined

using the Nelder-Mead Simplex method. It is possible to observe that at these conditions the calculation converges rapidly with less than 800 iterations. Results shown in Figures 3 and 4, along with the calculated overall error, indicate that model predictions are suitable, bearing in mind that the model was made on the basis of the existence of one type of active site, which may be far from the reality of intrinsic phenomenon that occurs in the reactions considered. Note that this approach is presented as a good alternative despite having been selected, because it facilitates the mathematical treatment and leads to a smaller number of experiments since it reduces the number of degrees of freedom. Other authors (Okamoto, Tomioka, Imanaka & Teranishi, 1980; Kasztelan & Guillaume, 1994) also used this simplification, and the deviations they obtained were similar to those presented in this work. Despite the error associated with the conceptual part of the mechanism, the reality is that the obtained model parameters lead to results that have a significantly small dispersion compared to experimental results seen in Figures 3 and 4. In this context, we believe that the mathematical modelling used for the application of genetic algorithms associated with the

implementation of the Nelder-Mead Simplex method, contributed to this success.

The estimated thermodynamic properties and frequency factors are shown in Table 5. For the parameters estimations with the GAs, an average of 51 iterations was reached in approximately 165 min. Additionally, there are some values reported in the literature and the confidence intervals for each parameter. As shown in Table 5, the confidence interval for each estimated parameter exhibits small values, and this indicates the validity of the approximation. Compared with previous studies (Lancheros & Carreño, 2008) in which a Levenberg-Marquardt routine was performed to determine the kinetic parameters, the GAs show a rapid convergence, and also, estimations with best accuracy, comparing the activities calculated through these parameters (see Figures 3 and 4). The average errors obtained from the Levenberg-Marquardt routine were considerably high. The above-mentioned reasons lead us to prefer the GAs instead of the gradient based methodologies. Also, other authors (Vanrysselberghe *et al.*, 1996) used successfully the Marquardt routine with 98 experiments, instead of 27 experiments required in our methodology.

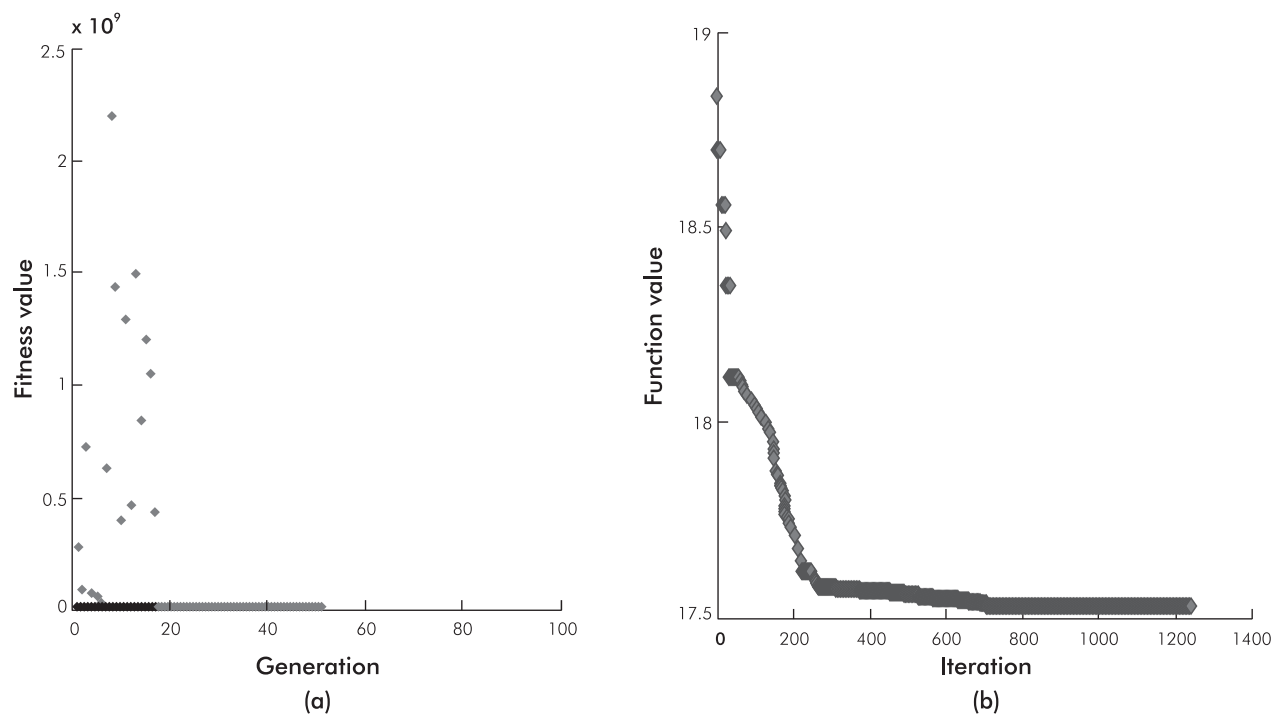


Figure 5. (a) objective function minimization in parameters determination using GAs Best: 18.1609, Mean: 77.2759.
(b) refinement using the Nelder-Mead simplex direct search, current function value: 17.5309.

Table 5. Frequency factors and thermodynamic properties estimated from modelling.

Estimated parameters		Other authors*	Confidence intervals (\pm) 95%
A_R	2333×10^{-3}		0.01957
A_{RS}	22692×10^{-3}		0.2117
A_{H_2S}	4.265×10^{-3}		8.19×10^{-5}
A_{H_2}	5.825×10^2		10.68
A_S	321.4×10^{-3}		0.006561
A_{HDS}	5.746×10^3		0.1851
A_{HYD}	1.036×10^3		1.008
ΔH_R (J/mol)	-4.189×10^3		30.9
ΔH_{RS} (J/mol)	-2.054×10^4	-5.2×10^4 to -1.9×10^4	34.46
ΔH_{H_2S} (J/mol)	-1.1907×10^5		513.9
ΔH_{H_2} (J/mol)	-2.4998×10^4	-2.5×10^4 to -1.4×10^5	505.4
ΔH_S (J/mol)	-2.2943×10^4		505.5
E_{aHDS} (J/mol)	9.1253×10^4	6×10^4 to 1.63×10^5	0.1641
E_{aHYD} (J/mol)	5.9570×10^4	5.9×10^4	3.708

* Vanrysselberghe & Froment, 1996; Vanrysselberghe, Del Gall & Froment, 1998.

The activation energies for HDS are higher compared with calculated values for HYD. This is expected accordingly to the observed behavior of these two reactions depending on the temperature, as shown in Figure 4. Moreover, a similar behavior is observed for the constants K_R and K_{RS} . Adsorption constants for H_2S and H_2 are significantly higher than the others, as observed in Table 4. This result is in good agreement with the possible difficulty that can produce a dissociative adsorption of H_2S and H_2 on the catalyst surface, as discussed in previous works by Kaztelan and Guillaume (1995).

As observed in Figure 2, at equal conditions the activity of HDS is always lower than that for the HYD. This is remarkable at 250°C, and the gap tends to disappear at higher temperatures. The above-mentioned behavior is in agreement with previous works (Vrinat, 1983). In this sense, the kinetic parameters determined in this work reproduce this important behavior and is described as a function of the temperature, in accordance with Arrhenius and Van't Hoff's laws.

4. CONCLUSIONS

- A kinetics model for the HDT of FCC gasoline that considers simultaneous HDS and HYD reactions was obtained. Despite considering only one active site for the competitive adsorption of reactants, it leads to a close prediction of the experimental results. Thus, it was possible to determine kinetic and thermodynamic parameters such as activation energies, adsorption heats and frequency factors with a fairly accurate approximation.
- It is remarkable that the activation energy of the HDS is higher than the calculated for HYD, and this behavior was experimentally observed. Additionally, the improvement of this kinetics would lead to a better understanding of the HDS/HYD selectivity, a very important relation in the FCC gasoline desulfurization.
- The mathematical strategy developed in this work, based on the application of genetic algorithms asso-

ciated with the Nelder-Mead Simplex optimization method, proved to be an adequate strategy for predicting parameters when the number of experiments is relatively low. Using the methodology proposed in this article, it is possible to develop more rigorous kinetic models, which could include other types of active sites, close HDS conditions and reactions of interest in the HDT, leading to a better modeling of the catalytic system.

ACKNOWLEDGEMENTS

This work was possible thanks to funding from the *Vicerrectoría de Investigación y Extensión -Universidad Industrial de Santander-* through Project 5462. This article is dedicated posthumously to Professor Aristóbulo Centeno from UIS.

REFERENCES

- Abassi, R. & Fatemi, S. (2009). Mathematical modelling of gas oil HDS and optimization of operational conditions in Trickle-Bed reactor by genetic algorithm. *Int. J. Chem. Reactor Eng.*, 7(1), 1542-6580.
- Brunet, S., Mey, D., Pérot, G., Bouchy, C. & Diehl, F. (2005). On the hydrodesulfurization of FCC gasoline: a review. *Appl. Catal. A*, 278(2), 143-172.
- Daudin, A., Perot, G., Brunet, S., Raybaud, P. & Bouchy, C. (2007). Transformation of a model FCC gasoline olefin over transition monometallic sulfide catalysts. *J. Catal.*, 248(1), 111-119.
- Daudin, A., Lamic, A., Perot, G., Brunet, S., Raybaud, P. & Bouchy, C. (2008). Microkinetic interpretation of HDS/HYDO selectivity of the transformation of a model FCC gasoline over transition metal sulfides. *Catal. Today*, 130(1), 221-230.
- Edgar, T. F., Himmelblau, D. M. & Lasdon, L. S. (2001). *Optimization of chemical processes*. Pennsylvania: Mc Graw Hill.
- Elliott, L., Ingham, D. B., Kyne, A. G., Mera, N. S., Pourkashanian, M. & Wilson, C. W. (2004). Genetic algorithms for optimisation of chemical kinetics reaction mechanism. *Prog. Energy Combust. Sci.*, 30(3), 297-328.
- Farooji, N. R., Vatani, A. & Mokhtari, S. (2010). Kinetic simulation of oxidative coupling of methane over perovskite catalyst by genetic algorithm: Mechanistic aspects. *J. Nat. Gas. Chem.*, 19(4), 385-391.
- Forrest, S. (1993). Genetic algorithms: Principles of natural selection applied to computation. *Science*, 261(5123), 872-878.
- Jarullah, A., Mujtaba I. & Wood, A. S. (2011). Kinetic parameter estimation and simulation of trickle-bed reactor for hydrodesulfurization of crude oil. *Chem. Eng. Sci.*, 66(5), 859-871.
- Jongpatiwut, S., Li, Z., Resasco, D. E., Alvarez, W. E., Sughrue, E. L. & Dodwell, G. W. (2004). Competitive hydrogenation of poly-aromatic hydrocarbons on sulfur-resistant bimetallic Pt-Pd catalyst. *Appl. Catal. A*, 262: 241-253.
- Kasztelan, S. & Guillaume, D. (1994). Inhibiting effect of hydrogen sulfide on toluene hydrogenation over a molybdenum disulfide/alumina catalyst. *Ind. Eng. Chem. Res.*, 33(2), 203-210.
- Kaufmann, T., Kaldor, A., Stuntz, G., Kerby, M. & Ansell, L. (2000). Catalysis science and technology for cleaner transportation fuels. *Appl. Catal. Today*, 62(1), 77-90.
- Le Page, J. F. (1987). *Applied Heterogeneous Catalysis*. Paris: Editions Technip.
- Li, M., Li, H., Jiang, F., Chu, Y. & Nie, H. (2009). Effect of surface characteristics of different alumina on metal-support interaction and hydrodesulfurization activity. *Fuel*, 88(7), 1281-1285.
- Martínez-González, J. L. (2001). Optimización y ajuste de parámetros mediante el Método Simplex (Nelder - Mead). *Ia Reunión de Usuarios de EcosimPro*, UNED, Madrid: EcosimPro.
- Mey, D., Brunet, S., Canaff, C., Maugé, F., Bouchy, C. & Diehl, F. (2004). HDS of a model FCC gasoline over a sulfided $\text{CoMo}/\gamma\text{-Al}_2\text{O}_3$ catalyst: Effect of the addition of potassium. *J. Catal.*, 227(2), 436-447.
- Miller, J., Reagan, W., Kaduk, J., Marshall, C. & Kropf, A. (2000). Selective hydrodesulfurization of FCC naphtha

- with supported MoS_2 catalysts: The role of cobalt. *J. Catal.*, 193(1), 123-131.
- Montgomery, D. C. & Runger, C. G. (2006). *Probabilidad y estadística aplicadas a la ingeniería*. 2nd Ed. México D.F: Limusa Wiley.
- Morterra, C. & Magnacca, G. (1996). A case of study: Surface chemistry and surface structure of catalytic aluminas, as studied by vibrational spectroscopy of adsorbed species. *Catal. Today*, 27(3-4), 497-532.
- Navidi, W. (2006). *Estadística para ingenieros y científicos*, México, D.F.: McGraw Hill.
- Lancheros, N. B. & Carreño, S. A. (2008). Determinación de la cinética de las reacciones simultáneas de hidrodesulfuración del 2-metiltofeno e hidrogenación del 2,4,4 trimetilpenteno sobre el catalizador $CoMo/\gamma-Al_2O_3$. *Tesis de pregrado, Ingeniería Química*. UIS, Bucaramanga, Colombia, 51pp.
- Okamoto, Y., Tomioka, H., Imanaka, T. & Teranishi, S. (1980). Surface structure and catalytic activity of sulfided $CoMo/Al_2O_3$ catalysts: Hydrodesulfurization and hydrogenation activities. *J. Catal.*, 66(1), 93-100.
- Parijs, I. & Froment, G. F. (1986). Kinetics of hydrodesulfurization on a $CoMo/\gamma-Al_2O_3$ catalyst. 1. Kinetics of the hydrogenolysis of thiophene. *Ind. Eng. Chem. Prod. Res. Dev.*, 25(3), 431-436.
- Pérez-Martínez, D. J., Eloy, P., Gaigneaux, E. M., Giraldo, S. A. & Centeno, A. (2010). Study of the selectivity in FCC naphtha hydrotreating by modifying the acid base balance of $CoMo/Al_2O_3$ catalysts. *Appl. Catal. A*, 390(1-2), 59-70.
- Ratnasamy, P. & Sivasanker, S. (1980). Structural chemistry of $Co-Mo$ -Alumina catalysts. *Catal. Rev. Sci. Eng.*, 22(3), 401-429.
- Slomkiewicz, P. M. (2004). Determination of the Langmuir-Hinshelwood kinetic equation of synthesis of ethers. *Appl. Catal. A*, 269(1-2), 33-42.
- Song, C. (2003). An overview of new approaches to deep desulfurization for ultra-clean gasoline, diesel fuel and jet fuel. *Catal. Today*, 86(1-4), 211-263.
- Truhlar, D. G., Garrett, B. C. & Klippenstein, S. J. (1996). Current status of transition-state theory. *J. Phys. Chem.*, 100(31), 12771-12800.
- United States Environmental Protection Agency – EPA (2011). Standards for gasoline. United States. Accessed: May 12, 2013. Available in: <<http://www.epa.gov/otaq/fuels/gasolinefuels/index.htm>>
- Vanrysselberghe, V. & Froment, G. F. (1996). Hydrodesulfurization of dibenzothiophene on a $CoMo/\gamma-Al_2O_3$ catalyst: Reaction network and kinetics. *Ind. Eng. Chem. Res.*, 35(10), 3311-3318.
- Vanrysselberghe, V., Le Gall, R. & Froment, G. F. (1998). Hydrodesulfurization of 4-methyldibenzothiophene and 4,6-dimethyldibenzothiophene on a $CoMo/\gamma-Al_2O_3$ catalyst: Reaction network and kinetics. *Ind. Eng. Chem. Res.*, 37: 1235-1242.
- Vrinat, M. (1983). The kinetics of the hydrodesulfurization process: A review. *Appl. Catal.*, 6(2), 137-158.
- Vrinat, M., Laurenti, D. & Geantet, C. (2012). Use of competitive kinetics for the understanding of deep hydrodesulfurization and sulfide catalysts behavior. *Appl. Catal. B*, 128: 3-9.

AUTHORS

Carlos-Mauricio Celis-Cornejo

Affiliation: *Universidad Industrial de Santander*.
Chemical Engineer, Ph. D. Graduate Student, *Universidad Industrial de Santander*.
e-mail: ransereg@hotmail.com

Gustavo-Alberto Granados-Zarta

Affiliation: *Universidad Industrial de Santander*.
Chemical Engineer, *Universidad Industrial de Santander*.
e-mail: gagz.07@gmail.com

Carlos-Eduardo Bravo-Villarreal

Affiliation: *Universidad Industrial de Santander*.
Chemical Engineer, *Universidad Industrial de Santander*.
e-mail: bravovillarreal1098@hotmail.com

David de Jesús Pérez-Martínez

Affiliation: *ECOPETROL S.A. - Instituto Colombiano del Petróleo*.
Chemical Engineer, Ph. D. *Universidad Industrial de Santander*.
e-mail: davidje.perez@ecopetrol.com.co

Sonia A. Giraldo-Duarte

Affiliation: *Universidad Industrial de Santander*.
Chemical Engineer, M. Sc. *Universidad Industrial de Santander*.
Docteur En Sciences Naturelles Appliquées, *Université Catholique De Louvain*.
e-mail: sgiraldo@uis.edu.co

NOTATION

<i>2MT</i>	2-methylthiophene
<i>4,6-DMDBT</i>	4,6-dimethyldibenzothiophene
<i>A</i>	Arrhenius frequency factor, $\text{L}\cdot\text{mol}^{-1}\cdot\text{s}^{-1}$
<i>C</i>	Concentration of sites
<i>C5s</i>	n-pentanes
<i>Ea</i>	Activation energy
<i>F_{A0}</i>	Molar flow, $\text{mol}\cdot\text{s}^{-1}$
<i>FCC</i>	Fluid Catalytic Cracking
<i>GAs</i>	Genetic Algorithms
<i>HDS</i>	Hydrodesulfurization
<i>HDT</i>	Hydrotreating
<i>HYD</i>	Hydrogenation
<i>k</i>	Rate constant, $\text{L}\cdot\text{mol}^{-1}\cdot\text{s}^{-1}$
<i>K</i>	Equilibrium constant
<i>P_{H2}</i>	Hydrogen partial pressure, Pa
<i>P_{H2S}</i>	Hydrogen sulfide partial pressure, Pa
<i>R</i>	Gas constant
<i>r_{HDS}</i>	Hydrodesulfurization reaction rate, $\text{mol}\cdot\text{s}^{-1}$
<i>r_{HYD}</i>	Hydrogenation reaction rate, $\text{mol}\cdot\text{s}^{-1}$
<i>SSE</i>	Sum of Squared Errors
<i>T</i>	Temperature, K
<i>TMP</i>	2,4,4-trimethylpentene
<i>TST</i>	Transition State Theory
<i>W</i>	Catalyst weight, kg
<i>x</i>	Conversion
ΔH	Enthalpy change, $\text{J}\cdot\text{mol}^{-1}$

SUFFIXES

H_2	Hydrogen
H_2S	Hydrogen Sulfide
M^*	Available active site
MH	Adsorbed hydrogen on an active site
MR	Adsorbed R on an active site
MRS	Adsorbed RS on an active site
MS	Adsorbed sulfur on an active site
MSH	Adsorbed SH on an active site
R	2,4,4-trimethylpentene
RS	2-methylthiophene
S	Sulfur

