



Journal of Applied Research and Technology

ISSN: 1665-6423

jart@aleph.cinstrum.unam.mx

Centro de Ciencias Aplicadas y Desarrollo

Tecnológico

México

Davoudi Kashkoli, Mosayeb; Zamani Nejad, Mohammad
Effect of Heat Flux on Creep Stresses of Thick-Walled Cylindrical Pressure Vessels
Journal of Applied Research and Technology, vol. 12, núm. 3, junio-, 2014, pp. 585-597
Centro de Ciencias Aplicadas y Desarrollo Tecnológico
Distrito Federal, México

Available in: <http://www.redalyc.org/articulo.oa?id=47431368022>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

redalyc.org

Scientific Information System

Network of Scientific Journals from Latin America, the Caribbean, Spain and Portugal

Non-profit academic project, developed under the open access initiative

Effect of Heat Flux on Creep Stresses of Thick-Walled Cylindrical Pressure Vessels

Mosayeb Davoudi Kashkoli and Mohammad Zamani Nejad*

Mechanical Engineering Department,
Yasouj University, P.O. Box 75914-353, Yasouj, Iran.
*m.zamani.n@gmail.com

ABSTRACT

Assuming that the thermo-creep response of the material is governed by Norton's law, an analytical solution is presented for the calculation of time-dependent creep stresses and displacements of homogeneous thick-walled cylindrical pressure vessels. For the stress analysis in a homogeneous pressure vessel, having material creep behavior, the solutions of the stresses at a time equal to zero (i.e. the initial stress state) are needed. This corresponds to the solution of materials with linear elastic behavior. Therefore, using equations of equilibrium, stress-strain and strain-displacement, a differential equation for displacement is obtained and then the stresses at a time equal to zero are calculated. Using Norton's law in the multi-axial form in conjunction with the above-mentioned equations in the rate form, the radial displacement rate is obtained and then the radial, circumferential and axial creep stress rates are calculated. When the stress rates are known, the stresses at any time are calculated iteratively. The analytical solution is obtained for the conditions of plane strain and plane stress. The thermal loading is as follows: inner surface is exposed to a uniform heat flux, and the outer surface is exposed to an airstream. The heat conduction equation for the one-dimensional problem in polar coordinates is used to obtain temperature distribution in the cylinder. The pressure, inner radius and outer radius are considered constant. Material properties are considered as constant. Following this, profiles are plotted for the radial displacements, radial stress, circumferential stress and axial stress as a function of radial direction and time.

Keywords: Thick Cylindrical Pressure Vessel, Time-Dependent, Creep, Heat Flux.

1. Introduction

Axisymmetric component such as a cylindrical vessel is more often used as the basic process component in various structural and engineering applications such as pressure vessels (e.g. hydraulic cylinders, gun barrels, pipes, boilers, fuel tanks and gas turbines), accumulator shells, cylinders for aerospace industries, nuclear reactors and military applications, pressure vessel for industrial gases or a media transportation of high-pressurized fluids and piping of nuclear reactors [1, 2]. In most of these applications, the cylinder has to operate under severe mechanical and thermal loads, causing significant creep and thus reducing its service life [1, 2, 3, 4]. Therefore, the analysis of long term steady state creep deformations is very important in these applications. [1, 2].

Weir [5] investigated creep stresses in pressurized thick walled tubes. Bhatnagar and Gupta [6] obtained solution for an orthotropic thick-walled internally pressurized cylinder by using constitutive

equations of anisotropy creep and Norton's creep law. Yang [7] obtained an analytical solution to calculate thermal stresses of thick cylindrical shells made of functionally graded materials with elastic and creep behavior. Creep damage simulation of thick-walled tubes using the theta projection concept investigated by Loghman and Wahab [8]. Gupta and Pathak [9] studied thermo creep analysis in a pressurized thick hollow cylinder. Assuming that the creep response of the material is governed by Norton's law, Zamani Nejad et. al. [10] presented a new exact closed form solution for creep stresses in isotropic and homogeneous thick spherical pressure vessels. In this paper all results have been obtained in nondimensional form. Hoseini et. al. [11] presented a new analytical solution for the steady state creep in rotating thick cylindrical shells subjected to internal and external pressure. In this paper the creep response of the material is governed by Norton's law and exact solutions for stresses are obtained under plane

strain assumption. Wah [12] developed a theory for the collapse of cylindrical shells under steady-state creep and under external radial pressure and high temperature (300 to 500 F). Pai [13] studied the steady-state creep of a thick-walled orthotropic cylinder subjected to internal pressure. They observed that the creep anisotropy has a significant effect on the cylinder behavior particularly in terms of creep rates which may differ by an order of magnitude compared to an isotropic analysis. Sankaranarayanan [14] studied the steady creep behaviour of thin circular cylindrical shells subjected to combined lateral and axial pressures. The analysis is based on the Tresca criterion and the associated flow rule. Assuming that the total strain is consist of elastic and creep components, Murakami and Iwatsuki [15] investigated the transient creep analysis of circular cylindrical shells on the basis of the strain-hardening and time-hardening theories. Murakami and Suzuki [16] developed a numerical analysis of the steady state creep of a pressurized circular cylindrical shell on the basis of Mises' criterion and the power law of creep. Sim and Penny [17] studied the deformation behaviour of thick-walled tubes subjected to a variety of loadings during stress redistribution caused by creep. Murakami and Iwatsuki [18] investigated the steady state creep of simply supported circular cylindrical shells with open ends under internal pressure by using Norton's law. Using finite-strain theory Bhatnagar and Arya [19] studied the creep behaviour of a thick-walled cylinder under large strains. Murakami and Tanaka [20] investigated the creep buckling of clamped circular cylindrical shells subjected to axial compression combined with internal pressure with special emphasis on the concept of creep stability and the accuracy of the analysis. Jahed and Bidabadi [21] presented a general axisymmetric method for an inhomogeneous body for a disk with varying thickness. An approximation has been employed during their solution algorithm. It means that they avoid considering the differentiation constitutive terms of governing equations for creep analysis. Chen et al. [22] studied the creep behavior of a functionally graded cylinder under both internal and external pressures. They observed that an asymptotic solution can be derived on the basis of a Taylor series expansion if the properties of the graded material are axisymmetric and dependent on radial coordinate. In order to investigate creep

performance of thick-walled cylindrical vessels or cylinders made of functionally graded materials, You et al. [23] proposed a simple and accurate method to determine stresses and creep strain rates in thick-walled cylindrical vessels subjected to internal pressure. Based on the power law constitutive equation, Altenbach et al. [24] presented the classical solution of the steady-state creep problem for a pressurized thick-walled cylinder. In this paper they applied an extended constitutive equation which includes both the linear and the power law stress dependencies. Singh and Gupta [25-28] developed a mathematical model to describe the steady-creep behaviour of functionally graded composite cylinders containing linearly varying silicon carbide particles in a matrix of pure aluminum involving threshold stress-based creep law. The model developed is used to investigate the effect of gradient in distribution of SiCp on the steady-state creep response of the composite cylinder. Assuming total strains to be the sum of elastic, thermal and creep strains, Loghman et al. [29] studied the time-dependent creep stress redistribution analysis of a thick-walled FGM cylinder placed in uniform magnetic and temperature fields and subjected to an internal pressure. Following Norton's law for material creep behavior and using equations of equilibrium, strain displacement and stress-strain relations in the rate form and considering Prandtl-Reuss relations for creep strain rate-stress equation, they obtained a differential equation for the displacement rate and then calculated the radial and circumferential creep stress rates. Sharma et al. [30] investigated the creep stresses in thick-walled circular cylinders under internal and external pressure, using transition theory, which is based on the concept of 'generalized principal strain measure'. Jamian et al. [31] investigated the creep analysis for a thick-walled cylinder made of functionally graded materials (FGMs) subjected to thermal and internal pressure. Singh and Gupta [32] studied the steady state creep behavior in a functionally graded thick composite cylinder subjected to internal pressure in the presence of residual stress. Hoffman's yield criterion is used, to describe the yielding of the cylinder material in order to account for residual stress. In this article, assuming that the thermo-creep response of the material is governed by Norton's law, an analytical solution is presented for the calculation of time-

dependent creep stresses and displacements of thick-walled cylindrical pressure vessels under internal heat flux.

2. Heat conduction formulation

In the steady state case, the heat conduction equation for the one-dimensional problem in polar coordinates simplifies

$$\frac{\partial}{\partial r} \left[r \lambda \frac{\partial T}{\partial r} \right] = 0 \quad (1)$$

where $T = T(r)$ is temperature distribution in the thick cylindrical pressure vessel. We may determine the temperature distribution in the cylindrical vessel by solving Eq. 1 and applying appropriate boundary conditions. Eq. 1 may be integrated twice to obtain the general solution

$$T(r) = A_1 \ln r + A_2 \quad (2)$$

The boundary conditions for when that inner surface is exposed to a uniform heat flux q_a , and the outer surface is exposed to an airstream temperature, are as follows

$$\begin{cases} -\lambda T' = q_a & , \quad r = a \\ -\lambda T' = h_\infty (T - T_\infty) & , \quad r = b \\ T' = \frac{dT}{dr} \end{cases} \quad (3)$$

Here λ , T_∞ and h_∞ are thermal conductivity, temperatures and heat transfer coefficient of the surrounding media, respectively. Substituting Eq. 2 into Eq. 3 yields

$$\begin{cases} A_1 = -\frac{aq_a}{\lambda} \\ A_2 = T_\infty + aq_a \left(\frac{1}{bh_\infty} + \frac{\ln b}{\lambda} \right) \end{cases} \quad (4)$$

Therefore:

$$T(r) = T_\infty + \frac{aq_a}{bh_\infty} - \frac{aq_a}{\lambda} \ln \left(\frac{r}{b} \right) \quad (5)$$

3. Linear elastic behavior analysis of the cylinder

For the stress analysis in a cylinder, having material creep behavior, the solutions of the stresses at a time equal to zero (i.e. the initial stress state) are needed, which correspond to the solution of materials with linear elastic behavior. In this section, equations to calculate such linear stresses in cylinder analytically will be given briefly for two cases: (a) plane strain; (b) plane stress. Consider a thick-walled cylinder with an inner radius a , and an outer radius b , subjected to internal pressure P_i and external pressure P_o that are axisymmetric (Figure 1).

3.1 The case of plane strain

The displacement in the r-direction is denoted by u_r . Three strain components can be expressed as

$$\varepsilon_{rr} = \frac{du_r}{dr} \quad (6)$$

$$\varepsilon_{\theta\theta} = \frac{u_r}{r} \quad (7)$$

$$\varepsilon_{zz} = 0 \quad (8)$$

where ε_{rr} , $\varepsilon_{\theta\theta}$ and ε_{zz} are radial, circumferential and axial strains. The stress-strain relations for homogenous and isotropic materials are

$$\sigma_{rr} = \frac{E(1-\nu)}{(1+\nu)(1-2\nu)} \left[\varepsilon_{rr} + \frac{\nu}{1-\nu} \varepsilon_{\theta\theta} - \frac{1+\nu}{1-\nu} \alpha T \right] \quad (9)$$

$$\sigma_{\theta\theta} = \frac{E(1-\nu)}{(1+\nu)(1-2\nu)} \left[\varepsilon_{\theta\theta} + \frac{\nu}{1-\nu} \varepsilon_{rr} - \frac{1+\nu}{1-\nu} \alpha T \right] \quad (10)$$

$$\sigma_{zz} = \nu(\sigma_{\theta\theta} + \sigma_{rr}) - E\alpha T \quad (11)$$

where σ_{rr} , $\sigma_{\theta\theta}$ and σ_{zz} are radial, circumferential and axial stresses, respectively. Here E , ν and α are the Young's modulus, Poisson's ratio and thermal expansion coefficient, respectively.

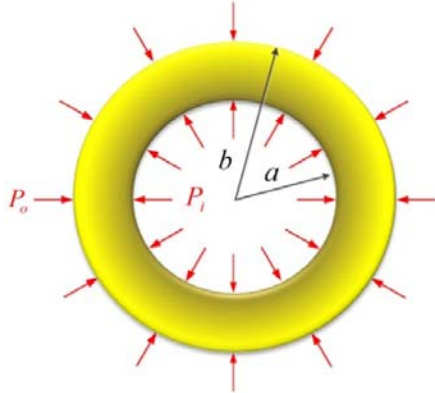


Figure 1. Configuration of the cylinder.

The equilibrium equation of the cylindrical pressure vessel, in the absence of body forces, is expressed as

$$\frac{d\sigma_{rr}}{dr} + \frac{\sigma_{rr} - \sigma_{\theta\theta}}{r} = 0 \quad (12)$$

Using Eqs. 5-12, the essential differential equation for the displacement u_r can be obtained as

$$\begin{aligned} & \frac{d^2 u_r}{dr^2} + \frac{du_r}{dr} \left[\frac{1}{r} + \frac{d(\ln E)}{dr} \right] \\ & + \frac{u_r}{r} \left[\frac{\nu}{1-\nu} \frac{d(\ln E)}{dr} - \frac{1}{r} \right] \\ & = \frac{1+\nu}{1-\nu} \left[T \frac{d\alpha}{dr} + \alpha \frac{dT}{dr} + \alpha T \frac{d(\ln E)}{dr} \right] \end{aligned} \quad (13)$$

For a homogenous and isotropic material, Young's modulus, Poisson's ratio ν , and the thermal expansion coefficient α , are constant, therefore, Eq. 13 on simplifying yields

$$\frac{d^2 u_r}{dr^2} + \frac{1}{r} \frac{du_r}{dr} - \frac{u_r}{r^2} = \frac{(1+\nu)\alpha}{(1-\nu)r} \frac{dT}{dr} \quad (14)$$

The general solution of the displacement u_r is

$$u_r = C_1 r + \frac{C_2}{r} + \frac{\alpha}{r(1-\nu)} \int_a^r T r dr \quad (15)$$

The corresponding stresses are

$$\begin{aligned} \sigma_{rr} = & \frac{E}{(1+\nu)(1-2\nu)} \left[C_1 - (1-2\nu) \frac{C_2}{r^2} \right. \\ & \left. + \frac{\alpha \nu(1+\nu)}{r^2(1-\nu)} \int_a^r T r dr \right] \end{aligned} \quad (16)$$

$$\sigma_{\theta\theta} = \frac{E}{(1+\nu)(1-2\nu)} \left[C_1 + (1-2\nu) \frac{C_2}{r^2} \right. \quad (17)$$

$$\left. - \frac{(1+\nu)(1-2\nu)}{1-\nu} \alpha T + \frac{\alpha(1+\nu)}{r^2(1-\nu)} \int_a^r T r dr \right]$$

$$\sigma_{zz} = \nu(\sigma_{\theta\theta} + \sigma_{rr}) - E\alpha T \quad (18)$$

To determine the unknown constants C_1 and C_2 in each material, boundary conditions have to be used, which are

$$\begin{cases} \sigma_{rr} = -P_i & , \quad r = a \\ \sigma_{rr} = -P_o & , \quad r = b \end{cases} \quad (19)$$

The unknown constants C_1 and C_2 are given in Appendix.

3.2 The case of plane stress

For the case of plane stress the stress-strain relations are

$$\sigma_{rr} = \frac{E}{1-\nu^2} [\epsilon_{rr} + \nu \epsilon_{\theta\theta} - (1+\nu) \alpha T] \quad (20)$$

$$\sigma_{\theta\theta} = \frac{E}{1-\nu^2} [\varepsilon_{\theta\theta} + \nu\varepsilon_{rr} - (1+\nu)\alpha T] \quad (21)$$

$$\sigma_{zz} = 0 \quad (22)$$

For The case of plane stress the differential equation for displacement u_r is

$$\frac{d^2 u_r}{dr^2} + \frac{1}{r} \frac{du_r}{dr} - \frac{u_r}{r^2} = \frac{(1+\nu)\alpha}{r} \frac{dT}{dr} \quad (23)$$

The solution of Eq. 23 is

$$u_r = C'_1 r + \frac{C'_2}{r} + \frac{(1+\nu)\alpha}{r} \int_a^r T r dr \quad (24)$$

The corresponding stresses are

$$\sigma_{rr} = \frac{E}{1-\nu} \left[C'_1 - \frac{(1-\nu)}{(1+\nu)} \frac{C'_2}{r^2} \right. \quad (25)$$

$$\left. + \frac{\nu\alpha}{r^2} \int_a^r T r dr \right]$$

$$\sigma_{\theta\theta} = \frac{E}{1-\nu} \left[C'_1 + \frac{(1-\nu)}{(1+\nu)} \frac{C'_2}{r^2} \right. \quad (26)$$

$$\left. - (1-\nu)\alpha T + \frac{\alpha}{r^2} \int_a^r T r dr \right]$$

To determine the constants C'_1 and C'_2 , boundary conditions have to be used which are the same as those for the case of plane strain (see Eq. 19). The unknown constants C'_1 and C'_2 are given in Appendix.

4. Creep behavior analysis of the cylinder

For materials with creep behavior, we use Norton's law to describe the relations between the rates of stress ($\dot{\sigma}_{ij}$) and strain ($\dot{\varepsilon}_{ij}$) in the multi-axial form

$$\dot{\varepsilon}_{ij} = \frac{1+\nu}{E} \dot{\sigma}_{ij} - \frac{\nu}{E} \dot{\sigma}_{kk} \delta_{ij} + \frac{3}{2} D \sigma_e^{(N-1)} S_{ij} \quad (27)$$

$$S_{ij} = \sigma_{ij} - \frac{1}{3} \sigma_{kk} \delta_{ij} \quad (28)$$

$$\sigma_{eff} = \sqrt{\frac{3}{2} S_{ij} S_{ij}} = \frac{1}{\sqrt{2}} \times$$

$$\sqrt{(\sigma_{rr} - \sigma_{\theta\theta})^2 + (\sigma_{rr} - \sigma_{zz})^2 + (\sigma_{zz} - \sigma_{\theta\theta})^2} \quad (29)$$

where D and N are material constants for creep. σ_{eff} is the effective stress, S_{ij} is the deviator stress tensor. The relations between the rates of strain and displacement are

$$\dot{\varepsilon}_{rr} = \frac{du_r}{dr} \quad (30)$$

$$\dot{\varepsilon}_{\theta\theta} = \frac{\dot{u}_r}{r} \quad (31)$$

And the equilibrium equation of the stress rate is

$$\frac{d\dot{\sigma}_{rr}}{dr} + \frac{\dot{\sigma}_{rr} - \dot{\sigma}_{\theta\theta}}{r} = 0 \quad (32)$$

For the case of plane strain ($\dot{\varepsilon}_{zz} = 0$), the relations between the rates of stress and strain are

$$\dot{\sigma}_{rr} = \frac{E(1-\nu)}{(1+\nu)(1-2\nu)} \left\{ \dot{\varepsilon}_{rr} + \frac{\nu}{1-\nu} \dot{\varepsilon}_{\theta\theta} - \frac{3}{2} D \sigma_{eff}^{(N-1)} \left[S'_{rr} + \frac{\nu}{1-\nu} S'_{\theta\theta} \right] \right\} \quad (33)$$

$$\dot{\sigma}_{\theta\theta} = \frac{E(1-\nu)}{(1+\nu)(1-2\nu)} \left\{ \dot{\varepsilon}_{\theta\theta} + \frac{\nu}{1-\nu} \dot{\varepsilon}_{rr} - \frac{3}{2} D \sigma_{eff}^{(N-1)} \left[S'_{\theta\theta} + \frac{\nu}{1-\nu} S'_{rr} \right] \right\} \quad (34)$$

where

$$S'_{rr} = S_{rr} + \nu S_{zz} \quad (35)$$

$$S'_{\theta\theta} = S_{\theta\theta} + \nu S_{zz}$$

For the case of plane stress ($\dot{\sigma}_{zz} = 0$), the relations between the rates of stress and strain are

$$\dot{\sigma}_{rr} = \frac{E}{1-\nu^2} \left\{ \dot{\epsilon}_{rr} + \nu \dot{\epsilon}_{\theta\theta} - \frac{3}{2} D \sigma_{eff}^{(N-1)} S''_{rr} \right\} \quad (36)$$

$$\dot{\sigma}_{\theta\theta} = \frac{E}{1-\nu^2} \left\{ \dot{\epsilon}_{\theta\theta} + \nu \dot{\epsilon}_{rr} - \frac{3}{2} D \sigma_{eff}^{(N-1)} S''_{\theta\theta} \right\} \quad (37)$$

where

$$S''_{rr} = S_{rr} + \nu S_{\theta\theta}$$

$$S''_{\theta\theta} = S_{\theta\theta} + \nu S_{rr} \quad (38)$$

4.1 The case of plane strain

Substituting Eqs. 30 and 31 into Eqs. 33 and 34 and then into Eq. 32 gives the differential equation for \dot{u}_r in cylinder

$$\begin{aligned} & \frac{d^2 \dot{u}_r}{dr^2} + \frac{d \dot{u}_r}{dr} \left[\frac{1}{r} + \frac{d(\ln E)}{dr} \right] \\ & + \frac{\dot{u}_r}{r} \left[\nu' \frac{d(\ln E)}{dr} - \frac{1}{r} \right] \\ & = \frac{3}{2} \frac{d(\ln E)}{dr} D \sigma_{eff}^{(N-1)} (S'_{rr} + \nu' S'_{\theta\theta}) \\ & + \frac{3}{2} \frac{d}{dr} \left[D \sigma_{eff}^{(N-1)} (S'_{rr} + \nu' S'_{\theta\theta}) \right] \\ & + \frac{3}{2} D \sigma_{eff}^{(N-1)} (1-\nu') \left(\frac{S'_{rr} - S'_{\theta\theta}}{r} \right) \end{aligned} \quad (39)$$

where

$$\nu' = \frac{\nu}{1-\nu} \quad (40)$$

For a homogeneous and isotropic material, Young's modulus (E) is constant, also the case of

ν , D and N being constant is studied in this article, therefore, Eq. 39 on simplifying yields

$$\begin{aligned} & \frac{d^2 \dot{u}_r}{dr^2} + \frac{d \dot{u}_r}{r dr} - \frac{\dot{u}_r}{r^2} \\ & = \frac{3}{2} \frac{d}{dr} \left[D \sigma_{eff}^{(N-1)} (S'_{rr} + \nu' S'_{\theta\theta}) \right] \\ & + \frac{3}{2} D \sigma_{eff}^{(N-1)} (1-\nu') \left(\frac{S'_{rr} - S'_{\theta\theta}}{r} \right) \end{aligned} \quad (41)$$

In general, the quantities σ_{eff} , S'_{rr} and $S'_{\theta\theta}$ are very complicated functions of the coordinate r , even in an implicit function form. Therefore, it is almost impossible to find an exact analytical solution of Eq. 41. We can find an asymptotical solution of Eq. 41. At first, we assume that σ_{eff} , S'_{rr} and $S'_{\theta\theta}$ are constant, i.e. they are independent of the coordinate r . Then, the solution of Eq. 41 is

$$\begin{aligned} \dot{u}_r &= D_1 r + \frac{D_2}{r} + \frac{1}{2} \times \frac{3}{2} D \sigma_{eff}^{(N-1)} \\ & \times \left\{ (S'_{rr} + \nu' S'_{\theta\theta}) \left(r - \frac{a^2}{r} \right) \right. \\ & \left. + \frac{1-2\nu}{1-\nu} (S'_{rr} - S'_{\theta\theta}) \right. \\ & \left. \times \left[r \ln(r) - \frac{r}{2} - \frac{a^2}{r} \ln(a) + \frac{a^2}{2r} \right] \right\} \end{aligned} \quad (42)$$

where the unknown constants D_1 and D_2 can be determined from the boundary conditions. The corresponding stress rates are

$$\begin{aligned} \dot{\sigma}_{rr} &= \frac{1}{2} \times \frac{3}{2} D \sigma_{eff}^{(N-1)} \frac{E}{1-\nu^2} \\ & \times \left\{ S'_{rr} \left[\ln(r) + \frac{1}{2} \frac{a^2}{r^2} + (1-2\nu) \right] \right. \end{aligned}$$

$$\times \frac{a^2}{r^2} \ln(a) - \frac{1}{2} \Big] + S'_{\theta\theta} \Big[-\ln(r) + \frac{1}{2} \frac{a^2}{r^2} \Big] \quad \begin{cases} \dot{\sigma}_{rr} = 0 & , \quad r = a \\ \dot{\sigma}_{rr} = 0 & , \quad r = b \end{cases} \quad (46)$$

$$- (1 - 2\nu) \frac{a^2}{r^2} \ln(a) - \frac{1}{2} \Big] \Big\} \quad \text{Using these boundary conditions the constants } D_1 \text{ and } D_2 \text{ are obtained}$$

$$+ \frac{E}{(1 + \nu)(1 - 2\nu)} \Big[D_1 - \frac{D_2}{r^2} (1 - 2\nu) \Big] \quad (43) \quad D_1 = -\frac{1}{2} \times \frac{3}{2} D\sigma_{eff}^{(N-1)} (S'_{rr} - S'_{\theta\theta})$$

$$\dot{\sigma}_{\theta\theta} = \frac{1}{2} \times \frac{3}{2} D\sigma_{eff}^{(N-1)} \frac{E}{1 - \nu^2} \times \frac{1 - 2\nu}{1 - \nu} \Big\{ 2(1 - \nu) \ln(a) \Big[1 - \frac{b^2}{b^2 - a^2} \Big]$$

$$\times \Big\{ S'_{rr} \Big[\ln(r) - \frac{1}{2} \frac{a^2}{r^2} - (1 - 2\nu) \Big] + \frac{b^2}{(b^2 - a^2)} \Big[(1 - 2\nu) \frac{a^2}{b^2} \ln(a) + \ln(b) \Big] \Big\} \quad (47)$$

$$\times \frac{a^2}{r^2} \ln(a) + \frac{1}{2} \Big] + S'_{\theta\theta} \Big[-\ln(r) - \frac{1}{2} \frac{a^2}{r^2} \Big] \quad D_2 = \frac{1}{2} \times \frac{3}{2} D\sigma_{eff}^{(N-1)} \frac{(ab)^2}{(1 - \nu)(b^2 - a^2)}$$

$$+ (1 - 2\nu) \frac{a^2}{r^2} \ln(a) - \frac{3}{2} \Big] \Big\} \quad - (1 - 2\nu) \Big\{ (S'_{rr} - S'_{\theta\theta}) \Big[2(1 - \nu) \ln(a) \times \frac{a^2}{b^2} \ln(a) + \ln(b) \Big]$$

$$+ \frac{E}{(1 + \nu)(1 - 2\nu)} \Big[D_1 + \frac{D_2}{r^2} (1 - 2\nu) \Big] \quad (44) \quad - \frac{1}{2} (S'_{rr} + S'_{\theta\theta}) \Big(\frac{a^2}{b^2} - 1 \Big) \Big\} \quad (48)$$

$$\dot{\sigma}_{zz} = \nu \Big\{ \frac{3}{2} D\sigma_{eff}^{(N-1)} \frac{E}{1 - \nu^2} \Big[(S'_{rr} - S'_{\theta\theta}) \times \ln(r) - S'_{\theta\theta} \Big] + \frac{2E}{(1 + \nu)(1 - 2\nu)} D_1 \Big\}$$

$$- \frac{3}{2} D\sigma_{eff}^{(N-1)} ES_{zz} \quad (45)$$

To determine the unknown constants D_1 and D_2 in each material, boundary conditions have to be used. Since inside and outside pressures do not change with time, the boundary conditions for stress rates at the inner and outer surfaces may be written as

When the stress rate is known, the calculation of stresses at any time t_i should be performed iteratively

$$\sigma_{ij}^{(i)}(r, t_i) = \sigma_{ij}^{(i-1)}(r, t_{i-1}) + \dot{\sigma}_{ij}^{(i)}(r, t_i) dt^{(i)} \quad (49)$$

where

$$t_i = \sum_{k=0}^i dt^{(k)} \quad (50)$$

To obtain a generally useful solution, a higher order approximation of σ_{eff} , S'_{rr} and $S'_{\theta\theta}$ should be made

$$\begin{aligned}\sigma_{eff}(r) = & \sigma_{eff}(\bar{r}) + \frac{d[\sigma_{eff}(r)]}{dr}\bigg|_{r=\bar{r}}(r-\bar{r}) \\ & + \frac{d^2[\sigma_{eff}(r)]}{dr^2}\bigg|_{r=\bar{r}}(r-\bar{r})^2 \\ & + \frac{d^3[\sigma_{eff}(r)]}{dr^3}\bigg|_{r=\bar{r}}(r-\bar{r})^3 + \dots\end{aligned}\quad (51)$$

$$\begin{aligned}S'_{rr}(r) = & S'_{rr}(\bar{r}) + \frac{d[S'_{rr}(r)]}{dr}\bigg|_{r=\bar{r}}(r-\bar{r}) \\ & + \frac{d^2[S'_{rr}(r)]}{dr^2}\bigg|_{r=\bar{r}}(r-\bar{r})^2 \\ & + \frac{d^3[S'_{rr}(r)]}{dr^3}\bigg|_{r=\bar{r}}(r-\bar{r})^3 + \dots\end{aligned}\quad (52)$$

$$\begin{aligned}S'_{\theta\theta}(r) = & S'_{\theta\theta}(\bar{r}) + \frac{d[S'_{\theta\theta}(r)]}{dr}\bigg|_{r=\bar{r}}(r-\bar{r}) \\ & + \frac{d^2[S'_{\theta\theta}(r)]}{dr^2}\bigg|_{r=\bar{r}}(r-\bar{r})^2 \\ & + \frac{d^3[S'_{\theta\theta}(r)]}{dr^3}\bigg|_{r=\bar{r}}(r-\bar{r})^3 + \dots\end{aligned}\quad (53)$$

where \bar{r} is the center point of the wall thickness in the following analysis.

4.2. The case of plane stress

The differential equation for \dot{u}_r is

$$\frac{d^2\dot{u}_r}{dr^2} + \frac{d\dot{u}_r}{rdr} - \frac{\dot{u}_r}{r^2} = \frac{3}{2} \frac{D}{r} \sigma_{eff}^{(N-1)} (S'_{rr} - S''_{\theta\theta}) \quad (54)$$

The solution of Eq.54 is

$$\begin{aligned}\dot{u}(r) = & D'_1 r + \frac{D'_2}{r} + \frac{1}{2} \times \frac{3}{2} D \sigma_{eff}^{(N-1)} \\ & \times (S''_{rr} + S''_{\theta\theta}) \left[r \ln(r) - a \ln(a) - \frac{1}{2}(r-a) \right]\end{aligned}\quad (55)$$

where the unknown constants D'_1 and D'_2 can be determined from the boundary conditions. The corresponding stress rates are

$$\begin{aligned}\dot{\sigma}_{rr} = & \frac{E}{1-\nu^2} \left\{ D'_1(1+\nu) - \frac{D'_2}{r^2}(1-\nu) \right. \\ & + \frac{3}{4} D \sigma_{eff}^{(N-1)} (S''_{rr} + S''_{\theta\theta}) [(1+\nu) \ln(r) \\ & - \frac{1}{2}(1-\nu) - \nu \frac{a}{r} \ln(a) + \frac{\nu a}{2r}] \\ & \left. - \frac{3}{2} D \sigma_{eff}^{(N-1)} S''_{rr} \right\}\end{aligned}\quad (56)$$

$$\begin{aligned}\dot{\sigma}_{\theta\theta} = & \frac{E}{1-\nu^2} \left\{ D'_1(1+\nu) + \frac{D'_2}{r^2}(1-\nu) + \frac{3}{4} D \right. \\ & \times \sigma_{eff}^{(N-1)} (S''_{rr} + S''_{\theta\theta}) \left[(1+\nu) \ln(r) - \frac{1}{2}(1-\nu) \right. \\ & \left. \left. - \frac{a}{r} \ln(a) + \frac{a}{2r} \right] - \frac{3}{2} D \sigma_{eff}^{(N-1)} S''_{\theta\theta} \right\}\end{aligned}\quad (57)$$

$$\begin{aligned}D'_1 = & \frac{-b^2}{(a^2 - b^2)(1+\nu)} \times \frac{3}{4} D \sigma_{eff}^{(N-1)} (S''_{rr} + S''_{\theta\theta}) \\ & \times \left[(1+\nu) \ln\left(\frac{a}{b}\right) + \nu \left(\frac{b-a}{a}\right) \left(\frac{1}{2} - \ln(a)\right) \right] \\ & - \frac{1}{(1+\nu)} \times \frac{3}{4} D \sigma_{eff}^{(N-1)} (S''_{rr} + S''_{\theta\theta}) \left[\ln(a) + \frac{1}{2} \right]\end{aligned}$$

$$+ \frac{1}{(1+\nu)} \frac{3}{2} D \sigma_{eff}^{(N-1)} S''_{rr} \quad (58)$$

$$D'_2 = \frac{-(ab)^2}{(a^2 - b^2)(1-\nu)} \times \frac{3}{4} D \sigma_{eff}^{(N-1)} (S''_{rr} + S''_{\theta\theta})$$

$$\times \left[(1+\nu) \ln\left(\frac{a}{b}\right) + \nu \left(\frac{b-a}{a} \right) \left(\frac{1}{2} - \ln(a) \right) \right] \quad (59)$$

5. Numerical results and discussion

In the previous sections, the analytical solution of creep stresses for homogeneous thick-walled cylindrical vessels subjected to uniform pressures on the inner and outer surfaces were obtained. In this section, some profiles are plotted for the radial displacement, radial stress, circumferential stress and axial stress as a function of radial direction and time.

A cylinder with creep behavior under internal and external pressure is considered. Radii of the cylinder are $a=20$ mm, $b=40$ mm. The other data are

$$E=207 \text{ GPa}, \quad \nu=0.292, \quad \alpha=10.8 \times 10^{-6} \text{ K}^{-1},$$

$$N=2.25, \quad \lambda=43 \text{ W/m}^\circ\text{C}, \quad P_i=80 \text{ MPa},$$

$$P_o=0 \text{ MPa}, \quad D=1.4 \times 10^{-8}, \quad q_a=3000 \text{ W/m}^2,$$

$$h_\infty=6.5 \text{ W/m}^2 \cdot ^\circ\text{C}, \quad T_\infty=25 \text{ }^\circ\text{C}$$

The thermal loading is as follows: inner surface is exposed to a uniform flux, q_a , and the outer surface is exposed to an airstream at T_∞ .

5.1 The case of plane strain

The stress distribution after 10h of creeping are plotted in Figure. 2, Figure 3 and Figure 4 for the stress components σ_{rr} , $\sigma_{\theta\theta}$ and σ_{zz} respectively. It must be noted from Figure. 2, Figure 3 and Figure 4 that, all three stresses are compressive and the values of all three stresses decreases as radius increases. The absolute maximums of radial, circumferential and

axial stresses occur at the inner edge. It means the maximum shear stress which is $\tau_{max} = \sigma_{\theta\theta} - \sigma_{rr}/2$ will be very high on the inner surface of the vessel.

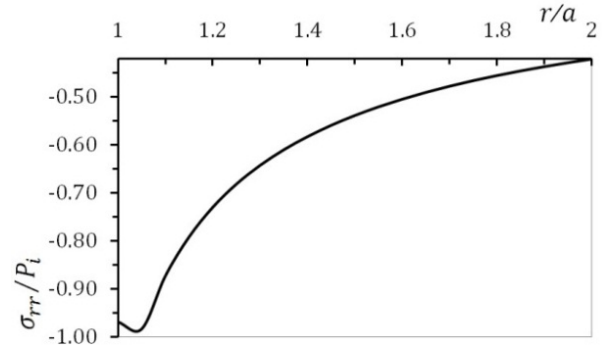


Figure 2. The radial stress calculated from the asymptotic solution after 10 h of creeping.

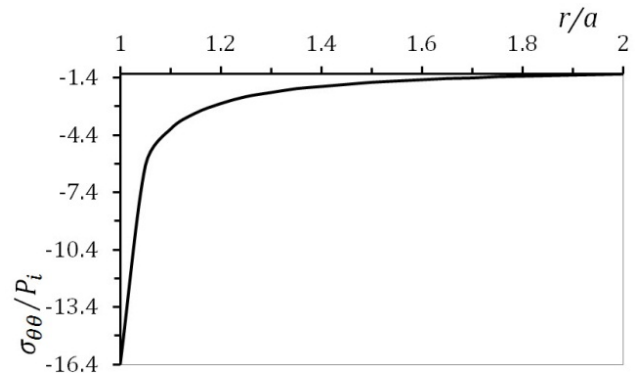


Figure 3. The circumferential stress calculated from the asymptotic solution after 10 h of creeping.

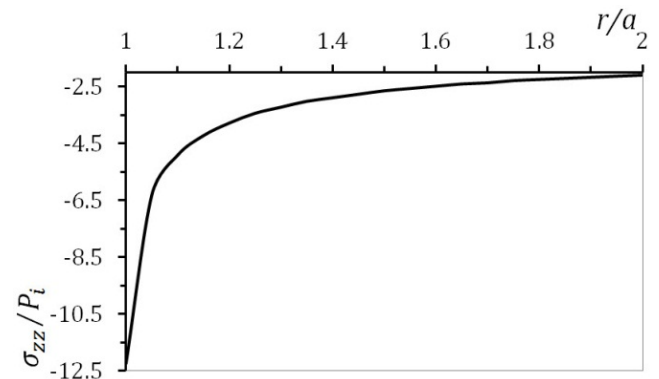


Figure 4. The axial stress calculated from the asymptotic solution after 10 h of creeping.

The time dependent stresses at point are plotted in Figure. 5, Figure 6 and Figure 7. Radial, circumferential and axial stresses decreases as time increases.

According to Figure. 5 to Figure 7, all three stresses are compressive. The radial displacement along the radius for the condition of plane strain is plotted in Figure 8. It must be noted from Figure. 8 that the maximum value of radial displacement is at the inner surface.

5.2 The case of plane stress

The stress distribution after 10h of creeping are plotted in Figure. 9 and Figure 10 for the stress components σ_{rr} and $\sigma_{\theta\theta}$ respectively. It must be noted from Figure. 9, that for $r/a < 1.08$, the value

of radial stress increases as radius increases while for $r/a > 1.08$, The value of radial stress decreases as radius increases. According to Figure 10, the value of circumferential stress decreases as radius increases. It can be seen that, radial and circumferential stresses are compressive.

The time dependent stresses at point $r = 30$ mm, are plotted in Figure. 11 and Figure 12. The radial and circumferential stresses decreases as time increases.

According to Figure. 11 and 12, radial and circumferential stresses are compressive. The radial displacement along the radius for the condition of plane stress is plotted in Figure 13. There is an decrease in the value of the radial displacement as radius increases.

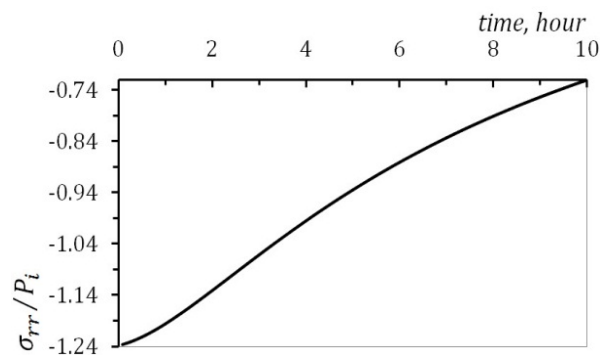


Figure 5. Time-dependent radial stress at the point $r = 30$ mm.

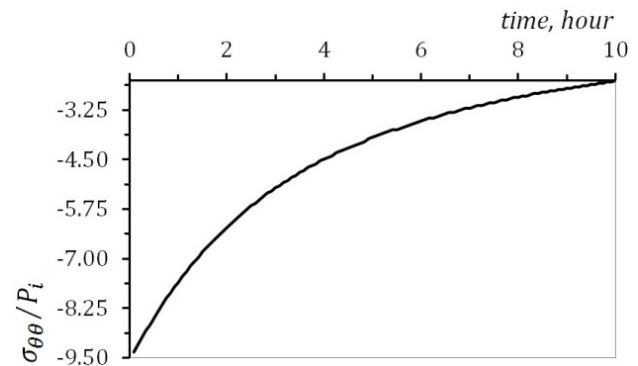


Figure 6. Time-dependent circumferential stress at the point $r = 30$ mm.

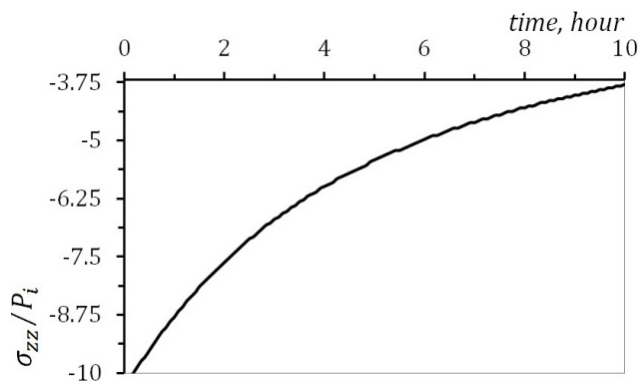


Figure 7. Time-dependent axial stress at the point $r = 30$ mm.

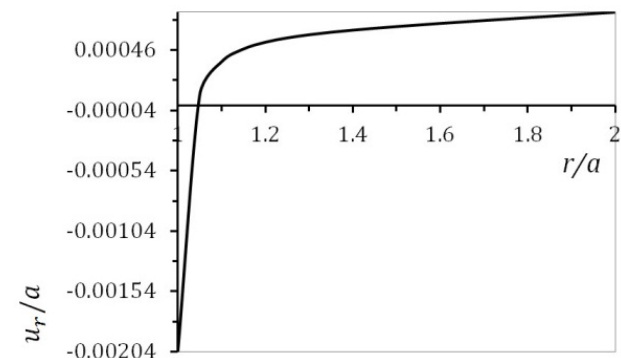


Figure 8. The radial displacement calculated from the asymptotic solution after 10 h of creeping.

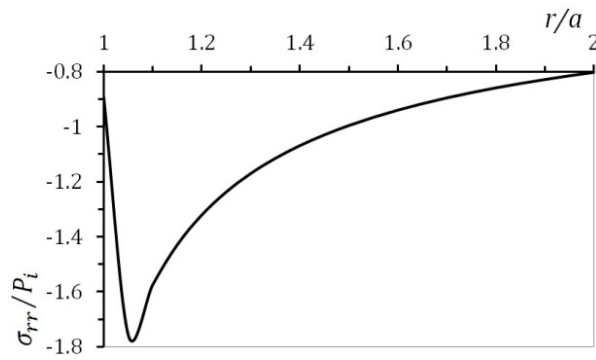


Figure 9. The radial stress calculated from the asymptotic solution after 10 h of creeping.

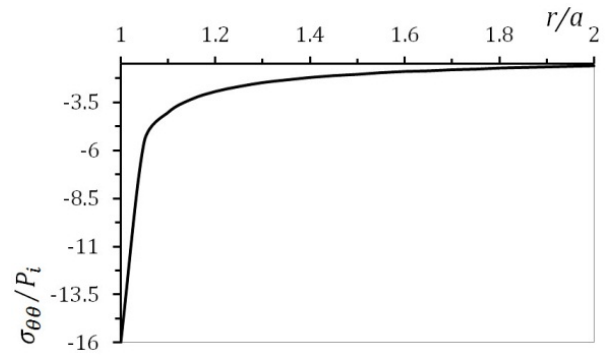


Figure 10. The circumferential stress calculated from the asymptotic solution after 10 h of creeping.

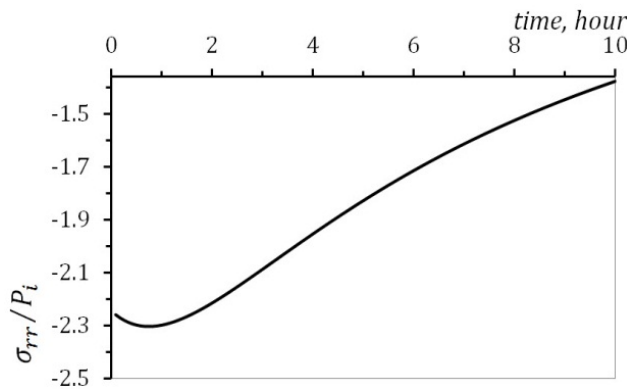


Figure 11. Time-dependent radial stress at the point $r = 30$ mm.

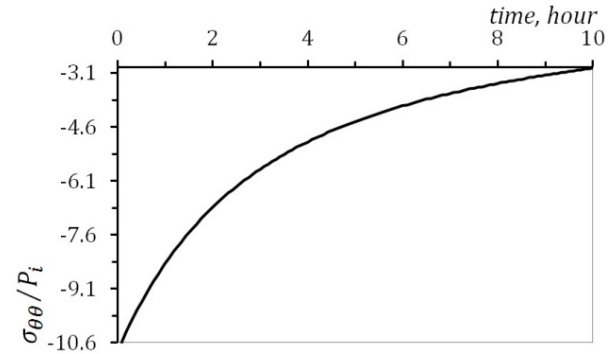


Figure 12. Time-dependent circumferential stress at the point mm.

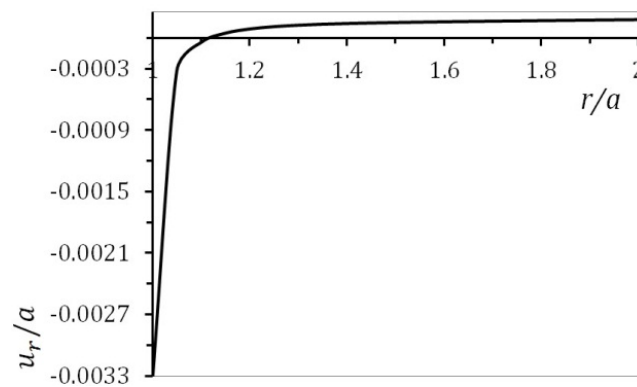


Figure 13. The radial displacement calculated from the asymptotic solution after 10 h of creeping.

6. Conclusions

In the present study, an analytical solution procedure has been developed for the time-dependent creep analysis of an internally and externally pressurized, thick-walled cylindrical pressure vessel subjected to internal heat flux. For the stress analysis in a cylinder, having material creep behavior, the solutions of the stresses at a time equal to zero (i.e. the initial stress state) are needed, which correspond to the solution of materials with linear elastic behavior. The analytical solution is obtained for the conditions of plane strain and plane stress. Norton's power law of creep is employed to derive general expressions for stresses and strain rates in the thick cylinder. The pressure, inner radius and outer radius are considered constant. Material properties are considered as constant. The heat conduction equation for the one-dimensional problem in polar coordinates is used to obtain temperature distribution in the cylinder.

According to stress distribution after 10h of creeping for the case of plane stress, both radial and circumferential stresses remains compressive over the entire cylinder radius. It must be noted that for the case of plane stress, the maximum value of circumferential stress at the point mm, is at a time equal to zero (i.e. the initial stress state) and it decreases as time increases. According to stress distribution after 10h of creeping for the case of plane strain, the maximum value of all three stresses are at a time equal to zero, in other word all three stresses decreases as time increases.

References

- [1] T. Singh and V. K. Gupta, "Effect of anisotropy on steady state creep in functionally graded cylinder", *Composite Structures*, vol. 93, no. 2, pp. 747-758, 2011.
- [2] N. S. Bhatnagar et al. "Creep analysis of orthotropic rotating cylinder", *Journal of Pressure Vessel Technology*, Transactions of the ASME, vol.102, no. 1, pp. 371-377, 1980.
- [3] A. Behdashti et al., "Field experiments and technical evaluation of an optimized media evaporative cooler for gas turbine power augmentation", *Journal of Applied Research and Technology*, vol. 10, no. 3, pp. 458-471, 2012.
- [4] T. K. Ibrahim, M. M. Rahman, "Thermal impact of operating conditions on the performance of a combined cycle gas turbine", *Journal of Applied Research and Technology*, vol. 10, no. 4, pp. 567-578, 2012.
- [5] C. D. Weir, "The creep of thick walled tube under internal pressure", *Journal of Applied Mechanics*, pp. 424-464, 1957.
- [6] N. S. Bhatnagar and S. K. Gupta, "Analysis of thick-walled orthotropic cylinder in the theory of creep", *Journal of the Physical Society of Japan*, vol. 6, no. 27, pp. 1655-1662, 1969.
- [7] Y. Y. Yang, "Time-dependent stress analysis in functionally graded materials", *International Journal of Solids and Structures*, vol. 37, no. 51, pp. 7593-7608, 2000.
- [8] A. Loghman and M. A. Wahab, "Creep damage simulation of thick-walled tubes using the theta projection concept", *International Journal of Pressure Vessels and Piping*, vol. 67, no. 1, pp. 105-111, 1996.
- [9] S. K. Gupta and S. Pathak, "Thermo creep transition in a thick walled circular cylinder under internal pressure", *Indian Journal of Pure and Applied Mathematics*, vol. 2, no. 32, pp. 237-253, 2001.
- [10] M. Z. Nejad et al., "A new analytical solution for creep stresses in thick-walled spherical pressure vessels", *Journal of Basic and Applied Scientific Research*, vol. 1, no. 11, pp. 2162-2166, 2011.
- [11] Z. Hoseini et al., "New exact solution for creep behavior of rotating thick-walled cylinders", *Journal of Basic and Applied Scientific Research*, vol. 1, no. 10, pp. 1704-1708, 2011.
- [12] T. Wah, "Creep collapse of cylindrical shells", *J. F. I.*, pp. 45-60, 1961.
- [13] D. H. Pai, "Steady-state creep analysis of thick-walled orthotropic cylinders", *International Journal of Mechanical Science*, vol. 9, no. 6, pp. 335-348, 1967.
- [14] R. Sankaranarayanan, "Steady creep of circular cylindrical shells under combined lateral and axial pressures", *International Journal of Solids Structures*, vol. 5, no. 1, pp. 17-32, 1969.
- [15] S. Murakami and sh. Iwatsuki, "Transient creep of circular cylindrical shells", *International Journal of Mechanical Science*, vol. 11, no. 11, pp. 897-912, 1969.
- [16] S. Murakami and K. Iwatsuki, "on the creep analysis of pressurized circular cylindrical shells", *International Journal of Non-Linear Mechanics*, vol. 6, no. 3, pp. 377-392, 1971.

- [17] R. G. Sim and R. K. Penny, "Plane strain creep behaviour of thick-walled cylinders", *International Journal of Mechanical Sciences*, vol. 12, no. 12, pp. 987-1009, 1971.
- [18] S. Murakami and K. Iwatsuki, "Steady-state creep of circular cylindrical shells", *Bulletin of the JSME*, vol. 14, no. 73, pp. 615-623, 1971.
- [19] N. S. Bhatnagar and V. K. Arya, "Large strain creep analysis of thick-walled cylinders", *International Journal of Non-Linear Mechanics*, vol. 9, no. 2, pp. 127-140, 1974.
- [20] S. Murakami and E. Tanaka, "on the creep buckling of circular cylindrical shells", *International Journal of Mechanical Science*, vol. 18, no. 4, pp. 185-194, 1976.
- [21] H. Jahed and J. Bidabadi, "An axisymmetric method of creep analysis for primary and secondary creep", *International Journal of Pressure Vessels and Piping*, vol. 80, pp. 597-606, 2003.
- [22] J. J. Chen et al., "Creep analysis for a functionally graded cylinder subjected to internal and external pressure", *Journal of Strain Analysis*, vol. 42, no. 2, pp. 69-77, 2007.
- [23] L. H. You et al., "Creep deformations and stresses in thick-walled cylindrical vessels of functionally graded materials subjected to internal pressure", *Composite Structures*, vol. 78, no. 2, pp. 285-291, 2007.
- [24] H. Altenbach et al., "Steady-state creep of a pressurized thick cylinder in both the linear and the power law ranges", *Acta Mechanica*, vol. 195, no. 1, pp. 263-274, 2008.
- [25] T. Singh and V. K. Gupta, "Creep analysis of an internally pressurized thick cylinder made of a functionally graded composite", *Journal of Strain Analysis*, vol. 44, no. 7, pp. 583-594, 2009.
- [26] T. Singh and V. K. Gupta, "Effect of material parameters on steady state creep in a thick composite cylinder subjected to internal pressure", *The Journal of Engineering Research*, vol. 6, no. 2, pp. 20-32, 2009.
- [27] T. Singh and V. K. Gupta, "Modeling steady state creep in functionally graded thick cylinder subjected to internal pressure", *Journal of Composite Materials*, vol. 44, no. 11, pp. 1317-1333, 2010.
- [28] T. Singh and V. K. Gupta, "Modeling of creep in a thick composite cylinder subjected to internal and external pressures", *International Journal of Materials Research*, vol. 101, no. 2, pp. 279-286, 2010.
- [29] A. Loghman et al., "Magnetothermoelastic creep analysis of functionally graded cylinders", *International Journal of Pressure Vessels and Piping*, vol. 87, no. 7, pp. 389-395, 2010.
- [30] S. Sharma et al., "Creep transition in non homogeneous thick-walled circular cylinder under internal and external pressure", *Applied Mathematical Sciences*, vol. 6, no. 122, pp. 6075-6080, 2012.
- [31] S. Jamian et al., "Creep analysis of functionally graded material thick-walled cylinder", *Applied Mechanics and Materials*, vol. 315, pp. 867-871, 2013.
- [32] T. Singh and V. K. Gupta, "Analysis of steady state creep in whisker reinforced functionally graded thick cylinder subjected to internal pressure by considering residual stress", *Mechanics of Advanced Materials and Structures*, vol. 21, no. 5, pp. 384-392, 2014.

Appendix

The unknown constants in Eqs. 16 and 17 are

$$C_1 = \frac{-P_i(1+\nu)(1-2\nu)}{E} + \frac{(1+\nu)(1-2\nu)(P_i - P_o)b^2}{E(b^2 - a^2)} - \frac{\alpha}{b^2 - a^2} \frac{\nu(1+\nu)}{1-\nu} \int_a^b T r dr$$

$$C_2 = \frac{(P_i - P_o)(1+\nu)(ab)^2}{E(b^2 - a^2)} - \frac{\alpha a^2}{b^2 - a^2} \frac{\nu(1+\nu)}{(1-\nu)(1-2\nu)} \int_a^b T r dr$$

The unknown constants in Eqs. 25 and 26 are

$$C'_1 = \frac{-P_i(1-\nu)}{E} + \frac{(1-\nu)(P_i - P_o)b^2}{E(b^2 - a^2)} - \frac{\nu\alpha}{b^2 - a^2} \int_a^b T r dr$$

$$C'_2 = \frac{(P_i - P_o)(1+\nu)(ab)^2}{E(b^2 - a^2)} - \frac{\alpha a^2}{b^2 - a^2} \frac{\nu(1+\nu)}{1-\nu} \int_a^b T r dr$$