



Maderas. Ciencia y Tecnología

ISSN: 0717-3644

anantias@ubiobio.cl

Universidad del Bío Bío

Chile

Tufan, Mürit; Akba, Selçuk; Aslan, Mustafa  
DECAY RESISTANCE, THERMAL DEGRADATION, TENSILE AND FLEXURAL  
PROPERTIES OF SISAL CARBON HYBRID COMPOSITES  
Maderas. Ciencia y Tecnología, vol. 18, núm. 4, 2016, pp. 599-606  
Universidad del Bío Bío  
Concepción, Chile

Available in: <http://www.redalyc.org/articulo.oa?id=48547628007>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

redalyc.org

Scientific Information System

Network of Scientific Journals from Latin America, the Caribbean, Spain and Portugal

Non-profit academic project, developed under the open access initiative

# DECAY RESISTANCE, THERMAL DEGRADATION, TENSILE AND FLEXURAL PROPERTIES OF SISAL CARBON HYBRID COMPOSITES

Mürşit Tufan<sup>1,\*</sup>, Selçuk Akbaş<sup>1</sup>, Mustafa Aslan<sup>2</sup>

## ABSTRACT

Sisal-carbon hybrid composites were produced from mixtures having different weight ratios of sisal, carbon fibers and recycled polypropylene. All formulations were tested and evaluated for tensile and flexural properties. In addition, the thermal stability of the sisal-carbon hybrid composites were examined via thermogravimetric analysis and decay tests were conducted to determine the degradation of the hybrid composites. Results showed that the biological durability and mechanical and thermal properties improved with the increasing weight ratios of carbon fiber in the hybrid composites. According to the mechanical tests, the optimum hybrid composite formulation was found to be 12% sisal fiber + 28% carbon fiber + 60% rPP.

**Keywords:** *Coniophora puteana*, mechanical properties, modulus of elasticity, modulus of rupture, *Pinus sylvestris*, thermogravimetric analysis, *Trametes versicolor*.

## INTRODUCTION

Wood polymer composites (WPCs) are used extensively due to their outstanding properties such as enhanced strength, stiffness and creep resistance as well as their high dimensional stability. As a result, their market shares have grown dramatically (18% in North America and 14% in Europe) over the last several years. The WPCs may consist of organic fiber (wood and annual plant fiber or flours) and polymeric materials such as polyethylene, polypropylene or polyvinyl chloride (Jarukumjorn and Suppakarn 2009, Nourbakhsh and Ashori 2010, Moreno *et al.* 2013). When used in WPCs, organic fillers provide lower density, less abrasiveness and less energy consumption as well as being inexpensive, non-hazardous and renewable. Hence, they can be used as an excellent reinforcement for thermoplastics (Khanam *et al.* 2010). However, these fillers can be biodegradable over time, and their incompatibility with the hydrophobic thermoplastic matrix and poor resistance to moisture cause dimensional changes, thus restricting their potential use in WPCs (Matuana *et al.* 1998, Kim *et al.* 2008). The addition of small amounts of synthetic fibers (carbon, glass, etc.) can improve the technological properties of WPCs for industrial applications. These fibers provide material with high specific strength, resistance, rigidity, biological durability and high thermal stability. However, these fillers are costly and abrasive to the processing equipment (Caulfield *et al.* 2005, La Manita *et al.* 2005, Sharma *et al.* 2014). Hybrid composites are fabricated with a combination of organic and synthetic fibers to produce materials with the advantages of the desired high technological features. The incorporation of natural fibers such as sisal/jute with synthetic fibers such as glass/carbon in composites has gained increasing attention in many studies (Ramesh *et al.* 2013, Bajracharya *et al.* 2014). In this study, sisal-carbon hybrid composites were produced with different sisal-carbon rates and their mechanical and thermal properties and biological durability were investigated and compared in detail.

<sup>1</sup>Department of Forest Products Engineering, Faculty of Forestry, Artvin Coruh University, Artvin, Turkey.

<sup>2</sup>Department of Metallurgical and Materials Engineering, Faculty of Engineering, Karadeniz Technical University, Trabzon, Turkey.

\*Corresponding author: mtufan35@hotmail.com

Received: 08.10.2015 Accepted: 16.07.2016

## MATERIALS AND METHODS

### Materials

Recycled polypropylene (rPP), sisal fiber (SF) and carbon fiber (CF) were used as the thermoplastic matrix, organic and synthetic fillers, respectively. The recycled polypropylene (rPP) was obtained from Ayan Plastik Industry and Trade Co. Ltd., Samsun, Turkey. The fibers, in the form of short, recycled fibers left over from final manufacturing processes, were provided by two Turkish companies: the Esenteks Co., Ltd., for the sisal fibers and Dowaksa, Inc., for the carbon fibers (CF). The density of the SF and CF were 1,43 and 1,5 g/cm<sup>3</sup>, respectively. The experimental design of the study is presented in Table 1.

**Table 1.** Composition of the polymer hybrid composites.

Group ID	Sisal (%)	Carbon (%)	rPP (%)
A	40	0	60
B	33	7	60
C	26	14	60
D	19	21	60
E	12	28	60
F	5	35	60

### Methods

#### Preparation of compression-molded polymer composites

Using a Willey mill, the air-dried sisal fibers were ground into small particles which were then screened to 60- and 80-mesh size and dried to oven-dry moisture level. The SF flour, CF and rPP granulates were processed in a co-rotating single-screw extruder (RONDOL 3212). The four barrel temperature zones of the extruder were controlled at 165-170-175-180 °C, respectively. The extruded strand samples were collected, cooled and granulated into pellets. Finally, the pellets were compression molded in a hot press for 3 min at 175 °C.

#### Mechanical properties

The property evaluations of the manufactured hybrid composites were conducted in a climate-controlled testing laboratory at 23 °C and 65% RH. Flexural and tensile properties were determined using specimens with the dimensions of 150 mm (length) × 13 mm (width) × 5 mm (thickness). The modulus of rupture (MOR) and modulus of elasticity (MOE) were measured in a three-point bending test in accordance with ASTM D 790 (2004). Dog-bone shaped (type III) samples were used for the tensile tests, which were carried out according to ASTM D 638 (2004). The specimens were tested with a crosshead speed of 2 mm/min and all tests were performed on a Zwick 10kN Universal Testing Machine (Zwick Inc., Germany). Seven test samples for each group were tested in order to get average values of tensile and flexural properties.

#### Thermogravimetry and differential scanning calorimetry

The thermal behavior of the rPP and hybrid composites was examined using the PelkinElmer STA 6000 thermal analyzer. The test samples, each weighting 3-5 mg, were heated in an aluminum crucible from room temperature to 600 °C with the heating rate of 10 °C/min and kept at this temperature for 2 min to monitor thermal history. The thermal decomposition temperature of each sample was examined under nitrogen with a 30 mL/min flow rate.

## Decay tests

Hybrid composites and Scots pine (*Pinus sylvestris* L.) solid wood specimens were carried out according to European standard EN 113. Six pieces of samples with size 20 (length) x 20 (width) x 5 (thick) mm were prepared each fungus. The specimens were dried at  $103 \pm 2$  °C for 24 h and weighed to the nearest 0,01 g to determine the initial weight ( $M_1$ ). One white rot fungi, *Trametes versicolor* L.Pilat (Mad-697) and one brown rot fungi, *Coniophora puteana* (Schumach.: Fr.) P. Karst (Mad-15) were used for the decay tests. All test fungi were grown on a malt extract agar medium (concentration 48g/L). The solution was autoclaved at 120 °C for 20 min and poured into petri dishes. After cooling of the medium, a mycelium plug was transferred to the center of each petri dish. The dishes were incubated at  $24 \pm 2$  °C and 75% RH until the fungal mycelium reached the edges of the dishes. Six specimens of each formulation were sterilized in an autoclave for 30 min at 121 °C and placed in the pre-inoculated petri dishes. At the end of the exposure time (16 weeks), the surfaces of the specimens were cleaned. The specimens were then dried at  $103 \pm 2$  °C for 24 hours ( $M_2$ ) for the calculation of the mass loss. The percent mass loss (ML) was calculated as follows,  $ML(\%) = [(M_1 - M_2)/M_1] \times 100$ .

A set of Scots pine (*Pinus sylvestris*) specimens were also tested as control against both fungi used in this experiment.

## RESULTS AND DISCUSSION

### Mechanical properties

The effects of filler type and rate on flexural and tensile properties are shown in Table 2. All the hybrid composites had higher flexural and tensile properties than the SF composites (group ID A). Statistical analysis showed that filler type and rate significantly affected the flexural and tensile properties. Flexural and tensile strength values increased sharply with the rate of CF addition up to 28% (Group ID E). Flexural and tensile strength values also increased in the composites where the CF rate was 35%; however, this increase was not statistically significant. A similar trend was observed with the tensile modulus values.

The flexural modulus values were improved in the hybrid composites with the addition of CF content; however, the increase was not significant with the CF ratio of more than 21% (Group ID D).

It is recognized that the addition of synthetic fibers in hybrid composites causes substantial changes in the mechanical properties (Abu *et al.* 2005, Indicula *et al.* 2005, Haneefa *et al.* 2008, Khanam *et al.* 2010). As shown in Table 2, it is clear that the flexural and tensile properties in the hybrid composites were enhanced with the increase the CF content.

**Table 2.** Mechanical properties of hybrid composites.

Group ID	Flexural Strength (MPa)	Flexural Modulus (GPa)	Tensile Strength (MPa)	Tensile Modulus (GPa)
<b>A</b>	30,33 <i>a</i> (3,46)	2,55 <i>a</i> (0,14)	15,24 <i>a</i> (0,68)	3,05 <i>a</i> (0,08)
<b>B</b>	31,39 <i>ab</i> (1,01)	2,76 <i>a</i> (0,30)	15,60 <i>a</i> (0,79)	3,10 <i>a</i> (0,33)
<b>C</b>	33,92 <i>b</i> (0,47)	3,17 <i>b</i> (0,21)	17,07 <i>a</i> (1,05)	3,31 <i>ab</i> (0,23)
<b>D</b>	36,92 <i>c</i> (2,61)	3,81 <i>c</i> (0,36)	17,25 <i>ab</i> (0,37)	3,66 <i>b</i> (0,34)
<b>E</b>	43,59 <i>d</i> (1,24)	4,03 <i>c</i> (0,46)	20,85 <i>c</i> (0,40)	3,86 <i>c</i> (0,58)
<b>F</b>	45,33 <i>d</i> (2,14)	4,06 <i>c</i> (0,33)	22,40 <i>c</i> (2,49)	4,12 <i>c</i> (0,31)

Note:


-The value in parenthesis is the standard deviation.

-Each value is the average of seven samples tested.

-Groups with same letters in column indicate that there is no statistical difference ( $p < 0,05$ ).

### Thermogravimetric analysis

The thermal behavior of the rPP and hybrid composites was evaluated using thermogravimetric analysis (TGA). The results of the TGA thermographs of the samples are shown in Figure 1, where two main decomposition peak areas can be seen. The first decomposition peak starts at around 200-220 °C. Lignocellulosic fibers are known to have low thermal stability, and the degradation temperatures of hemicelluloses, lignin and cellulose start at 180, 200 and 210 °C, respectively (Jarukumjorn and Suppakarn 2009, Tufan *et al.* 2015). With the increased CF content, the decomposition value of the hybrid composites was enhanced. The second peak area gives the highest decomposition temperatures as 440-460 °C. It is known that PP degrades around this temperature. In addition, after the final decomposition temperature, the residual mass amount in the hybrid composites increased with the increase in the CF rate (Mallick 2008, Paiva *et al.* 2009).

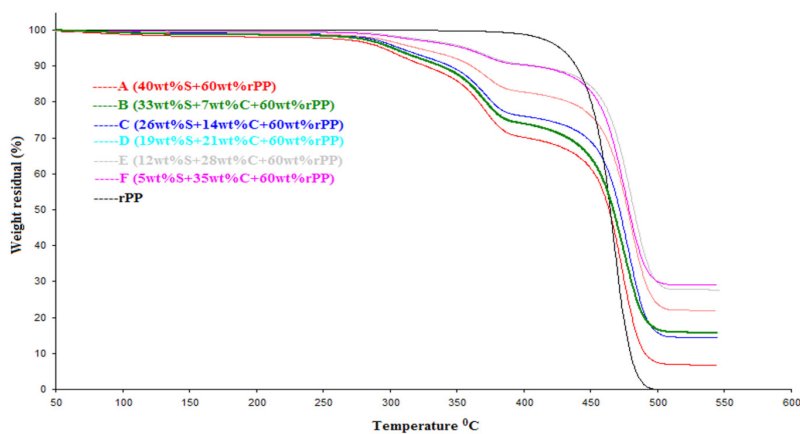

**Figure 1.** TGA results of rPP and hybrid composites.

Decay tests

Table 3 shows the mean mass loss rate of the hybrid composites and Scots pine control after exposure to white-rot (*Trametes versicolor*) and brown-rot (*Coniophora puteana*) fungi for 16 weeks. In general, the mass loss rate was very limited in the hybrid composites, while that of the control samples (Scots pine) was found to be very high. The highest mass loss rate was found in the control samples; at 29,35% for white rot and 40,99% for brown rot. These results demonstrated that the decay activity was acceptable for test conditions. Moreover, this rate did not exceed 6,37% and 4,44% for white and brown rot fungi, respectively, in any of the hybrid composites. The mass loss rate decreased in all hybrid composites with the addition of CF. The smallest mass losses found for white rot and brown rot were 0,14% and 0,78%, respectively (GroupID F). This rate increased to 2,50% and 3,78% (GroupID A) with the increase of the sisal fiber ratio in the composites. Previous literature has indicated that wood or natural fiber polymer composites are not fully protected against fungal attack. Composites with higher wood flour or fiber content in particular exhibit increasing mass loss. Due to less encapsulation, increasing the rate of wood flour or natural fiber in polymer composites causes poor moisture resistance and this leads to greater decay susceptibility (Morris and Cooper 1998, Verhey and Laks 2002, Clemson and Ibach 2004). Similar results were observed in the current study. The SF ratio negatively affected the fungal resistance of the hybrid composites. It is accepted that CF is more durable against moisture and fungi degradation than SF. Studies have reported that water absorption decreases in hybrid composites using CF (Thwe and Liao 2003, Samal et al. 2009). Therefore, in this study, increasing the CF rate resulted in hybrid composites which were more resistant to fungi.

Table 3. Mean mass loss (%) of hybrid composites.

Group ID	Mass loss (%)	
	<i>Trametes versicolor</i>	<i>Coniophora puteana</i>
A	4,44 <i>b</i> (0,43)	6,37 <i>f</i> (0,85)
B	2,50 <i>a</i> (0,34)	3,78 <i>e</i> (0,58)
C	1,68 <i>a</i> (0,40)	2,90 <i>cde</i> (0,47)
D	0,63 <i>a</i> (0,47)	1,68 <i>abc</i> (0,56)
E	0,85 <i>a</i> (0,23)	1,92 <i>bcd</i> (0,54)
F	0,14 <i>a</i> (0,17)	0,78 <i>ab</i> (0,38)
Scots pine	29,35 <i>c</i> (6,98)	40,99 <i>g</i> (4,20)

- Note:
- The value in parenthesis is the standard deviation.
  - Each value is the average of six samples tested.
  - Groups with same letters in column indicate that there is no statistical difference (p < 0,05).

## CONCLUSIONS

Based on the results of this study, the following facts were observed.

The flexural and tensile properties of the hybrid composites were increased with the addition of CF. The optimum ratio of CF in the produced composites was determined as 28%; however, no significant improvement in mechanical properties was seen with CF ratios higher than 28%.

From the results it can be concluded that the hybrid composites exhibited better biological performance than the SF composites.

The addition of CF improved the thermal stability of the hybrid composites. The thermal decomposition values of the hybrid composites were enhanced with increased CF content.

## ACKNOWLEDGEMENTS

This study was supported by BAP (Directory of Scientific Research Projects of Artvin Çoruh University) under grant number 2014.F11.02.03.

## REFERENCES

- Abu, B.H.A.; Abdul, K.H.P.S. 2005.** Lignocellulose-based hybrid bilayer laminate composite. Part 1: studies on tensile and impact behavior of oil palm fiber-glass fiber- reinforced epoxy resin. *J Compos Mater* 39:663-684.
- ASTM D 638. 2004.** Standard Test Method for Tensile Properties of Plastics. American Society for Testing and Materials. West Conshohocken, PA. 08 (01).
- ASTM D 790. 2004.** Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials. American Society for Testing and Materials. West Conshohocken, PA. 08 (01).
- Bajracharya, R.M.; Manalo, A.C.; Karunasena, W.; Lau, K. 2014.** An Overview of Mechanical Properties and Durability Of Glass-Fibre Reinforced Recycled Mixed Plastic Waste Composites. *Materials and Design* 62:98-112.
- Caulfield, D.F.; Clemons, C.; Jacopson, R.E.; Rowell, R.M. 2005.** Handbook of wood chemistry and wood composites. Taylor & Francis. London, New York, Singapore, p. 365.
- Clemson, C.M.; Ibach, R.E. 2004.** Effects of processing method and moisture history on laboratory fungal resistance of wood-HDPE composites. *Forest Prod J* 54(4):50-57.
- EN 113. 1996.** Test method for determining the protective effectiveness against wood destroying basidiomycetes. Determination of the toxic values. European Committee for Standardization, Brussels.
- Haneefa, A.; Bindu, P.; Aravind, I.; Thomas, S. 2008.** Studies on tensile and flexural properties of short banana/glass hybrid fibre reinforced polystyrene composites. *J Compos Mater* 42:1471-1489.



**Indicula, M.; Malhotra, S.K.; Joseph, K.; Thomas, S. 2005.** Dynamic mechanical analysis of randomly oriented intimately mixed short banana/sisal hybrid fibre reinforced polyester composites. *Compos Sci Technol* 65:1077-1087.

**Jarukumjorn, K.; Suppakarn, N. 2009.** Effect of glass fiber hybridization on properties of sisal fiber- polypropylene composites. *Composites: Part B* 40:623-927.

**Khanam, P.N.; Khalil, H.P.S.A.; Jawaid, M.; Reddy, G.R.; Narayana, C. S.; Naidu, S.V. 2010.** Sisal/ Carbon fibre reinforced hybrid composites: Tensile, flexural and chemical resistance properties. *J Polym Environ* 18:727-733.

**Kim, S.S.; YU, H.N.; Hwang, I.U.; Lee, D.G. 2008.** Characteristics of wood–polymer composite for journal bearing materials. *Compos Struct* 86:279-284.

**La Manita, F.P.; Morreale, M.; Ishak, Z.A. 2005.** Processing and mechanical properties of organic filler-Polypropylene composites. *J Appl Polym Sci* 96:1906-1913.

**Mallick, P.K. 2008.** *Fiber reinforced composites: material, manufacturing and design*. 3<sup>rd</sup> ed. CRC Press, New York.

**Matuana, L.M.; Park, C.P.; Balatinecz, J.J. 1998.** Cell morphology and property relationships of microcellular foamed PVC/Wood-fiber composites. *Polym Eng Sci* 38:1862-1872.

**Moreno, P.; Rodrigue, D.; Giroux, Y.; Ballerini, A.; Gacitua, W. 2013.** Morphological and mechanical characterization of recycled thermoplastic foams reinforced with wood sub-products. *Maderas-Cienc Tecnol* 15(1):3-16.

**Morris, P.I.; Cooper, P. 1998.** Recycled plastic/wood composite lumber attacked by fungi. *Forest Prod J* 48(1):86-88.

**Nourbakhsh, A.; Ashori, A. 2010.** Wood plastic composites from agro-waste materials: Analysis of mechanical properties. *Bioresource Technol* 101:2525-2528.

**Paiva, J.M.F; Santos, A.N; Rezende, M.C. 2009.** Mechanical and morphological characterizations of carbon fiber fabric reinforced epoxy composites used in aeronautical field. *Mater Res* 2(3):367-374.

**Ramesh, M.; Palanikumar, K.; Reddy, K.H. 2013.** Comparative evaluation on properties of hybrid glass fiber-sisal/jute reinforced epoxy composites. *Procedia Engineering* 51:745-750.

**Samal, S. K.; Mohanty, S.; Nayak, S. K. 2009.** Polypropylene–bamboo/glass fiber hybrid composites: Fabrication and analysis of mechanical, morphological, thermal, and dynamic mechanical behavior. *J Rein Plas Comp* 28(22):2729-2747.

**Sharma, M.; Gao, S.; Mader, E.; Sharma, H.; Wei, L.Y.; Bijwe, J. 2014.** Carbon fiber surfaces and technology. *Comp Sci Tech* 102:35-50.

**Thwe, M. M.; Liao, K. 2003.** Environmental effects on bamboo–glass/polypropylene hybrid composites. *Journal of Materials Science* 38(2): 363-376.

**Tufan, M.; Akbaş, S.; Güleç, T.; Taşcıoğlu, C.; Alma, M.H. 2015.** Mechanical, Thermal, Morphological Properties And Decay Resistance Of Filled Hazelnut Husk Polymer Composites. *Maderas-Cienc Tecnol* 17(4):865-874.



**Verhey, S.A.; Laks, P.E. 2002.** Wood particle size affects the decay resistance of woodfiber/thermoplastic composites. *Forest Prod J* 52(11/12):78-81.