



Maderas. Ciencia y Tecnología

ISSN: 0717-3644

anantias@ubiobio.cl

Universidad del Bío Bío

Chile

Chen, Taian; Gu, Lianbai

Development of elastic strain and mechano-sorptive strain during conditioning of eucalyptus  
camaldulensis lumber in batch kiln

Maderas. Ciencia y Tecnología, vol. 8, núm. 1, 2006, pp. 49-56

Universidad del Bío Bío

Concepción, Chile

Available in: <http://www.redalyc.org/articulo.oa?id=48580108>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

redalyc.org

Scientific Information System

Network of Scientific Journals from Latin America, the Caribbean, Spain and Portugal

Non-profit academic project, developed under the open access initiative

## DEVELOPMENT OF ELASTIC STRAIN AND MECHANO-SORPTIVE STRAIN DURING CONDITIONING OF *EUCALYPTUS CAMALDULENSIS* LUMBER IN BATCH KILN

Taian Chen<sup>1</sup>, Lianbai

### ABSTRACT

Final conditioning of 25mm thick dried *E. camaldulensis* lumber was carried out in small capacity batch drying kiln in laboratory, and the elastic (EL) strain and mechano-sorptive (MS) strain was analyzed by slicing method. Mean moisture content (MC) of boards increases 2.5-3.0% while surface MC increases from 9.8% to 14.2% and center MC always keeps at 12.3% or lower. Difference of each slice oven-dried length, through the thickness of the board decreases with going on of conditioning. Compressive EL strain in the surface decreases significantly during first 9h of conditioning, and tensile EL strain in the center doesn't change significantly with going on of conditioning. Compressive EL strain of sub-surface is greater than that of surface during middle and final period of conditioning, so reverse stress gradient is formed. Casehardening surface is softened by moisture picking-up and then complementary shrinkage makes EL strain and MS strain decrease, but because of the effect of drying history, the change of MS strain lags behind that of MC.

**Keywords:** *E. camaldulensis*; Final conditioning; MC; Elastic strain; Mechano-sorptive strain

### INTRODUCTION

Due to wood shrinkage below fiber saturation point (FSP), tensile stress will occur in the surface layer of the board during drying. This stress combined with the change in moisture causes mechano-sorptive creep. If the process is abruptly terminated when the target MC is reached, there will be a considerable internal moisture and stress gradients, which will cause distortion in subsequent machining.

Steaming with high humidities at atmosphere pressure has been a successful way of relaxing residual stresses in lumber after drying. Stress relaxation is achieved within one to two hours, merely depending on board dimensions and initial stress distribution (Moren, 1994a, b). However, steaming often causes overheat phenomena, especially with large, well-insulated kilns, so the desired wet-bulb depression cannot be obtained (Hart, 1990). Water sprays are very effective in reducing kiln overheat and when used in conjunction with steaming they improved moisture pick-up and stress relief, but the required duration may be up to three times the durations of steaming (Haslett et al., 2001).

Now, the procedures of conditioning are often experiential according to the methods reported by Mcmillen (1963), especially in China. So, many studies were carried out following these procedures during conditioning. Moren (1994a) reported the possibility of estimating the average

moisture pickup from measuring or calculating core temperatures in the boards during conditioning, so the possibility of settling the average moisture pickup by means of controlling the core temperature could be used to predict the required duration of the conditioning process. For the same objective as reported by Moren (1994a), Sandland (2001) determined the casehardening level after the drying period from the relation between distortion gap and MC gradient.

The analysis of conditioning phase with a wood drying model reported by Salin (2001) shows that traditional conditioning with a constant climate cannot completely release the distortion, even at very long conditioning times. So, an optimizing procedure with a varying climate was developed by him and the residual stress can be relieved completely with this optimizing procedure.


Mechano-sorptive effect caused by moisture change during conditioning may be the main reason of stress relieving, especially when residual drying stress is far below the proportional point (Pao 2000).

It is well acknowledged that the total strain during drying consists of shrinkage strain, visco-elastic strain and MS strain. Shrinkage strain occurs when the MC of lumber falls below FSP, which is the essential property of wood and cannot be changed. Visco-elastic strain is the time/stress-dependent movement of wood in the absence of any change in moisture content. Compared with the service time in other environments such as in building and furniture, drying time is so short that the magnitude of visco-elastic strain is minimal and can be neglected, so this component is neglected in this research. On the basis of the above thoughts, only EL strain and MS strain in the total strain are studied in the experiment.

Eucalyptus is one of the main fast-grown species in south China and much research has been performed to control collapse and checking during drying while little in relieving residual drying stress. The objective of this study was to gain knowledge about the development of EL strain and MS strain during conditioning. This would be beneficial to illustrate the mechanism of casehardening relief during conditioning, and also beneficial to develop a proper schedule for Eucalyptus lumber drying.

## MATERIALS AND METHODS

The boards came from 18-year-old plantation *E. camaldulensis* grown in Lufeng, Yunnan, South China. Average diameter at breast height (1.3m) was 44.5cm. The conditioning board dimension was 900x100x25mm, which was already dried to 11% MC.

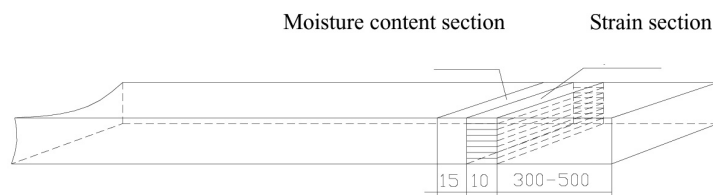

Conditioning was immediately done in batch kiln in Wood Drying Lab. of Nanjing Forestry University and lasted 24h with wet air at 62°C and 14% EMC. Test samples for evaluating EL strain, EL strain and moisture content were taken at five conditioning times (0, 1, 3, 9 and 24 h) as illustrated by Fig. 1. At each sampling time, the freshly cut board were end-sealed with sili before the boards were replaced in the stack.

$$\varepsilon_E = (L_2 - L_1) / L_1 \quad (1)$$

$$\varepsilon_{MS} = (L_4 - L_3) / L_0 \quad (2)$$

EL strain ( $\varepsilon_E$ ) and MS strain ( $\varepsilon_{MS}$ ) were calculated individually according to Formula 1 and Formula 2, where the parameters  $L_0$ ,  $L_1$ ,  $L_2$ ,  $L_3$  and  $L_4$  were determined as follows:

a. Initial length of each slice  $L_0$  was measured to the nearest 0.02mm before drying, which is the width of board before drying.

b. 10mm thick section was cut from sample board at each sampled time during conditioning. The same thin slices was acquired across section and labeled as slice 1 to slice 8 sequentially from bark to center. Each slice length was measured to 0.02mm before and after slicing, which is  $L_1$  and  $L_2$ , respectively. Each slice was weighed to the nearest 0.01g immediately after slicing to calculate MC.

c. Each slice was dried in a stepwise sequence, e.g. room air-drying/low-temperature drying first at 30°C, second and then at 60°C, then finally at oven-drying at 103±2°C. Each oven-dried slice was immediately weighed and its absolute length was measured to 0.02mm, which is  $L_3$ .

d. Before drying, the same thickness slices taken from the same board were firstly dried with the same stepwise sequence as illustrated in procedure c and then the length of each slices was measured, which is  $L_4$ .

Some hypotheses were assumed during the above procedures, which were as follows:

First, moisture distribution is even in each slice with no MC gradient because the slices are thin only approximately 3mm. Second, during procedure, because the slicing and measuring were done as soon as possible, the slice length difference between before and after slicing can be regarded as EL strain. Third, no new MS creep was developed during slice drying as described in procedure c because the drying condition was very mild. Finally, in procedure d the shrinkage coefficient difference between  $L_4$  slice and the slice sampled during conditioning is negligible because they were both taken from one straight-grain sample board.

## RESULTS AND DISCUSSION

### Change of Moisture Content during Conditioning

During conditioning, mean MC of sample board increased 2.5%-3.0%. Fig.2 shows that MC of surface slice 1 and slice 8 increases from 9.8% to 14.2% while that of center slice 4 and 5 does not change significantly. Difference between surface MC and media EMC can be regarded as the

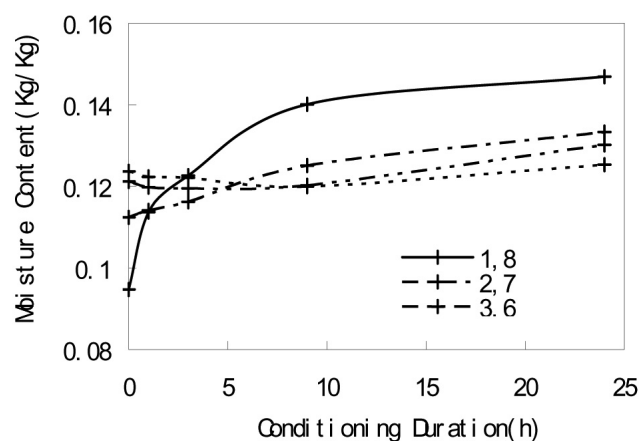


Fig.2 MC curve of sample board during conditioning

Change of core moisture content is dominated by moisture diffusion in the board. The moisture was gained in surface, the surface MC was yet lower than that of center in the first several hours of conditioning, so the center moisture diffused to outer layers, driven by the moisture content gradient. With more moisture gained in surface, the surface moisture content would be higher than the center moisture content, so the moisture in surface moved to the center driven by the reverse moisture content gradient. Above all, the change of core MC before and after conditioning was insignificant, though it oscillating during middle period of conditioning.

MC development in the hyper-center slice 3 and 6 was analogous to that in surface slice 1 and 8. During the first hour of conditioning, MC of subsurface 2 and 7 increase with moisture diffusion from inner layers to subsurface, and then increase by the combined effect of moisture diffusion from center to subsurface and moisture picking-up in surface. When the reversed MC gradient formed at the 6th hour of conditioning, the MC increase of subsurface was entirely caused by moisture picking-up in surface.

#### Change of slice oven-dried length during conditioning

Effect of MC gradient on drying stress was assessed in conventional drying stress theory. Virtually, shrinkage difference between neighboring slice, which is caused by MC difference and also by shrinkage coefficient difference, is the direct reason of drying stress. Differential shrinkage across board, but not MC gradient, was used to reflect drying stress by Stohr(1998), and surface shrinkage was used to control drying process by Fuller(1999). The basic theory in their research is that differential shrinkage is the original of stress developing. With the decreasing of log radial shrinkage coefficient difference makes more contribution to stress developing closer to the p

It was observed from Fig.3 that oven-dried length difference between neighboring slice during conditioning progressed was dependent on position: of surface slices (1 and 8) decreased with that of center slices (4 and 5) increase. This is related to residual plastic set because there is compressive set in center and tensile set in surface. During conditioning, casehardening in surface is reduced, was softened and shrinkage was also reduced because of moisture picking up in surface.

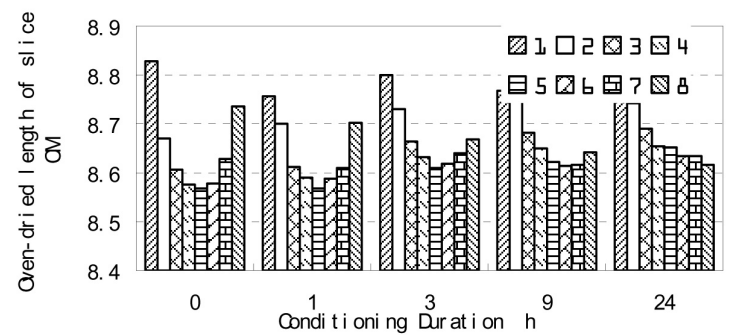


Fig.3 Oven-dried length profile of sample board during conditioning

#### Change of EL strain during Conditioning

It was observed from Fig.4 that compressive ES in surface passed a transient increase and then decreased from 0.449% to 0.133% rapidly during conditioning. When conditioning started, surface was wetted rapidly and swollen, but the neighboring subsurface (2-7) was not wetted and did not swell, so the compressive EL strain in surface increased. Mcmillen (1963) had reported wetting and softening of surface resulted in complementary shrinkage, which caused the compressive stress increase in surface. With the continuous wetting, the surface was softened and complementary shrinkage happened in surface, which resulted in the decrease of compressive strain. With conditioning continuing, moisture gain in surface became slow and subsequently the effect of softening decreased and the complementary shrinkage decreased, so the decrease rate of compressive ES became slow. The above results were the same as Fuller's reports in 1995 (Fuller 1995a,b).

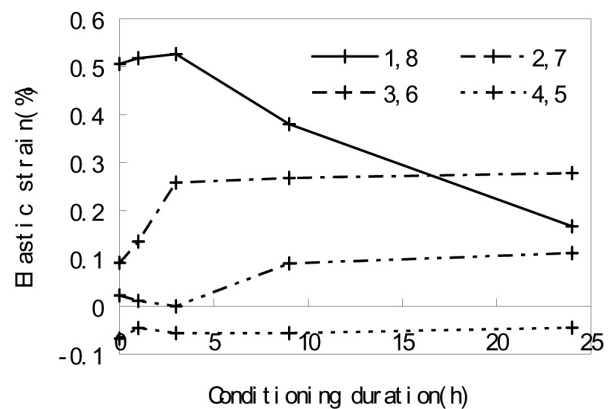


Fig.4 Elastic strain curve of sample board during conditioning

During the middle and final period of conditioning, subsurface EL strain is greater than the

Developing of EL strain in subsurface (2-7) was analogous to that in surface, while hyper-center (3-6) was analogous to center (4-5).

It was a pity that the zero sum of internal stress across section was not validated in this research because of the effects of settlements and methods, though the zero sum of internal stress is common knowledge. But development of EL strain in each layer during conditioning could be illustrated sufficiently above.

#### Change of MS Strain during Conditioning

MS strain occurs as a consequence of moisture content change when the wood is under stress. During drying, this behavior is beneficial because it can relieve drying stress. However, this is not desirable when the lumber is in service, for this causes the dried lumber to deform after re-sawing and equalizing of the moisture content. So the minimization of MS strain can be used to evaluate the effect of conditioning.

According to Armstrong and Kingston's report in 1960, MS creep during conditioning below Case 2: Increasing the moisture content to a value above the previous lowest moisture content decreases the MS strain. During conditioning, with moisture vapor entering wood, vaporization latent heat and differential wetting heat are generated at the lumber surface, so the surface temperature will arise rapidly (Hart, 1994; Pang, 2000). Heat and moisture will make the casehardened surface soften, so the MS strain is reduced.

Fig.5 shows MS Strain of each layer during conditioning decrease significantly. Compressive MS strain in subsurface (2-7), hyper-center (3-6) and center (4-5) shifted from 0.848%, 0.1326 to 0.355%, 0.343% and 0.452% individually, while tensile MS strain in surface shifted from 2.031% to 0.329%. Fig.5 also shows the decrease was significant during initial and middle period of conditioning while it was minimal during the final stage of conditioning. So if the conditioning lasts, the decrease of MS strain will be insignificant and even cause reverse casehardening.

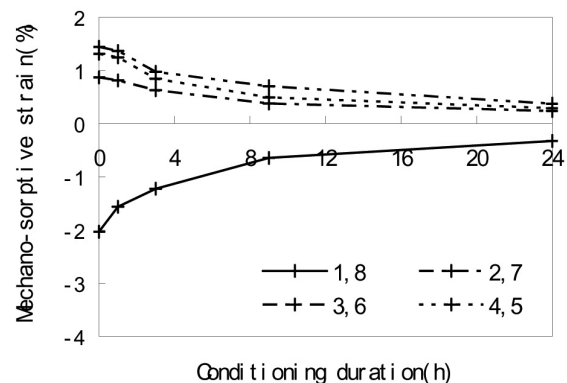


Fig.5 Mechano-sorptive strain curve of sample board during conditioning

## CONCLUSION

Moisture content data obtained by slicing the board show that mean MC of surface s increased about 5% after being conditioned for 24h in temperature 62°C, EMC 14% wet air, w the mean MC of board increased from 11% to 13.5% and center MC doesn't change significan

With the picking-up of moisture during conditioning, surface stress was found to attain maximum value and then to decrease rapidly. This was accomplished through mechano-sorp recovery, which was not only observed by slicing method, but also proved by the minimization oven-dried length difference between neighboring layers during conditioning. Minimization MS creep caused by surface wetting slightly lagged behind that of MC, so MS creep was affected not only by drying stress, but also by drying history.

## ACKNOWLEDGE

The authors gratefully acknowledge the financial support of the Nature Science Foundation of Yunnan Province.

## REFERENCES

- Fuller, J. 1995a.** Conditioning stress development and factors that influence the prong test. Res. Rap. FPL-RP-537. Madison, WI: U.S. Department of agriculture, Forest Service. Forest Products Laboratory
- Fuller, J. 1995b.** Modeling prong test response during conditioning of red oak lumber. Res. Rap. FPL-RP-540. Madison, WI: U.S. Department of agriculture, Forest Service. Forest Products Laboratory
- Fuller, J. 1999.** Stress Based Kiln Monitor/Control: Concept & Industrial Trial. U.S. Patent 5,873,182 & 5,992,407
- Hart, C.A. 1994.** Kiln overheat when conditioning lumber *Forest Prod. J.*, 40(4): 9-14
- Haslett, T.; Simpson, I.; Riley, S. 2001.** Comparison of Final conditioning using water spray and water bath steaming. 7<sup>th</sup> International IUFRO Wood drying Conference, Tsukuba, Japan~9-1995.
- Mcmillen, J. 1963.** Stresses in wood during drying. Res. Rap. 1652 USDA Forest Service Forest Products Lab. Madison, WI.
- Moren, T. 1994<sup>a</sup>.** Steaming conditioning after low temperature drying. *Holz als Roh-Werkstoff*, 52: 77-82



**Pang, S. 2000.** Modeling of stress development during drying and relief during steaming of *Pinus radiata* Lumber. *Drying Technology* 18(8): 1677-1696

**Salin, J-G. 2001.** Analysis and optimization of the conditioning phase in timber drying. *Drying Technology*, 19(8): 1711-1724

**Sandland, K. M. 2001.** Prediction of required duration of the conditioning process to reach the casehardening level in LT-dried sawn timber-Inertial experiments. *Holz als Roh-und Werkstoff* 59: 183-189

**Stohr, H. P. 1988.** Shrinkage differential as a measure for drying stress determination. *Wood Science and Technology* 22: 121-128