



Dyna

ISSN: 0012-7353

dyna@unalmed.edu.co

Universidad Nacional de Colombia
Colombia

Salazar, Alejandro; Yepes, María; Correa, Guillermo; Mora, Amanda
Polyhydroxyalkanoate production from unexplored sugar substrates

Dyna, vol. 81, núm. 185, junio, 2014, pp. 73-77

Universidad Nacional de Colombia

Medellín, Colombia

Available in: <http://www.redalyc.org/articulo.oa?id=49631031011>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

redalyc.org

Scientific Information System

Network of Scientific Journals from Latin America, the Caribbean, Spain and Portugal

Non-profit academic project, developed under the open access initiative

Polyhydroxyalkanoate production from unexplored sugar substrates

Producción de polihidroxialcanoatos a partir de sustratos azucarados inexplorados

Alejandro Salazar^a, María Yepes^b, Guillermo Correa^c & Amanda Mora^{d*}

^a Faculty of Science. Universidad Nacional de Colombia, Medellín. salazar7@purdue.edu.

^b Faculty of Science. Universidad Nacional de Colombia, Medellín. msyepes@unal.edu.co.

^c Faculty of Agricultural Sciences. Universidad Nacional de Colombia, Medellín. gcorrea@unal.edu.co.

^{d*} Faculty of Science. Universidad Nacional de Colombia, Medellín. almora@unal.edu.co.

Received: January 21th, de 2013. Received in revised form: November 1th, 2013. Accepted: December 23th, 2013.

Abstract

Industrial-scale production of biopolymers is restricted by its elevated production costs in comparison with those associated with synthetic (no-biodegradable and no-biocompatible) polymers. In this study we tested for the first time two low-cost carbon substrates (i.e. carob pulp and fique juice) for lab-scale production of polyhydroxyalkanoate (PHA) with *Bacillus megaterium*. PHA detection and quantification was conducted by gas chromatography/mass spectrometry-selected ion monitoring (GC/MS-SIM). The results suggest that PHA production using carob pulp (from *Hymenaea courbaril*) may be as high as with sugar cane molasses. Moreover, it could serve for the synthesis of the most commercialized type of PHA (i.e. polyhydroxybutyrate; PHB) and/or other varieties (e.g. polyhydroxy-butyrate-co-valerate; PHBV) with different properties and potential applications.

Keywords: polyhydroxyalkanoate (PHA); polyhydroxybutyrate (PHB); carob pulp; fique juice.

Resumen

La producción de biopolímeros a escala industrial es restringida por los elevados costos de producción, en comparación con aquellos asociados a polímeros sintéticos (no biodegradables y no biocompatibles). En este estudio evaluamos por primera vez dos sustratos de carbono de bajo costo (i.e. pulpa de algarrobo y jugo de fique) para la producción a escala de laboratorio de polihidroxialcanoato (PHA) con *Bacillus megaterium*. La detección e identificación de PHA se hizo mediante cromatografía de gases con detector selectivo de masas operado en el modo de Monitoreo de Ion Selectivo (GC-MS/SIM). Los resultados sugieren que la producción de PHA a partir de pulpa de algarrobo (de *Hymenaea courbaril*) puede ser tan alta como con melaza de caña. Más aún, puede servir para la síntesis del tipo de PHA más comercializado (i.e. polihidroxibutirato; PHB) y/o de otras variedades (e.g. polihidroxibutirato-co-valerato; PHBV) con diferentes propiedades y posibles aplicaciones.

Palabras clave: polihidroxialcanoato (PHA); polihidroxibutirato (PHB); pulpa de algarrobo; jugo de fique.

1. Introduction

Polyhydroxyalkanoates (PHA) are organic polyesters produced by a variety of bacterial species to store carbon and energy, especially under environmental/nutritional stress [1]. These biopolymers are a good alternative to replace petroleum-based polymers, because they have similar mechanical properties to conventional polymers such as polypropylene [2], but additionally are biodegradable and can be produced from a wide range of renewable sources. [3,4]. However, industrial-scale PHA production is restricted by its elevated costs in comparison with those associated with traditional nonbiodegradable polymers [2]. One of the most extended approaches to reduce these costs is the use of inexpensive carbon substrates [1,5,6].

Colombia has a great variety of plants with carbon-rich fruit that can potentially serve as substrates for bioplastic production. One of these is the *Hymenaea courbaril* (carob tree), a timber tree that extends from the west coast of central Mexico southward into Bolivia and south central Brazil. It is also found in Spain, Portugal, Arabia, Somalia and the West

Indies [7]. The fruit of this tree consist in a woody capsule with hard seeds and a dry pulp rich in carbohydrates (Table 1), that is currently used for medical purposes [8] and for human and animal consumption [7].

Table 1.
Composition of carob pulp.

Component	Content per 100g pulp
Total carbohydrates	75.3 g
Water	14.6 g
Fiber	13.4 g
Proteins	5.9 g
Fat	2.2 g
Phosphorus	143 mg
Calcium	24 mg
Ascorbic acid	11 mg
Niacin	4.1 mg
Iron	3.2 mg
Thiamine	0.24 mg
Riboflavin	0.14 mg

Source: Adapted from [7]

Another plant that produces a potentially valuable carbon substrate is the *Furcraea bedinghausii* (fique).

This plant is highly used in Colombia and other South American countries to produce a natural fiber called *cabuya*. In its production, large amounts of fique juice (which represents the 90% of fique leaves) are discarded in soils and water streams [9]. This juice is composed of sugars (3% total sugars), lignin (1%), proteins (0.96%), calcium (0.24%), potassium (0.03%), magnesium (0.03%), phosphorus (0.02%), and trace amounts of sodium, iron, copper, and zinc (from a bromatological analysis conducted in our lab).

The purpose of this study was to investigate the production of PHA by *Bacillus megaterium*, using carob pulp and fique juice as the sole carbon sources. Glucose and sugar cane molasses were used as a control and a reference, respectively, of inexpensive carbon substrates. Although the last has been reported as an effective and inexpensive substrate for PHA production [5,10], its extensive use in the biopolymer industry is restricted by the food and biodiesel industries.

2. Materials and methods

Bacterial strain

A strain of *Bacillus megaterium* was isolated from soil in Colombia, and characterized by molecular (16S rDNA sequence similarity), morphological and biochemical techniques [11]. The cultures were maintained on nutrient agar at -4 °C and a stock was stored at -20 °C in 15% (v/v) glycerol.

2.1. Culture medium and inoculum preparation

The culture medium was comprised of 0.6 g/l Na_2HPO_4 , 2.0 g/l KH_2PO_4 , 2.0 g/l $(\text{NH}_4)_2\text{SO}_4$, 0.2 g/l $\text{MgSO}_4 \cdot 7\text{H}_2\text{O}$, 0.02 g/l CaCl_2 , 0.1 g/l yeast extract, 10 ml/l trace solution (FeSO_4 2 g/l, MnCl_2 4H₂O 10.2 g/l, NiCl_2 6H₂O 0.02 g/l, $(\text{NH}_3)_6\text{MoO}_7$ 4H₂O 0.03 g/l y $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$ 0.1 g/l) and 20 g/l sugar substrate (glucose, sugar cane molasses, carob pulp or raw fique juice). After homogenization, the medium was centrifuged (2000 g, 10 min) and filtered (0.45 μm). The pH was adjusted to 7.0 with NaOH. Culture media with carob pulp and fique juice was also sterilized by autoclaving (121 °C, 15 min).

Inoculums were prepared in test tubes containing 5 ml (10% of the total volume) of sterile culture medium. Each test tube was inoculated with a single *B. megaterium* colony and incubated at 30 °C, 150 rpm for 24 h.

2.3. Fermentation studies

Inoculums (5 ml) were transferred into 250 ml erlenmeyers containing 45 ml of sterile culture medium. Fermentations were conducted at 30 °C and 150 rpm. Shake flask cultures were harvested and assayed for biomass production and reducing sugar concentration at 0, 36, 72 and 144 h.

2.2. Biomass production

After harvesting, culture media were centrifuged at 5000 g for 15 min. The pellets were resuspended in Tris-HCl 0.01 M (pH 7.0) and frozen at -75 °C. Finally, the pellets were lyophilized at -50 °C, 0.05 mBar for 24 h and weighed [12].

2.3. PHA extraction and chromatography analysis

PHA was extracted by digestion with sodium hypochlorite and chloroform [13]. Lyophilized samples were combined with a hypochlorite:chloroform (1:1) solution and shaken at 200 rpm for 1h. This solution was centrifuged at 8000 g for 10 min to isolate the PHA in the organic phase. The biopolymer was precipitated from the chloroform solution with methanol (1:3) added dropwise. The methanol solution remained at 4 °C for 24 h. The precipitated PHA was purified by washing several times with methanol. Finally, excess methanol was eliminated by evaporation and PHA polymer was identified by Gas Chromatography/Mass Spectrometry – Selected Ion Monitoring (GC/MS-SIM) [3]. The analyses were conducted using a DB-WAX (60 m x 0.25 mm x 0.25 μm) column, and a standard PHB (19.6 g; from Aldrich) as a reference. The injection was conducted in splitless mode (volume of injection = 1 μl).

2.4. Reducing sugar concentration

The dinitrosalicylic (DNS) technique (Miller 1959) was used to measure the reducing sugar concentration throughout each fermentation period. Briefly, after doing a calibration curve with glucose (0 to 2 g/l), 500 μl of supernatant, obtained by centrifugation, was added to 500 μl of the color reagent. These solutions were heated in boiling water for 5 min and immediately transferred to cold water for 5 min. Finally, absorbance was measured at 540 nm.

3. Results

3.1. Biomass production and sugar substrates consumption

The highest biomass production was obtained with glucose at 36 h (Fig. 1, A), followed by those obtained with carob pulp and sugar cane molasses (Fig. 1, B and C, respectively). For fique juice this maximum was at 72 h (Fig. 1, D). Similarly, the largest decrease in reducing sugar concentration for media supplemented with carob pulp and fique juice was between 0 and 36 h (Fig. 1, B and D, respectively). Reducing sugar concentration in sugar cane molasses-supplemented media, increased between 0 h and 36 h and then decreased slowly to 1.06 g/l at 144 h (Fig. 1, C). The sugar concentration in media with glucose was higher than 8 g/l during all the fermentation period.

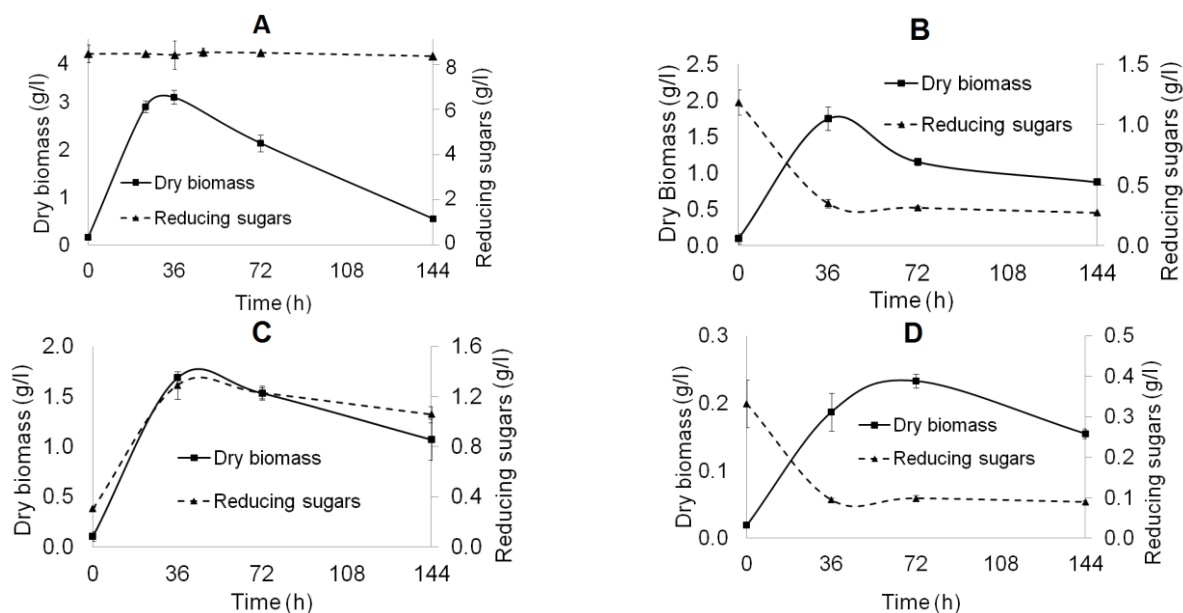


Figure 1. Dry biomass and reducing sugars concentration in media supplemented with: A) glucose; B) carob pulp; C) sugar cane molasses and D) fique juice. Notice that the scales for dry biomass and reducing sugars are not the same.

Without considering the glucose (due to its expense as a substrate), the highest dry biomass was obtained with carob pulp (1.75 ± 0.16 g/l) and sugar cane molasses (1.69 ± 0.02 g/l) at 36 h. Fique juice-supplemented media shows the maximum production at 72 h (0.23 ± 0.01 g/l), but it is significantly lower than those obtained with the others substrates. After all these maximum points, the biomass production decreased 55% for carob pulp, 30% for sugar cane molasses, and 33% for fique juice, at 144 h.

The highest (1.18 ± 0.10 g/l) and lowest (0.33 ± 0.06 g/l) values of initial reducing sugar were obtained with carob pulp and fique juice, respectively. The highest reducing sugar concentration (1.29 ± 0.11 g/l) with sugar cane was obtained at 36 h. From these maximum points to 144 h, the reducing sugar concentration decreased 77%, 73% and 18% for carob pulp, fique juice, and sugar cane molasses, respectively.

3.2. PHA extraction and characterization

The mass spectrum of the monomers obtained by derivatization of the reference PHB (Fig. 2A) and the produced PHA (Fig. 2, B to E), confirms the presence of hydroxybutyric (HB) monomers in all samples except in those from fique juice (Fig. 2, E). Besides HB monomers, another compound (possibly hydroxyvalerate) was detected when glucose and carob pulp were used as the sole carbon source (peaks at 27 min in Fig. 2, B and C, respectively). The PHA production with glucose, carob pulp, sugar cane molasses and fique juice were 2.5, 0.8, 0.8 and < 0.002 g/l, respectively.

4. Discussion

All substrates tested in this research can be used as the sole carbon source for the growth of *B. megaterium*, which is a common bacteria used for PHA production [1,5]. Nevertheless, there are significant differences between the

amount and composition of the biopolymers produced from each substrate. Similar results have been observed when comparing PHA productions from different carbon sources. Valappil et al. (2007) were able to produce PHA (using a strain of *Bacillus cereus*) with 3-HB, 3-HV, and 4-hydroxybutyryl (4-HB)-like monomer units from structurally unrelated carbon sources, such as fructose, glucose, and gluconate [3]. Similarly, Pijuan et al. (2009) found that different phosphorus-removal microbial communities produced PHA with different compositions [amount of PHB, PHV, and polyhydroxy-2-methylvalerate (PH2MV)], depending on the type of carbon source (i.e. acetate, propionate, butyrate, and glucose) [14]. Therefore, studies focused on novel carbon sources for PHA production (such as this one) have to consider not just the amount but the type of PHA produced with each carbon source.

Biomass and PHA production were related to the availability of reducing sugars. The highest and lowest biomass and biopolymer productions were obtained with glucose and fique juice, which respectively showed the highest and lowest reducing sugar concentrations. Although sugar concentrations are higher in sugar cane molasses than in carob pulp, the PHB production from both substrates were similar. There are two aspects that must be considered in this case: (1) sugar cane molasses are rich in polysaccharides (mainly sucrose) that cannot be detected by the DNS technique (Miller 1959), but as the culture grows these polysaccharides are metabolized and reducing sugars are released to the culture media (Fig. 1, C and 3); (2) carob pulp has volatile compounds as methylpropanoic, methylbutanoic, hexanoic and heptanoic acids [15], that microorganisms can use for PHA synthesis [16]. It is possible that these volatile compounds have compensated for the deficiency of reducing sugars in carob pulp with respect to cane molasses, so that both PHB productions were similar.

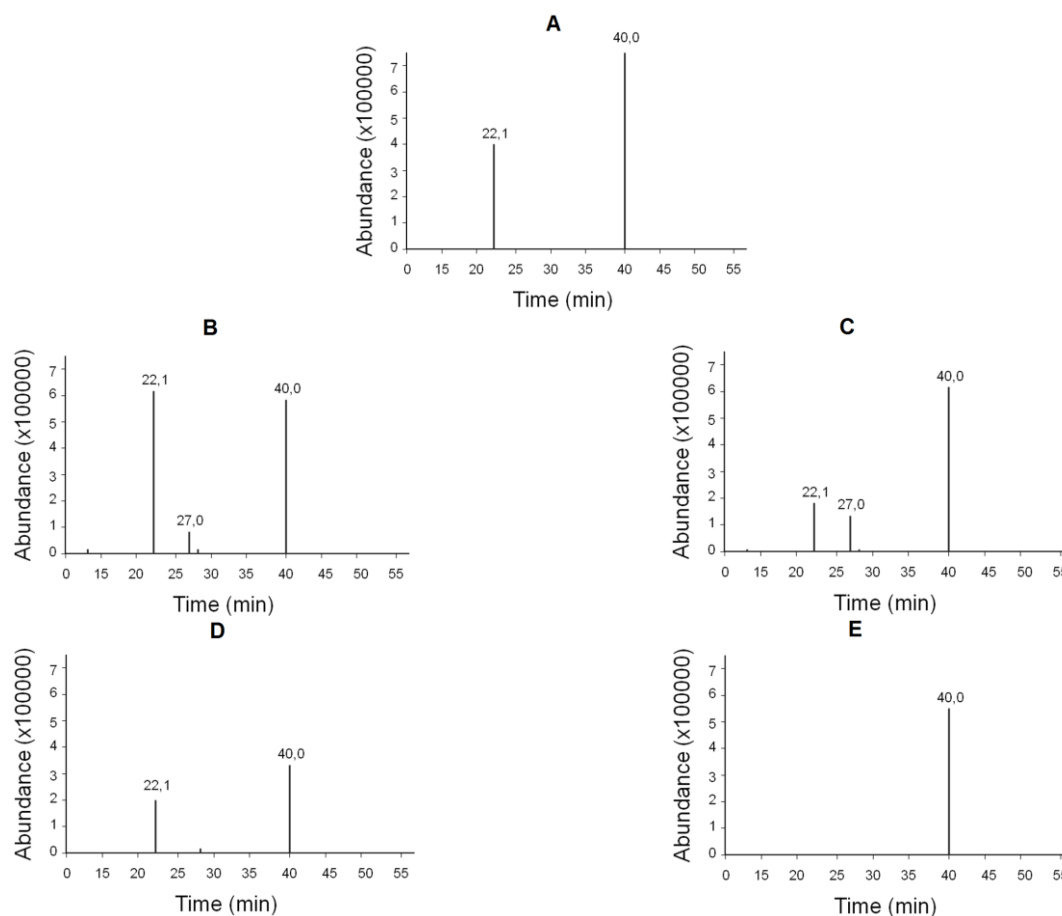


Figure 2. GC/MS-SIM chromatograms of monomers prepared from: A) reference PHB; and from those obtained from media supplemented with B) glucose (PHB at 22.1 and possible PHV at 27.0); C) carob pulp (PHB at 22.1 and possible PHV at 27.0); D) sugar cane molasses (PHB at 22.1); and E) fiqué juice (undetected).

Besides HB monomers, another compound was detected in the PHA produced from glucose and carob pulp. Based on the results reported by Keum et al. (2008), the peak at 27 min in Fig. 2 B and C could represent the production of hydroxyvalerate (HV) monomers. This suggests that the PHA obtained from glucose and carob pulp is the copolymer poly(hydroxybutyrate-co-valerate) (PHBV) [17]. This biopolymer has different properties than the common PHB, and is used for different biomedical and industrial applications [18,19].

In summary, this is, to our understanding, the first evidence that carob pulp can be used as a carbon source for PHA production. The use of this and other inexpensive carbon substrates, such as beet molasses [20], extruded rice bran [21], and dairy wastes [1], could lead to significant reductions in the production costs of PHA.

5. Conclusions

Carob pulp is a promising carbon source for PHA production. Moreover, it may be used for the production of biopolymers with composition and properties different than those of the traditional PHB. This may be due to the presence of volatile fatty acids in carob pulp. An additional advantage of this novel carbon source is that carob trees are widely spread and their fruits are mostly unexploited.

Contrary to carob pulp, raw fiqué juice does not seem to be an adequate carbon source for PHA production. However, due to the large amounts of fiqué juice that are annually wasted in Colombia and other South American countries, it could be economically viable to consider pretreatments (e.g. to increase sugar concentration) to enhance the efficiency of fiqué juice as a substrate for PHA production.

Although carob pulp represents an opportunity to reduce the production costs of PHA, more research is needed in order to reduce the gap in production costs between petroleum-based and biodegradable polymers.

Acknowledgments

We would like to thank the DIME (Dirección de Investigación de la Universidad Nacional de Colombia, Sede Medellín), Vicerrectoría de Investigaciones de la Universidad Nacional de Colombia, and the Colciencias (Departamento Administrativo de Ciencia Tecnología e Innovación de la República de Colombia) program “Jóvenes Investigadores e Innovadores – Virginia Gutiérrez de Pineda” for their financial support. Also we would like to thank Dr. Mauricio Marín and M.Sc. Silvia Sánchez for their contribution in the isolation and characterization of the strain.

References

- [1] Pandian, S., Deepak, V., Kalishwaralal, K., Rameshkumar, N., Jeyaraj, M. and Gurunathan, S., Optimization and fed-batch production of PHB utilizing dairy waste and sea water as nutrient sources by *Bacillus megaterium* SRKP-3. *Bioresource. Technology*, 101 (2), pp. 705-711, 2010.
- [2] Hong, C., Hao, H. and Haiyun, W., Process optimization for PHA production by activated sludge using response surface methodology. *Biomass and Bioenergy*, 33 (4), pp. 721-727, 2009.
- [3] Valappil, S., Peiris, D., Langley, G., Hermiman, J., Boccaccini, A., Bucke, C. and Roy, I., Polyhydroxyalkanoate (PHA) biosynthesis from structurally unrelated carbon sources by a newly characterized *Bacillus* spp. *Journal of Biotechnology*, 127 (3), pp. 475-487, 2007.
- [4] Villano, M., Beccari, M., Dionisi, D., Lampis, S., Micchelli, A., Vallini, G. and Majone, M., Effect of pH on the production of bacterial polyhydroxyalkanoates by mixed cultures enriched under periodic feeding. *Process Biochemistry*, 45 (5), pp. 714-723, 2010.
- [5] Kulprecha, S., Boonruangthavorn, A., Meksiriporn, B. and Thongchul, N., Inexpensive fed-batch cultivation for high poly(3-hydroxybutyrate) production by a new isolate of *Bacillus megaterium*. *Journal of Bioscience and Bioengineering*, 107 (3), pp. 240-245, 2009.
- [6] Kim, B., Production of poly(3-hydroxybutyrate) from inexpensive substrates. *Enzyme and Microbial Technology*, 27 (10), pp. 774-777, 2000.
- [7] Aalate, L., Artega, D. and Jaramillo, Y., Propiedades farmacológicas del algarrobo (*Hymenaea courbaril* Linnaeus) de interés para la industria de alimentos. *Revista Lasallista de Investigación*, 5 (2), pp. 100-111, 2008.
- [8] Cartaxo, S., Souza, M. and de Albuquerque, Medicinal plants with bioprospecting potential used in semi-arid northeastern Brazil. *Journal of Ethnopharmacology*, 131 (2), pp. 326-342, 2010.
- [9] Martínez, L.F., Guía ambiental para el subsector fique. Ministerio del Medio Ambiente, Fedefique y Sociedad de Agricultores de Colombia, Colombia, 2000.
- [10] Bengtsson, S., Pisco, A., Reis, M. and Lemos, P., Production of polyhydroxyalkanoates from fermented sugar cane molasses by a mixed culture enriched in glycogen accumulating organisms. *Journal of Biotechnology*, 145 (3), pp. 253-263, 2010.
- [11] Sánchez, A., Marin, M., Mora, A. and Yepes, M., Identificación de bacterias productoras de polihidroxicanoatos (PHAs) en suelos contaminados con desechos de fique, *Revista Colombiana de Biotecnología*, 14 (2), pp. 89-100, 2012.
- [12] Barbosa, M., Eespinoza-Hernández, A., Malagón-Romero, D. and Moreno-Sarmiento, N., Producción de poli-β-hidroxibutirato (PHB) por *Ralstonia eutropha* ATCC 17697. *Universitas Scientiarum*, 10 (1), pp. 45-54, 2005.
- [13] Jacquél, N., Lo, C.W., Wei, Y.H., Wu, H.S. and Wang, S., Isolation and purification of bacterial poly(3-hydroxyalkanoates). *Biochemical Engineering Journal*, 39 (1), pp. 15-27, 2008.
- [14] Pijuan, M., Casas, C. and Baeza, J., Polyhydroxyalkanoate synthesis using different carbon sources by two enhanced biological phosphorus removal microbial communities. *Process Biochemistry*, 44 (1), pp. 97-105, 2009.
- [15] Mastelić, J., Jerković, I., Blazević, I., Randonić, A. and Krstulović, L., Hydrodistillation-adsorption method for the isolation of water-soluble, non-soluble and high volatile compounds from plant materials. *Talanta*, 76 (4), pp. 885-891, 2008.
- [16] Suriyamongkol, P., Weselake, R., Narine, S., Moloey, M. and Shah, S., Biotechnological approaches for the production of polyhydroxyalkanoates in microorganisms and plants – A review. *Biotechnology Advances*, 25 (2), pp. 148-175, 2007.
- [17] Keum, Y.S., Seo, J.S., Li, Q.X. and Kim, J.H., Comparative metabolomic analysis of *Sinorhizobium* sp. C4 during the degradation of phenanthrene. *Applied Microbiology and Biotechnology*, 80 (5), pp. 863-872, 2008.
- [18] Jacobs, T., Declercq, H., de Geyter, N., Cornelissen, R., Dibrue, P., Leys, C., Beaurain, A., Payen, E. and Morent, R., Enhanced cell-material interactions on medium-pressure plasma treated polyhydroxybutyrate/polyhydroxyvalerate. *Journal of Biomedical Materials Research Part A*, 101(6), pp. 1778-1786, 2013.
- [19] Pardo-Ibáñez, P., López-Rubio, A., Martínez-Sanz, M., Cabedo, L. and Lagaron, J., Keratin-polyhydroxyalkanoate melt-compounded composites with improved barrier properties of interest in food packaging applications. *Journal of Applied Polymer Science*, pp. 131 (4), 2014.
- [20] Page, W., Production of polyhydroxyalkanoates by *Azotobacter vinelandii* UWD in beet molasses culture. *FEMS Microbiology Letters*, 103 (2), pp. 149-157, 1992.
- [21] Huang, T., Duan, K., Huang, S. and Chen, C., Production of polyhydroxyalkanoates from inexpensive extruded rice bran and starch by *Haloferax mediterranei*. *Journal of Biotechnology*, 33, (8), pp. 701-706, 2006.

Alejandro Salazar, received the Bs. in Biological Eng. in 2009, and the MS degree in Biotechnology in 2012, at the Universidad Nacional de Colombia, Medellín. Currently, he is a PhD candidate in the Department of Biological Sciences at Purdue University, US.

María Yepes, received the Bs. in Chemistry in 1988 and the MS degree in Chemistry in 1996. From 1996, she is a full time Professor in the School of Chemistry, Facultad de Ciencias, Universidad Nacional de Colombia. She is a member of the research group Production, Application, and Characterization of Biomolecules (PROBIOM) from the same University, and leads different research projects on areas of chemistry, food biotechnology, and environmental biotechnology, aimed at environmental, food, and social sustainability.

Guillermo Correa, received the Bs. Eng in Forest Engineering in 1995, the MS degree in Statistics in 1999, and the PhD degree in Multivariate Statistics in 2008. From 1996, he is a full time Professor in the Agronomical Sciences Department, Facultad de Ciencias Agrarias, Universidad Nacional de Colombia. He collaborates in different topics of biological and agricultural research through the design and analysis experiments.

Amanda Mora, received the Bs. in Chemistry in 1992, the MS degree in Chemistry in 1997, and the PhD degree in Chemistry in 2006. From 2000, she is a full time Professor in the School of Chemistry, Facultad de Ciencias, Universidad Nacional de Colombia. She is a member of the research group Production, Application, and Characterization of Biomolecules (PROBIOM) from the same University, and leads different research projects on areas of environmental chemistry and biotechnology, aimed at environmental remediation and generation of value-added products from inexpensive substrates (e.g. agroindustrial wastes).