



Revista Mexicana de Ingeniería Química

ISSN: 1665-2738

amidiq@xanum.uam.mx

Universidad Autónoma Metropolitana

Unidad Iztapalapa

México

López-Chavez, M.C.; Osorio-Revilla, G.; Arellano-Cárdenas, S.; Gallardo-Velazquez, T.;  
Flores-Valle, S.O.; López-Cortez, MS.

PREPARATION OF STARCH/CLAY/GLYCEROL NANOCOMPOSITE FILMS AND THEIR  
FTIR, XRD, SEM AND MECHANICAL CHARACTERIZATIONS

Revista Mexicana de Ingeniería Química, vol. 16, núm. 3, 2017, pp. 793-804

Universidad Autónoma Metropolitana Unidad Iztapalapa

Distrito Federal, México

Available in: <http://www.redalyc.org/articulo.oa?id=62053304009>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

redalyc.org

Scientific Information System

Network of Scientific Journals from Latin America, the Caribbean, Spain and Portugal

Non-profit academic project, developed under the open access initiative

**PREPARATION OF STARCH/CLAY/GLYCEROL NANOCOMPOSITE FILMS AND THEIR FTIR, XRD, SEM AND MECHANICAL CHARACTERIZATIONS****PREPARACIÓN DE PELÍCULAS CON NANOCOMPUESTOS DE ALMIDÓN/ARCILLA/GLICEROL Y SU CARACTERIZACIÓN MECÁNICA, FTIR, XRD Y SEM**

M.C. López-Chavez<sup>1</sup>, G. Osorio-Revilla<sup>2</sup>, S. Arellano-Cárdenas<sup>1</sup>, T. Gallardo-Velázquez<sup>1</sup>,  
S.O. Flores-Valle<sup>3</sup>, M.S. López-Cortez<sup>1\*</sup>

<sup>1</sup>Departamento de Biofísica. <sup>2</sup>Departamento de Ingeniería Bioquímica. Escuela Nacional de Ciencias Biológicas-IPN, Prol. de Carpio y Plan de Ayala, s/n. Col. Santo. Tomás. Apartado Postal 42-186, C.P. 11340, Ciudad de México, México.

<sup>3</sup>Laboratorio de Catálisis. Escuela Superior de Ingeniería Química e Industrias Extractivas-IPN. Unidad Profesional Adolfo López Mateos. Colonia Lindavista, Gustavo A. Madero, C.P. 07738, Ciudad de México, México.

Received November 15, 2016; Accepted July 2, 2017

**Abstract**

In the present work, Mexican natural clay (NC) was used to prepare an organoclay (OC), and both were added to a mix of starch/glycerol to obtain nanocomposite films of starch (TPS)/clay/plasticizer. The average thickness of the TPS/5% NC/25% glycerol films was  $81 \pm 3 \mu\text{m}$ , and it was  $91 \pm 2 \mu\text{m}$  for the TPS/5% OC/25% glycerol films. Both the X-ray diffraction and infrared analyses showed that the glycerol and starch molecules can be intercalated into the clay galleries. A good dispersion of the components in the mix was observed via an electron scanning microscope. Using the nanoindentation method, it was observed that the materials with the highest elasticity had the lowest amount of clay and the highest concentration of glycerol. The moisture permeability of the films was reduced by 80% in the presence of the clay materials utilized in this study.

**Keywords:** clay, composite films, organoclay, thermoplastic starch.

**Resumen**

En la presente investigación se utilizó una arcilla natural (NC) de origen mexicano a partir de la cual se preparó una organoarcilla (OC). Las arcillas natural y orgánica, se adicionaron a una mezcla de almidón/glicerol para obtener películas con nanocompuestos de almidón (TPS)/arcilla/plastificante. El espesor promedio de las películas preparadas con TPS/5% NC/25% glicerol fue de  $81 \pm 3 \mu\text{m}$ , y de  $91 \pm 2 \mu\text{m}$  para las películas TPS/5% OC/25% glicerol. Los análisis de difracción de rayos X e infrarrojo mostraron que las moléculas de almidón y de glicerol pueden intercalarse en la región interlamilar de la arcilla. Mediante la microscopía electrónica de barrido se observó una buena dispersión de los componentes en las mezclas. Por el método de nanoindentación, se observó que las películas con mayor elasticidad fueron las que contenían menor cantidad de arcilla y mayor concentración de glicerol. La permeabilidad al vapor de agua de las películas preparadas se redujo en un 80% con la presencia de las arcillas utilizadas.

**Palabras clave:** arcilla, películas, nanocompuestos, organoarcilla, almidón termoplástico.

**1 Introduction**

Currently, it is possible to find many studies on the preparation of biodegradable thermoplastic starch (TPS) composite films, which can be used for food packages. Usually, TPS films are obtained via structural modification inside starch granules processed with a low water content under thermal and mechanical forces, and starch may be combined with plasticizers, such as glycerol, which are not

easily evaporated during the processing (Avella *et al.*, 2004; Villada *et al.*, 2008; Borges *et al.*, 2015; Esmaeili *et al.*, 2017). However, TPS films have low mechanical stability and are sensitive to moisture due to the highly hydrophilic nature of its components. Such properties may be improved by the addition of other materials, such as cellulose fiber, nano-clays or other biodegradable polymers (Park *et al.*, 2003; Averous and Boquillon, 2004; Chang *et al.*, 2010; Fialho and Moraes *et al.*, 2017; Khan *et al.*, 2017; Flores-Martínez *et al.*, 2017). A promising alternative

\* Corresponding author. E-mail: socolc@prodigy.net.mx

is the preparation of nanocomposites by combining biopolymer-clays (Azeredo, 2009; Santos *et al.*, 2014; Wilpiszewska *et al.*, 2015; Cheviron *et al.*, 2016; Staroszczyk *et al.*, 2017). Natural clays (NC), such as montmorillonites, have a laminar structure and are readily available, non-toxic and inexpensive. Mexican montmorillonites have suitable properties, such as cation exchange, surface area and swellability, that make them very versatile and readily modifiable via the intercalation of surfactants (typically quaternary ammonium salts) in the interlaminar region to obtain hydrophobic organoclays (OC) (López *et al.*, 2008; Arellano-Cárdenas *et al.*, 2012, 2013; Almazán-Sánchez *et al.*, 2016; Jiménez-Castañeda and Medina, 2017). Recent research has shown that the use of the right combination of starch/NC or OC plus glycerol as a plasticizer may improve the physical properties of films, such as the thermal stability, and decrease their permeability to water vapor and gases, such as O<sub>2</sub> and CO<sub>2</sub> (Park *et al.*, 2003; Yu *et al.*, 2007; Zhang *et al.*, 2007; Kho *et al.*, 2008; Rhim *et al.*, 2009; Cyras *et al.*, 2008; Hongguang *et al.*, 2009; Gao *et al.*, 2014; Chung *et al.*, 2010; Müller *et al.*, 2012, 2014; Romero-Bastida *et al.*, 2015; Nguyen *et al.* 2016;). Nevertheless, the incorporation of-nanoclays onto a TPS matrix to obtain homogeneous films with good mechanical and barrier properties has remained a challenge because the chemical and physical properties depend on the type and origin of the clay and its morphological and chemical characteristics.

The present study proposes the use of a Mexican NC with a hydrophilic nature and the hydrophobic OC obtained from it for the preparation of TPS/clay/glycerol nanocomposite films. The effect of both materials on the microstructure and mechanical and barrier properties of the obtained films is described.

## 2 Materials and methods

### 2.1 Materials

The natural clay used in the present work was a Perfbont montmorillonite from northern Mexico and was supplied by Arcillas Industriales de Durango, S.A. This clay was sieved through a number 65 sieve (mesh size 0.210 mm). Preparation and characterization of the OC was described previously by López *et al.*, 2008, and the surfactant cetylpyridinium chloride (CPC) (C<sub>21</sub>H<sub>38</sub>ClN·H<sub>2</sub>O from Sigma-Aldrich

Chemical Co.) was added to the NC in an amount equivalent to 100% of its cationic exchange capacity (CEC). The CEC value reported for the NC is 101 meq/100 g and 45 meq/100 g for the OC. The basal spacing *d*(001) values for NC and OC are 1.24 and 2.14 nm, respectively.

### 2.2 Preparation of the films

The starch-based films were prepared according to the methods proposed by Park *et al.*, 2003, and Lilichenco *et al.*, 2008, with some modifications. Clay (NC or OC) was dispersed in water, and starch was gelatinized in hot water at 90°C. Then, both suspensions were mixed to obtain three proportions starch/clay on a dry basis (95/5, 90/10, 85/15) and glycerol was added at two concentrations of 25 and 30%, based on the amount of starch on a dry basis. The mix was stirred and placed in a sonicator (ultrasonicator Branson 1200, Branson 50/60 HZ, 117 volts, 0.7 amperes) for 30 min. The films were obtained by casting them in polyethylene Petri dishes 8.5 cm in diameter and drying them at 50 °C for 24 h in a THELCO model 19 vacuum stove. The dried films were peeled off and stored in a vacuum desiccator until further analysis. Three types of films were obtained: pure starch (TPS)/glycerol, TPS/NC/glycerol and TPS/OC/glycerol composite films.

### 2.3 Characterization of the films

The thickness of the films was determined using a Mitutoyo electronic micrometer (sensitivity of 1 μm) by measuring ten different points along the film (Müller *et al.*, 2012; Sothornvit and Krochta, 2001). The films obtained were read directly in an FTIR Perkin Elmer Spectrum 2000 spectrophotometer using 8 scans and 4000 to 400 cm<sup>-1</sup> as the wavenumber range (Chang *et al.*, 2010). Diffractograms were recorded for the powders (NC, OC and starch) or films using a Siemens D-500 diffractometer with a nickel filter and Cu Kα radiation of λ = 1.5406 Å, operating at 30 kV and 20 mA and scanning the 2θ angle from 2 to 64°. The basal spacing *d*(001) was calculated using Bragg's equation (Brindley and Brown, 1980). Images of the microstructures of the films (degree of dispersion) were obtained using an electron scanning microscope, JEOL model JSM-5800 LV.

The mechanical properties were determined according to the method reported by Fisher, 2006. Samples of 1 cm<sup>2</sup> were cut and pasted with glue on a slide. The samples were fixed on a support,

and the moving axis was operated with computer software. The conditions of the test were a maximum load of 5 mN (miliNewtons), a load speed and unloading of 15 mN/min and a pause of 15 s. The instrument used in this study was a Nanoindentator NHT, CSM Instruments (Switzerland), with an optic microscope coupled to a Berkovich diamond tip (standard). The Oliver and Pharr 1992 method was used to calculate the tensile strength (TS) and elastic modulus (Young's modulus, E) via a puncture test. The nanoindentator software draws the graphic strength *versus* the penetration to obtain the punctual S slopes, which allow the calculation of TS and E.

The velocity of the moisture transmission was measured using the Payne Permeability cup, according to ASTM E96-80 and following the technique proposed by Ning *et al.*, 2010 with some modifications. Samples 7 cm in diameter were cut and placed in the base of a cell that contains calcium chloride,  $\text{CaCl}_2$ , as a desiccant, and the samples were secured with a metallic ring and screw cap, leaving an exposed area of  $25 \text{ cm}^2$  for the exchange. Additionally, a desiccant with 300 mL of a saturated solution of  $\text{Mg}(\text{NO}_3)_2$  was prepared to give a relative humidity (RH) of 51.4%. This solution was obtained via hot mixing and magnetic stirring 235 g of magnesium nitrate hexahydrate  $\text{Mg}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  and 300 mL of distilled water. When the solution was cooled to  $30^\circ\text{C}$ , the formation of nitrite salt crystals was observed, which indicated the formation of a saturated solution. To secure the homogeneity of the RH, a fan was coupled under the ceramic base of the desiccator, and foam was placed between the rim and the lid. Once the lid was closed, the system was placed inside a stove at a controlled temperature of  $30^\circ\text{C}$ . The capsules were weighed, and the first reading was recorded at time zero. Afterwards, the capsules were placed back into the desiccator, and the weights of the capsules were recorded again at one hour time intervals for seven hours.

The water vapor transmission rate (WVTR) was calculated using a linear regression of the slope of the weight gained in the test cup (G) *versus* the time (t) and dividing the slope by the exposed area of the films (A), as shown in Eq. (1):

$$\text{WVTR} = \frac{G}{tA} \quad (1)$$

Permeance was calculated using Eq. (2):

$$\text{Permeance} = \frac{(\text{WVTR})}{P_2 - P_1} \quad (2)$$

where  $P_2$  and  $P_1$  are the partial pressures at the inner surface of the films and the surface of the desiccant, respectively. The value of  $P_1$  was considered to be zero, while  $P_2$  was calculated using RH = 51.4% in the desiccator and  $P_{\text{sat}}$  of 4.24 kPa, which is the pressure of the saturation of water vapor at  $30^\circ\text{C}$ .

The water vapor permeability (WVP) was calculated as the product of the permeance and the average thickness of the film.

Each sample was analyzed in triplicate, and the WVP value for each film is presented as the mean and standard deviation of these results.

### 3 Results and discussion

#### 3.1 Thickness of the films

The determination of the thickness of the films is important because this parameter affects the mechanical and barrier properties. Table 1 shows the thicknesses of the films made with different proportions of TPS/clay/glycerol. The values are the average of three samples, and each one was measured in ten different areas, as explained in the materials and methods section. The thickness of the pure starch and 25% glycerol film registered an average of  $85 \pm 5 \text{ }\mu\text{m}$  and  $53 \pm 6 \text{ }\mu\text{m}$  for the pure starch and 30% glycerol film. Regarding the TPS/NC films, it was observed that higher proportions of natural clay slightly increased the thickness for both proportions of glycerol. The TPS/OC films (mean thickness value of  $89 \pm 5 \text{ }\mu\text{m}$ ) showed the glycerol content had no effect on the thickness. When the clay proportion increases, a small increase in the thickness was observed, although this difference was not statistically significant. Regarding the type of clay, it was observed that the TPS/NC films have lower thicknesses (mean values of  $81 \pm 5 \text{ }\mu\text{m}$  for 25% glycerol and  $62 \pm 5 \text{ }\mu\text{m}$  for 30% glycerol) compared to the TPS/OC films (mean thickness value of  $89 \pm 5 \text{ }\mu\text{m}$ ). The thicknesses obtained for the films using two types of clay are within the values reported for starch/clay biofilms. Souza *et al.*, 2012, reported a range of 76.72 to  $91.84 \text{ }\mu\text{m}$ , and Borges *et al.*, 2015, reported a range of 60 to  $80 \text{ }\mu\text{m}$ .

Table 1: Thickness ( $\mu\text{m}$ ) of TPS/NC and TPS/OC starch/clay composite films with 25% and 30% glycerol content

TPS/NC	glycerol		TPS/OC	glycerol	
	25%	30%		25%	30%
100/0	85 $\pm$ 5	53 $\pm$ 6	—	—	—
95/5	75 $\pm$ 2	59 $\pm$ 5	95/5	83 $\pm$ 5	88 $\pm$ 3
90/10	84 $\pm$ 5	64 $\pm$ 3	90/10	96 $\pm$ 2	85 $\pm$ 2
85/15	86 $\pm$ 3	64 $\pm$ 3	85/15	96 $\pm$ 8	89 $\pm$ 5

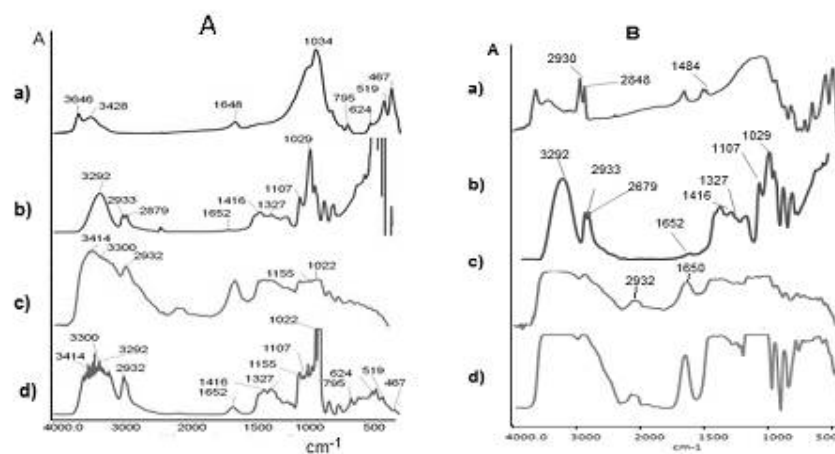


Fig. 1 A) FTIR spectra of a) Natural clay, b) glycerol, c) TPS and d) TPS/NC 95/5, 25% glycerol film. B) FTIR spectra of a) Organoclay, b) glycerol, c) TPS and d) TPS/OC 95/5, 25% glycerol film.

### 3.2 Infrared analysis (FTIR) of the films

Fig. 1A shows the IR spectra for each component of the TPS/NC film with a starch/clay ratio 95/5 and 25% glycerol. Fig. 1A (a) corresponds to the IR spectrum of the NC, whose main bands are at 3646 and 3428  $\text{cm}^{-1}$  (OH stretching), 1648  $\text{cm}^{-1}$  (OH flexion) and 1034  $\text{cm}^{-1}$  (stretching of the Si-O and Si-O- bonds in the structure) (López *et al.*, 2008). The IR spectrum of the glycerol molecule, Fig. 1A (b), shows absorption bands at 3292  $\text{cm}^{-1}$  (OH groups), 2933  $\text{cm}^{-1}$  and 2879  $\text{cm}^{-1}$  (stretching of the CH groups for  $\text{CH}_3$  and  $\text{CH}_2$ , respectively), 1652  $\text{cm}^{-1}$  (OH groups), 1416 and 1327  $\text{cm}^{-1}$  (CH groups), and 1107 and 1029  $\text{cm}^{-1}$  (OH groups). Fig. 1A (c) corresponds to the IR spectrum of starch, and a wide band is located between 3300 and 3414  $\text{cm}^{-1}$ , which is attributed to the stretching of the OH groups in the glucose molecule. The width of the band indicates the presence of intermolecular hydrogen bonds in the structure of starch, and the peak at 2932  $\text{cm}^{-1}$  is due to the stretching vibrations of

the  $\text{CH}_2$  in the glucose rings. The last bands in this spectrum are at 1155  $\text{cm}^{-1}$  (stretching vibrations of C-O in the C-OH groups) and 1022  $\text{cm}^{-1}$  (stretching vibrations of C-O in the C-OC groups) (Huang *et al.*, 2004, Ruiz, 2006.). The IR spectrum of the TPS/NC film (95/5, 25% glycerol), Fig. 1A (d), shows intense bands due to the thickness of the film (81 $\pm$ 2  $\mu\text{m}$ ), which agrees with other reports on plastic films of this type (Wilhelm *et al.*, 2003). It has also been reported that NC, glycerol and starch may present a physical interaction with hydrogen bonds (Dean *et al.*, 2008). The spectrum of the film has a shift in the pure NC band (3428  $\text{cm}^{-1}$ ) to a lower wavelength (3414  $\text{cm}^{-1}$ ), which is characteristic of the hydroxyl groups that participate in the formation of hydrogen bonds. Santos *et al.*, 2014, suggested that this indicates a possible interaction among starch, glycerol and clay molecules. The peak at 2932  $\text{cm}^{-1}$  (in the starch spectrum) did not change; therefore, as mentioned by Majdzadeh *et al.* (2010), the glucose ring does not seem to be involved in the plasticizing process.



Table 2: XRD parameters:  $2\theta$  angle and basal spacing  $d(001)$  of clay (NC and OC); TPS/NC and TPS/OC starch/clay composite films with 25% and 30% glycerol content.

NC		OC			
glycerol content (%)	Composition TPS/clay	$2\theta$ (°)	$d(001)$ (nm)	$2\theta$ (°)	$d(001)$ (nm)
25	Clay	7.12	1.24	4.12	2.14
	95/5	4.96	1.78	3.24	2.73
	90/10	5.11	1.73	3.51	2.51
	85/15	5.08	1.74	3.67	2.41
30	95/5	4.99	1.77	3.5	2.52
	90/10	5.01	1.76	3.62	2.44
	85/15	4.84	1.82	3.44	2.56

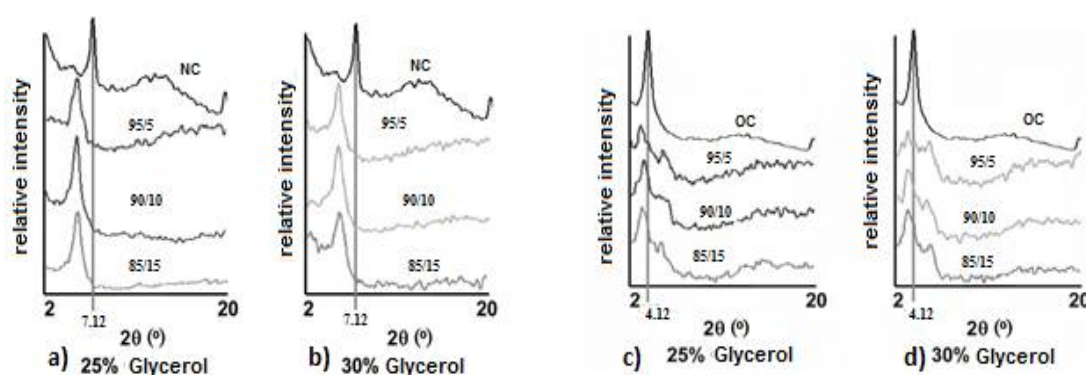


Fig. 2 XRD diffractograms of natural clay, organoclay and composite films: a) and b) TPS/NC; c) and d) TPS/OC, with proportions TPS/clay 95/5, 90/10, 85/15 with 25% and 30% of glycerol.

The FTIR spectra of the TPS/OC composite films are shown in Fig. 1B and are similar to the ones obtained for the TPS/NC films. The FTIR spectrum of OC in Fig. 1B (a) shows the same bands as the host clay with additional strong bands at 2930 and 2848  $\text{cm}^{-1}$  (asymmetric and symmetric stretching vibrations, respectively, of the  $-\text{CH}_2$  groups in the aliphatic hydrocarbon chains) and a peak at 1484  $\text{cm}^{-1}$  (indicative of the  $-\text{CH}_2$  bending vibration mode). These peaks indicate the presence of the CPC surfactant intercalated in the natural clay (López *et al.*, 2008). In Fig. 1B (d), an overlap of the main bands makes it difficult to distinguish them. A very intense band is observed in the region of 3000 - 3500  $\text{cm}^{-1}$ , which is due to the responses from each component in the OH,  $\text{CH}_2$  and  $\text{CH}_3$  groups. The similarities in the spectra of the mixes suggest that the interaction between starch and glycerol is physical in nature and not chemical (Ruiz, 2006).

### 3.3 X-ray diffraction (XRD) of the films

Fig. 2 shows the diffractograms of the TPS/NC and TPS/OC films and compares them to those of pure NC and OC. The characteristic first-order reflection peak  $d(001)$ , is related to the basal spacing between the silicate sheets. Table 2 summarizes the values for the  $2\theta$  angle of the peaks and the corresponding  $d(001)$  distances calculated using Bragg's equation (mean value of three analyses). It was observed (Figs. 2 a and b) that the intensity and sharpness of the  $d(001)$  peak is maintained in the diffractograms of the TPS/NC film, which indicates the presence of nanostructured crystalline composites (Arellano-Cárdenas *et al.*, 2012). This is also a function of the amount of plasticizer added to the samples, since a lower proportion forms exfoliated structures and loses the crystallinity. This was reported by Tang *et al.*, 2005, who used 15 and 20% glycerol to form biofilms and obtained intercalated nanoclays. Wilhelm *et al.*, 2003, demonstrated using X-ray diffraction

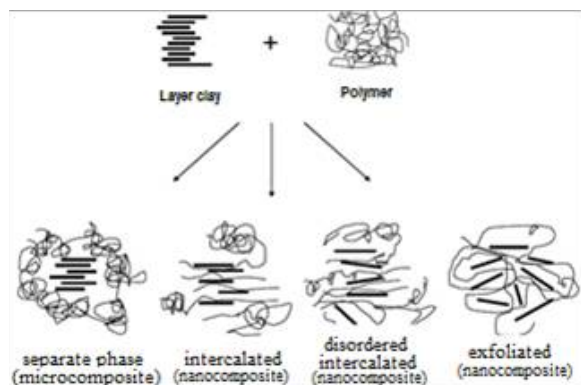


Fig. 3 Schematic depicting of the intercalation nanocomposites between polymer and sheets of clay (Ray and Bousmina, 2005).

on TPS/NC films that glycerol is intercalated in the interlaminal space of the clay, and the films made without glycerol showed completely exfoliated clay in the starch matrix; therefore, the corresponding peak did not appear in the XRD pattern. On the other hand, the same figures show a displacement of the peak to smaller  $2\theta$  angles, which implies an increase in the interlaminal distance compared to NC (1.24 nm). All the composite films showed an increase in the basal spacing of the layers, and the TPS/NC 85/15 film with 30% glycerol had the highest value, 1.82 nm (an increase of 32%) (Table 2). This may be due to the intercalation of starch and glycerol molecules in the interlaminal space of the clay to form interspersed starch/clay nanocomposites, as suggested by some authors (Santos *et al.*, 2014; Cheviron *et al.*, 2016; Zhang *et al.*, 2007; Müller *et al.*, 2012; Chen and Evans, 2005). Fig. 3 depicts the intercalation or exfoliation phenomenon that may occur between the polymers and clay as reported by Ray and Bousmina, 2005, and the phenomenon depends on the particular starch/clay proportions (Azeredo, 2009; Weiss *et al.*, 2006).

Figs. 2 (c) and (d) show a large decrease in the intensity and sharpness of the first peak,  $d(001)$ , in the three TPS/OC samples compared to OC, indicating the presence of compounds with low crystallinity that may have formed through a disordered intercalation process, as reported by Ray and Bousmina, 2005 (Fig. 3). The decrease in the peak intensity could be because during the preparation of OC, the clay was first intercalated with the CPC polymer, and, subsequently, in the films, starch and glycerol were interspersed in the free spaces, contributing to the exfoliation and loss of crystallinity. Hsin-Tzu and Chin-San, 2004, studied OC-CPC formulas in different proportions (0 to 12%) and observed with X-ray diffraction that the exfoliation phenomenon occurs at lower clay proportions. The same figures (Figs. 2 c and d) also show a displacement of the peak to lower  $2\theta$  angles, i.e., from a value of  $4.12^\circ$  for OC to a mean value of  $3.5^\circ$  for the TPS/OC films with three clay proportions (Table 2). This displacement implies an increase of 16% in the average basal distance from 2.14 to 2.55 nm, which is lower than the interlaminal increase in the TPS/NC film (32%) and may be due to a lower affinity between the hydrophobic OC and the hydrophilic starch and glycerol molecules (Santos *et al.*, 2014; Müller *et al.*, 2012).

### 3.4 Scanning electron microscopy (SEM) of the films

Fig. 4 shows the micrographs of a) TPS, b) TPS/NC, and c) TPS/OC films, the last two films were made with 90/10 starch/clay ratio with 30% glycerol. The homogeneous appearance of the TPS/NC film is due to the good dispersion of its components. On the other hand, the TPS/OC films seem heterogeneous, which may be explained by the lack of affinity between the hydrophilic starch and glycerol matrix with the modified, hydrophobic clay (Park *et al.*, 2003; Zhang *et al.*, 2007).

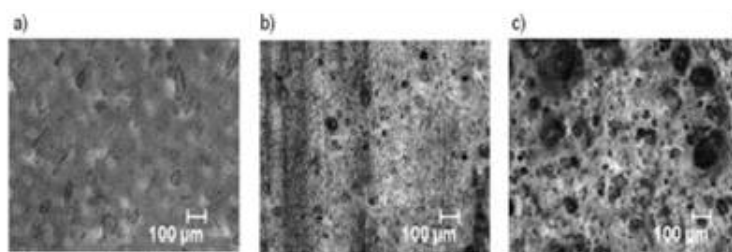


Fig. 4 SEM micrographs of a) TPS b)TPS/NC 90/10, 30% of glycerol, and b) TPS/OC 90/10, 30% of glycerol starch/clay composite films.

Table 3: Tensile strength (TS) and Young's Modulus (E) of TPS pure starch composite films with 25% and 30% glycerol content.

glycerol content (%)	TS (MPa)	E (GPa)
25	112.25±18.03	1.116±0.122
30	33.69±0.06	0.42±0.001

### 3.5 Mechanical properties of the films

The mechanical properties of the samples depend on the type of clay used in the formula and the amount of plasticizer. These also depend on the dispersion degree and the compatibility of the clay and plasticizer with the starch. Table 3 summarizes the tensile strength (TS) and Young's modulus (E) of the pure TPS films. As the glycerol content increases from 25 to 30%, the TS and E values have a significant decrease. It is known that a low E value indicates a higher elasticity; therefore, the addition of glycerol gives the films less strength and more elasticity because the glycerol molecules may facilitate the movement of the starch chains, increasing the flexibility (Tang *et al.*, 2005; Chang *et al.*, 2010; Koh *et al.*, 2008).

On the other hand, the mechanical properties of the films measured using the nanoindentation method were affected by the clay dispersion. Therefore, a statistical analysis was carried out on all the data obtained from the clays (NC and OC), the three combinations of starch/clay (95/5, 90/10, 85/15) and the two concentrations of glycerol (25 and 30%). The results obtained are shown in a main effect graphics.

Fig. 5 (I) shows the effect of the starch/clay ratio on the strength of the films. The TS increases as the clay (NC or OC) content increases, and the hardest structures are the 85/15 starch/clay ratio films. These results agree with other reports. Sothornvit *et al.*, 2009, proposed that the mechanical properties of biofilms such as hardness, may be attributed to the high rigidity of the structure and the affinity between the biopolymer and the particular type of clay. The same Fig. 5 (I) shows that increasing the glycerol content decreases the hardness of the films, as mentioned before.

The Young's modulus values were also affected by the clay dispersed in the polymer matrix, therefore, a statistical analysis was also performed on all the data. The results are shown in Fig. 5 (II). The significant effect of the starch/clay ratio on the elasticity is observed, and the films with the lowest elasticity are also the hardest, with a ratio of 85/15. This behavior is common in polymer materials reinforced with silicate fillers (Nguyen *et al.*, 2016; Romero-Bastida *et al.*, 2015). According to Muller *et al.*, 2012, the addition of clay to biofilms confers hardness due to the formation of intercalated structures. Park *et al.*, 2003, reported that a better clay dispersion results in better mechanical properties. The effect of glycerol on the elasticity of the films is also statistically significant, resulting in a higher elasticity at a concentration of 30% glycerol.

However, all the TPS/clay films had a lower elasticity than the pure TPS films. Nevertheless, it is possible to obtain starch films that show moderate mechanical properties by choosing the appropriate concentration of clay and glycerol.

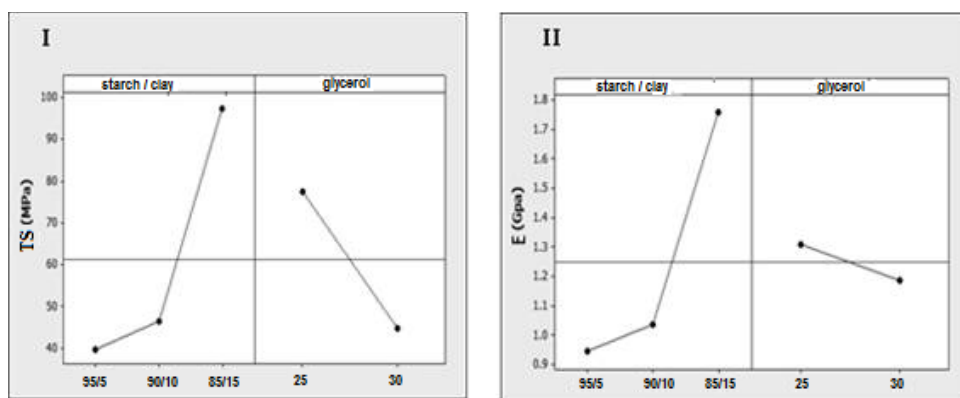


Fig. 5 Graphic of principal effects constructed with statistical analysis using all data obtained from clays (NC and OC) of: I) tensile strength (TS), II) Young's modulus (E) of the TPS/clay and glycerol (25% and 30%) composite films.



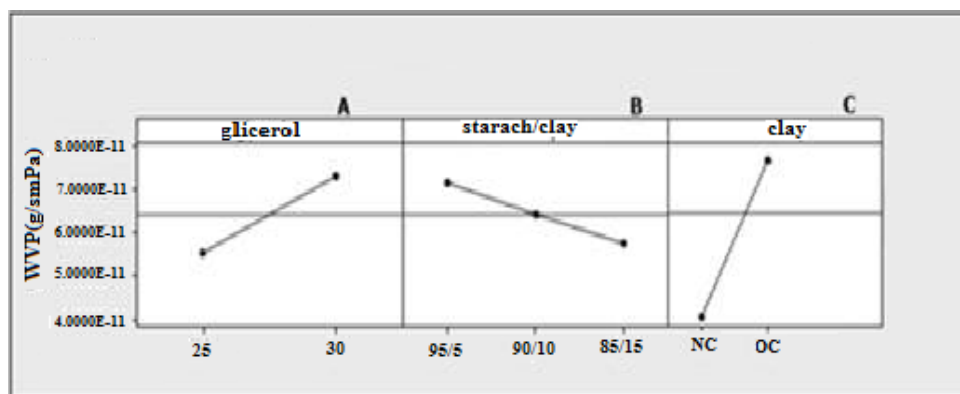


Fig. 6 Graphic of principal effects of water vapor permeability (WVP): A) as a function of glycerol content, B) as function of TPS/clay proportion, C) as a function of clay type.

### 3.6 Water vapor permeability (WVP) of the films

Fig. 6 presents a statistical analysis showing the independent effect of each variable on the WVP on the films made with two types of clay (NC and OC), three starch/clay ratios, and glycerol at 25 and 30%. The effect of glycerol is statistically significant on the WVP (Fig. 6 A), and the highest permeability was found on the films with 30% glycerol compared to 25%. This may be due to the formation of hydrogen bonds between the glycerol and starch molecules, which replace the interaction between the hydroxyl groups of the starch and silicate sheets in clay. Therefore, high glycerol content increases the hydrophilic character of the starch films. These results agree with the report by Tang *et al.*, 2005. Al-Hassan and Norziah, 2012, also mentioned that the hydrophilic character of the plasticizer increases the water vapor permeability, which in turn has a positive effect on the water vapor transfer velocity.

The WVP of films decreases when the proportion of clay (NC or OC) increases (Fig. 6 B), and this may be due to the higher number of silicate sheets dispersed in the matrix of the sample. However, the water vapor permeability also depends on the thickness of the film and the amount of plasticizer used in the formula, as shown in Table 4. It was observed that the permeability of the TPS/NC film (95/5 and 25% glycerol) was  $4.11 \times 10^{-11}$  (g/smPa), which is higher than the reported by Ning *et al.*, 2010 ( $0.23 \times 10^{-11}$  g/smPa), who used the same proportion in their TPS/NC films with 5% glycerol. The same fact occurs with the TPS/OC film, which had a higher permeability value than that

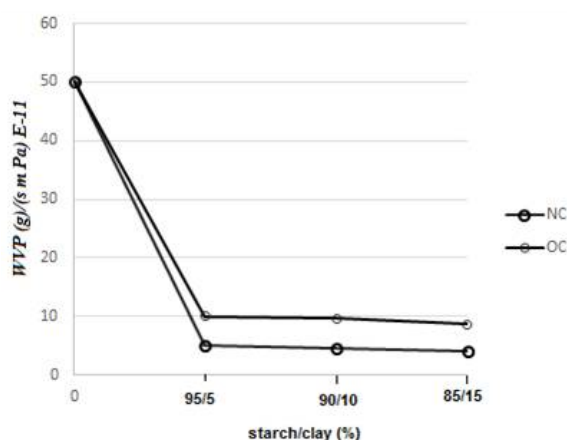


Fig. 7 Water vapor permeability (WVP) of TPS/NC and TPS/OC starch/clay composite films with 30% of glycerol. WVP of control TPS (pure starch) =  $50 \times 10^{-11}$  (g/smPa). Note: the experimental error for each point is 0.02 in average.

reported by Rhim *et al.*, 2009, for an organic clay.

On the other hand, it was also observed that WVP is a function of the particular type of clay (Fig. 6 C). The TPS/OC films showed higher WVP values compared to the TPS/NC films. This may be due to the lower crystallinity and heterogeneity in the former, as demonstrated by the X-ray diffraction and electronic microphotography results, because a lower dispersion of OC in the matrix decreases the tortuosity and favors water permeability. These results agree with Park *et al.*, 2003, who observed better barrier properties in films made from natural sodium clay (Cloisite Na<sup>+</sup>) than in films made from Cloisite 30B, which is partially hydrophobic.

Table 4: Water vapor permeability (WVP) at 25 °C and RH (50 to 60%) of TPS/NC and TPS/OC 95/5 starch/clay composite films with 25% glycerol content.

Composition TPS/clay	WVP (g/smPa)	Thickness (mm)	Reference
TPS/ clay (95/5, 5\% glycerol)	$0.23 \times 10^{-11}$	60	Ning <i>et al.</i> , 2010
PLA/NC	$2.08 \times 10^{-11}$	80	Rhim <i>et al.</i> , 2009
PLA/Cloisite 30B (OC) (Both 95/5)	$1.7 \times 10^{-11}$	79	
TPS/NC (95/5, 25% glycerol)	$4.11 \times 10^{-11}$	75	This work
TPS/OC (95/5, 25% glycerol)	$6.76 \times 10^{-11}$	83	This work

Fig. 7 shows the WVP of the TPS/NC and TPS/OC composite films compared to TPS pure starch using 30% glycerol. The same trend is observed with 25% glycerol. This figure shows that the WVP (average value  $< 10 \times 10^{-11} \text{ g s}^{-1} \text{ m}^{-1} \text{ Pa}^{-1}$ ) of the films prepared with clay (NC or OC) is 80% lower than that of the films based on only starch ( $50 \times 10^{-11} \text{ g s}^{-1} \text{ m}^{-1} \text{ Pa}^{-1}$ ). This decrease has been reported for starch/clay nanocomposites (Park *et al.*, 2003) and has been attributed to the dispersion of the silicate sheets in the matrix of the polymer. This obstructs the starch hydroxyl groups decreasing the transmission of water vapor through the matrix or from slowing water diffusion due to the generated tortuosity (Müller *et al.*, 2012; Ning *et al.*, 2010). The process of mass transfer depends on the affinity between the water and the polymeric matrix and on the resistance to the molecular movement of water within the matrix (Ning *et al.*, 2010).

## Conclusions

Mechanical and barrier properties are improved when using clay materials as additives in starch-based films. The thickness of the resulting films depends on the type and proportion of the particular clay. The strength is greater when the concentration of the clay increases, and the elasticity is greater when the lowest proportion of clay is used and the glycerol content is increased. Films made with both types of clay, NC or OC, have decreased water vapor permeability by 80%, compared to films prepared with only starch.

## Acknowledgements

Financial support from the Secretaría de Estudios de Posgrado e Investigación del Instituto Politécnico Nacional (SIP-IPN) and the Consejo Nacional de Ciencia y Tecnología (CONACYT) is appreciated.

## Nomenclature

CEC	Cationic exchange capacity
E	Young's Modulus
NC	Natural clay
OC	Organoclay
TPS	Thermoplastic starch
TS	Tensile strength
WVPTR	Water vapor transmission rate
WVP	Water vapor permeability

## References

- Al-Hassan, A.A., Norziah, M.H. (2012). Starch gelatin edible films water vapor permeability and mechanical properties as affected by plasticizers. *Food Hydrocolloids* 26, 108-117.
- Almazán-Sánchez, P.T., Solache-Ríos, M.J., Linares-Hernández, I., Martínez-Miranda, V. (2016). Adsorption-regeneration by heterogeneous fenton process using modified carbon and clay materials for removal of indigo blue. *Environmental Technology (United Kingdom)* 37, 1843-1856.
- Arellano-Cárdenas, S., Gallardo-Velázquez, T., Poumian-Gamboa, G.V., Osorio-Revilla, G.,

- López-Cortez, S., Rivera-Espinoza, Y. (2012). Sorption of naringin from aqueous solution by modified clay. *Clays and Clay Minerals* 60, 153-161.
- Arellano-Cárdenas, S., López-Cortez, S., Cornejo-Mazón, M., Mares-Gutiérrez, J.C. (2013). Study of malachite green adsorption by organically modified clay using a batch method. *Applied Surface Science* 280, 74-78.
- Avella, M., De Vlieger, J., Errico, E., Fischer, S., Vacca, P., Volpe, M. (2004). Biodegradable starch/clay nanocomposite films for food packaging applications. *Food Chemistry* 93, 467-474.
- Averous, L., Boquillon, N. (2004). Biocomposites based on plasticized starch: thermal and mechanical behaviors. *Carbohydrate Polymers* 56, 111-122.
- Azeredo, H. (2009). Nanocomposites for food packaging applications. *Food Research International* 42, 1240-1253.
- Borges, J.A., Romani, V.P., Cortez-Vega, W.R., Martins, V.G. (2015). Influence of different starch sources and plasticizers on properties of biodegradable films. *International Food Research Journal* 22, 2346-2351.
- Brindley, G., Brown, G. (1980). *Crystal Structures of Clay Minerals and their X-ray Identification*. Third edition. Mineralogical Society, London
- Chang, P., Jian, R., Zheng, P., Yu, J., Ma, X. (2010). Preparation and properties of glycerol plasticized-starch (GPS)/cellulose nanoparticle (CN) composites. *Carbohydrate Polymers* 79, 301-305.
- Chen, B., Evans, J. (2005). Thermoplastic starch-clay nanocomposites and their characteristics. *Carbohydrate Polymers* 61, 455-463.
- Cheviron, P., Gouanvé, F., Espuche, E. (2016). Preparation, characterization and barrier properties of silver/montmorillonite/starch nanocomposite films. *Journal of Membrane Science* 497, 162-171.
- Chung, Y.L., Ansari, S., Estevez, L., Hayrapetyan, S., Giannelis, E.G., Lai, H.M. (2010). Preparation and properties of biodegradable starch-clay nanocomposites. *Carbohydrate Polymers* 79, 391-396.
- Cyras, V., Manfredi, L.B., Ton-That, M., Vázquez, A. (2008). Physical and mechanical properties of thermoplastic starch/montmorillonite nanocomposite films. *Carbohydrate Polymers* 73, 55-63.
- Dean, K., Dieu, M., Petinakis, E., Yu, L. (2008). Key interactions in biodegradable thermoplastic starch/poly(vinyl alcohol)/montmorillonite micro- and nanocomposites. *Composites Science and Technology* 68, 1453-1462.
- Demirgöz, D.E. (2000). Chemical modification of starch based biodegradable polymeric blends: effects on water uptake, degradation behavior and mechanical properties. *Polymer Degradation and Stability* 70, 161-170.
- Esmaeili, M., Pircheraghi, G., Bagheri, R. (2017). Optimizing the mechanical and physical properties of thermoplastic starch via tuning the molecular microstructure through coplasticization by sorbitol and glycerol. *Polymer International* 66, 809-819.
- Fialho e Moraes, A.R., Pola, C.C., Bilck, A.P., Yamashita, F., Tronto, J., Medeiros, E.A.A., Soares, N.D.F.F. (2017). Starch, cellulose acetate and polyester biodegradable sheets: effect of composition and processing conditions. *Materials Science and Engineering C* 78, 932-941.
- Fisher, A.C. (2006). Critical review of analysis and interpretation of nanoindentation test data. *Surface and Coatings Technology* 200, 4153-4165.
- Flores-Martínez, N.L., Valdez-Fragoso, A., Jiménez-Islas, H., Pérez-Pérez, M.C. (2017). Physical, barrier, mechanical and microstructural properties of Aloe vera-gelatin-glycerol edible films incorporated with *Pimenta dioica* L. Merrill essential oil. *Revista Mexicana de Ingeniería Química* 16, 109-119.
- Gao, Y., Yangyong, D., Zhang, H., Enjie, D., Hanxue, H., Haizhou, D. (2014). Effects of organic modification of montmorillonite on the performance of starch-based nanocomposite films. *Applied Clay Science* 99, 201-206.

- Hongguang, D., Chang, P.R., Geng, F., Yu, J., Ma, X. (2009). Preparation and properties of thermoplastic starch/montmorillonite nanocomposite using N-(2-Hydroxyethyl) formamide as a new additive. *Journal of Polymer Environment* 17, 225-232.
- Hsin-Tzu, L., Chin-San, W. (2004). Synthesis and characterization of polyethylene-octene elastomer/clay/biodegradable starch nanocomposites. *Journal of Applied Polymer Science* 97, 397-404.
- Huang, M., Yu, J., Ma, X. (2004). Studies on the properties of montmorillonite-reinforced thermoplastic starch composites. *Polymer* 45, 7017-7023.
- Jiménez-Castañeda, M.E., Medina, D.I. Use of surfactant-modified zeolites and clays for the removal of heavy metals from water. *Water* 9, 1-12.
- Khan, B., Bilal, Khan, Niazi, M., Samin, G., Jahan, Z. (2017). Thermoplastic starch: a possible biodegradable food packaging material-a review. *Journal of Food Process Engineering* 40, 1-17.
- Koh, H., Park, J., Jeong, M., Hwang, H., Hong, Y., Ha, S., Nam, S. (2008). Preparation and gas permeation properties of biodegradable polymer/layered silicate nanocomposite membranes. *Desalination* 233, 201-209.
- Lilichenko, N., Maksimov, R., Zicans, J., Merijs, M., Plume, E. (2008). A biodegradable polymer nanocomposite: mechanical and barrier properties. *Mechanics of Composite Materials* 44, 45-56.
- López, S., Osorio, G., Gallardo, T., Arellano, S. (2008). Adsorption of vapor-phase VOCs (benzene and toluene) on modified clays and its relation with surface properties. *Canadian Journal of Chemistry* 86, 305-311.
- Majdzadeh-Ardakani, K., Navarchian, A., Sadeghi, F. (2010). Optimization of mechanical properties of thermoplastic starch/clay nanocomposites. *Carbohydrate Polymers* 79, 547-554.
- Muller, C.M.O., Laurindo, B.J., Yamashita, F. (2012). Composites of thermoplastic starch and nanoclays produced by extrusion and thermopressing. *Carbohydrate Polymers* 89, 504-510.
- Müller, P., Kapin, E., Fekete, E. (2014). Effects of preparation methods on the structure and mechanical properties of wet conditioned starch/montmorillonite nanocomposite films. *Carbohydrate Polymers* 113, 569-576.
- Nguyen, D.M., Vu, T.T., Grillet, A.C., Ha Thuc, H., Ha Thuc, C.N. (2016). Effect of organoclay on morphology and properties of linear low density polyethylene and Vietnamese cassava starch biobased blend. *Carbohydrate Polymers* 136, 163-170.
- Ning, W., Xingxiang, Z., Na, H., Haihui, L. (2010). A Facile method for preparation of thermoplastic starch/urea modified montmorillonite nanocomposites. *Journal of Composite Materials* 44, 27-39.
- Oliver, W., Pharr, G. (1992). An improved technique for determining hardness and elastic modulus using load and displacement sensing indentation experiments. *Journal of Materials Research* 7-6, 1564-1583.
- Park, H., Lee, W., Park, C., Cho, W., Ha, C. (2003). Environmentally friendly polymer hybrids. Part I mechanical, thermal, and barrier properties of thermoplastic starch/clay nanocomposites. *Journal of Materials Science* 38, 909-915.
- Ray, S.S., Bousmina, M. (2005). Biodegradable polymers and their layered silicate nanocomposites: in green the 21st century materials word. *Progress Material Science* 50, 962-1079.
- Rhim, J., Hong, S., Ha, C.S. (2009). Tensile, water vapor barrier and antimicrobial properties of PLA/nanoclay composite films. *LWT-Food Science and Technology* 42, 612-617.
- Romero-Bastida, C.A., Bello-Pérez, L.A., Velázquez, G., Álvarez-Ramírez, J. (2015). Effect of the addition order and amylose content on mechanical, barrier and structural properties of films made with starch and montmorillonite. *Carbohydrate Polymers* 127, 195-201.
- Ruiz, G. (2006). Obtención y caracterización de un polímero biodegradable a partir del almidón de yuca. *Ingeniería y Ciencia* 2, 5-28.

- Santos, R.A.L., Muller, C.O.M., Grossmann, M.V.E., Mali, S., Yamashita, F. (2014). Starch/poly (butylene adipate-co-terephthalate)/montmorillonite films produced by blow extrusion. *Quimica Nova* 37, 937-942.
- Sothornvit, R., Krochta, J.M. (2001). Plasticizer effect on oxygen permeability of  $\beta$ -lactoglobulin films. *Journal of Food Engineering* 48, 6298-6302.
- Sothornvit, R., Jong-Whan, R., Seok-In, H. (2009). Effect of nano-clay type on the physical and antimicrobial properties of whey protein isolate/clay composite films. *Journal of Food Engineering* 91, 468-473.
- Souza, A.C., Benze, R., Ferrão, E.S., Ditchfield, C., Coelho, A.C.V., Tadini, C.C. (2012). Cassava starch biodegradable films: Influence of glycerol and clay nanoparticles content on tensile and barrier properties and glass transition temperature. *LWT-Food Science and Technology* 46, 110-117.
- Staroszczyk, H., Gottfried, K., Malinowska-Panczyk, E., Kolodziejska, I. (2017). Clay-filled starch films. Part I: effect of clay kind and glycerol concentration on functional properties of composites. *Starch/Starke* 69, 1-8.
- Tang, X., Alavi, S., Herald, T. (2005). Effects of plasticizers on the structure and properties of starch-clay nanocomposite films. *Carbohydrate Polymers* 74, 552-558.
- Villada, H.S., Acosta, H.A., Velasco, R.J. (2008). Research on thermoplastic starches, biodegradable products precursors. *Información Tecnológica* 19, 3-14.
- Weiss, J., Takhistov, P., McClements, J. (2006). Functional materials in food nanotechnology. *Scientific Status Summary* 71, 107-116.
- Wilhelm, H.M., Sierakowski, M.R., Souza, M.G.P., Wypych, F. (2003). Starch films reinforced with mineral clay. *Carbohydrate Polymers* 52, 101-110.
- Wilpiszewska, K., Antosik, A.K., Spychaj, T. (2015). Novel hydrophilic carboxymethyl starch/montmorillonite. *Carbohydrate Polymers* 128, 82-89.
- Yu, L., Dean, K., Li, L. (2006). Polymer blends and composites from renewable resources. *Progress in Polymer Science* 31, 576-602.
- Yu, Z., Yin, J., Yan, S., Xie, Y., Ma, J., Chen, X. (2007). Biodegradable poly(L-lactide)/poly( $\epsilon$ -caprolactone)-modified montmorillonite nanocomposites: preparation and characterization. *Polymer* 48, 6439-6447.
- Zhang, Q., Yu, Z., Xie, X., Naito, K., Kagawua, Y. (2007). Preparation and crystalline morphology of biodegradable starch/clay nanocomposites. *Polymer* 48, 7193-7200.