



Vojnotehnicki glasnik/Military Technical
Courier

ISSN: 0042-8469

vojnotehnicki.glasnik@mod.gov.rs

University of Defence
Serbia

Jovani, Nikola S.; Adnaevi, Borivoj K.; Jovanovi, Jelena D.
Kinetics of the non-isothermal desorption of ethanol absorbed onto CMS-3A
Vojnotehnicki glasnik/Military Technical Courier, vol. 65, núm. 2, 2017, pp. 359-377
University of Defence

Available in: <https://www.redalyc.org/articulo.oa?id=661770078007>

- How to cite
- Complete issue
- More information about this article
- Journal's homepage in redalyc.org

redalyc.org

Scientific Information System
Network of Scientific Journals from Latin America, the Caribbean, Spain and Portugal
Non-profit academic project, developed under the open access initiative

KINETICS OF THE NON-ISOTHERMAL DESORPTION OF ETHANOL ABSORBED ONTO CMS-3A

Nikola S. Jovančić^a, Borivoj K. Adnađević^b, Jelena D. Jovanović^c

University of Belgrade, Faculty of Physical Chemistry, Belgrade, Republic of Serbia

^a e-mail: nikola.jovancic82@gmail.com,

ORCID iD: <http://orcid.org/0000-0003-4917-9104>

^b e-mail: bora@ffh.bg.ac.rs,

ORCID iD: <http://orcid.org/0000-0002-9555-8191>

^c e-mail: jelenaj@ffh.bg.ac.rs,

ORCID iD: <http://orcid.org/0000-0002-7537-9591>

<https://dx.doi.org/10.5937/vojtehg65-12187>

FIELD: Chemical Technology

ARTICLE TYPE: Original Scientific Paper

ARTICLE LANGUAGE: English

Abstract:

The kinetics of the desorption of ethanol previously absorbed onto carbon molecular sieves (CMS-3A) was studied using the non-isothermal thermogravimetric technique. The dependence of activation energy ($E_{a,\alpha}$) for a particular degree of desorption (α) was established. It was confirmed that the non-isothermal desorption of ethanol was a kinetically complex process. A novel mathematical model for the kinetics of non-isothermal desorption for the absorbed ethanol is established. This model is based on the proposed dependence of the specific desorption rate on time/temperature. The correlation dependences of the model parameters β and η on heating rates were established. A general kinetic equation for the non-isothermal desorption of ethanol was developed. It was found that the specific desorption rate at every single heating rate increases, whereas $E_{a,\alpha}$ decreases during the desorption process.

Key words: dependant, absorbers, molecular sieves, analytical models, model, zeolites, CMS-3A, kinetics, ethanol, desorption.

ACKNOWLEDGEMENT: This investigation was supported by the Ministry of Science and Technical Development of the Republic of Serbia through Project 172015OI.

Introduction

Bioethanol nowadays presents a main alternative source for the economic production of novel fuels and ethanol (Kosaric, et al, 2001). Ethanol is produced by fermentation of sugars obtained by hydrolyses of biomass. Three sources of biomass are commonly used: sugar, corn and lignocellulose materials. The most promising source is the lignocellulose biomass because it can use agricultural and forest residues and prevent the heated fuel-versus-food debate (Hashi, et al, 2010, pp.4628-4637). The only barrier for a broad application of production of ethanol is a high production cost (Kaminski, et al, 2008, pp.95-102).

Produced bioethanol contains a certain amount of water. The distillation process used for bioethanol separation and purification requires a large amount of energy which is approximately equal to 50% of the combustion energy of produced bioethanol (Fujita, et al, 2011, pp.869-879). Selective ethanol adsorption on a hydrophobic material of the zeolite type is a way to reduce the energy consumption of this process, presently the most promising procedure for an energetically rational bioethanol production (Adnadjevic, Jovanovic, 2012, pp.761-768). The introduction of this new separation process for bioethanol production requires solving a novel problem of cheap and effective selective procedure of adsorbed ethanol desorption onto a zeolite type adsorbent. The key role in this solution is in the kinetics of ethanol desorption from the zeolite adsorbent. It was shown that the most effective adsorbents are carbon molecular sieves such as CMS - 3A. Knowing the kinetics of ethanol desorption can contribute to better and more economical production of bioethanol. Unfortunately, to the best of our knowledge, the literature data is sparse with data concerning this topic.

Fujita and co-workers investigated the kinetics of desorption of ethanol and water from various types of commercial zeolite (MSC-3A, 4A, -5A, -6A, -7A, HiSiV3000, ZSM-5 ($\text{SiO}_2/\text{AlO}_3 = 30$), hydrophilic 5A) in the gaseous phase and evaluated the effectiveness of the proposed process (Fujita, et al, 2011, pp.869-879). The desorption of 1-butanol from water solution adsorbed onto ZSM-5 with a high Si/Al ratio was discussed in the work of Saravanan et al. (Saravanan, et al, 2010, pp.68-69). Oudshoorn et al. investigated the desorption rate of 1-butanol from zeolite CVB28014, CVB901 (Oudshoorn, et al, 2012, pp.167-172).

Keeping that in mind, this work thoroughly investigates the kinetics of the non-isothermal desorption of ethanol adsorbed onto carbon molecular

sieves (CMS-3A). Therefore, a kinetic model, kinetic complexity and the values of the kinetics parameters were determined and discussed.

Materials and Methods

Materials

The following materials were used: a carbon molecular sieve type 3A (CMS-3A), produced by Takeda Chem. Ind., Japan; ethanol 99.8 vol. % of p.a. purity purchased from Hemos, Belgrade, Serbia, and bidistilled water obtained from Hemofarm, Serbia. Before use, the CMS-3A was thermally activated at a temperature of 393 K for 2 hours, cooled and kept in a dessicator until use.

Characterization

The texture properties of the activated sample used were determined by N₂ (77 K) adsorption using a Micrometrics ASAP 2010 volumetric adsorption apparatus. The BET surface area was measured from the adsorption isotherms by applying the Brunauer-Emmett-Teller equation to calculate the micropore volume (V_{mp}). The total volume (V_t) was obtained at a relative pressure of 0.99. The pore size distribution (PSD) was obtained by the Horvath-Kawazoe analysis.

Sample preparation

Ethanol was absorbed onto the CMS-3A as follows. One gram of thermally activated CMS-3A was added to 50 mL of ethanol. Ethanol adsorption was undertaken for 24 hours. The ethanol adsorbed-CMS (CMS-ethanol) sample was separated from the ethanol excess by decantation. The sample was kept in the exicator to prevent ethanol desorption.

Thermogravimetric measurements

The non-isothermal thermogravimetric curves were recorded using a TA Instruments SDT simultaneous TGA-DSC thermal analyzer, model 2960. These experiments were performed with the CMS-ethanol absorbed

samples weighing 20 ± 5 mg. The samples were placed in the platinum pans under (99.9995 vol. %) nitrogen flowing at a rate of 20 mL min^{-1} . Four different heating rates ($v_h = 5, 10, 15$ and 20 K min^{-1}) were used in this study. All experiments in this work were conducted in the temperature range from ambient temperature up to 400 K. For isothermal methods, it is necessary that the process of desorption is performed at a lower temperature range from ambient to 500K. The original mass loss versus temperature (TG) curves obtained at a constant heating rate were transformed into the degree of desorption (α) versus temperature curves by means of the following equation:

$$\alpha = \frac{m_0 - m}{m_0 - m_f} \quad (1)$$

where m_0 , m and m_f refer to the initial, actual and final mass of the sample.

Kissinger–Akahira–Sunose (KAS) method

The Kissinger-Akahira-Sunose method (Akahira, Sunose, 1971, pp.22-31) is the isoconversional integral method which uses Coats-Redfern approximation (Coats, Redfern, 1964, pp.1273-1278) of the temperature integral that leads to the equation:

$$\ln\left(\frac{v_h}{T^2}\right) = \ln\left(\frac{AR}{E_a g(\alpha)}\right) - \frac{E_a}{RT} \quad (2)$$

where $g(\alpha)$ is the integral form of the selected kinetic model. For $\alpha = \text{const.}$, the plot of $\ln(v_h / T^2)$ vs. T^{-1} should be a straight line the slope of which can be used to evaluate the apparent activation energy.

Kinetic model

Desorption kinetics model

The ethanol desorption process is affected by many parameters such as temperature, time, pressure, ethanol concentration, pH of the solution, as well as the structural characteristics of carbon molecular sieves. The mathematical models of desorption presented below are based on the following assumptions listed below: (a) The desorption process is a kinetically complex process; (b) Leaving the molecules of a certain part of

the absorbed phase (desorption) leads to structural changes in the absorbed phase and its nearby surroundings (structural rearrangement); (c) The desorption rate is significantly higher than the structural rearrangement rate; (d) As a consequence of the above, the specific desorption rate (k) is a function of both time (t) and temperature (T), which can be described by the equation:

$$k = \frac{\beta}{\eta} \left(\frac{t}{\eta} \right)^{\beta-1} \quad (3)$$

i.e

$$k = \frac{\beta}{\eta} \left(\frac{T - T_0}{v_h \eta} \right)^{\beta-1} \quad (4)$$

where β and η are the Weibull's parameters, T_0 is the initial temperature and v_h is the heating rate; (e) the rate of desorption (dN/dt) is proportional to the amount of the remaining molecules in the adsorbed phase. In this case, the desorption rate is given as:

$$\frac{dN}{dT} = \frac{k}{v_h} (N_0 - N) \quad (5)$$

where N_0 is the amount of the adsorbed molecules in the beginning of the desorption process, and N is the amount of the desorbed molecules at T . Introducing Eq (4) into Eq (5) yields:

$$\frac{dN}{dT} = \frac{\beta}{v_h \eta} \left(\frac{T - T_0}{v_h \eta} \right)^{\beta-1} (N_0 - N) \quad (6)$$

The separation of the variables in equation (3) leads to:

$$\int_0^N \frac{dN}{(N_0 - N)} = \int_{T_0}^T \frac{\beta}{v_h \eta} \left(\frac{T - T_0}{v_h \eta} \right)^{\beta-1} dT \quad (7)$$

The integration of equation (7) should be done in the limits of N from 0 to N and of T from T_0 to T , to yield:

$$\ln \left(\frac{N_0 - N}{N_0} \right) = \left(\frac{T - T_0}{v_h \eta} \right)^{\beta} \quad (8)$$

The results is:

$$\frac{N_0 - N}{N_0} = \exp \left[- \left(\frac{T - T_0}{v_h \eta} \right)^\beta \right] \quad (9)$$

Since: $\alpha = N / N_0$, equation (9) is transformed into the form:

$$\alpha = 1 - \exp \left[- \left(\frac{T - T_0}{v_h \eta} \right)^\beta \right] \quad (10)$$

Results and discussion

Figure 1 shows the thermogravimetric curves for the desorption of ethanol from CMS at various heating rates.

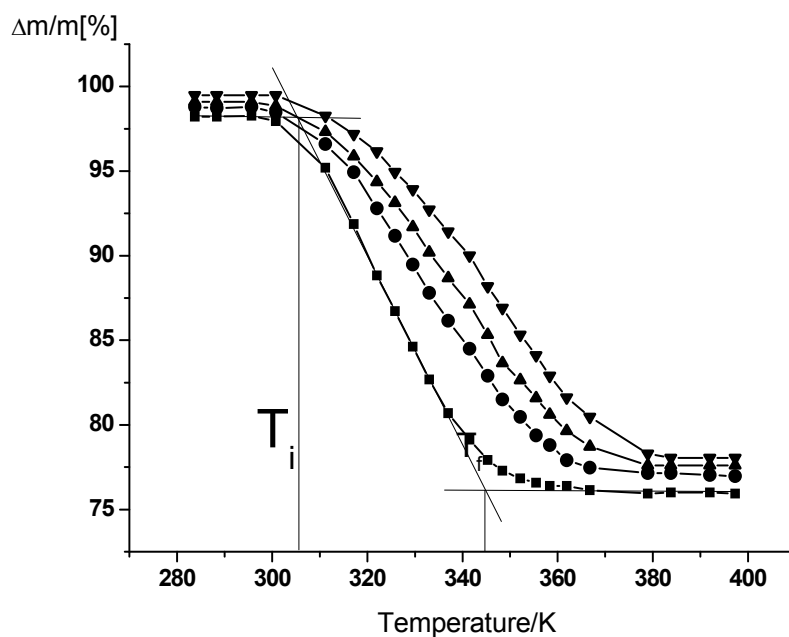


Figure 1 – The TG curves for the desorption of ethanol from CMS at various heating rates: 5Kmin⁻¹, ●- 10Kmin⁻¹ ▲- 15Kmin⁻¹ ▼- 20Kmin⁻¹

Рис. 1 – TG кривая десорбции этанола с CMS при разных скоростях нагревания: 5 К мин⁻¹, ●- 10 К мин⁻¹ ▲- 15 К мин⁻¹ ▼- 20 К мин⁻¹

Слика 1 – TG крива десорпције етанола са CMS на различитим брзинама загревања: 5Kmin⁻¹, ●- 10Kmin⁻¹ ▲- 15Kmin⁻¹ ▼- 20Kmin⁻¹

As it can be seen from Figure 1, the TG curves for the desorption of ethanol at all investigated heating rates are of a complex sigmoid shape. As it is obvious from the TG curves, both the initial temperature (T_i) and the final temperature (T_f), the reaction interval ($\Delta T = T_f - T_i$) and the degree of asymmetry of the curves change with the change in the heating rates. Table 1 summarizes the effects of heating rates on the values of T_i , T_f , ΔT and the residual ($\Delta m / m$).

Table 1 – Data for the heating rates, initial temperatures, final temperatures, reaction intervals and percentage of residual masses for Fig.1

Таблица 1 – Значения температуры в начале десорбции, при завершении десорбции, температурного интервала и остаток массы в процентах
Табела 1 – Вредности температуре почетка десорпције, температуре завршетка десорпције, температурског интервала и процентни остатак масе

ν_h [K/min]	T_i [K]	T_f [K]	ΔT [K]	$\Delta m / m$ [%]
5	305.63	344.59	38.96	76.04
10	308.09	358.63	50.54	76.97
15	310.54	366.65	56.11	77.72
20	312.29	373.73	61.44	78.02

As it is obvious from the results presented in Table 1, the increase of the heating rate leads to the increase in the values of T_i , T_f and ΔT , where the residual insignificantly varies within the experimental error. In order to preliminary determine the kinetic model of ethanol desorption, the shape of the dependence $d\alpha/dt$ on α is analyzed. (Khawam, Flangan, 2005, pp.10073-10080). The dependence of $d\alpha/dt$ on α is presented in Figure 2.

The dependence of $d\alpha/dt$ on α shows a broad asymmetric peak with a clear maximum - α_{\max} . With the increase of the heating rate, the value of α_{\max} increases almost linearly. Since the dependence of $d\alpha/dt$ on α has a complex shape, the dependence of $E_{a,\alpha}$ on α is determined by applying the KAS method. The dependence of $E_{a,\alpha}$ on α is shown in Figure 3.

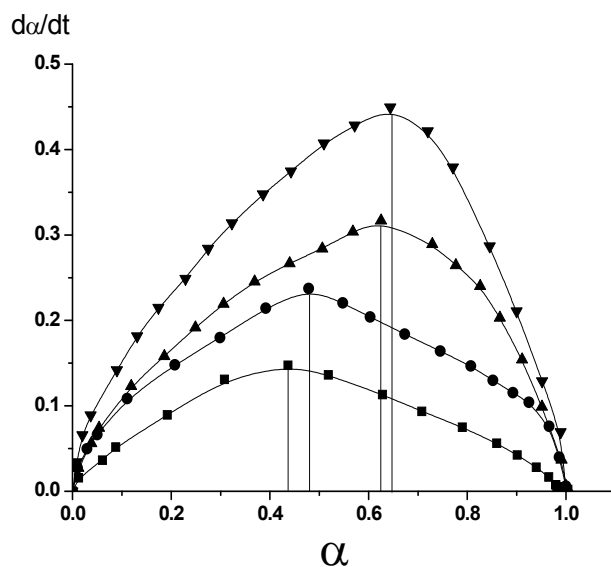


Figure 2 – The dependence of $d\alpha/dt$ on α at various heating rates:

■ - 5 K min⁻¹, ● - 10 K min⁻¹ ▲ - 15 K min⁻¹ ▼ - 20 K min⁻¹

Рис. 2 – зависимость $d\alpha/dt$ при разных скоростях нагревания:

■ - 5 K мин-1, ● - 10 K мин-1 ▲ - 15 K мин-1 ▼ - 20 K мин-1

Слика 2 – зависност $d\alpha/dt$ на различитим брзинама загревања:

■ - 5 K min⁻¹, ● - 10 K min⁻¹ ▲ - 15 K min⁻¹ ▼ - 20 K min⁻¹

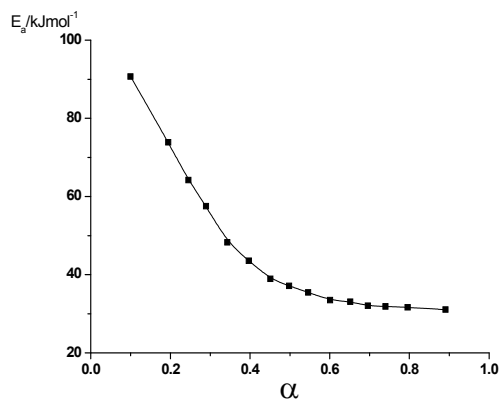


Figure 3 – The dependence of $E_{a,\alpha}$ on α

Рис. 3 – Зависимость $E_{a,\alpha}$ от α

Слика 3 – зависност $E_{a,\alpha}$ од α

The values of $E_{a,\alpha}$ decrease with the increase in the values of α . The analysis of the shape of the dependence of $E_{a,\alpha}$ on α clearly reveals two characteristic shapes of changes in $E_{a,\alpha}$ with the increasing α . In the range of $0 \leq \alpha \leq 0.25$, $E_{a,\alpha}$ decreases almost linearly with increasing the α values from $\sim 100 \text{ kJ mol}^{-1}$ to $\sim 60 \text{ kJ mol}^{-1}$. In contrast to this, when $\alpha \geq 0.25$, the increase of α leads to concave decrease in the value $E_{a,\alpha}$ from $\sim 60 \text{ kJ mol}^{-1}$ to $\sim 20 \text{ kJ mol}^{-1}$. A complex shape of the dependence of $E_{a,\alpha}$ on α , in accordance with Vyazovkin's criteria (Vyazovkin, Linert, 1995, pp.109-118), indicates that the process of desorption of the ethanol from the CMS is a kinetics complex process which takes place through numerous elementary stages. In regard to that, the ability of a mathematical description of the kinetics of ethanol desorption with equation (10) was evaluated. Figure 4 presents the dependence of $\ln[-\ln(1-\alpha)]$ on $\ln\left[\frac{T-T_0}{v_h}\right]$ at different heating rates.

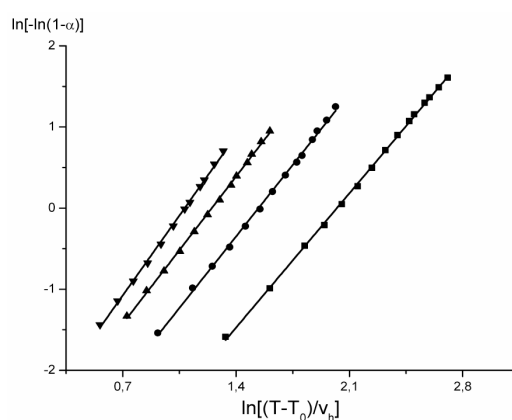


Figure 4 – Dependence of $\ln[-\ln(1-\alpha)]$ on $\ln\left[\frac{T-T_0}{v_h}\right]$ at different heating rates:

■- 5 K min-1, ●- 10 K min-1 ▲- 15 K min-1 ▼- 20 K min-1

Рис. 4 – Зависимость $\ln[-\ln(1-\alpha)]$ от $\ln\left[\frac{T-T_0}{v_h}\right]$ при разных скоростях нагревания:

■- 5 К мин-1, ●- 10 К мин-1 ▲- 15 К мин-1 ▼- 20 К мин-1

Слика 4 – Зависност $\ln[-\ln(1-\alpha)]$ од $\ln\left[\frac{T-T_0}{v_h}\right]$ на различитим брзинама загревања:

■- 5 K min-1, ●- 10 K min-1 ▲- 15 K min-1 ▼- 20 K min-1

Table 2 – Values of the Weibull's parameters at different heating rates
 Таблица 2 – Значения параметров Вейбулла при разных скоростях нагревания
 Табела 2 – Вредности Вејбулових параметара на различитим брзинама загревања

v_h [K/min]	β	η [min]
5	2.35	7.57
10	2.47	4.69
15	2.63	3.47
20	2.82	2.95

Obviously, the dependencies of $\ln[-\ln(1-\alpha)]$ on $\ln\left[\frac{T-T_0}{v_h}\right]$ for all of the investigated heating rates are linear. The values of the parameters β and η were calculated based on the slopes and intercepts the dependencies of $\ln[-\ln(1-\alpha)]$ on $\ln\left[\frac{T-T_0}{v_h}\right]$. The effect of heating rates on the Weibull's parameters β and η is shown in Table 2.

As it can be seen from the results presented in Table 3, the increase in the heating rates leads to the increase in the values of the parameter β while the values of the parameter η decrease. The found changes in the values of the parameters β and η can be mathematically described by the expressions:

$$\beta(v_h) = \exp(0.827 + 0.05v_h + 0.0003v_h^2) \quad (11)$$

$$\eta(v_h) = \exp(2.658 - 0.143v_h + 0.003v_h^2) \quad (12)$$

The mathematical expressions (11) and (12) enable to derive an equation which can successfully describe the kinetics of the investigated process as a function of temperature and heating rates:

$$\frac{d\alpha}{dT} = \frac{\beta(v_h)}{v_h\eta(v_h)} \left[\frac{(T-T_0)}{v_h\eta(v_h)} \right]^{\beta(v_h)-1} \exp \left[- \left(\frac{T-T_0}{v_h\eta(v_h)} \right)^{\beta(v_h)} \right] \quad (13)$$

Based on the knowledge on the values of the parameters β and η by using Eq (4), it is possible to calculate the values of a specific desorption rate for different temperatures at different heating rates. Figure 5 pre-

sents the dependence of the specific desorption rate with temperatures for different heating rates.

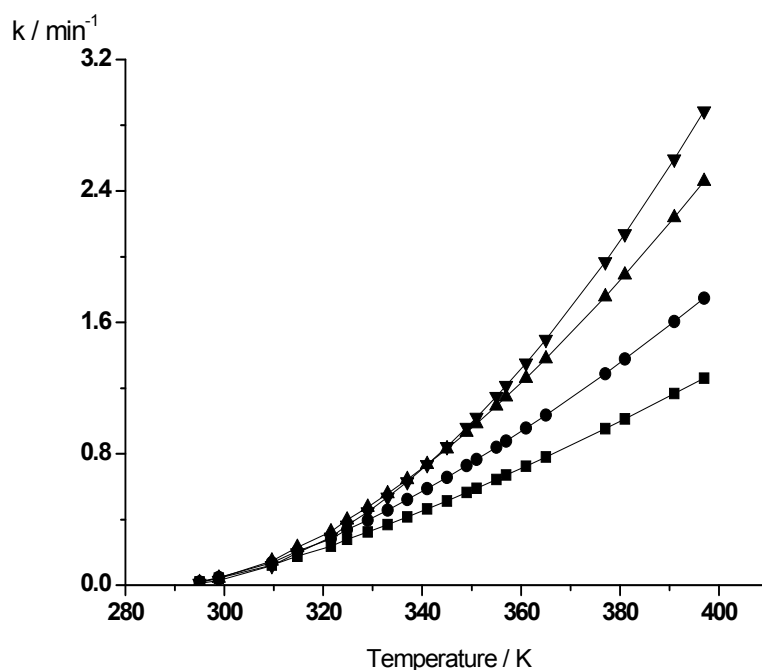


Figure 5 – Dependence of k on temperature at different heating rates:

■ - 5 K min⁻¹, ● - 10 K min⁻¹ ▲ - 15 K min⁻¹ ▼ - 20 K min⁻¹

Рис. 5 – Зависимость k от температуры при различных скоростях нагревания

■ - 5 K мин⁻¹, ● - 10 K мин⁻¹ ▲ - 15 K мин⁻¹ ▼ - 20 K мин⁻¹

Слика 5 – Зависност k од температуре на различитим брзинама загревања

■ - 5 K min⁻¹, ● - 10 K min⁻¹ ▲ - 15 K min⁻¹ ▼ - 20 K min⁻¹

The increase in temperature leads to the increase in the values of the specific desorption rate at all of the investigated heating rates. Also, the increase in the heating rates at all investigated temperature values leads to the increase in the values of the specific desorption rate. The established dependencies of k on T allow applying the Arrhenius equation to calculate the values of activation energies at different temperatures for different heating rates. The dependence of E_a on temperature at the investigated heating rates is presented in Figure 6.

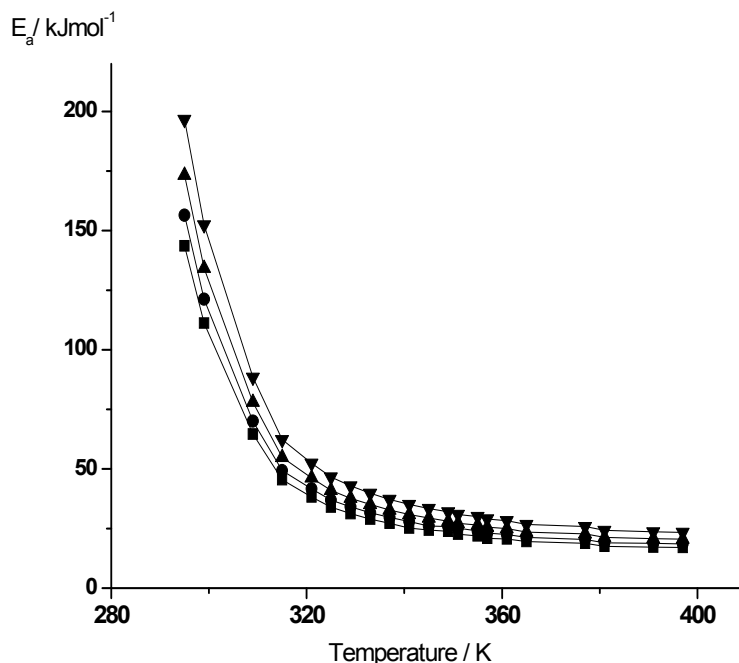


Figure 6 – The dependence of E_a on temperature at different heating rates:

■ - 5 K min⁻¹, ● - 10 K min⁻¹ ▲ - 15 K min⁻¹ ▼ - 20 K min⁻¹

Рис. 6 – Зависимость E_a от температуры при различных скоростях нагревания

■ - 5 K мин⁻¹, ● - 10 K мин⁻¹ ▲ - 15 K мин⁻¹ ▼ - 20 K мин⁻¹

Слика 6 – Зависност E_a од температуре на различитим брзинама загревања:

■ - 5 K min⁻¹, ● - 10 K min⁻¹ ▲ - 15 K min⁻¹ ▼ - 20 K min⁻¹

The E_a value decreases with the increasing temperature at all of the investigated heating rates. The two characteristic shapes of changes of $E_{a,T}$ with increasing T are obvious. In the range of $290 \leq T \leq 315$ K, the dependence $E_{a,T}$ on T almost linearly decreases with increasing temperature, whereas at temperatures $315 \leq T \leq 400$ K, the value of E_a decreases concavely with increasing temperature. At a particular value of temperature, the value of E_a increases with the increase in the heating rate. Based on the dependence of E_a on temperature at a particular heating rate, it is

possible to get the dependence of $E_{a,\alpha}$ on α for that heating rate. Figure 7 presents the dependence of $E_{a,\alpha}$ on α for different heating rates.

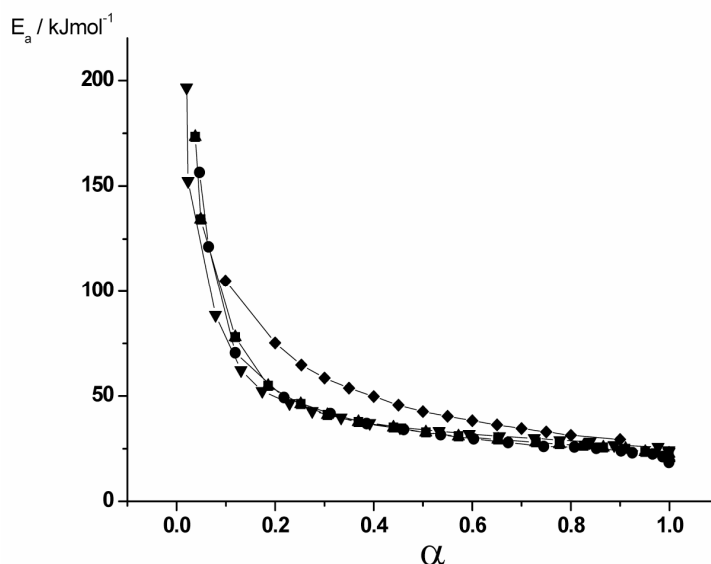


Figure 7 – Dependence of $E_{a,\alpha}$ on α for different heating rates

Рис. 7 – Зависимость E_a от α при различных скоростях нагревания

Слика 7 – Зависност $E_{a,\alpha}$ од α на различитим брзинама загревања

The curves of the dependence of $E_{a,\alpha}$ on α at all investigated heating rates are of similar shapes. The curves of the dependence of $E_{a,\alpha}$ on α show two different shapes of changes of the dependence of $E_{a,\alpha}$ on α . The two characteristic shapes of changes of $E_{a,\alpha}$ with increasing α are obvious. For the range of values $0 \leq \alpha \leq 0.2$, the dependence $E_{a,\alpha}$ on α linearly decreases with increasing α . For the values of $\alpha > 0.2$, the values of $E_{a,\alpha}$ decrease concavely with increasing $E_{a,\alpha}$. The comparison of the shapes of the dependences of E_a on α at different heating rates with the dependence of $E_{a,\alpha}$ on α obtained by the isoconversion method (Fig 3) clearly shows their mutual similarity, especially at extremely low and high degrees of desorption. The found similarity confirms physical reality of the previously suggested model for the non-isothermal desorption based on the assumption about the changes in the values of the specific rate of

desorption with temperature. Since with the increasing temperature the specific rate of desorption increases more rapidly than the rate of internal rearrangement of ethanol's molecules in the absorbed phase, the activation energy decreases, the kinetics complexity changes and the specific rate of desorption increases.

Conclusion

The non-isothermal desorption of ethanol absorbed onto CMS-3A is a kinetically complex process. Kinetic's complexity of the desorption of ethanol is a consequence of the changes in the specific rate of desorption and activation energy with temperature. The conversion kinetics curves of the non-isothermal desorption of ethanol, at all heating rates, can be entirely mathematically described by the suggested model. The correlation dependences of the parameters of the kinetics model on heating rates are established. A general kinetics equation of the non-isothermal desorption of ethanol is developed. It was found that the value of the specific desorption rate of ethanol, at every single heating rate, increases with the increase in temperature, whereas the activation energy decreases. The functional dependences of activation energy on time for each heating rate were determined. The results obtained by this work can be used to enhance the knowledge of the desorption kinetics of ethanol, which is a key factor for its more economical production.

Symbols

E_a [kJ mol ⁻¹]	activation energy
$E_{a,\alpha}$ [kJ mol ⁻¹]	activation energy at α
$E_{a,T}$ [kJ mol ⁻¹]	activation energy at T
V_{mp} V_{mp} [cm ³ g ⁻¹]	micropore volume
V_t [cm ³ g ⁻¹]	total volume
d [nm]	average pore size
m_0 [g]	the initial mass of the sample
m [g]	actual mass of the sample
m_f [g]	final mass of the sample
$\Delta m / m$ [%]	percentage of residual mass
$g(\alpha)$	integral form of the selected kinetic mode

T [K]	temperature
T^{-1} [K ⁻¹]	inverse temperature
T_i [K]	initial temperature at TG
T_f [K]	final temperature at TG
ΔT [K]	reaction interval
R [J mol ⁻¹ K ⁻¹]	universal gas constant (8.314)
k [min ⁻¹]	specific desorption rate
t [min]	time
T_0 [K]	initial temperature
dN / dt	rate of desorption
N_0	amount of the adsorbed molecules in the beginning of the desorption process
N	amount of the desorbed molecules at temperature
v_h [K min ⁻¹]	heating rate

Greek symbols

α [-]	degree of desorption
α_{\max} [-]	maximum degree of desorption
β [-]	Weibull's parameter
η [min]	Weibull's parameter

Abbreviations

CMS-3A	Carbon molecular sieves type 3A
CMS-ethanol	Ethanol adsorbed carbon molecular sieves
PSD	Pore size distribution
TG	Thermogravimetric curve
KAS method	Kissinger-Akahira-Sunose method
MSC-3A	Molecular Sieving Carbon type 3A
MSC-4A	Molecular Sieving Carbon type 4A
MSC -5A	Molecular Sieving Carbon type 5A
MSC -6A	Molecular Sieving Carbon type 6A
MSC -7A	Molecular Sieving Carbon type 7A
HiSiv3000	Silicalite zeolite
ZSM-5	Zeolite Socony Mobil-5
CVB28014	Zeolite ammonium ZSM-5
CVB901	Zeolite H-SDUSY

References

- Adnadjevic, B., & Jovanovic, J., 2012. Kinetics of Isothermal Ethanol Adsorption onto a Carbon Molecular Sieves under Conventional and Microwave heating. *Chemical Engineering Technology*, 34(4), pp.761-768. Available at: <http://dx.doi.org/10.1002/ceat.201100153>.
- Akahira, T., & Sunose, T., 1971. Trans. Joint Convention of Four Electrical Institutes. *Research Report, Chiba Institute of Technology*, 16(246), pp.22-31.
- Coats, A.W., & Redfern, J.P., 1964. Kinetic Parameters from Thermogravimetric Data. *Nature*, 201(4914), pp.68-69. Available at: <http://dx.doi.org/10.1038/201068a0>.
- Fujita, H., Qian, Q., Fujii, T., Moschizuki, K., & Sakoda, A., 2011. Isolation of ethanol from its aqueous solution by liquid phase adsorption and gas phase desorption using molecular sieving carbon. *Adsorption*, 17, pp.869-879.
- Hashi, M., Tezel, F.H., & Thibault, J., 2010. Ethanol Recovery from Fermentation Broth via Carbon Dioxide Stripping and Desorption. *Energy & Fuels*, 24(9), pp.4628-4637.
- Kaminski, W., Marszalek, J., & Ciolkowska, A., 2008. Renewable energy source: Dehydrated ethanol. *The Chemical Engineering Journal*, 135(1), pp.95-102. Available at: <http://dx.doi.org/10.1016/j.cej.2007.03.017>.
- Khawam, A., & Flanagan, R.D., 2005. Complementary use of model-free and modelistic methods in the analysis of solid-state kinetics. *J Phys Chem B*, 109(20), pp.10073-80. pmid:16852219.
- Kosaric, N., Vardar-Sukan, F., & Pieper, H.J., 2001. The Biotechnology of ethanol: Classical and Future Application. In: M. Roehel Ed., Weinheim: Wiley - VCH.
- Oudshoorn, A., van der Wielen, L.A.M., & Straathof, A.J.J., 2012. Desorption of butanol from zeolite material. *Biochemical Engineering Journal*, 67, pp.167-172.
- Saravanan, V., Waijers, A.D., Ziari, M., & Noordemeer, M.A., 2010. Recovery of 1-butanol from aqueous solutions using zeolite ZSM-5 with a high Si/Al ratio; suitability of a column process for industrial applications. *Biochemical Engineering Journal*, 49, pp.33-39.
- Vyazovkin, S., & Linert, W., 1995. Thermally induced reactions of solids, isokinetic relationship of nonisothermal decomposition of solids. *Chem Phys*, 193, pp.109-118.

НЕИЗОТЕРМИЧЕСКАЯ КИНЕТИКА ДЕСОРБЦИИ ЭТАНОЛА, АБСОРБИРОВАННОГО НА УГЛЕРОДНОМ МОЛЕКУЛЯРНОМ СИТЕ CMS-3A

Никола С. Йованчић, Боривой К. Аднаджевич, Елена Д. Йованович
Университет в Белграде, Факультет физической химии, г. Белград,
Республика Сербия

ОБЛАСТЬ: химические технологии
ВИД СТАТЬИ: оригинальная научная статья
ЯЗЫК СТАТЬИ: английский

Резюме:

В данной статье описаны проведенные исследования по кинетике десорбции этанола, абсорбированного на углеродном молекулярном сите CMS-3A. Главным источником биоэтанола являются: сахар, кукуруза и лигноцеллюлозные материалы. Выработанный биоэтанол содержит определенное количество воды. Для его очистки используются различные сепарационные методы, которые в настоящий момент еще недостаточно испытаны. Главная проблема очистки биоэтанола заключается в высокой стоимости процедуры и больших затратах энергии – на 50% превышающих производимую биоэтанолом энергию. Селективная адсорбция этанола на цеолите значительно снижает затраты энергии при производстве, но, к сожалению, данный метод требует много времени. В целях улучшения кинетики десорбции могут применяться различные технологии, однако они на сегодняшний день недостаточно испытаны. Одним из самых практичных и наиболее экономичных методов очистки биоэтанола является десорбция этанола на углеродном молекулярном сите, при этом вода остается на поверхности углеродного молекулярного сита. С учетом того, что данный метод недостаточно испытан, необходимо полагаться на знания о кинетике десорбции этанола на цеолитах. Хотя на сегодняшний день опубликовано малое количество научных работ, посвященных исследованиям кинетики десорбции этанола на цеолитах. В данной работе применена неизотермическая термогравиметрическая техника. В ходе исследования была утверждена полная зависимость энергии активации от степени десорбции, а также установлена модель процесса десорбции. Данная модель основана на полной зависимости скорости десорбции от времени и температуры. Благодаря применению данной модели можно повлиять на скорость процесса десорбции и энергию активации с температурой. Математическая модель, описанная в данной работе основана на полной зависимости скорости процесса десорбции и энергии активации от

температуры. Данная модель также отражает последовательность этапов процесса десорбции. Настоящая модель кинетики процесса десорбции этанола может значительно улучшить технологию производства биоэтанола и уменьшить производственные затраты.

Ключевые слова: зависимость, абсорбенты, молекулярные сита, аналитические модели, модели, цеолиты, CMS-3A, кинетика, этанол, десорбция.

НЕИЗОТЕРМНА КИНЕТИКА ДЕСОРПЦИЈЕ ЕТАНОЛА АДСОРБОВАНОГ НА УГЉЕНИЧНОМ МОЛЕКУЛСКОМ СИТУ CMS-3A

Никола С. Јованчић, Боровој К. Аднађевић, Јелена Д. Јовановић
Универзитет у Београду, Факултет за физичку хемију,
Београд, Република Србија

ОБЛАСТ: хемијске технологије
ВРСТА ЧЛАНКА: оригинални научни чланак
ЈЕЗИК ЧЛАНКА: енглески

Сажетак:

У овом раду проучавана је кинетика десорпције етанола претходно адсорбованог на угљеничном молекулском ситу CMS-3A. Главни извори биоетанола су ферментабилни шећери, кукуруз и лигноцелулозни отпадни материјал. Произведени биоетанол садржи одређену количину воде, а да би се пречистио користе се разне сепарационе методе које још нису довољно испитане. Главни проблем при пречишћавању биоетанола је висока цена, као и знатан утрошак енергије који представља више од 50% енергије коју биоетанол производи. Селективна адсорпција етанола са зеолита знатно смањује утрошак енергије при производњи. Нажалост, ова метода је веома спора. Ради побољшања кинетике десорпције користе се различите технике, које нису довољно испитане. Једну од практичних и јефтинијих метода која се користи при пречишћавању биоетанола представља десорпција етанола са угљеничног молекулског сита, при чему вода остаје задржана на угљеничном молекулском ситу. Међутим, ова метода није довољно испитана, а ради побољшања производње (брзине производње) потребно је познавати кинетику десорпције етанола са зеолита. Мало је научних радова и литературе који проучавају кинетику десорпције (брзину десорпције) етанола са зеолита. За одређивање кинетике десорпције у овом раду је коришћена неизотермна термогравиметријска техника.

Установљена је комплексна зависност енергије активације од степена десорпције, као и математички модел по којем се десорпција одиграва. Овај модел заснован је на комплексној зависности брзине десорпције од времена и температуре. Због комплексности модела долази до промене брзине десорпције и енергије активације са температуром. Математички модел установљен у овом раду заснива се на комплексној зависности брзине десорпције и енергије активације од температуре и показује на који начин се десорпција одиграва у неколико ступњева. Познавање кинетике процеса десорпције етанола може допринети бољој и економичнијој производњи биоетанола.

Кључне речи: зависност, апсорбенти, молекулска сита, аналитички модели, модели, зеолити, CMS-3A, кинетика, етанол, десорпција.

Paper received on / Дата получения работы / Датум пријема чланка: 24.10.2016.
Manuscript corrections submitted on / Дата получения исправленной версии работы / Датум достављања исправки рукописа: 28.11.2016.
Paper accepted for publishing on / Дата окончательного согласования работы / Датум коначног прихватања чланка за објављивање: 30.11.2016.

© 2017 The Authors. Published by Vojnotehnički glasnik / Military Technical Courier (www.vtg.mod.gov.rs, втг.мо.упр.срб). This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution license (<http://creativecommons.org/licenses/by/3.0/rs/>).

© 2017 Авторы. Опубликовано в «Военно-технический вестник / Vojnotehnički glasnik / Military Technical Courier» (www.vtg.mod.gov.rs, втг.мо.упр.срб). Данная статья в открытом доступе и распространяется в соответствии с лицензией «Creative Commons» (<http://creativecommons.org/licenses/by/3.0/rs/>).

© 2017 Аутори. Објавио Војнотехнички гласник / Vojnotehnički glasnik / Military Technical Courier (www.vtg.mod.gov.rs, втг.мо.упр.срб). Ово је чланак отвореног приступа и дистрибуира се у складу са Creative Commons licencom (<http://creativecommons.org/licenses/by/3.0/rs/>).

